

2014

Substitution and Disorder Effects in Ternary Intermetallics

LaRico Juan Treadwell

Louisiana State University and Agricultural and Mechanical College, treadwell500@gmail.com

Follow this and additional works at: https://digitalcommons.lsu.edu/gradschool_dissertations



Part of the [Chemistry Commons](#)

Recommended Citation

Treadwell, LaRico Juan, "Substitution and Disorder Effects in Ternary Intermetallics" (2014). *LSU Doctoral Dissertations*. 1380.
https://digitalcommons.lsu.edu/gradschool_dissertations/1380

This Dissertation is brought to you for free and open access by the Graduate School at LSU Digital Commons. It has been accepted for inclusion in LSU Doctoral Dissertations by an authorized graduate school editor of LSU Digital Commons. For more information, please contact gradetd@lsu.edu.

SUBSTITUTION AND DISORDER EFFECTS IN TERNARY INTERMETALLICS

A Dissertation

Submitted to the Graduate Faculty of the
Louisiana State University and
Agricultural and Mechanical College
in partial fulfillment of the
requirements for the degree of
Doctor of Philosophy

in

The Department of Chemistry

by
LaRico Juan Treadwell
B.S., The University of Mississippi, 2010
December 2014

*I am grateful for my family and loved ones, thank you for the love and support.
To GOD, thank you for blessing me and allowing me to do your will.*

Acknowledgements

In this section, I would like to highlight and express my gratitude to the people that have helped me throughout my graduate school tenure. I first would like to thank GOD, because without him nothing is possible. He has greatly blessed me and guided me through the process.

To my father and mother, Stephen and Adrienne Robinson, I wish to express how grateful I am to have such wonderful parents. With my parents' constant guidance, love, and support I have made it through life and the process of receiving a Ph.D. I would not be where I am today or the person I am today without them. I also like to recognize my son, LaTrell Treadwell, for being the best son ever for being patient and supporting his father during this lengthy process. As a child, he encouraged me to finish as much as anybody. He is truly a God-sent blessing. I also wish to express my gratitude to my siblings: Brycen, Byron, Bryen, and Melissa Robinson for being my motivation to set a good example as the oldest brother and for allowing me to torture them. To my Grandma, Great Grandma, my three aunties, and my Papa, (Patricia Bobo, Mary Sanford, Mary Sanford, Julia Chambers, Earlene Sanford, and Nathaniel Bobo) thank you for the encouragement and all your support. I also would like to thank my entire family for backing me in my decision for pursuing a higher education and their support through twenty-two years of school. I love each and every one of my family members. A special thank you goes to my fiancée, Tasharus Williams, for helping me get over the hump of my last year with the support and motivation.

I would like to give an extraordinary thanks to my research advisor Dr. Julia Y Chan. I am so grateful for the chance that you gave me to pursue a higher education under your guidance. I am at this point in my career because Dr. Julia Y Chan saw potential in me and gave me a chance. I am truly grateful for her patience, guidance, and advice. She nurtured me into the scientist that

I am today, and when times were rough and tough, she continued to push and motivate me to do my best and achieve my goal of obtaining a Ph.D. She allotted so many opportunities for me to excel in research and present my results on numerous occasions. These opportunities introduced me to the world of solid state chemistry, and I am very grateful for them. I consider Dr. Chan my academic mother, who I love dearly. In all I owe a great deal of my success and future success to my great mentor Dr. Julia Y. Chan. Also, I promise not to let you down, “Changing the world one step at a time”.

There are multiple people in the Chemistry and Physics departments at LSU that I would like to recognized and thank. First, I would to thank my committee members Professors George Stanley, Jayne Garno, Andrew Maverick, and David Young, for their guidance, support, encouragement, and professionalism throughout my tenure as a graduate student. I am very grateful for Dr. George Stanley who has been a co-advisor and mentored me on several occasions. Special thanks go to Dr. Frank Fronczek (Chemistry, LSU) and Dr. Gregory McCandless (Chemistry, UT Dallas) who have put up with my numerous question and for teaching/helping me with crystallography. I would like to especially thank the physics faculty members Professors David Young (Physics, LSU), Shane Stadler (Physics, LSU), and John DiTusa (Physics, LSU), for enriching my knowledge of physics and for the collaborative work on multiple projects. Special thanks are also in order for Dr. Neel Haldolaarachchige and Joseph Prestigiacomo for their invaluable assistance with the measurements of electrical and magnetic properties for many of my compounds.

I sincerely want to thank the former and current members of Dr. Chan’s research group a.k.a. “The Chanites” as we have been labeled. I would like to thank Drs. Melissa Menard, Brenton Drake, W. Adam Phelan, Gregory Morrison, Devin C. Schmitt, and Michael Kangas for showing

me the ropes when I first join the group and setting good examples. I would like to highlight Michael Kangas for working with me on my first project and teaching me good research practice. I am thankful for Dr. Brad Fulfer. He really took me under his wings and pushed me to the next level. Brad Fulfer has my deepest gratitude. I would like to give a loud shout-out to Pilanda and Luis Reyes for being such excellent friends, colleagues, and graduate students. I look at them as colleagues but also as my brother and sister. I will never forget the countless events we have shared and how they have impacted my life. I would like to thank the “newbies”, Dr. Roy McDougald and Iain Oswald. I am very great to have crossed path with them. In a short amount of time they have grown to be like an academic uncle (Roy) and nephew (Iain). Last, but certainly not least, my sincere thanks go to the undergraduates: Kristin, Jacob, Geoffrey, Dorothy that worked so closely with me and are co-authors of several manuscripts so closely with me.

The work presented here was performed in part due to funding from National Science Foundation (Division of Materials Research DMR-1358975) and Department of Energy (DE-FG0208ER46528).

Table of Contents

| | |
|--|-----|
| Acknowledgements | iii |
| Abstract..... | ix |
| Chapter 1. Introduction..... | 1 |
| 1.1 Motivation | 1 |
| 1.2 Synthesis | 3 |
| 1.3 Characterization | 5 |
| 1.4 Properties..... | 7 |
| 1.5 Substitution Effects in Rare Earth Intermetallics..... | 8 |
| Chapter 2. The physical properties of $\text{Ln}_6\text{W}_4\text{Al}_{43}$ and substitution studies of Mn and Fe in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ (Ln = Gd, Yb) | 11 |
| 2.1 Introduction..... | 11 |
| 2.2 Experimental..... | 12 |
| 2.2.1 Synthesis | 12 |
| 2.2.2 Single-Crystal X-ray Diffraction..... | 13 |
| 2.2.3 Elemental Analysis..... | 21 |
| 2.2.4 Physical Properties..... | 22 |
| 2.3 Results and Discussion..... | 22 |
| 2.3.1 Crystal Structure..... | 22 |
| 2.3.2 Magnetic Properties..... | 23 |
| 2.4 Conclusion..... | 28 |
| Chapter 3. Investigation of Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ (Ln = La, Gd, Yb) with ^{57}Fe Mössbauer and single crystal X-ray diffraction..... | 30 |
| 3.1 Introduction..... | 30 |
| 3.2 Experimental Section | 31 |
| 3.2.1 Synthesis | 31 |
| 3.2.2 Structural Characterization..... | 32 |
| 3.2.3 Elemental Analysis..... | 38 |
| 3.2.4 Magnetization and Electrical Transport..... | 39 |
| 3.2.5 Mössbauer Spectroscopy..... | 39 |
| 3.3 Results and Discussion..... | 39 |
| 3.3.1 Crystal Structure..... | 39 |
| 3.3.2 Mössbauer Spectroscopy..... | 41 |
| 3.2.3 Crystal Structure Refinements..... | 43 |
| 3.2.4 Magnetization | 45 |
| 3.4 Conclusions..... | 47 |
| Chapter 4. Crystal growth and physical properties of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, a disordered variant of the $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ -structure type | 49 |
| 4.1 Introduction..... | 49 |
| 4.2 Experimental..... | 50 |

| | |
|--|-----|
| 4.2.1 Synthesis | 50 |
| 4.2.2 Powder and Single Crystal X-ray Diffraction..... | 51 |
| 4.2.3 Structural Refinement..... | 51 |
| 4.2.4 Physical Properties..... | 53 |
| 4.3 Results and Discussion..... | 54 |
| 4.3.1 Crystal Structure..... | 54 |
| 4.3.2 Magnetization and Electrical Transport..... | 58 |
| 4.4 Conclusion..... | 61 |
| Chapter 5. Investigation of Fe and Ni incorporation in CeCo ₂ Al ₈ | 62 |
| 5.1 Introduction..... | 62 |
| 5.2 Experimental..... | 62 |
| 5.2.1 Synthesis | 62 |
| 5.2.2 Elemental Analysis..... | 63 |
| 5.2.3 Single Crystal X-ray Diffraction..... | 63 |
| 5.2.4 Structure Refinement..... | 64 |
| 5.3 Results and Discussion..... | 64 |
| 5.3.1 Crystal Structure..... | 64 |
| 5.4 Conclusion..... | 72 |
| Chapter 6. Conclusion and Future Work..... | 73 |
| 6.1 Summary..... | 73 |
| 6.2 Future Work | 77 |
| References..... | 79 |
| Appendix A. Investigating the chemical stability and physical properties of ErM _x Ga ₃ (M = Fe, Co; x < 0.2)..... | 91 |
| A.1 Objective..... | 91 |
| A.2 Synthesis..... | 91 |
| A.3 Elemental Analysis..... | 91 |
| A.4 Physical Properties..... | 92 |
| A.5 Results and Discussion..... | 92 |
| A.6 Crystal Structure..... | 94 |
| A.7 Magnetism..... | 95 |
| A.8 References..... | 96 |
| Appendix B. Investigation of Ce and Yb intermetallics..... | 97 |
| B.1 Introduction..... | 97 |
| B.2 Results and Discussion | 100 |
| B.3 References..... | 102 |
| Appendix C. Letters of Permission..... | 104 |
| C.1 Elsevier..... | 104 |
| C.2 American Chemical Society..... | 111 |
| C.2 Taylor & Francis..... | 114 |

| | |
|---|-----|
| Appendix D. CIF of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ | 115 |
| Appendix E. CIF of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}; 0 \leq x < 1$) | 122 |
| Appendix F. CIF of ErM_xGa_3 ($\text{M} = \text{Fe}, \text{Co}; x < 0.2$) | 170 |
| Vita..... | 185 |

Abstract

The focal point of this dissertation is the investigation of substitution and disorder effects in ternary intermetallics. The crystal growth, crystal structure, and physical properties are reported on single crystals of $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{T}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}$; $\text{T} = \text{Mn}, \text{Fe}$), $\text{LnCr}_2\text{Fe}_x\text{Al}_{20-x}$ ($\text{Ln} = \text{Yb}, \text{Gd}$), $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, and $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Mn}, \text{Fe}, \text{Ni}$; $0 \leq x < 1$). The reported compounds were grown via the flux growth method with the strategic synthetic parameters described. Correlations between the structural and physical properties in relation to substitution and disorder of $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{T}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}$; $\text{T} = \text{Mn}, \text{Fe}$), $\text{LnCr}_2\text{Fe}_x\text{Al}_{20-x}$ ($\text{Ln} = \text{Yb}, \text{Gd}$), $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, and $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Mn}, \text{Fe}, \text{Ni}$; $0 \leq x < 1$) are discussed.

The synthesis and characterization of Mn- and Fe- substituted $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd}, \text{Yb}$) are reported. The compounds adopt the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ structure type with lattice parameters of $a \sim 11 \text{ \AA}$ and $c \sim 17.8 \text{ \AA}$ with structural site preferences for Mn and Fe. The magnetization of $\text{Yb}_6\text{W}_4\text{Al}_{43}$ is sensitive to Mn and Fe doping, which is evident by an increase in the field dependent magnetization. $\text{Gd}_6\text{W}_4\text{Al}_{43}$, $\text{Gd}_6\text{W}_4\text{Al}_{42.31(11)}\text{Mn}_{0.69(11)}$, and $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$ order antiferromagnetically in the ab - and c -direction at 15, 14, and 13 K, respectively, with positive Weiss constants, suggesting the presence of ferromagnetic exchange interactions. Anisotropic magnetization data of $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{T}_y$ ($\text{T} = \text{Mn}, \text{Fe}$) analogs are discussed.

Crystal growth, structure determination, and magnetic properties of $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$) adopting the $\text{CeCr}_2\text{Al}_{20}$ structure type with space group $Fd\bar{3}m$, $a \sim 14.5 \text{ \AA}$, type are reported. Single crystal X-ray diffraction and Mössbauer spectroscopy are employed to fully characterize the crystal structure of $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$). $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$) are the first pseudo-ternaries adopting the $\text{CeCr}_2\text{Al}_{20}$ structure type with a transition metal occupying the main group site. The Yb analogues are Pauli paramagnets with the Yb ion adopting

an electronic configuration close to Yb^{2+} , while the Gd analogues show paramagnetic behavior with no magnetic order down to 3 K.

The synthesis and characterization of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is reported. $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ adopts a disordered variant of the $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ -structure type with lattice parameters of $a = 4.353(5)$ and $c = 38.98(4)$ Å and $V = 639.70(12)$ Å³. The structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is composed of three distinct building blocks: Pd_2Ga_4 , PdGa_2 , and $\text{Sm}_{0.67}\text{Ga}$. The $\text{Sm}_{0.67}\text{Ga}$ slab does not magnetically order, which directly affect the structure. $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is a temperature independent paramagnet. Field dependent magnetization of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ displays anisotropic behavior.

Single crystals of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Mn, Fe, Ni}$; $0 \leq x < 1$) were grown and crystallize in the CaCo_2Al_8 structure type with space group $Pbam$. Single crystal X-ray diffraction data suggest that the Ce $4f$ -state is valence fluctuating as Fe concentration increases, whereas the Ni-doped analogues do not exhibit valence fluctuating. The results suggest that hole doping leads to an admixture of $\text{Ce}^{3+}/\text{Ce}^{4+}$.

Chapter 1. Introduction

1.1 Motivation

Determining the structure and physical properties of materials is one important area of solid state research. Pinpointing the structural features that are responsible for unique physical properties can lead to targeted structure types to consider for optimizing desired properties. Identifying promising candidates that possess the desired properties is approached by first selecting compounds with unique structural motifs. For example, CeIn_3 of the AuCu_3 -structure type orders antiferromagnetic, $T_N \sim 11$ K, and upon application of pressure, the compound become superconducting at ~ 2.3 K.¹ The related homologous series $\text{Ce}_n\text{MIn}_{3n+2}$ ($n = 1, 2$; $\text{M} = \text{Co}, \text{Rh}, \text{Ir}$)²⁻⁷ also exhibit magnetically mediated superconductivity and adopt the HoCoGa_5 - and Ho_2CoGa_8 -structure type,⁸ respectively. CeMIn_5 ($\text{M} = \text{Co}, \text{Rh}, \text{Ir}$) is composed of CeIn_3 cuboctahedra layers stacked periodically with alternating rectangular polyhedra of MIn_2 layers along the c -axis, while Ce_2MIn_8 ($\text{M} = \text{Co}, \text{Rh}, \text{Ir}$) is composed of CeIn_3 cuboctahedra layers stacked along the c -axis with two intervening rectangular polyhedra of MIn_2 layers.⁸ Another example is the AlB_2 type MgB_2 that exhibit superconductivity at $T_c \sim 39$ K⁹ MgB_2 is composed of honeycomb boron planar nets stacked along the c -axis with Mn atoms located in the hexagonal voids like intercalated graphite.⁹ The cause of superconductivity in MgB_2 has been attributed to the metallic nature of the covalently bonded 2D boron sheets and attributed as phonon-mediated BCS-type mechanism.¹⁰

Intermetallic compounds with atoms arranged in a triangular motifs can exhibit magnetic frustration, which can lead to exotic properties. Geometric frustration is correlated to the geometry of the network of spins and inherent to the nearest neighbor antiferromagnetic interactions. Frustrated sublattices are constructed by triangles made of magnetic ions as seen in triangular and

tetrahedral motifs. Triangles and tetrahedra motifs can be packed by corner sharing or edge sharing in two or three dimensions as seen in hexagonal and Kagome networks and pyrochlore lattices, respectively.^{11, 12} The nearest neighbors of any spins in the aforementioned arrangements are themselves nearest neighbors of each other thus making it intrinsically impossible to build a consistent antiferromagnetic configuration leading to numerous degenerate manifolds of spin configurations. Magnetic frustration arises when magnetic ions cannot arrange in favorable interactions causing suppression of long range magnetic ordering to temperature considerably lower than the Weiss constant.^{12, 13} As result exotic behavior can persist such as spin glass behavior. Spin glass system is where the magnetic moments freeze at a temperature into random orientations without long-range order leading to exotic properties such as isothermal time-dependent relaxation.^{14, 15} There are three factors linked to magnetic frustration such as the symmetry of the magnetic sublattice, site disorder, and the dimensionality of the magnetic sublattice. These parameters are attached in extended solids. Intermetallic compounds that adopt the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ -¹⁶ and $\text{CeCr}_2\text{Al}_{20}$ -structure type¹⁷ have Kagome and pyrochlore like networks made up of rare earth atoms or transition metals, respectively. It is of interest to investigate compounds of the aforementioned structure types and to study the effects of substitution on the magnetic ions interactions to discover competing and exotic properties.

Substitution of one element for another or introducing disorder in the structure has been successful in affecting the physical properties of materials. For instance, the LaCo_2B_2 of the ThCr_2Si_2 structure type¹⁸ and is composed of layers of CoB_4 edge sharing tetrahedra alternating with layers of isolated La atom along the *c*-axis.¹⁹ LaCo_2B_2 exhibits metallic resistivity and paramagnetic behavior down to 2 K. Upon isovalent substitution of Y for La, $\text{La}_x\text{Y}_x\text{Co}_2\text{B}_2$, bulk superconductivity was observed at 4.2 K which is attributed to chemical pressure.²⁰ Hole

substitution studies, Fe for Co, led to $\text{La}(\text{Co}_{1-x}\text{Fe}_x)_2\text{B}_2$ that superconducts at ~ 4 K caused by Fe raising the hole concentration to an optimal level for the appearance of superconductivity. Electron doping Si for B, led to $\text{LaCo}_2\text{Bi}_{2-x}\text{Si}_x$ with no superconducting behavior presence.²⁰ Recently quantum criticality has been observed without tuning any control parameters such as pressure in $\beta\text{-YbAlB}_4$, an intermediate valent heavy fermion compound with a Sommerfeld coefficient of ~ 300 mJ/mol K².^{21, 22} Its counterpart, $\alpha\text{-YbAlB}_4$, has a Sommerfeld coefficient of ~ 130 mJ/mol K².²² Heavy fermion behavior is a consequence of the *f*-electrons coupling with conduction electrons, which results in the electrons behaving as if they have an increased mass that results in a large Sommerfeld coefficient, γ , where $C_p = \gamma T + \beta T^3$ ($\gamma > 200$ mJ/mol-K²). Both α - and $\beta\text{-YbAlB}_4$ exhibits Kondo behavior, which can be described as the screening of the local magnetic moment by conduction electrons. In α - and $\beta\text{-YbAlB}_4$, the Yb and Al atoms lie in the *ab*-plane, which is in the middle of two boron networks consisting of pentagonal and heptagonal rings.²² Substitution of Fe for Al led to a volume contraction indicating that Fe substitution applies chemical pressure in α and $\beta\text{-YbAlB}_4$. As a result the Kondo temperature is suppressed and antiferromagnetic ordering persist at ~ 7 and 9 K for $\alpha\text{-YbAlB}_4$ and $\beta\text{-YbAlB}_4$, respectively.²³

1.2 Synthesis

The growth of high quality single crystals is necessary to determine the structure of materials and allows the determination of intrinsic properties of materials necessary to study the physics of materials. The single crystalline compounds presented in this dissertation are grown via the flux growth method.²⁴⁻²⁷ The flux growth method uses metals with relatively low melting points such as gallium (m.p. 30°C), aluminum (m.p. 660°C), tin (m.p. 232°C), lead (m.p. 327°C), indium (m.p. 157°C) and zinc (m.p. 420°C).²⁴ The metallic flux can serve as an inert flux (non-reactive) or reactive (incorporated into the products) flux. Taking advantage of the relatively

low temperature of main group elements, the reaction can be slow-cooled to yield high quality single crystals. This does not discount the possibility of crystal formation during the ramp-up and ramp-down sequence or during dwelling at high temperature. In the flux-growth method, reaction ratios and temperature profiles can be varied to target the growth of the product. The synthetic parameters are strategically mapped out by first consulting the binary phase diagrams.²⁸ An example of a phase diagram is shown in Figure 1. 1.

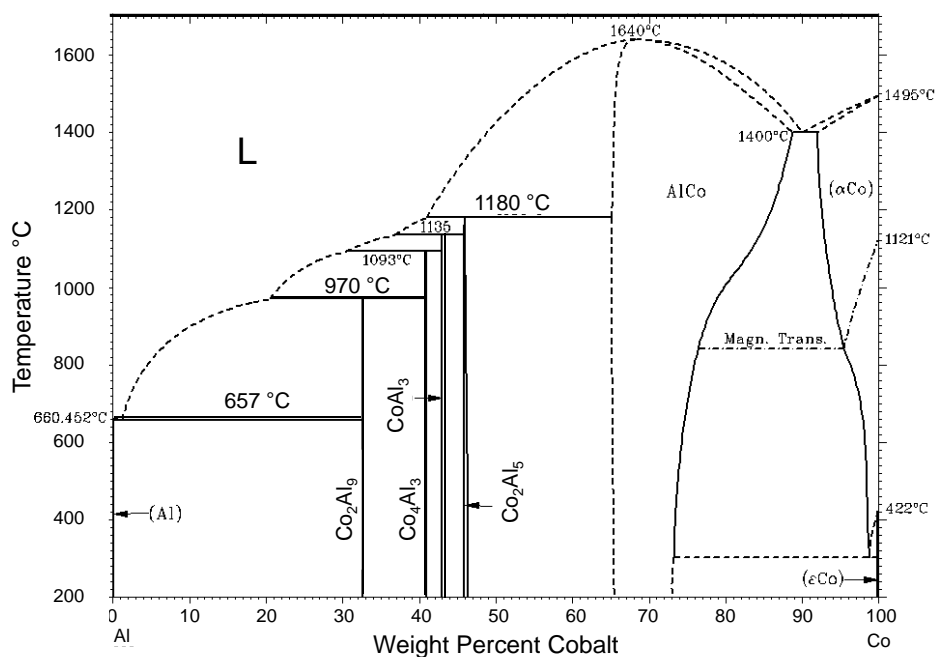


Figure 1.1. Binary phase diagram of Al and Co, as obtained from reference 33.

The binary phase diagram shows the conditions at which a compound is thermodynamically favorable at a specific composition of the two elements.²⁹ Phase boundary lines separate these areas indicating which phase will be stable in that particular region. Every point within this area represents a specific temperature and composition of the respective elements. For the flux growth method, the starting ratios of reactants are chosen to a certain ratio composition in the phase diagram which is often close to the targeted composition of the desired ternary or

binary compound. A typical temperature profile is shown in Figure 1.2. The temperature profile is strategically chosen considering variables such as temperature rates, dwell temperatures, dwell times, and the spin temperature which is typically above the melting point of the metallic flux. All variables in the temperature profile are important and have an effect on the final product. The heating and cooling rates can be adjusted to avoid undesirable phases and change the rate of nucleation and growth.

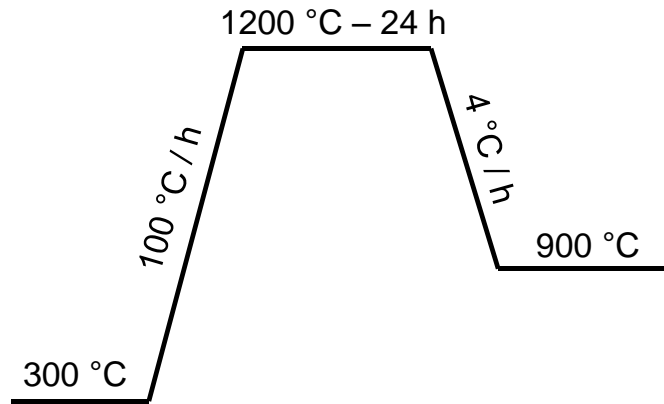


Figure 1.2. A generic temperature profile.

1.3 Characterization

Structure determination in crystalline materials can be achieved by X-ray diffraction. Both powder X-ray diffraction and single crystal X-ray diffraction are used for structural determination. Crystalline samples are bombarded by X-rays, which are scattered in all possible directions by the electrons in the material. The scattered X-rays can be in phase or out of phase given the distance traveled between the X-rays from the source to the sample. When the distance travel between the scattered waves are integral numbers of the wavelength, the X-rays are interacting constructively (in phase). This can be rationalized by Bragg's law, $2d\sin\theta = n\lambda$, where d is the interplanar spacing, θ is the angle between the X-ray beam and the reflecting lattice, n is an integer, and λ is the X-ray wavelength.³⁰ The scattered X-rays are observed in an array of reflection which is

known as the diffraction pattern.³¹ The diffraction pattern provides information by the location and intensity of each reflection. The symmetry and dimensions of the crystalline material is determined by the symmetry of the diffraction pattern and the space separating the reflections. A unique atom and the position of that atom in a crystalline material is determined by the intensity and position of the reflections in the diffraction pattern. The interactions between atoms in the material under investigation are determined through refinement of the crystal structure and is based on the number of electrons of that particular atom. The interatomic distances and angles are determined by the refinement of the structural model, which can lead to insight of the nature of the atoms in a material. Powder and single crystal X-ray diffraction provides an average picture of the crystal structure. The structure can have irregular order of atoms known as disorder.^{32, 33} Disorder in materials can be evident in the structural model by anomalous atomic displacement parameters, unrealistic interatomic distances, and residual electron density peaks. Structural elucidation of the disorder present in a material is essential to the investigation of the structure-property relationship due to the fact the properties are dependent on the particular atom at a unique position and its nearest contacts.

Site disorder in a crystalline material can be rationalized as an irregularity at a specific crystallographic sites from an ordered atomic arrangement in a crystalline material.^{32, 33} Disorder can have a direct effect on the intrinsic physical properties of a material because disorder at one site will alter its nearest neighbors. Disorder can be categorized as dynamic or statistical disorder. Dynamic disorder can be classified as a physical motion in a crystal structure. Statistical disorder can be subdivided into positional and substitutional disorder.^{32, 33} Positional disorder can be classified as the statistical distribution of an atom at different crystallographic sites in a unit cell, while substitutional disorder can be classified as the statistical occupation of the same

crystallographic site by different of atoms.^{32, 33} Both dynamic and statistical disorder are often exhibited in disordered structures, which is observed in their X-ray diffraction pattern by directional and irregularly shaped reflections. The extent of dynamic and statistical disorder can be studied by collecting data at high and low temperatures and comparing the refined models. Dynamic disorder is not significantly affected by thermal fluctuations, so the structural models refined from the high and low data will be similar. However, statistical disorder is affected by thermal fluctuations that is evident in the structural models obtain from the refinement of different temperatures.

The research presented is focused on the investigation of how disorder affects the properties in ternary intermetallics, specifically substitutional disorder.³² By strategically substituting specific elements the carrier concentration can be systematically changed as well as the nearest neighbors contact. One can then investigate the structural and magnetic properties of these compounds to draw general conclusions about the subtle changes caused by substitution.

In addition to X-ray diffraction, scanning electron microscope equipped with an energy dispersive X-ray detector was used to confirm the composition of our products. Mössbauer spectroscopy is a non-destructive technique and can provide information such as electron structure, symmetry, magnetism, phase transition, and lattice dynamics.³⁴⁻³⁶ In particular, ⁵⁷Fe Mössbauer spectroscopy was also used to determine the chemical nature of the Fe-substituted compounds.

1.4 Properties

Our goal is to determine the first-order physical properties of materials including temperature and field dependent magnetic measurements and electrical resistivity. Magnetic behavior of most materials can be classified by the following: diamagnetism, paramagnetism, ferromagnetism, and antiferromagnetism. Magnetic susceptibility, χ , is the ratio of magnetization,

M, to the magnetic field, H. The modified Curie-Weiss law $\chi = \chi_o + (C/(T-\Theta))$ where χ_o is the diamagnetic contribution, C is the Curie Constant and Θ represents the Weiss constant describes the temperature dependency of the magnetic susceptibility of a material. The Curie constant directly relates to the magnetic moment of a sample and is described by the equation $C = (N\mu_B^2\mu_{\text{eff}}^2)/3k_B$, where N, μ_B , μ_{eff} , and k_B represents Avagadro's number, Bohr magneton, effective moment, and the Boltzmann constant, respectively.²⁹ The experimental effective moment can be obtained by a Curie-Weiss fit of the paramagnetic region in the susceptibility. The Weiss constant is related to the strength of the magnetic interactions. The temperature dependence of the resistivity of a material can suggest whether the material is metallic, semiconducting, or superconducting. The resistivity is related to this equation $\rho = R \times (A/l)$, where R is the measured resistance, A is the area of the sample, and l is the length of the sample. The quality of the sample can be evaluated by the residual resistivity ratio (RRR) and strongly dependent on disorder. The magnetic and electrical properties of ternary intermetallics depend on the interactions between the local magnetic moments and conduction electrons.

1.5 Substitution Effects in Rare Earth Intermetallics

The focus on the structural and physical properties of high quality crystalline materials through disorder sets the scope for the body of work presented in this dissertation. Ternary intermetallics can display highly correlated electron behavior such as superconductivity, Kondo behavior, and heavy fermion behavior due to the strong interactions of the conduction electrons with the local magnetic moment. The idea is to study the effects of chemical substitution and disorder in highly correlated extended solids. Four projects will be given to illustrate the effects of disorder in rare earth ternary intermetallics.

The first project involves investigating Mn and Fe in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd}, \text{Yb}$) that adopts the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ -structure type.¹⁶ We were motivated to investigate Mn and Fe substitution in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd}, \text{Yb}$) because of the Kagome network of the Ln atoms. Single crystals of the pseudo-ternary compounds $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}$; $\text{M} = \text{Mn}, \text{Fe}$) were grown using excess Al-flux.³⁷ The Yb analogs are nonmagnetic consistent with the Yb adopting the divalent configuration, Yb^{2+} . Temperature dependent magnetization of $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{T}_y$ ($\text{T} = \text{Mn}, \text{Fe}$) was measured in the *ab*- and *c*-direction. The easy axis is the *ab*-plane which constitutes the Kagome lattice. The Gd-analogues exhibit antiferromagnetic ordering in the *ab*- and *c*- with T_N decreasing in the order of $\sim 15, 14$, and 13 K for $\text{Gd}_6\text{W}_4\text{Al}_{43}$, $\text{Gd}_6\text{W}_4\text{Al}_{42.31(11)}\text{Mn}_{0.69(11)}$, and $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$, respectively. The Gd-analogues also show positive Weiss suggesting net ferromagnetic exchange interaction.

For the second project, we investigated $\text{LnCr}_2\text{Al}_{20}$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$) adopting the $\text{CeCr}_2\text{Al}_{20}$ -structure type¹⁷ because of their Frank-Kasper cages formed by the main group element and pyrochlore like network formed by the transition metals. By means of single crystals X-ray diffraction and ^{57}Fe Mössbauer spectroscopy, we determined that Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ and this is the first pseudo-ternary of the $\text{CeCr}_2\text{Al}_{20}$ -structure type where the transition metal dopant (Fe) substitutes for the main group element: $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{Yb}, \text{Gd}$). Single crystals of $\text{GdCr}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$ exhibit paramagnetic behavior down to 3 K with no magnetic ordering contrary to the polycrystalline $\text{GdCr}_2\text{Al}_{20}$ that display antiferromagnetic ordering at 3.90(5) K. $\text{GdCr}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$ show negative Weiss constant which indicate a dominate antiferromagnetic exchange interaction between the Gd ions.

For the third project we targeted $\text{Sm}_2\text{Pd}_3\text{Ga}_9$ because of the structural complexity of $\text{Yb}_2\text{Pd}_3\text{Ga}_9$.²⁷ However, we grew $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ that adopts a disordered variant of the $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ -

structure type.³⁸ The structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is composed of three distinct building blocks: $\text{Pd}_2\text{Ga}_4 + 2 \times [\text{Sm}_{0.67}\text{Ga}] + \text{PdGa}_2$. The disorder, $\text{Sm}_{0.67}\text{Ga}$, plays a critical role in the structure by not ordering magnetically. As a result $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ adopts a trigonal symmetry instead of a triclinic symmetry like the $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ -structure type. The crystal structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is highly anisotropic given the $(\text{Sm}-\text{Sm})_{ab}$, 4.353(5) Å, and $(\text{Sm}-\text{Sm})_c$, ~ 5.3391 Å and 8.1846 Å, distances. Single crystals of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ exhibit temperature independent paramagnetic behavior. Field dependent of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ exhibits anisotropic behavior.

For the fourth project, we investigated the Fe and Ni substitution in CeCo_2Al_8 . The motivation of this project stems from the fact that CeCo_2Al_8 exhibits Curie Weiss behavior with an effective moment consistent with Ce^{3+} , whereas CeFe_2Al_8 exhibits valence fluctuation consistent with $\text{Ce}^{3+}/\text{Ce}^{4+}$ and Fe not carrying a local moment. The Fe and Ni-doped compounds adopt the CaCo_2Al_8 -structure type which is very robust. Single crystal X-ray diffraction data suggest that the Ce $4f$ -state is valence fluctuating as Fe concentration increases, whereas the Ni-doped analogues do not exhibit valence fluctuating.

Herein, detailed studies of the synthesis, crystal structure, and physical properties of $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}$; $T = \text{Mn}, \text{Fe}$),³⁷ $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$),³⁹ $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, and $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($M = \text{Fe}, \text{Ni}$; $0 \leq x < 1$) are presented, along with the magnetic and structural effects of chemical substitution and disorder.

Chapter 2. The physical properties of $\text{Ln}_6\text{W}_4\text{Al}_{43}$ and substitution studies of Mn and Fe in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ (Ln = Gd, Yb)*

2.1 Introduction

Substitution of elements in rare earth intermetallics can lead to the discovery of competing structural and physical property behavior.⁴⁰⁻⁴⁷ Recently, $\alpha\text{-YbAlB}_4$ ⁴⁸ was reported to form a heavy Fermi liquid state with the specific heat coefficient of $\gamma \sim 130 \text{ mJ mol}^{-1} \text{ K}^{-2}$, while the $\beta\text{-YbAlB}_4$ analog^{21, 49} exhibits quantum criticality without tuning of any control parameters. Motivated by the role of chemical pressure on both polymorphs of YbAlB_4 , it was discovered that Fe substitution leads to a suppression of the Kondo temperature and induces magnetism with $\alpha\text{-YbAlB}_4$ and $\beta\text{-YbAlB}_4$ antiferromagnetically order at ~ 7 and 9 K , respectively.²³ The concentration of the dopants can also lead to the stability of different structures types, as evident by our recent work on $\text{Yb}(\text{Mn}, \text{M})_x\text{Al}_{12-x}$ ($\text{M} = \text{Fe}, \text{Ru}; x \leq 2.5$),⁵⁰ where low concentrations of Fe leads to ThMn_{12} ⁵¹ and $\text{CaCr}_2\text{Al}_{10}$ ⁵² and higher concentrations of Fe leads to $\text{YbFe}_2\text{Al}_{10}$ structure type.⁵³

Recently, doping and substitution studies on compounds that adopt the $\text{CeCr}_2\text{Al}_{20}$ structure type have been investigated because of their structural motif, specifically the Frank-Kasper cages formed by the main group element and interpenetrating rare earth and transition metal sublattices. In particular, $\text{GdFe}_2\text{Zn}_{20}$ orders ferromagnetically at 86 K , while $\text{GdCo}_2\text{Zn}_{20}$ orders antiferromagnetically at 5.7 K . Doping of Co for Fe in $\text{GdFe}_2\text{Zn}_{20}$ leads to a competition between ferromagnetism and antiferromagnetism based on the filling of the electronic states.⁵⁴ Also, substitution of transition metals in $\text{RT}_2\text{Zn}_{20}$ can greatly impact ordering temperatures as seen in $\text{TbCo}_2\text{Zn}_{20}$ ($T_N \sim 2.5 \text{ K}$) and ferromagnetic $\text{TbFe}_2\text{Zn}_{20}$ ($T_c \sim 66 \text{ K}$).⁵⁵ Furthermore, such studies

*Reprinted with permission from Treadwell, L. J.; Watkins-Curry, P.; McAlpin, J. D.; Prestigiacomo, J.; Stadler, S.; Chan, J. Y., Substitution studies of Mn and Fe in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ (Ln=Gd, Yb) and the structure of $\text{Yb}_6\text{Ti}_4\text{Al}_{43}$. *J. Solid State Chem.* **2014**, 210, 267-274. Copyright 2014 Elsevier.

have led to the first pseudo-ternaries, $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La, Gd, Yb}$), adopting the $\text{CeCr}_2\text{Al}_{20}$ structure type with a transition metal occupying the main group site.³⁹

The $\text{CeCr}_2\text{Al}_{20}$ and $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ structure types share similar structural motifs such as interpenetrating rare earth and transition metal sublattices as well as one unique rare earth site.^{56,}
⁵⁷ The $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ structure type can be adopted for small lanthanides and mid transition metals ($\text{Ln} = \text{Y, Nd, Sm, Gd-Lu, U}$, and $\text{M} = \text{Ti, V, Nb, Ta, Cr, W}$, and Mo).¹⁶ Motivated by the structural motif of the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ structure type, we have chosen to synthesize and characterize $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd, Yb}$) and investigate Fe and Mn site preference and the influence of doping on the magnetic properties. Herein, we report the synthesis, crystal structure, and anisotropic magnetic properties of $\text{Ln}_6\text{W}_4\text{Al}_{43}$ and pseudo-ternary compounds $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd, Yb}$; $\text{M} = \text{Mn, Fe}$).

2.2 Experimental

2.2.1 Synthesis

The flux growth technique was selected to grow single crystals of $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd, Yb}$; $\text{M} = \text{Mn, Fe}$), as shown in Figure 2.1, and a summary of all reaction ratios and temperature profiles for $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd, Yb}$; $\text{M} = \text{Mn, Fe}$) are provided in Table 2.1. This technique uses a low-melting metal as a solvent (flux) which enables metals with higher melting points to dissolve at relatively low temperatures.²⁵⁻²⁷ Single crystals of $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd, Yb}$) were grown with excess Al flux. Ln, W, and Al were weighed in atomic ratios of 1:2:50 and placed in alumina crucibles. The crucibles were placed into a fused silica tube, which were then evacuated (50–70 mTorr) and sealed. The evacuated silica tubes were placed into a furnace, and heated at a rate of 160 °C/h to 1000 °C, where they dwelled for 5.2 h. Then the vessels were cooled to 700 °C at a ramp down rate of 5.5 °C/h. After this temperature was reached, the silica

tubes were centrifuged to separate crystals from the aluminum flux. The single crystal with approximate dimensions of $\sim 1 \times 1 \times 2 \text{ mm}^3$ were etched in dilute NaOH until aluminum flux was removed from the surface of the metallic crystals and then cleaned with dilute ($\sim 0.1 \text{ M}$) HNO_3 .

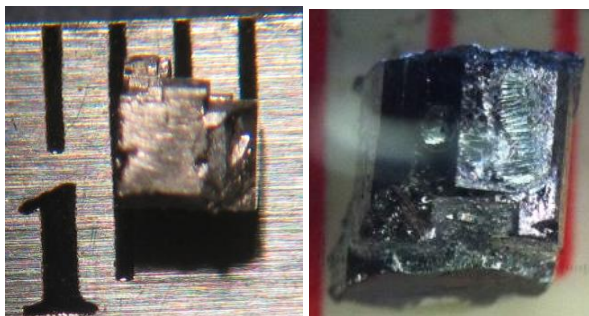


Figure 2.1. Aggregates of single crystal $\text{Yb}_6\text{W}_{4-x}\text{Al}_{43-y}\text{Mn}_{x+y}$ (left) and $\text{Gd}_6\text{W}_{4-x}\text{Al}_{43-y}\text{Mn}_{x+y}$ (right) are shown.

Table 2.1 $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (M = Mn, Fe) Reaction Profile

| Targeted compound | Ratio (Ln:M:Al:T) | Ramp rate up ($^{\circ}\text{C/h}$) | Dwell temp. ($^{\circ}\text{C}$) | Dwell time (h) | Ramp rate down ($^{\circ}\text{C/h}$) | Spin temp. ($^{\circ}\text{C}$) | Product(s) |
|--|-------------------|---------------------------------------|------------------------------------|----------------|---|-----------------------------------|--|
| $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{T}_{x+y}$ (Ln = Gd, Yb; T = Mn, Fe) | 1:1:50:1 | 160 | 1000 | 5.2 | 5.5 | 700 | Single crystals of $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{T}_{x+y}$ (Ln = Gd, Yb; T = Mn, Fe), LnAl_3 (Ln = Gd, Yb), and |
| | 1:1.5:50:0.5 | 160 | 1000 | 5.2 | 5.5 | 700 | $\text{LnT}_2\text{Al}_{10}$ (Ln = Gd, Yb; T = Mn, Fe) |

2.2.2 Single-Crystal X-ray Diffraction

For crystal structure determinations, fragments of single crystals with approximate dimensions of $\sim 0.05 \times 0.07 \times 0.08 \text{ mm}^3$ were chosen and glued onto glass fibers with epoxy. The fibers were mounted on a Nonius Kappa CCD X-ray diffractometer equipped with a Mo $K\alpha$ radiation source ($\lambda = 0.72073 \text{ \AA}$) at room temperature. Crystal structures were solved by direct methods with SIR92⁵⁸ and refined with SHELXL97.⁵⁹ The atomic positions, Wyckoff symmetries, displacement parameters, site occupancies, and interatomic distances of $\text{Ln}_6\text{W}_4\text{Al}_{43}$ and $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (Ln = Gd, Yb; M = Mn, Fe) are provided in Tables 2.2-2.7.

Table 2.2. Crystallographic Parameters of $\text{Ln}_6\text{W}_4\text{Al}_{43}$ (Ln = Gd, Yb)

| <i>Compound</i> | $\text{Gd}_6\text{W}_4\text{Al}_{43}$ | $\text{Yb}_6\text{W}_4\text{Al}_{43}$ |
|---------------------------------------|---------------------------------------|---------------------------------------|
| Crystal system | Hexagonal | Hexagonal |
| Space group | $P6_3/mcm$ | $P6_3/mcm$ |
| a (Å) | 11.0240(10) | 11.0040(3) |
| b (Å) | 11.0240(10) | 11.0040(3) |
| c (Å) | 17.7780(19) | 17.7280(7) |
| V (Å ³) | 1871.1(3) | 1859.05(10) |
| Z | 2 | 2 |
| Crystal dimensions (mm ³) | 0.05 x 0.07 x 0.1 | 0.05 x 0.08 x 0.1 |
| θ range (°) | 2.13 - 30.01 | 3.14 - 30.01 |
| μ (mm ⁻¹) | 23.735 | 23.36 |
| <i>Data Collection and Refinement</i> | | |
| Measured reflections | 6054 | 5974 |
| Independent reflections | 1026 | 1017 |
| Reflections with $I > 2\sigma(I)$ | 955 | 878 |
| R_{int} | 0.0349 | 0.0779 |
| h | -15 to 15 | -15 to 15 |
| k | -12 to 12 | -12 to 12 |
| l | -18 to 24 | -24 to 21 |
| R_1^a | 0.0221 | 0.0285 |
| wR_2^b | 0.0522 | 0.0573 |
| Reflections | 1026 | 1017 |
| Parameters | 54 | 54 |
| $\Delta\rho_{\text{max}}$ | 1.475 | 1.314 |
| $\Delta\rho_{\text{min}}$ | -1.836 | -1.713 |
| Extinction coefficient | 0.00056(5) | 0.00085(9) |
| GOF | 1.214 | 1.067 |

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|$$

$$^b R_w = [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0393 P)^2 + 22.11 P],$$

$$[\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0227 P)^2 + 25.53 P], \text{ and } [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2};$$

$$w = 1/[\sigma^2(F_o^2) + (0.0291 P)^2] \text{ for } \text{Yb}_6\text{W}_4\text{Al}_{43} \text{ and } \text{Gd}_6\text{W}_4\text{Al}_{43}, \text{ respectively.}$$

Table 2.3. Ln₆W₄Al₄₃ Atomic Positions (Ln = Gd, Yb)

| Element | Wyckoff position | Symmetry | x | y | z | Occupancy | U _{eq} ^a |
|---|------------------|------------|-------------|-------------|-------------|-----------|------------------------------|
| Gd ₆ W ₄ Al ₄₃ | | | | | | | |
| Gd1 | 12k | <i>m</i> | 0.53199(6) | 0 | 0.09572(3) | 1.00 | 0.01237(16) |
| W1 | 6g | <i>mm</i> | 0.73173(4) | 0 | 1/4 | 1.00 | 0.00620(12) |
| W2 | 2b | $\bar{3}m$ | 0 | 0 | 0 | 1.00 | 0.00648(16) |
| Al1 | 24l | 1 | 0.15864(19) | 0.39462(18) | 0.16372(10) | 1.00 | 0.0111(3) |
| Al2 | 12k | <i>m</i> | 0.1605(2) | 0 | 0.61382(14) | 1.00 | 0.0101(5) |
| Al3 | 12k | <i>m</i> | 0.2537(2) | 0 | 0.03015(15) | 1.00 | 0.0100(5) |
| Al4 | 12j | <i>m</i> | 0.1469(3) | 0.5962(3) | 1/4 | 1.00 | 0.0107(5) |
| Al5 | 12i | 2 | 0.24714(13) | 0.4943(3) | 0 | 1.00 | 0.0118(5) |
| Al6 | 8h | 3 | 1/3 | 2/3 | 0.12831(13) | 0.939(3) | 0.0123(7) |
| W6 | 8h | 3 | 1/3 | 2/3 | 0.12831(13) | 0.061(3) | 0.0123(7) |
| Al7 | 6g | <i>m2m</i> | 0.1486(3) | 0 | 1/4 | 1.00 | 0.0096(9) |
| Yb ₆ W ₄ Al ₄₃ | | | | | | | |
| Yb1 | 12k | <i>m</i> | 0.46896(4) | 0 | 0.09475(2) | 1.00 | 0.01041(15) |
| W1 | 6g | <i>mm</i> | 0.26884(4) | 0 | 1/4 | 1.00 | 0.00655(16) |
| W2 | 2b | $\bar{3}m$ | 0 | 0 | 0 | 1.00 | 0.0069(2) |
| Al1 | 24l | 1 | 0.2369(2) | 0.3944(2) | 0.16349(12) | 1.00 | 0.0110(4) |
| Al2 | 12k | <i>m</i> | 0.1610(3) | 0 | 0.11401(16) | 1.00 | 0.0113(6) |
| Al3 | 12k | <i>m</i> | 0.2544(3) | 0 | 0.53107(17) | 1.00 | 0.0110(6) |
| Al4 | 12j | <i>m</i> | 0.1464(3) | 0.5502(3) | 1/4 | 1.00 | 0.0107(6) |
| Al5 | 12i | 2 | 0.24704(15) | 0.4941(3) | 0 | 1.00 | 0.0117(6) |
| Al6 | 8h | 3 | 1/3 | 2/3 | 0.12613(19) | 0.673(12) | 0.0088(6) |
| Al7 | 6g | <i>m2m</i> | 0.8520(4) | 0 | 1/4 | 1.00 | 0.0103(8) |

^a U_{eq} is defined as one-third of the trace of the orthogonalized U_{ij} tensor.

Table 2.4. Selected Interatomic Distances of $\text{Ln}_6\text{W}_4\text{Al}_{43}$ (Ln = Gd, and Yb)

| | Gd ₆ W ₄ Al ₄₃ | Yb ₆ W ₄ Al ₄₃ |
|----------------------------|---|---|
| Ln (17 coordinate) | | |
| Al11 x 2 | 3.0680(18) | 3.059(2) |
| Al4 x 2 | 3.0877(13) | 3.0825(14) |
| Al5 x 2 | 3.1017(4) | 3.0872(4) |
| Al3 x 1 | 3.260(3) | 3.246(3) |
| Al3 x 1 | 3.267(2) | 3.248(3) |
| Al6 x 2 | 3.2535(5) | 3.2442(6) |
| Al1 x 2 | 3.3259(24) | 3.331(2) |
| Al5 x 2 | 3.3991(30) | 3.38(3) |
| Al2 x 2 | 3.0877(13) | 3.0825(14) |
| Ln1 x 1 | 3.4574(6) | 3.422(7) |
| W1 x 1 | 3.5309(5) | 3.5212(5) |
| W1 (12coordinate) | | |
| Al7 x 2 | 2.7271(18) | 2.730(2) |
| Al2 x 2 | 2.697(2) | 2.683(3) |
| Al4 x 2 | 2.697(2) | 2.683(3) |
| Al1 x 4 | 2.7271(18) | 2.730(2) |
| Ln1 x 2 | 3.5661(5) | 3.5675(5) |
| W2 (12 coordinate) | | |
| Al2 x 6 | 2.688(2) | 2.685(3) |
| Al3 x 6 | 2.847(2) | 2.854(3) |
| Ln-Ln Network | | |
| Ln-Ln NN ^a // c | 3.4574(6) | 3.422(7) |
| Ln-Ln NNN ^b //c | 5.4987(8) | 5.4940(7) |
| Ln-Ln //ab | 5.5432(6) | 5.54(4) |

^a Nearest Neighbor

^b Next Nearest Neighbor

Table 2.5. $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (M = Mn, Fe) Crystallographic Parameters

| Compound | $\text{Gd}_6\text{W}_4\text{Al}_{42.31(11)}\text{Mn}_{0.69(11)}$ | $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$ | $\text{Yb}_6\text{W}_{3.86(7)}\text{Al}_{41.76(7)}\text{Mn}_{1.39(7)}$ | $\text{Yb}_6\text{W}_4\text{Al}_{41.76(12)}\text{Fe}_{1.24(12)}$ |
|--|--|--|--|--|
| Crystal System | Hexagonal | Hexagonal | Hexagonal | Hexagonal |
| Space Group | $P6_3/mcm$ | $P6_3/mcm$ | $P6_3/mcm$ | $P6_3/mcm$ |
| a (Å) | 11.005(3) | 10.993(1) | 10.975(1) | 10.971(3) |
| c (Å) | 17.746(8) | 17.726(3) | 17.611(3) | 17.612(5) |
| V (Å ³) | 1861.3(1) | 1855.1(4) | 1837.06(4) | 1835.8(8) |
| Z | 2 | 2 | 2 | 2 |
| Crystal dimensions (mm ³) | 0.05 x 0.05 x 0.05 | 0.05 x 0.05 x 0.05 | 0.05 x 0.05 x 0.05 | 0.05 x 0.05 x 0.05 |
| θ range (°) | 3.14 – 30.97 | 3.14 – 32.00 | 2.55 – 32.03 | 3.15 – 32.03 |
| μ (mm ⁻¹) | 24.068 | 24.398 | 28.592 | 29.076 |
| Data Collection | | | | |
| Measured Reflections | 3693 | 3742 | 4005 | 4000 |
| Independent Reflections | 1100 | 1201 | 1192 | 1191 |
| Reflections with $I > 2\sigma(I)$ | 1053 | 1098 | 1048 | 1160 |
| R_{int} | 0.0193 | 0.0494 | 0.0326 | 0.0187 |
| h | -15 to 15 | -16 to 16 | -16 to 16 | -16 to 16 |
| k | -13 to 13 | -13 to 13 | -13 to 13 | -13 to 13 |
| l | -25 to 25 | -21 to 26 | -26 to 26 | -26 to 26 |
| Refinement | | | | |
| $R_1(F)^a$ | 0.0212 | 0.0316 | 0.0224 | 0.0196 |
| wR_2^b | 0.0565 | 0.0734 | 0.0496 | 0.0452 |
| Reflections | 1100 | 1201 | 1192 | 1191 |
| Parameters | 54 | 54 | 55 | 54 |
| $\Delta\rho_{\text{max}}$ (e Å ⁻³) | 1.455 | 1.955 | 1.83 | 1.295 |
| $\Delta\rho_{\text{min}}$ (e Å ⁻³) | -2.698 | -3.171 | -1.531 | -1.337 |
| Extinction coefficient | 0.00158(8) | 0.00126(9) | 0.00049(4) | 0.00059(4) |
| GOF | 1.114 | 1.138 | 1.06 | 1.219 |

$$^a R_1 = \Sigma ||F_o| - |F_c|| / \Sigma |F_o|$$

$^b wR_2 = [\Sigma [w(F_o^2 - F_c^2)^2] / \Sigma [w(F_o^2)^2]]^{1/2}$; $w = 1/[\sigma^2(F_o^2) + (0.0341 P)^2 + 8.6856 P]$, $[\Sigma [w(F_o^2 - F_c^2)^2] / \Sigma [w(F_o^2)^2]]^{1/2}$; $w = 1/[\sigma^2(F_o^2) + (0.0407 P)^2 + 2.0640 P]$, and $[\Sigma [w(F_o^2 - F_c^2)^2] / \Sigma [w(F_o^2)^2]]^{1/2}$; $w = 1/[\sigma^2(F_o^2) + (0.0278 P)^2 + 4.8451 P]$, and $[\Sigma [w(F_o^2 - F_c^2)^2] / \Sigma [w(F_o^2)^2]]^{1/2}$; $w = 1/[\sigma^2(F_o^2) + (0.0163 P)^2 + 15.2874 P]$, $[\Sigma [w(F_o^2 - F_c^2)^2] / \Sigma [w(F_o^2)^2]]^{1/2}$ for $\text{Gd}_6\text{W}_4\text{Al}_{42.31(11)}\text{Mn}_{0.69(11)}$, $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$, $\text{Yb}_6\text{W}_{3.86(7)}\text{Al}_{41.76(7)}\text{Mn}_{1.39(7)}$, and $\text{Yb}_6\text{W}_4\text{Al}_{41.76(12)}\text{Fe}_{1.24(12)}$ respectively.

Table 2.6. $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (M = Mn, Fe) Atomic Positions

| Element | Wyckoff position | Symmetry | x | y | z | Occupancy | U_{eq}^a |
|---|------------------|------------|-------------|-------------|--------------|-----------|-------------------|
| Gd₆W₄Al_{42.31(11)}Mn_{0.69(11)} | | | | | | | |
| Gd1 | 12k | <i>m</i> | 0.46913(3) | 0 | 0.095410(15) | 1.00 | 0.01031(10) |
| W1 | 6g | <i>mm</i> | 0.26799(3) | 0 | 1/4 | 1.00 | 0.00699(10) |
| W2 | 2b | $\bar{3}m$ | 0 | 0 | 0 | 1.00 | 0.00691(12) |
| Al1 | 24l | 1 | 0.23586(13) | 0.39526(13) | 0.16377(7) | 1.00 | 0.0116(2) |
| Al2 | 12k | <i>m</i> | 0.16061(16) | 0 | 0.11402(10) | 1.00 | 0.0110(3) |
| Al3 | 12k | <i>m</i> | 0.25427(16) | 0 | 0.53023(11) | 1.00 | 0.0108(3) |
| Al4 | 12j | <i>m</i> | 0.14763(19) | 0.55050(18) | 1/4 | 1.00 | 0.0110(3) |
| Al5 | 12i | 2 | 0.24748(9) | 0.49497(19) | 0 | 1.00 | 0.0161(4) |
| Al6 | 8h | 3 | 1/3 | 2/3 | 0.12809(11) | 0.826(11) | 0.0123(5) |
| Mn6 | 8h | 3 | 1/3 | 2/3 | 0.12809(11) | 0.174(11) | 0.0123(5) |
| Al7 | 6g | <i>m2m</i> | 0.8512(2) | 0 | 1/4 | | 0.0094(4) |
| Gd₆W₄Al_{41.69(12)}Fe_{1.30(12)} | | | | | | | |
| Gd1 | 12k | <i>m</i> | 0.46896(3) | 0 | 0.09546(2) | 1.00 | 0.01055(12) |
| W1 | 6g | <i>mm</i> | 0.26736(3) | 0 | 1/4 | 1.00 | 0.00654(12) |
| W2 | 2b | $\bar{3}m$ | 0 | 0 | 0 | 1.00 | 0.00648(15) |
| Al1 | 24l | 1 | 0.23586(16) | 0.39665(16) | 0.16311(10) | 1.00 | 0.0122(3) |
| Al2 | 12k | <i>m</i> | 0.1610(2) | 0 | 0.11382(14) | 1.00 | 0.0109(4) |
| Al3 | 12k | <i>m</i> | 0.25491(19) | 0 | 0.53025(14) | 1.00 | 0.0109(4) |
| Al4 | 12j | <i>m</i> | 0.1491(2) | 0.5510(2) | 1/4 | 1.00 | 0.0113(4) |
| Al5 | 12i | 2 | 0.24855(13) | 0.4971(3) | 0 | 1.00 | 0.0226(6) |
| Al6 | 8h | 3 | 1/3 | 2/3 | 0.13049(14) | 0.673(12) | 0.0156(7) |
| Fe6 | 8h | 3 | 1/3 | 2/3 | 0.13049(14) | 0.327(12) | 0.0156(7) |
| Al7 | 6g | <i>m2m</i> | 0.8500(3) | 0 | 1/4 | 1.00 | 0.0096(6) |
| Yb₆W_{3.86(7)}Al_{41.76(7)}Mn_{1.39(7)} | | | | | | | |
| Yb1 | 12k | <i>m</i> | 0.46796(2) | 0 | 0.095272(14) | 1.00 | 0.01039(9) |
| W1 | 6g | <i>mm</i> | 0.26692(3) | 0 | 1/4 | 0.952(3) | 0.00692(11) |
| Fe1 | 6g | <i>mm</i> | 0.26692(3) | 0 | 1/4 | 0.048(3) | 0.00692(11) |
| W2 | 2b | $\bar{3}m$ | 0 | 0 | 0 | 1.00 | 0.00671(12) |
| Al1 | 24l | 1 | 0.23643(14) | 0.39665(13) | 0.16249(8) | 1.00 | 0.0112(3) |

(Table 2.6. continued)

| Element | Wyckoff position | Symmetry | x | y | z | Occupancy | U_{eq}^a |
|---|------------------|------------|-------------|-------------|--------------|-----------|-------------|
| Al2 | 12k | <i>m</i> | 0.16010(16) | 0 | 0.11427(10) | 1.00 | 0.0096(3) |
| Al3 | 12k | <i>m</i> | 0.25532(16) | 0 | 0.53060(11) | 1.00 | 0.0105(4) |
| Al4 | 12j | <i>m</i> | 0.1485(2) | 0.54950(18) | 1/4 | 1.00 | 0.0117(4) |
| Al5 | 12i | 2 | 0.24838(10) | 0.4968(2) | 0 | 1.00 | 0.0205(5) |
| Al6 | 8h | 3 | 1/3 | 2/3 | 0.12932(11) | 0.688(10) | 0.0145(5) |
| Fe6 | 8h | 3 | 1/3 | 2/3 | 0.12932(11) | 0.312(10) | 0.0145(5) |
| Al7 | 6g | <i>m2m</i> | 0.8496(2) | 0 | 1/4 | 1.00 | 0.0098(5) |
| Yb₆W₄Al_{41.76(12)}Fe_{1.24(12)} | | | | | | | |
| Yb1 | 12k | <i>m</i> | 0.46819(2) | 0 | 0.095210(13) | 1.00 | 0.00830(7) |
| W1 | 6g | <i>mm</i> | 0.26727(2) | 0 | 1/4 | 1.00 | 0.00420(7) |
| W2 | 2b | $\bar{3}m$ | 0 | 0 | 0 | 1.00 | 0.00424(10) |
| Al1 | 24l | 1 | 0.23658(13) | 0.39730(12) | 0.16246(7) | 1.00 | 0.0098(2) |
| Al2 | 12k | <i>m</i> | 0.16069(16) | 0 | 0.11393(9) | 1.00 | 0.0086(3) |
| Al3 | 12k | <i>m</i> | 0.25599(15) | 0 | 0.53066(10) | 1.00 | 0.0095(3) |
| Al4 | 12j | <i>m</i> | 0.14877(19) | 0.55033(17) | 1/4 | 1.00 | 0.0097(3) |
| Al5 | 12i | 2 | 0.24844(10) | 0.49689(19) | 0 | 1.00 | 0.0199(4) |
| Al6 | 8h | 3 | 1/3 | 2/3 | 0.13003(10) | 0.673(12) | 0.0131(5) |
| Fe6 | 8h | 3 | 1/3 | 2/3 | 0.13003(10) | 0.327(12) | 0.0131(5) |
| Al7 | 6g | <i>m2m</i> | 0.8493(2) | 0 | 1/4 | 1.00 | 0.0087(4) |

^a U_{eq} is defined as one-third of the trace of the orthogonalized U_{ij} tensor

Table 2.7. $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (M = Mn, Fe) Selected Interatomic Distances

| | $\text{Gd}_6\text{W}_4\text{Al}_{42.31(11)}\text{Mn}_{0.69(11)}$ | $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$ | $\text{Yb}_6\text{W}_{3.86(7)}\text{Al}_{41.76(7)}\text{Mn}_{1.39(7)}$ | $\text{Yb}_6\text{W}_4\text{Al}_{41.76(12)}\text{Fe}_{1.24(12)}$ |
|--------------------|--|--|--|--|
| Ln (17 coordinate) | | | | |
| Al1 x 2 | 3.0649(14) | 3.0588(16) | 3.0519(13) | 3.0482(13) |
| Al4 x 2 | 3.0843(13) | 3.0865(12) | 3.0699(9) | 3.0720(11) |
| Al5 x 2 | 3.0969(7) | 3.0950(4) | 3.0797(2) | 3.0793(6) |
| Al3 x 1 | 3.2499(17) | 3.2407(19) | 3.2186(18) | 3.2147(18) |
| Al3 x 1 | 3.2563(14) | 3.2481(14) | 3.2436(18) | 3.2325(19) |
| Al6 x 2 | 3.2472(8) | 3.2515(6) | 3.2436(4) | 3.2447(8) |
| Al1 x 2 | 3.3136(17) | 3.2944(17) | 3.2829(18) | 3.2808(13) |
| Al5 x 2 | 3.0969(7) | 3.3893(21) | 3.3838(20) | 3.3812(20) |
| Al2 x 1 | 3.4113(13) | 3.4010(12) | 3.3953(9) | 3.3897(13) |
| Ln1 x 1 | 3.4538(15) | 3.4524(7) | 3.4286(3) | 3.4255(10) |
| M1 x 1 | 3.5250(10) | 3.5236(5) | 3.5062(2) | 3.5058(8) |
| W1 (12 coordinate) | | | | |
| Al7 x 2 | 2.5593(6) | 2.5516(30) | 2.5438(2) | 2.5463(19) |
| Al2 x 2 | 2.6869(19) | 2.6822(23) | 2.6623(17) | 2.6665(17) |
| Al4 x 2 | 2.6935(18) | 2.7015(19) | 2.6870(18) | 2.6906(18) |
| Al1 x 4 | 2.7213(13) | 2.7258(16) | 2.7278(13) | 2.7287(13) |
| Ln1 x 2 | 3.5250(10) | 3.5236(5) | 3.5062(2) | 3.5058(8) |
| W2 (12 coordinate) | | | | |
| Al2 x 6 | 2.6866(19) | 2.6839(24) | 2.6716(17) | 2.6710(17) |
| Al3 x 6 | 2.8492(18) | 2.8531(12) | 2.8535(18) | 2.8599(18) |
| Ln-Ln Network | | | | |
| Ln-Ln NN // c^a | 3.4538(15) | 3.4524(7) | 3.4286(3) | 3.4255(10) |
| Ln-Ln NNN // c^b | 5.4867(25) | 5.4788(11) | 5.4498(4) | 5.4523(16) |
| Ln-Ln // ab | 5.5339(14) | 5.5282(4) | 5.5212(1) | 5.5187(14) |

^aNearest neighbors^bNext nearest neighbor

An unusually small atomic displacement parameter (ADP) on the Al6, in comparison to the others Al sites, coupled with residual electron density was observed in $\text{Gd}_6\text{W}_4\text{Al}_{43}$ and $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (Ln = Gd, Yb; M = Mn, Fe). Therefore, in $\text{Gd}_6\text{W}_4\text{Al}_{43}$ and $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (Ln = Gd, Yb; M = Mn, Fe), the parent transition metal (W) and the dopant (M = Mn, Fe) were modeled on the Al6 site to identify the best statistical model. First, the parent transition metal (W) was modeled on the Al6 site, which resulted in suitable ADP for $\text{Gd}_6\text{W}_4\text{Al}_{43}$ and unusually large ADP in $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (Ln = Gd, Yb; M = Mn, Fe) signifying excessive electron density. As a result, the dopant (M) was modeled on the Al6 site which resulted in a well behaved ADP, concluding that the dopant (M = Mn, Fe) is occupying the Al6 site. There was no residual electron density observed on the Al6 site during refinement of $\text{Yb}_6\text{W}_4\text{Al}_{43}$, indicative of a fully occupied Al-site. The structural refinement of Mn in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ led to $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y$ and $\text{Yb}_6\text{W}_{4-x}\text{Al}_{43-y}\text{Mn}_{x+y}$ as the best statistical models. For $\text{Ln}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$ (Ln = Gd, Yb), the Fe was only modeled on the Al6 site because refining Fe on either transition metal site led to an unstable refinement model. This behavior is consistent with the fact that the latter transition metals do not form in the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ structure type.¹⁷

2.2.3 Elemental Analysis

Elemental analysis was performed via energy dispersive spectroscopy (EDS) using a EDAX detector equipped with a FEI Quanta 200 scanning electron microscope with an accelerating voltage of 20 kV. Spectra were integrated for 60 seconds and the results from 7-10 spots were averaged and normalized to Ln. The approximate compositions obtained by normalizing the EDS composition to the lanthanide are $\text{Gd}_6\text{W}_{3.5(1)}\text{Al}_{40.2(6)}$, $\text{Yb}_6\text{W}_{4.2(2)}\text{Al}_{46.5(2)}$, $\text{Gd}_6\text{W}_{3.76(14)}\text{Al}_{44.23(25)}\text{Mn}_{0.3(1)}$, $\text{Gd}_6\text{W}_{4.03(2)}\text{Al}_{45.33(26)}\text{Fe}_{1.29(3)}$, $\text{Yb}_6\text{W}_{4.2(2)}\text{Al}_{46.5(2)}$, $\text{Yb}_6\text{W}_{3.43(7)}\text{Al}_{41.68.33(18)}\text{Mn}_{1.12(3)}$, and $\text{Yb}_6\text{W}_{3.9(4)}\text{Al}_{46.33(25)}\text{Fe}_{0.2(1)}$.

2.2.4 Physical Properties

Magnetic data were collected on oriented single crystals using a Quantum Design Magnetic Property Measurement System (MPMS). The temperature-dependent susceptibility was measured under zero-field (ZFC) and field-cooled (FC) conditions between 1.8 and 300 K with an applied magnetic field of 0.1 T in the *ab*- and *c*-direction. Also, temperature-dependent susceptibility was measured in ZFC and FC conditions between 1.8 K and 50 K with 0.01 T in the *ab*- and *c*-directions. Field-dependent magnetization data were measured at 1.8 K with fields up to 9 T for all Gd-analogues and at 3 K with applied fields up to 7 T for the Yb-analogues.

2.3 Results and Discussion

2.3.1 Crystal Structure

$\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ (Ln = Gd, Yb; M = Mn, Fe) adopts the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ structure type (space group $P6_3/mcm$) with $a \sim 11$ Å and $c \sim 17$ Å. The crystal structure of $\text{Yb}_6\text{W}_4\text{Al}_{43}$ is shown in Figure 2.2. Each W1 polyhedron is surrounded by 10 Al and 2 Yb atoms, with W-Al interatomic distances ranging from 2.6027(9) to 2.7304(10) Å and a W-Yb interatomic distance of 3.5339(4) Å. The W1 icosahedra are corner-sharing with each other by Al atoms. W2 atoms are surrounded by 12 Al atoms with interatomic distances of 2.7047(14) Å and 2.8538(14) Å. Yb is 17 coordinate with Yb-Al distances ranging from 3.07454(10) Å for Al1 to 3.4966(7) Å for Al2 and Yb-W1 contact of 3.5339(4) Å, and Yb-Yb distance of 3.4709(3) Å. The Yb atoms form two pairs of Kagome lattices stacked in the *c*-direction shown in Figure 2.3. All triangular networks are equilateral with an in-plane distance of 5.54(4) Å separating Yb atoms. The two sets of triangular networks are separated by 3.422(7) Å, while 5.4940(7) Å separates the individual triangular nets. Instead of the triangular networks lining parallel in the *c*-direction, the latter pair is twisted by ~ 4 degrees, illustrated in Figure 2.3. All Al environments are 12 coordinate forming distorted

icosahedra around Al4, Al5, and Al6 and distorted bi-capped pentagonal prisms around Al1, Al2, Al3, and Al7. Uniquely, the Al6 position resides directly in-plane and in the voids of the triangular network formed by Yb atoms. Therefore, Al6 distorted icosahedron is capped with three Yb atoms making it the center piece of the Kagome network shown in Figure 2.4. The best statistical models of $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}; \text{M} = \text{Mn}, \text{Fe}$) consist of a dopant ($\text{M} = \text{Mn}, \text{Fe}$) occupying the Al6 site. The un-doped analog $\text{Yb}_6\text{W}_4\text{Al}_{43}$ consist of a fully occupied Al6 site whereas a mix-occupancy on the Al6 site (92.9 % Al and 6.1 % W) is observed for $\text{Gd}_6\text{W}_4\text{Al}_{43}$. As a result of Mn and Fe occupying the Al6 site, the Yb-Yb distance should increase and Gd-Gd should decrease. The Yb-Yb in-plane distance of the un-doped analog is 3.4209(7) Å, while the Yb-Yb distance in $\text{Yb}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{M} = \text{Mn}, \text{Fe}$) is 3.4286(3) and 3.4255(10) Å, respectively. The Gd-Gd in-plane distance in $\text{Gd}_6\text{W}_4\text{Al}_{43}$ and $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$ ($\text{M} = \text{Mn}, \text{Fe}$) is 3.4575(6) Å and 3.4538(15) Å and 3.4524(7) Å, respectively. Overall, all the bond distances in $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}; \text{M} = \text{Mn}, \text{Fe}$) decrease with the presence of the dopant ($\text{M} = \text{Mn}, \text{Fe}$), except Yb-Yb, in comparison to $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd}, \text{Yb}$). Also, there is a systematic decrease in volume from $\text{Gd}_6\text{W}_4\text{Al}_{43} > \text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y > \text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$, likewise for the Yb-analogs. The bond distance and volume trends are consistent and as expected.

2.3.2 Magnetic Properties

Temperature dependent magnetic susceptibility data of $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$ ($\text{M} = \text{Mn}, \text{Fe}$) with an applied field of 0.1 T are shown in Figure 2.5. With the field oriented in the *ab*-plane, the magnetic susceptibility increases with decreasing temperature until $T_N \sim 16$ K, followed by a decrease in magnetization. Interestingly, when the field is parallel to the *c*-direction there is a steady increase in susceptibility with decreasing temperature. All compounds exhibit Curie-Weiss behavior above T_N and were fitted to a modified Curie Weiss equation, $\chi = \chi_o + (C/(T-\theta))$, where

χ_o is the temperature independent contribution, θ is the Weiss constant, and C is the Curie constant.

The constants from the Curie Weiss fit are provided in Table 2.8.

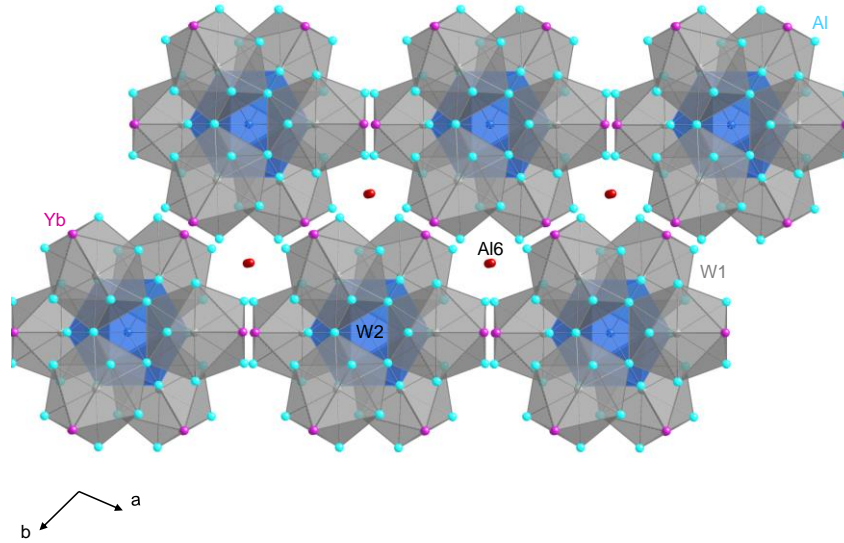


Figure 3.2. Transition metal sublattices of $\text{Yb}_6\text{W}_4\text{Al}_{43}$ viewed down the c -direction. W1 are shown as grey translucent icosahedra and W2 are blue icosahedra. Aluminum atoms are light blue spheres except Al6 which is represented as red spheres, while Yb are pink spheres forming Kagome lattice in the ab -plane and stacking in the c -direction.

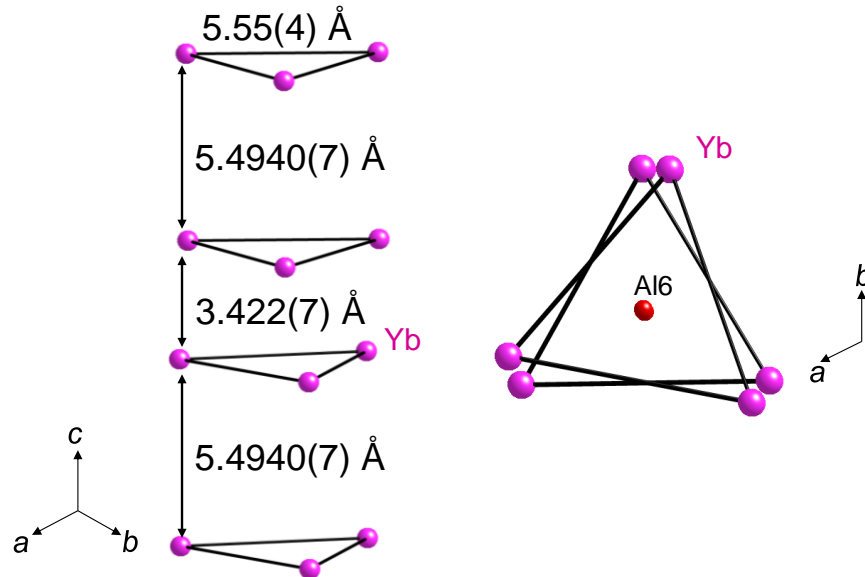


Figure 2.4. The Yb-network viewed in the ab - and c -direction. The Yb atoms (pink spheres) form equilateral triangles in the ab -direction, and stacking along the c -direction.

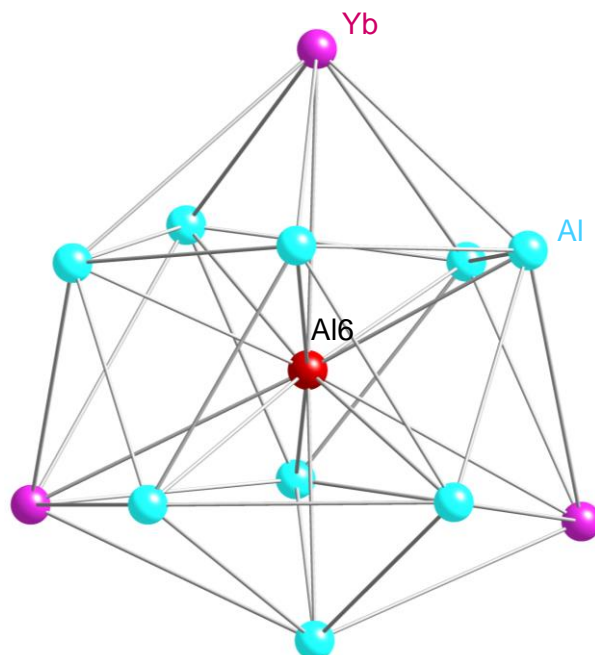


Figure 2.5. The local environment of Al6 is shown.

Table 2.8. Magnetic Properties of $\text{Gd}_6\text{W}_4\text{Al}_{43}$, $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y$, $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$

| Compound | $H_{\text{direction}}$ | Fit range (K) | $\chi_o \times 10^{-2}$ (emu/mol Gd) | θ_w (K) | T_N (K) | μ_{eff} ($\mu_B/\text{mol Gd}$) |
|--|------------------------|---------------|--------------------------------------|----------------|-----------|--|
| $\text{Gd}_6\text{W}_4\text{Al}_{43}$ | H// <i>ab</i> | >50 | -0.1406(6) | 13.62(7) | 15 | 7.92(3) |
| $\text{Gd}_6\text{W}_4\text{Al}_{43}$ | H// <i>c</i> | >45 | -0.0562(8) | 17.4(2) | 15 | 7.93(2) |
| $\text{Gd}_6\text{W}_4\text{Al}_{42.31(11)}\text{Mn}_{0.69(11)}$ | H// <i>ab</i> | >50 | -0.1773(6) | 9.91(6) | 14 | 7.94(1) |
| $\text{Gd}_6\text{W}_4\text{Al}_{42.31(11)}\text{Mn}_{0.69(11)}$ | H// <i>c</i> | >40 | -0.0658(3) | 11.82(5) | 14 | 7.94(1) |
| $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$ | H// <i>ab</i> | >50 | -0.0731(2) | 7.56(5) | 13 | 7.78(5) |
| $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$ | H// <i>c</i> | >50 | -0.1251(4) | 9.05(5) | 13 | 7.96(1) |

The ordering of spins in an antiferromagnet (AFM) can occur in a number of different configurations depending on the coordination of the magnetic ions. This is especially true in layered compounds, such as $[(1-x)\text{La}, x\text{Ca}]\text{MnO}_3$, where the spins may order ferromagnetically (FM) within the slab while ordering antiferromagnetically between neighboring slabs (A-type), or vice versa (C-type).⁶⁰ Furthermore, because the Weiss constant represents the global exchange

interaction of the system, it is possible for an AFM to yield values which are positive rather than negative when its high temperature susceptibility data are fitted.^{61, 62} The anisotropic behavior of $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$ ($\text{M} = \text{Mn}, \text{Fe}$) in Figure 2.5 implies that, if the peak is indeed associated with an AFM transition, the easy-axis of the magnetization lies in the ab -plane. This is interesting because in $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$ ($\text{M} = \text{Mn}, \text{Fe}$) the ab -plane constitutes a Kagome lattice. Thus, the possibility of observing glassy spin-dynamics in the ground-state arises because of the geometrical frustration present in this scenario. Although it is difficult to say for sure whether or not FM ordering exists between the slabs of magnetic ions (Gd) without having neutron diffraction data, this would help to explain the positive Weiss constants obtained from the fits of the modified Curie-Weiss equation and the increase in susceptibility with decreasing temperature when the field is applied parallel to the c -axis.

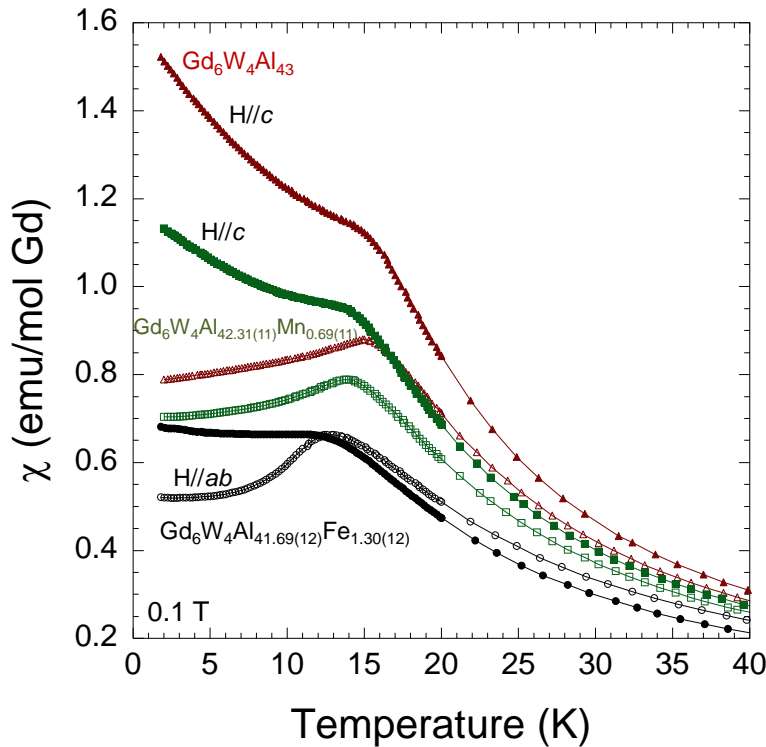


Figure 2.6. Temperature dependent ZFC magnetization of $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$ ($\text{M} = \text{Mn}, \text{Fe}$). $\text{G}_6\text{W}_4\text{Al}_{43}$, $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y$, $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$ are depicted as triangle, squares, circles, respectively, with the filled shapes representing the $H//c$ and unfilled shapes representing $H//ab$.

Field dependent magnetization of $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$ ($\text{M} = \text{Mn}, \text{Fe}$) at 2 K in applied fields up to 7 T are shown in Figure 2.6. The magnetization of all samples is linear at low fields followed by a change in slope at ~ 4.5 T. With the exception of $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$ ($\text{H} // c$), the magnetic moment saturates at $\sim 6.3 \mu_B/\text{mol Gd}$ for all compounds. Though this value is slightly less than the calculated spin-only Gd^{3+} ion, it is consistent with the previously reported magnetic data on single crystals and polycrystalline samples of $\text{Gd}_6\text{W}_4\text{Al}_{43}$. The anisotropy seen in the field dependent magnetization of $\text{Gd}_6\text{W}_4\text{Al}_{41.69(12)}\text{Fe}_{1.30(12)}$ is puzzling since the Gd^{3+} ion has a spherically symmetric spin state. However, the low M_s suggest antiparallel type of coupling between Gd ($4f$) and Fe ($3d$) in the c -plane, similar to $\text{Gd}(\text{Ni}_{1-x}\text{Fe}_x)_3$.⁶³

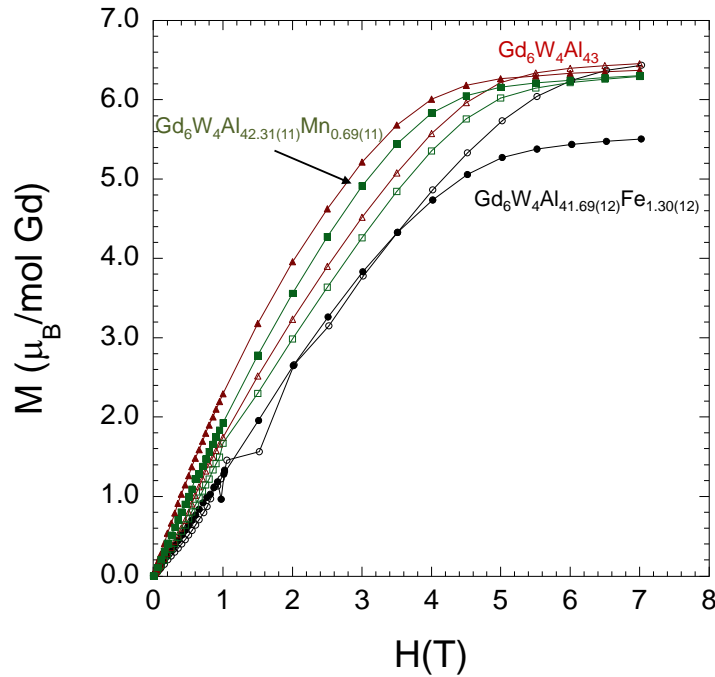


Figure 2.7. Field dependent magnetization of $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$ ($\text{M} = \text{Mn}, \text{Fe}$) are shown at 1.8 K. $\text{Gd}_6\text{W}_4\text{Al}_{43}$, $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y$, $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$ are depicted as triangles, squares, and circles, respectively, with the filled shapes representing the $\text{H} // c$ and unfilled shapes representing $\text{H} // ab$.

Figure 2.7 shows the field-dependent magnetization of $\text{Yb}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{M} = \text{Mn}, \text{Fe}$) at 3 K. The field-dependent magnetization of $\text{Yb}_6\text{W}_4\text{Al}_{43}$ exhibits a small increase in magnetization between 0 – 0.05 T followed by a decrease in magnetization. The high field portion is consistent

with the Yb ions adopting the non-magnetic divalent configuration and the increase in low field could be due to a weak paramagnetic contribution of the sample or the background due to geometry of the sample holder. $\text{Yb}_6\text{W}_4\text{Al}_{41.76(12)}\text{Fe}_{1.24(12)}$ shows similar behavior as the un-doped analog with the exceptions that the magnetization increases between 0 – 0.8 T and the negative slope at high field is less pronounced. However, $\text{Yb}_6\text{W}_{3.86(7)}\text{Al}_{41.76(7)}\text{Mn}_{1.39(7)}$ exhibits an increase in magnetization between 0 – 4 T followed by saturation which is typical paramagnetic response. Magnetic susceptibility, not shown, for $\text{Yb}_6\text{W}_4\text{Al}_{43}$ and $\text{Yb}_6\text{W}_4\text{Al}_{41.76(12)}\text{Fe}_{1.24(12)}$ is consistent with nearly temperature independent paramagnets, whereas $\text{Yb}_6\text{W}_{3.86(7)}\text{Al}_{41.76(7)}\text{Mn}_{1.39(7)}$ exhibits a small Curie tail at low temperatures.

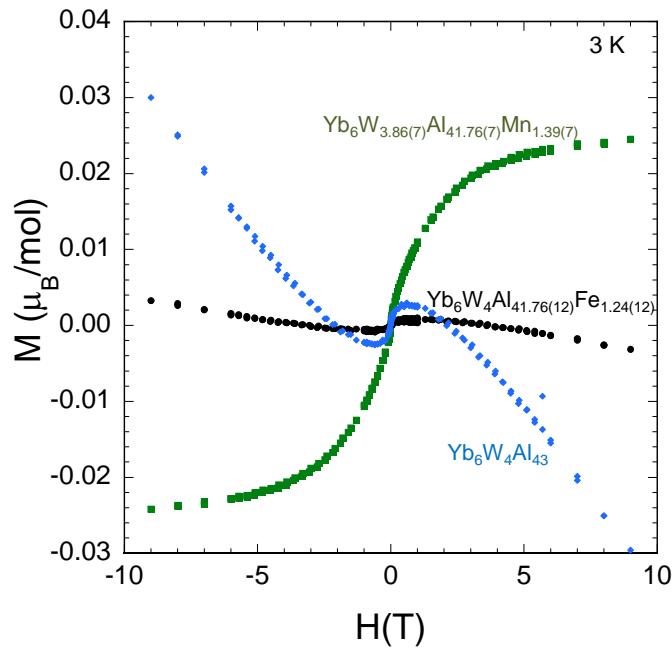


Figure 2.8. Field dependent magnetization of $\text{Yb}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{M} = \text{Mn}, \text{Fe}$) are shown at 3 K.

2.4 Conclusion

Herein, we mapped out the synthetic conditions to grow $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}$; $\text{M} = \text{Mn}, \text{Fe}$). The ability to control certain variables such as the flux, reaction ratios, and reaction profiles while utilizing the flux growth method allows for the growth of the desired compound

over competing ternaries and binaries. We successfully grew single crystals of the $\text{Ln}_6\text{W}_4\text{Al}_{43}$ and pseudo-ternary compounds, $\text{Ln}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{Ln} = \text{Gd}, \text{Yb}$; $\text{M} = \text{Mn}, \text{Fe}$). Refinement of the X-ray diffraction data of Fe- and Mn- doped $\text{GdW}_4\text{Al}_{43}$ shows that the dopants prefer to substitute for Al as opposed to W, similar to previously published $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$.³⁹ For the $\text{Yb}_6\text{W}_{4-x}\text{Al}_{43-y}\text{M}_{x+y}$ ($\text{M} = \text{Mn}, \text{Fe}$) phase, Mn occupies both W1 and Al6 site, while Fe prefers to occupy the Al6 site only. Furthermore, Mn prefers to occupy the W1 instead of W2 site because W1-Al distances have shorter contacts (2.5438(2), 2.6624(16), 2.6870(17), and 2.7278(13) Å) than W2-Al (2.6716(14) and 2.8535(9) Å). The cell volume in $\text{Gd}_6\text{W}_4\text{Al}_{43}$ (1871.2(3) Å³) is larger than $\text{Yb}_6\text{W}_4\text{Al}_{43}$ (1856.2(3) Å³) and therefore it is plausible to infer that Mn prefers to occupy the Al6 site in $\text{Gd}_6\text{W}_4\text{Al}_{43}$. The results indicate that $\text{Ln}_6\text{M}_4\text{Al}_{43}$ can be adopted for late lanthanides and early/mid transition metals and can be rationalized by both atomic volume and valence electron count arguments similar to $\text{LnT}_2\text{Al}_{20}$ compounds.⁶⁴

This first report of anisotropic magnetic behavior on compounds adopting the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ structure type ($\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{M}_y$; $\text{M} = \text{Mn}, \text{Fe}$) demonstrates the importance of growing single crystals to determine the intrinsic and anisotropic magnetic properties of materials.²⁷ The effective moments (μ_{eff}) of the Gd-analogs are close to the magnetic moment for a free Gd^{3+} ion (7.94 μ_B). However, there is a decrease in saturation magnetization M_s from $\text{Gd}_6\text{W}_4\text{Al}_{43} > \text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y > \text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$, which suggests the dopant (Mn/Fe (3d)) spins are participating in an antiparallel arrangement with Gd (4f).^{63, 65} The magnetization curves of the Yb-analogs are sensitive to doping with magnetic elements.

Chapter 3. Investigation of Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$) with ^{57}Fe Mössbauer and single crystal X-ray diffraction

3.1 Introduction

The study of intermetallics containing rare earth, transition metal, and group 13 elements has attracted much attention due to the strong interaction of the conduction electrons with the local magnetic moments.²⁷ This can lead to interesting magnetic and electrical properties, including superconductivity, Kondo behavior, valence instability, heavy fermion behavior, and quantum criticality. Ytterbium-containing compounds are particularly intriguing due to the potential valence instability between the Yb^{3+} (f^{13}) and Yb^{2+} (f^{14}) states, and heavy fermion behavior has recently been observed in YbSi (ThAl structure type),^{66, 67} YbCu_2Si_2 (ThCr₂Si₂ structure type),^{68, 69} and $\text{YbT}_2\text{Zn}_{20}$ ($\text{T} = \text{Fe}, \text{Co}, \text{Ru}, \text{Rh}, \text{Os}, \text{Ir}$; CeCr₂Al₂₀ structure type).^{56, 70} In addition, other members of the $\text{LnT}_2\text{Zn}_{20}$ ($\text{Ln} = \text{lanthanides}$; $\text{T} = \text{Fe}, \text{Co}, \text{Ru}, \text{Rh}, \text{Os}, \text{Ir}$) series have been investigated, and it was found that the magnetic properties greatly depend on the transition metal present and the valence electron count.^{40, 55, 56, 71}

Isostructural $\text{LnT}_2\text{Al}_{20}$ ($\text{Ln} = \text{lanthanides}$; $\text{T} = \text{Ti-Cr}, \text{Nb}, \text{Mo}, \text{Ta}, \text{W}$) compounds have also been reported.^{17, 72} Recently it was found that $\text{PrTi}_2\text{Al}_{20}$ and $\text{PrV}_2\text{Al}_{20}$ exhibits quadrupolar order at 2 K and 0.6 K, respectively, while $\text{PrCr}_2\text{Al}_{20}$ shows Kondo behavior at low temperatures.⁷³⁻⁷⁵ The $\text{SmT}_2\text{Al}_{20}$ ($\text{T} = \text{Ti-Cr}$) analogues show valence fluctuations and order antiferromagnetically below 7 K.⁷⁶ $\text{GdV}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{20}$ have also been shown to order antiferromagnetically at 2.35(5) and 3.90(5) K,⁷⁷ respectively, while $\text{CeT}_2\text{Al}_{20}$ ($\text{T} = \text{Ti-Cr}$) and $\text{YbCr}_2\text{Al}_{20}$ are temperature independent paramagnets consistent with Ce^{4+} and Yb^{2+} , respectively.⁷⁸⁻⁸⁰

*Reprinted with permission from Treadwell, L. J.; McAlpin, J. D.; Schmitt, D. C.; Kangas, M. J.; Sougrati, M. T.; Haldolaarachchige, N.; Young, D. P.; Jumas, J.-C.; Chan, J. Y., Investigation of Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$) with ^{57}Fe Mössbauer and single crystal X-ray diffraction. *Inorg. Chem.* **2013**, 52, 5055-5062. Copyright 2013 American Chemical Society.

Due to the robust structure of the $\text{CeCr}_2\text{Al}_{20}$ structure type and the Frank-Kasper cages formed by the main group element, several different doping atoms have been incorporated onto different sites to investigate the effect on magnetic and electronic properties. $\text{GdFe}_2\text{Zn}_{20}$ has an abnormally high Curie temperature T_c at 86 K, while $\text{GdCo}_2\text{Zn}_{20}$ orders antiferromagnetically at 5.7 K. A doping study of Co for Fe, $\text{Gd}(\text{Fe}_x\text{Co}_{1-x})_2\text{Zn}_{20}$, was performed to study the ferromagnetic to antiferromagnetic ordering associated with the filling of the electronic states.⁵⁴ Also, Al was doped for Zn in $\text{GdFe}_2\text{Zn}_{20}$, which leads to a ferromagnetic ordering, but T_c decreases with increasing Al doping.⁴⁰ We focus our efforts on doping Fe into $\text{LnCr}_2\text{Al}_{20}$ ($\text{Ln} = \text{La, Gd, Yb}$) in order to investigate Fe site preferences. The parent analogues of La and Yb adopting the $\text{CeCr}_2\text{Al}_{20}$ structure type are diamagnetic and Pauli paramagnetic, respectively, while the Gd analogue shows antiferromagnetic ordering at 3.90(5) K.^{77, 81} Herein, we report the synthesis, crystal structure, Mössbauer results, and magnetic properties of the first pseudo-ternary of the $\text{CeCr}_2\text{Al}_{20}$ -structure type where the transition metal dopant (Fe) substitutes for the main group element: $\text{LnCr}_2\text{Fe}_x\text{Al}_{20-x}$ ($\text{Ln} = \text{La, Gd, Yb}$).

3.2 Experimental Section

3.2.1 Synthesis

Single crystals of $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La, Gd, Yb}$) were prepared using the molten metal flux technique using Ln (99.9%), Cr (99.996 %), Fe (99.998 %), and Al (99.999%) in various ratios. A ratio of 1:1.5:0.5:50 and 1:1:1:50 Ln:Cr:Fe:Al were used to prepare Yb and Gd analogues, respectively. The ratios of 1:1.5:0.5:100 and 1:1:1:100 for La:Cr:Fe:Al, respectively, were used to synthesize the La-analogue. For all reactions, the elements were placed in an alumina crucible, topped with a second alumina crucible, and then sealed inside an evacuated fused-silica tube. The samples were placed in an oven and heated to 1000 °C at 100 °C/h, dwelled for 24 h,

and slowly (2 °C/h) cooled to 800 °C. The samples were then removed from the oven and centrifuged to remove excess flux. Residual flux was etched using (~ 1 M) NaOH. For the Yb-reactions, the lower Fe concentration (1:1.5:0.5:50) only yielded crystals adopting the CeCr₂Al₂₀ structure type (space group *Fd3m*, $a \sim 14.5$ Å), with octahedral morphology up to 3 mm in length.¹⁷ The larger Fe concentration (1:1:1:50) produced smaller crystals (≤ 1 mm³) adopting the CeCr₂Al₂₀ structure type and bar-shaped crystals of the YbFe₂Al₁₀ structure type (space group *Cmcm*, $a \sim 8.966$ Å, $b \sim 10.153$ Å, $c \sim 9.003$ Å)⁸² which could be separated based on morphology. As a result, higher concentrations of Fe were not attempted due to the presence of YbFe₂Al₁₀. The higher Fe-ratio of the Gd-synthesis yielded flat plates crystals (≤ 2.5 mm³) adopting the CeCr₂Al₂₀ structure type, while the lower Fe-concentration yielded compounds adopting the Ho₆Mo₄Al₄₃ structure type (space group *P6₃/mcm*, $a \sim 10.975$ Å, $c \sim 17.611$ Å),⁸⁰ which was determined by single crystal X-ray diffraction. As a result, only one Fe doped Gd-compound is reported. Single crystals of the La-analogue were synthesized with an increase Al concentration to avoid the Ho₆Mo₄Al₄₃ structure type in order to stabilize the CeCr₂Al₂₀ structure type.

3.2.2 Structural Characterization

Single crystals of Fe-doped LnCr₂Al₂₀ (Ln = La, Gd, Yb) were cleaved and attached to a glass fiber. The fiber was then mounted on the goniometer of a Nonius Kappa CCD diffractometer with Mo K α radiation ($\lambda = 0.71073$ Å). The diffraction pattern was indexed to a face-centered cubic unit cell with the lattice parameter $a \sim 14.5$ Å, consistent with the CeCr₂Al₂₀ structure type.¹⁷ A multi-scan absorption correction was applied to all data sets. The crystal structure was solved using SIR97⁵⁸ and refined with SHELXL97.⁵⁹ The final models were corrected for extinction, and atomic displacement parameters were modeled anisotropically. Collection and refinement parameters, atomic positions, and interatomic distances are provided in Tables 3.1-3.6,

respectively. Refinement of the iron occupancies is discussed in the Results and Discussion section below.

Table 3.1. Crystallographic parameters of $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$

| Formula | $\text{YbCr}_2\text{Al}_{20}^a$ | $\text{YbCr}_2\text{Al}_{19.9}\text{Fe}_{0.1}$ | $\text{YbCr}_2\text{Al}_{19.8}\text{Fe}_{0.2}$ |
|--|---------------------------------|--|--|
| Crystal System | Cubic | Cubic | Cubic |
| Space Group | $Fd\bar{3}m$ | $Fd\bar{3}m$ | $Fd\bar{3}m$ |
| a (Å) | 14.473(13) | 14.450(4) | 14.444(4) |
| V (Å ³) | 3032(5) | 3017.2(14) | 3013.4(14) |
| Z | 8 | 8 | 8 |
| Crystal dimensions (mm) | 0.03 x 0.03 x 0.03 | 0.05 x 0.08 x 0.1 | 0.05 x 0.08 x 0.1 |
| Temperature (K) | 293(2) | 296(1) | 296(1) |
| θ range (°) | 2.44 - 29.85 | 3.99 - 29.91 | 3.99 - 29.92 |
| μ (mm ⁻¹) | 8.666 | 8.794 | 8.909 |
| <i>Data Collection</i> | | | |
| Measured Reflections | 701 | 1785 | 1552 |
| Unique Reflections | 248 | 247 | 247 |
| Reflections with $I > 2\sigma(I)$ | 224 | 223 | 230 |
| R_{int} | 0.0409 | 0.0384 | 0.0296 |
| h | $-20 \leq h \leq 20$ | $-20 \leq h \leq 20$ | $-20 \leq h \leq 20$ |
| k | $-14 \leq k \leq 14$ | $-14 \leq k \leq 14$ | $-14 \leq k \leq 14$ |
| l | $-13 \leq l \leq 13$ | $-13 \leq l \leq 13$ | $-13 \leq l \leq 13$ |
| <i>Refinement</i> | | | |
| $\Delta\rho_{\text{max}}$ (eÅ ⁻³)/ $\Delta\rho_{\text{min}}$ (eÅ ⁻³) | 0.816 / -1.24 | 0.862 / -0.744 | 0.694 / -0.769 |
| GoF | 1.167 | 1.062 | 1.185 |
| Extinction coefficient | 0.00011(5) | 0.00035(5) | 0.00023(3) |
| Reflections | 248 | 247 | 247 |
| Parameters/Restraints | 17 / 0 | 21 / 3 | 21 / 3 |
| R_1 ($F^2 > 2\sigma F^2$) ^b | 0.0295 | 0.0215 | 0.0198 |
| wR_2 (F^2) ^c | 0.0553 | 0.0456 | 0.0337 |

^a Crystallographic data from reference.⁴⁰

^b $R_1 = \Sigma ||F_o| - |F_c|| / \Sigma |F_o|$

^c $R_w = [\Sigma [w (F_o^2 - F_c^2)^2] / \Sigma [w (F_o^2)^2]]^{1/2}$; $w = 1/[\sigma^2(F_o^2) + (0.0137P)^2 + 20.00 P]$, $w = 1/[\sigma^2(F_o^2) + (0.0188P)^2 + 14.48P]$, $w = 1/[\sigma^2(F_o^2) + (0.0055P)^2]$; $P = (F_o^2 + 2 F_c^2)/3$ for $\text{YbCr}_2\text{Al}_{20}$, $\text{YbCr}_2\text{Fe}_{0.1}\text{Al}_{19.9}$, and $\text{YbCr}_2\text{Fe}_{0.2}\text{Al}_{19.8}$, respectively.

Table 3.2. Crystallographic parameters of $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ (Ln = La, Gd)

| Formula | $\text{LaCr}_2\text{Al}_{20}$ | $\text{GdCr}_2\text{Al}_{20}$ | $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$ |
|--|-------------------------------|-------------------------------|--|
| Crystal System | Cubic | Cubic | Cubic |
| Space Group | $Fd-3m$ | $Fd-3m$ | $Fd-3m$ |
| a (Å) | 14.552(1) | 14.460(3) | 14.431(1) |
| V (Å ³) | 3081.5(6) | 3023.5(11) | 3005.3(5) |
| Z | 8 | 8 | 8 |
| Crystal dimensions (mm) | 0.05 x 0.08 x 0.1 | 0.05 x 0.08 x 0.1 | 0.05 x 0.08 x 0.1 |
| Temperature (K) | 293(2) | 293(2) | 293(2) |
| θ range (°) | 3.96 - 30.93 | 3.99 - 30.87 | 3.99 - 30.94 |
| μ (mm ⁻¹) | 5.229 | 6.89 | 7.8 |
| <i>Data Collection</i> | | | |
| Measured Reflections | 796 | 744 | 774 |
| Unique Reflections | 272 | 266 | 266 |
| Reflections with $I > 2\sigma(I)$ | 260 | 243 | 257 |
| R_{int} | 0.0133 | 0.0303 | 0.0135 |
| h | $-21 \leq h \leq 21$ | $-20 \leq h \leq 20$ | $-20 \leq h \leq 20$ |
| k | $-14 \leq k \leq 14$ | $-14 \leq k \leq 14$ | $-14 \leq k \leq 14$ |
| l | $-13 \leq l \leq 13$ | $-13 \leq l \leq 13$ | $-13 \leq l \leq 13$ |
| <i>Refinement</i> | | | |
| $\Delta\rho_{\text{max}}$ (eÅ ⁻³)/ $\Delta\rho_{\text{min}}$ (eÅ ⁻³) | 0.827 / -1.283 | 0.525 / -0.761 | 0.634 / -0.766 |
| GoF | 1.17 | 1.103 | 1.245 |
| Extinction coefficient | 0.00032(5) | 0.00029(4) | 0.00036(5) |
| Reflections | 272 | 266 | 266 |
| Parameters/Restraints | 17 / 0 | 16 / 0 | 18 / 0 |
| R_1 ($F^2 > 2\sigma F^2$) ^a | 0.0247 | 0.0216 | 0.0161 |
| wR_2 (F^2) ^b | 0.0649 | 0.0472 | 0.0418 |

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|$$

$$^b R_w = [\sum [w (F_o^2 - F_c^2)^2] / \sum [w (F_o^2)]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0137P)^2 + 20.00 P], w = 1/[\sigma^2(F_o^2) + (0.0188P)^2 + 14.48P], w = 1/[\sigma^2(F_o^2) + (0.0055P)^2]; P = (F_o^2 + 2 F_c^2)/3 \text{ for } \text{LaCr}_2\text{Al}_{20}, \text{GdCr}_2\text{Al}_{20}, \text{ and } \text{GdCr}_2\text{Fe}_{0.3}\text{Al}_{19.7}, \text{ respectively.}$$

Table 3.3. Atomic Positions of YbCr₂Al_{20-x}Fe_x

| Atom | Site | Symmetry | x | y | z | Occ. ^b | U _{eq} (Å ²) ^c |
|--|------|----------|-------------|------------|-------------|-------------------|--|
| YbCr ₂ Al ₂₀ ^a | | | | | | | |
| Yb1 | 8a | 43m | 1/8 | 1/8 | 1/8 | 1 | 0.0139(3) |
| Cr1 | 16d | 3m | 1/2 | 1/2 | 1/2 | 1 | 0.0078(4) |
| Al1 | 96g | mm | 0.48698(14) | 1/8 | 1/8 | 1 | 0.0091(4) |
| Al2 | 48f | 2mm | 0.05900(7) | 0.05900(7) | 0.32511(10) | 1 | 0.0117(4) |
| Al3 | 16c | 3m | 0 | 0 | 0 | 1 | 0.0182(8) |
| YbCr ₂ Al _{19.9} Fe _{0.1} | | | | | | | |
| Yb1 | 8a | 43m | 1/8 | 1/8 | 1/8 | 1 | 0.0113(2) |
| Cr1 | 16d | 3m | 1/2 | 1/2 | 1/2 | 1 | 0.0091(3) |
| Al1 | 96g | mm | 0.05899(5) | 0.05899(5) | 0.32525(8) | 0.996(3) | 0.0121(3) |
| Fe1 | 96g | mm | 0.05899(5) | 0.05899(5) | 0.32525(8) | 0.004(3) | 0.0121(3) |
| Al2 | 48f | 2mm | 0.4867(1) | 1/8 | 1/8 | 0.992(5) | 0.0099(4) |
| Fe2 | 48f | 2mm | 0.4867(1) | 1/8 | 1/8 | 0.008(5) | 0.0099(4) |
| Al3 | 16c | 3m | 0 | 0 | 0 | 1 | 0.0204(7) |
| YbCr ₂ Al _{19.8} Fe _{0.2} | | | | | | | |
| Yb1 | 8a | 43m | 1/8 | 1/8 | 1/8 | 1 | 0.01002(16) |
| Cr1 | 16d | 3m | 1/2 | 1/2 | 1/2 | 1 | 0.0081(2) |
| Al1 | 96g | mm | 0.05900(4) | 0.05900(4) | 0.32519(6) | 0.988(2) | 0.0119(3) |
| Fe1 | 96g | mm | 0.05900(4) | 0.05900(4) | 0.32519(6) | 0.012(2) | 0.0119(3) |
| Al2 | 48f | 2mm | 0.48672(8) | 1/8 | 1/8 | 0.988(4) | 0.0093(4) |
| Fe2 | 48f | 2mm | 0.48672(8) | 1/8 | 1/8 | 0.012(4) | 0.0093(4) |
| Al3 | 16c | 3m | 0 | 0 | 0 | 1 | 0.0194(5) |

^a Crystallographic data from reference.⁴⁰^b Site occupancy^c U_{eq} is defined as one-third of the trace of the orthogonalized U_{ij} tensor

Table 3.4. Atomic Positions of $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ (Ln = La, Gd)

| Atom | Site | Symmetry | x | y | z | Occ. ^a | $U_{\text{eq}} (\text{\AA}^2)$ ^b |
|--|------|----------|------------|------------|------------|-------------------|---|
| LaCr₂Al₂₀ | | | | | | | |
| La1 | 8a | 43m | 1/8 | 1/8 | 1/8 | 1 | 0.0123(2) |
| Cr1 | 16d | 3m | 1/2 | 1/2 | 1/2 | 1 | 0.0096(3) |
| Al1 | 96g | mm | 0.05818(4) | 0.05818(4) | 0.32698(6) | 1 | 0.0133(3) |
| Al2 | 48f | 2mm | 0.48822(8) | 1/8 | 1/8 | 1 | 0.0106(3) |
| Al3 | 16c | 3m | 0 | 0 | 0 | 1 | 0.0272(6) |
| GdCr₂Al₂₀ | | | | | | | |
| Gd1 | 8a | 43m | 1/8 | 1/8 | 1/8 | 1 | 0.0134(2) |
| Cr1 | 16d | 3m | 1/2 | 1/2 | 1/2 | 1 | 0.0099(2) |
| Al1 | 96g | mm | 0.05875(4) | 0.05875(4) | 0.32577(6) | 1 | 0.0122(2) |
| Al2 | 48f | 2mm | 0.48703(8) | 1/8 | 1/8 | 1 | 0.0106(3) |
| Al3 | 16c | 3m | 0 | 0 | 0 | 1 | 0.0251(5) |
| GdCr₂Al_{19.7}Fe_{0.3} | | | | | | | |
| Yb1 | 8a | 43m | 1/8 | 1/8 | 1/8 | 1 | 0.0133(1) |
| Cr1 | 16d | 3m | 1/2 | 1/2 | 1/2 | 1 | 0.0113(2) |
| Al1 | 96g | mm | 0.05884(3) | 0.05884(3) | 0.32565(5) | 0.97(2) | 0.0147(3) |
| Fe1 | 96g | mm | 0.05884(3) | 0.05884(3) | 0.32565(5) | 0.03(2) | 0.0147(3) |
| Al2 | 48f | 2mm | 0.48682(7) | 1/8 | 1/8 | 1 | 0.0113(2) |
| Al3 | 16c | 3m | 0 | 0 | 0 | 1 | 0.0278(5) |

^aSite occupancy^b U_{eq} is defined as one-third of the trace of the orthogonalized U_{ij} tensor

Table 3.5. Select Interatomic Distances (Å) of YbCr₂Al_{20-x}Fe_x

| Compound | YbCr ₂ Al ₂₀ ^a | YbCr ₂ Al _{19.9} Fe _{0.1} | YbCr ₂ Al _{19.8} Fe _{0.2} |
|---------------------|---|--|--|
| Yb - 16 coordinate | | | |
| Yb-Al3 (x4) | 3.133(3) | 3.1285(9) | 3.1269(9) |
| Ln-Al1 (x12) | 3.196(3) | 3.1929(15) | 3.1912(13) |
| Cr - 12 coordinate | | | |
| Cr-Al2 (x6) | 2.565(2) | 2.5615(7) | 2.5605(7) |
| Cr-Al1 (x6) | 2.804(3) | 2.7977(14) | 2.7965(12) |
| Al1 - 12 coordinate | | | |
| Al1-Al2 | 2.702(2) | 2.6945(19) | 2.6941(16) |
| Al1-Al1 | 2.705(3) | 2.699(2) | 2.6972(19) |
| Al1-Al1 (x2) | 2.745(3) | 2.7434(19) | 2.7418(16) |
| Al1-Cr | 2.804(3) | 2.7977(14) | 2.7965(12) |
| Al1-Al2 (x2) | 2.838(3) | 2.8316(13) | 2.8307(12) |
| Al1-Al1 (x2) | 2.923(2) | 2.9155(15) | 2.9143(13) |
| Al1-Al3 (x2) | 3.091(3) | 3.0869(11) | 3.0852(9) |
| Al1-Yb | 3.196(3) | 3.1930(13) | 3.1913(11) |
| Al2 – 12 coordinate | | | |
| Al2-Cr (x2) | 2.565(2) | 2.5615(7) | 2.5602(7) |
| Al2-Al1 (x2) | 2.705(3) | 2.5615(7) | 2.6941(16) |
| Al2-Al2 (x4) | 2.825(3) | 2.826(2) | 2.824(2) |
| Al2-Al1 (x4) | 2.838(3) | 2.8316(13) | 2.8306(12) |
| Al3 – 14 coordinate | | | |
| Al3-Al1 (x12) | 3.091(3) | 3.0869(11) | 3.0852(11) |
| Al3-Ln (x2) | 3.133(3) | 3.1287(9) | 3.1269(9) |

^a Crystallographic data obtained from reference.⁴⁰

Table 3.6. Select Interatomic Distances (Å) of $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ (Ln = La, Gd)

| Compound | $\text{LaCr}_2\text{Al}_{20}$ | $\text{GdCr}_2\text{Al}_{20}$ | $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$ |
|---------------------|-------------------------------|-------------------------------|--|
| Ln - 16 coordinate | | | |
| Ln-Al3 (x4) | 3.1505(16) | 3.1307(6) | 3.1244(3) |
| Ln-Al1 (x12) | 3.2446(10) | 3.2037(11) | 3.1949(8) |
| Cr - 12 coordinate | | | |
| Cr-Al2 (x6) | 2.5780(13) | 2.5631(5) | 2.5581(3) |
| Cr-Al1 (x6) | 2.7882(17) | 2.7912(10) | 2.7880(8) |
| Al1 - 12 coordinate | | | |
| Al1-Al2 | 2.7197(19) | 2.6968(14) | 2.6894(12) |
| Al1-Al1 | 2.750(2) | 2.7097(17) | 2.7005(14) |
| Al1-Al1 (x2) | 2.781(2) | 2.7508(15) | 2.7447(12) |
| Al1-Cr | 2.7882(10) | 2.7912(10) | 2.7880(8) |
| Al1-Al2 (x2) | 2.8373(10) | 2.8292(10) | 2.8248(7) |
| Al1-Al1 (x2) | 2.9076(18) | 2.9092(11) | 2.9054(9) |
| Al1-Al3 (x2) | 3.0896(8) | 3.0935(8) | 3.0859(5) |
| Al1-Yb | 3.2017(1) | 3.2037(1) | 3.1949(7) |
| Al2 - 12 coordinate | | | |
| Al2-Cr (x2) | 2.5780(13) | 2.5631(5) | 2.5581(3) |
| Al2-Al1 (x2) | 2.8373(10) | 2.6968(14) | 2.8248(7) |
| Al2-Al2 (x4) | 2.8202(18) | 2.8215(18) | 2.8201(15) |
| Al2-Al1 (x4) | 2.8373(10) | 2.8292(10) | 2.6894(12) |
| Al3 - 14 coordinate | | | |
| Al3-Al1 (x12) | 3.0915(7) | 3.0935(8) | 3.0859(5) |
| Al3-Ln (x2) | 3.1508(4) | 3.1307(4) | 3.1244(3) |

3.2.3 Elemental Analysis

Elemental analysis was performed via energy dispersive X-ray spectroscopy (EDXS) using a JEOL JSM-5600 scanning electron microscope with an accelerating voltage of 15 kV. For all compounds, two polished crystals were measured four times each, and the results were averaged. The compositions, normalized to Ln, were $\text{YbCr}_{2.03(12)}\text{Al}_{25.01(18)}\text{Fe}_{0.10(3)}$, $\text{YbCr}_{1.77(23)}\text{Al}_{20.11(33)}\text{Fe}_{0.18(2)}$, $\text{GdCr}_{2.19(11)}\text{Al}_{24.23(17)}\text{Fe}_{0.28(6)}$, and $\text{LaCr}_{2.1(3)}\text{Al}_{25.1(6)}\text{Fe}_{0.2(1)}$. The crystals selected for EDS were also characterized by X-ray diffraction.

3.2.4 Magnetization and Electrical Transport

Single crystals selected for physical property measurements were first characterized by X-ray diffraction and EDS. Magnetic data were collected using a Quantum Design Physical Property Measurement System (PPMS). The temperature-dependent susceptibility data were measured under zero-field cooled (ZFC) conditions between 3 K and 390 K with an applied field of 0.1 T. Field-dependent magnetization data were measured at 3 K with applied fields up to 9 T.

3.2.5 Mössbauer Spectroscopy

Single crystals used for physical property measurements were also used for Mössbauer spectroscopy. Powdered $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$ samples ($x = 0.1$ and 0.2) were analyzed at room temperature and at 77 K. The spectra were measured at two velocities (± 2 and ± 10 mm/s) with a constant-acceleration spectrometer which utilized a rhodium matrix cobalt-57 source and was calibrated at 300 K with α -iron powder. The Mössbauer spectral absorbers contained 20 mg/cm² of sample powder mixed with boron nitride. The quoted errors for the Mössbauer spectral parameters are the relative statistical errors.

3.3 Results and Discussion

3.3.1 Crystal Structure

The crystal structure of $\text{GdCr}_2\text{Al}_{20}$ is shown in Figure 3.1 and consists of a diamond-like network of Gd polyhedra and a pyrochlore-like network of Cr polyhedra. The $\text{GdCr}_2\text{Al}_{20}$ lattice parameter is 14.460(3) Å, and upon substitution of Fe for Al ($\text{GdCr}_2\text{Fe}_{0.3}\text{Al}_{19.7}$), the lattice parameter decreases to 14.4310(15) Å. The lattice parameter of $\text{YbCr}_2\text{Al}_{20}$ is 14.473(3) Å and decreases to 14.450(4) Å and 14.444(4) Å for $\text{YbCr}_2\text{Fe}_{0.1}\text{Al}_{19.9}$ and $\text{YbCr}_2\text{Fe}_{0.2}\text{Al}_{19.8}$, respectively, with the incorporation of the smaller iron atoms. The contraction of lattice parameters is a strong indication and consistent with Fe incorporated in the compounds. The $\text{GdCr}_2\text{Al}_{20}$ crystal structure

has one Gd site ($8a$), one Cr site ($16d$) and three Al sites ($96g$, $48f$, $16c$). The local environments of the five sites are depicted in Figure 3.2. The Gd polyhedron is 16 coordinate and is made up of 4 Al₃ and 12 Al₁ atoms with Gd-Al bond distances of 3.1307(6) and 3.2037(11) Å, respectively. The Gd polyhedron corner shares with 4 other Gd polyhedra with Gd-Gd distances of 6.269(6) Å. The Cr environment is 12-coordinate, forming a distorted icosahedron and is surrounded by 6 Al₁ and 6 Al₂ atoms with Cr-Al distances of 2.5631(5) and 2.7912(10) Å, respectively. Al₁ (12-coordinate), Al₂ (12-coordinate), and Al₃ (14-coordinate) polyhedra, respectively, can be described as a distorted bi-capped pentagonal prism, a bi-capped pentagonal prism, and a bi-capped hexagonal prism, respectively. The Al-Al distances range from 2.6968(14) to 3.0935(8) Å, and are longer than the expected distance of 2.42 Å from covalent radii.⁸³

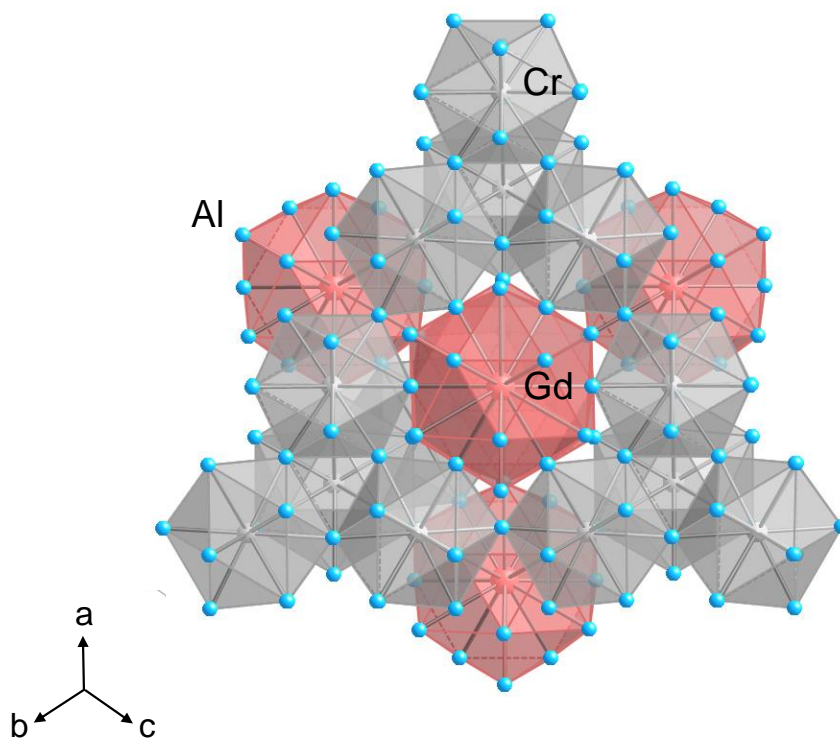


Figure 3.9. The crystal structure of GdCr₂Al₂₀ showing the interpenetrating network of the Gd and Cr polyhedra. The Gd polyhedra are shown as light pink and the Cr polyhedra are shown as grey. Aluminum atoms are depicted as small light blue spheres.

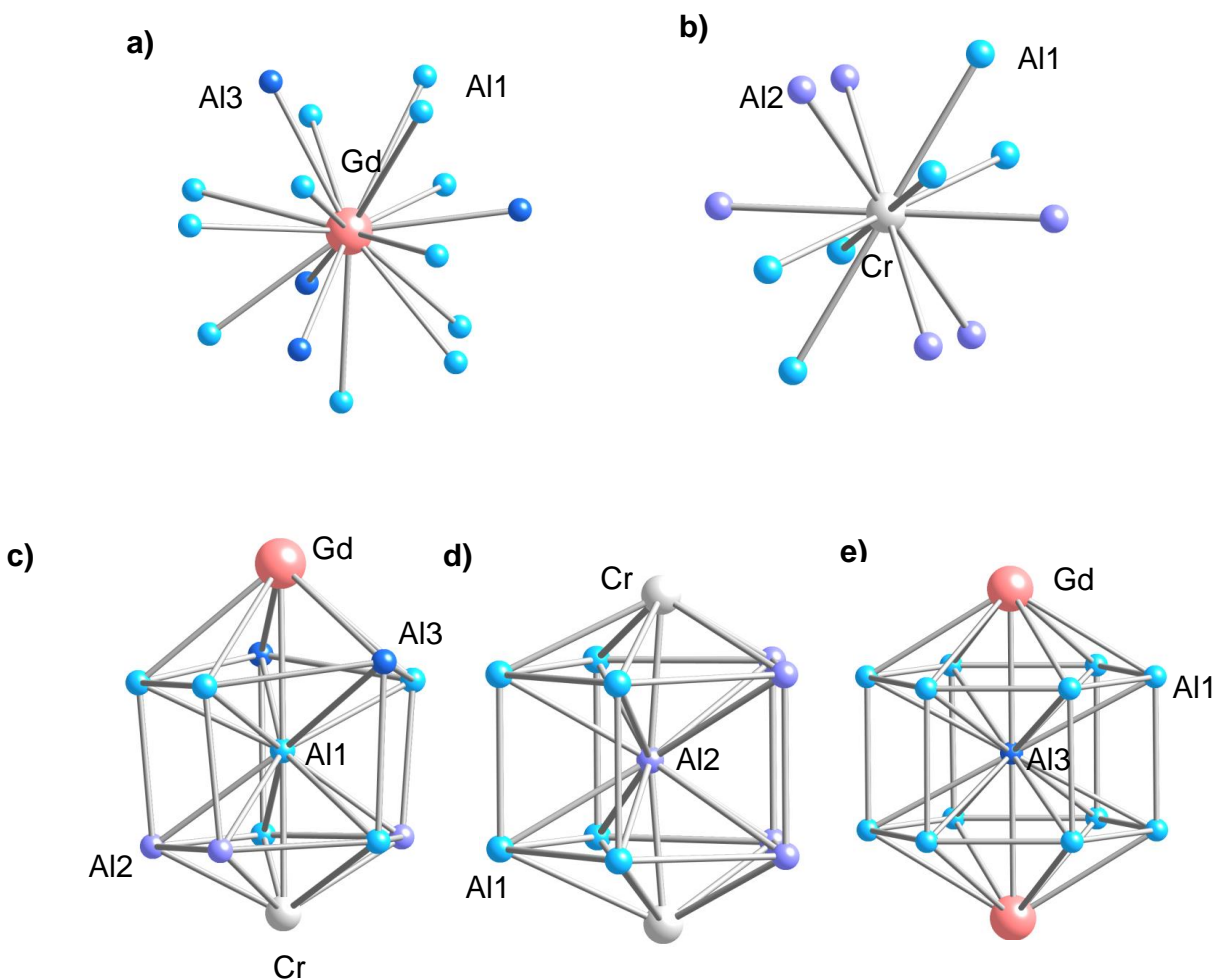


Figure 3.10. The local environments of Gd, Cr, Al1, Al2, and Al3 are shown in a-e, respectively. Gd atoms and Cr atoms are depicted as light pink spheres and grey spheres, respectively, while the Al1, Al2, and Al3 atoms are depicted as light blue.

3.3.2 Mössbauer spectroscopy

Mössbauer spectra for $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($x = 0.1$ and 0.2) are shown in Figure 3.3. An attempt to fit the data with only one iron site using one asymmetric doublet (Model 1) leads to a difference in the experimental model and the calculated fit (misfit). The second attempt to fit the data with considering two iron sites (Model 2), leads to a minuscule misfit compared to Model 1, which suggests that our compound has two unique Fe-sites. In this case, the isomer shifts are quite

similar while the quadrupole splittings corresponding to the two sites are clearly different, indicating that electronic charges are different for the two iron sites. Schematically, the quadrupole splitting is indicative of the site distortion, an iron atom occupying a regular geometry site will have a smaller quadrupole splitting and vice-versa. Whichever the model used to fit the experimental data, the isomer shifts and the quadrupole splittings (provided in Table 3.7) are in the range of iron atoms in an intermetallic environment rich in aluminum^{41, 84-88} concluding that the Fe is substituting on Al sites.

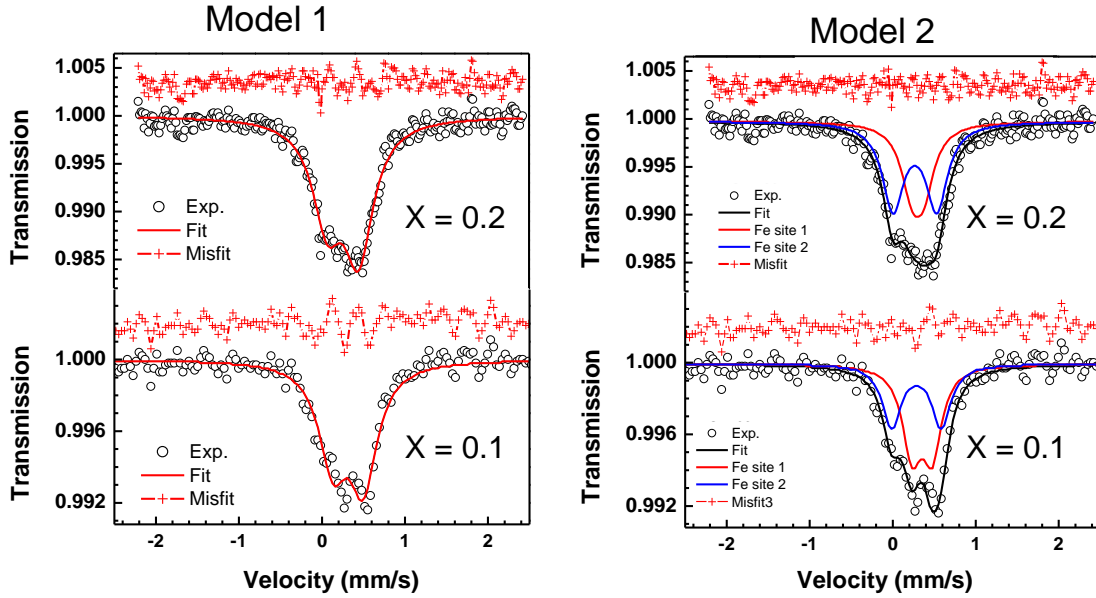


Figure 3.11. Room temperature Mössbauer data for $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$ samples (with $x = 0.1$ and 0.2) fitted with two different models as described in the text.

Table 3.7. Fitted Mössbauer parameters for spectra measured at room temperature. IS, QS, LW, and R.A. are the isomer shift (relative to $\alpha\text{-Fe}$ at 300 K), the quadrupole splitting, the line width and the relative areas, respectively.

| Sample | IS (mm/s) | QS (mm/s) | LW (mm/s) | R.A. (%) |
|----------|-----------|-----------|-----------|----------|
| Fe = 0.2 | 0.31(1) | 0.14(5) | 0.31(3) | 40(7) |
| | 0.27(1) | 0.53(3) | - | 60(7) |
| Fe = 0.1 | 0.35(2) | 0.24(3) | 0.27(4) | 57(6) |
| | 0.28(2) | 0.60(5) | - | 43(6) |

Since Model 2 has the best statistical data, we can conclude that there are two iron sites present. Model 2 suggests that the two iron sites can be distinguished based on distortion in both compositions ($x = 0.1$ and 0.2). The site having the bigger quadrupole splitting (in blue shown in Figure 3.3) should correspond to the most distorted site. This model can only be explained if we assume that iron atoms go simultaneously into two aluminum crystallographic sites. Finally, Mössbauer spectra have been recorded at 77 K and 300 K in a larger velocity range (Figure 3.4). The interest of recording spectra at such velocity (10 mm/s) is to check if there is any iron oxide. In fact, iron oxides give absorption peaks at around 8-9 mm/s which are not present in our spectra. From the results, we can also confirm the absence of any magnetic ordering between 77 K and 300 K.

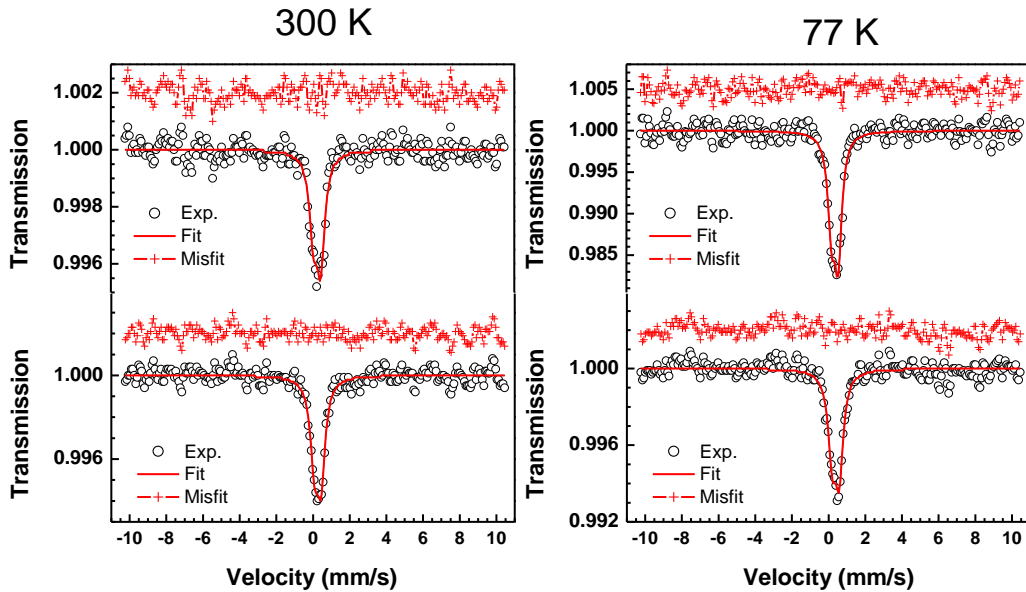


Figure 3.12. Mössbauer spectra at 300 K and 77 K for $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$ samples (with $x = 0.1$ and 0.2).

3.2.3 Crystal Structure Refinements

Because the Mössbauer results indicate two aluminum sites are occupied with iron, the X-ray diffraction models were re-examined to determine those sites. Bond lengths, atomic

displacement parameters (ADP), and site occupancies can be useful in determining partial or mixed occupancy in extended solids. As shown in Table 3.5, all bond lengths decrease as a function of iron content, so the iron sites could not be identified in this manner. Similarly, no ADP values were found to be anomalous, and all refined sites were within ~1% of fully occupied. Therefore, to identify the Fe occupied sites, refinements were conducted with Fe occupying pairs of atomic positions. The total Fe in the unit cell was constrained to the EDS values, and the SUMP command in SHELX was used to refine the iron occupancy of the two sites. Seven of the 10 possibilities were successfully refined and gave similar quality metrics (R factors, goodness of fit, and residual electron density). The remaining three refinements were unstable or resulted in negative site occupancies. Sites were designated as more ordered (higher symmetry) or disordered (lower symmetry) to compare to the Mössbauer results. The model with iron occupying the Al1 and Al2 sites gave the best agreement with the site occupancies of the more ordered and disordered sites obtained from Mössbauer spectroscopy. This analysis assumes that the Fe occupies the same two crystallographic sites in each of the two doping levels.

The Fe doped Gd-analogue has a site preference for iron that is different from the Yb-analogues. The Fe can only be refined for the Al1 site for the Gd-analogue. Modeling other Al sites with Fe leads to an unstable refinement model, thus, we cannot conclusively determine the presence of Fe on the Al2 site for the Gd-analogue. As far as the La-analogue, no Fe was modeled on any sites, indicating that Fe was not successfully substituted for Al or that the concentration of Fe is so minuscule that we are not able to distinguish it. Modeling Fe on any site in the La-analogue leads to an unstable refinement of the model.

3.2.4 Magnetization

Temperature dependent magnetic susceptibility data for $\text{GdCr}_2\text{Al}_{20-x}\text{Fe}_x$ are shown in Figure 3.5. The susceptibility for the three Yb compounds is nearly temperature independent consistent with non-magnetic Yb^{2+} . This is similar to $\text{CeT}_2\text{Al}_{20}$ ($T = \text{Ti-Cr}$) compounds,⁷⁸⁻⁸⁰ which were also reported to be nearly temperature independent paramagnets. The doped and undoped Gd-analogues show no magnetic ordering down to 3 K, which is in contrast with previous literature that reported an antiferromagnetic ordering at 3.90(5) for $\text{GdCr}_2\text{Al}_{20}$.⁷⁷ A reason for the discrepancy is that previous magnetic data were measured on polycrystalline $\text{GdCr}_2\text{Al}_{20}$, and our present work is on single crystalline material, which allows us to directly measure intrinsic properties. Both the doped and undoped Gd-compounds yield $\mu_{\text{eff}} = 7.69(8)$ and $7.67(6) \mu_B/\text{Gd}$ and Weiss constants of -8.22(6) and -5.31(2) K, respectively, by using the modified Curie Weiss equation from 80 to 370 K. Although no magnetic ordering is apparent, the negative Weiss temperatures indicate a dominate antiferromagnetic exchange interaction between the Gd magnetic moments. The magnetic susceptibility of $\text{LaCr}_2\text{Al}_{20}$ is essentially temperature independent, which would indicate that Cr is non-magnetic. There is no indication of magnetic ordering down to 3 K in any of the $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La, Gd, Yb}$) analogues.

Field dependent magnetization data (3 K) for $\text{GdCr}_2\text{Al}_{20-x}\text{Fe}_x$ are shown in Figure 3.6. The magnetization of $\text{YbCr}_2\text{Al}_{19.8}\text{Fe}_{0.2}$ and $\text{YbCr}_2\text{Al}_{19.9}\text{Fe}_{0.1}$ is very low and saturates at ~ 0.005 - $0.007 \mu_B/\text{mol}$ at 9 T. The $\text{GdCr}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$ magnetization data show linear dependence as a function of field at low field (< 3 T), which is typical of paramagnetic samples, then begin to deviate around $6 \mu_B/\text{mol Gd}$, which is close to the saturation magnetization of Gd^{3+} ($7 \mu_B/\text{mol}$). The nearly identical form and magnitude of the field dependent magnetization data for both Gd analogues is a good indication that the Fe is non-magnetic in the sample.

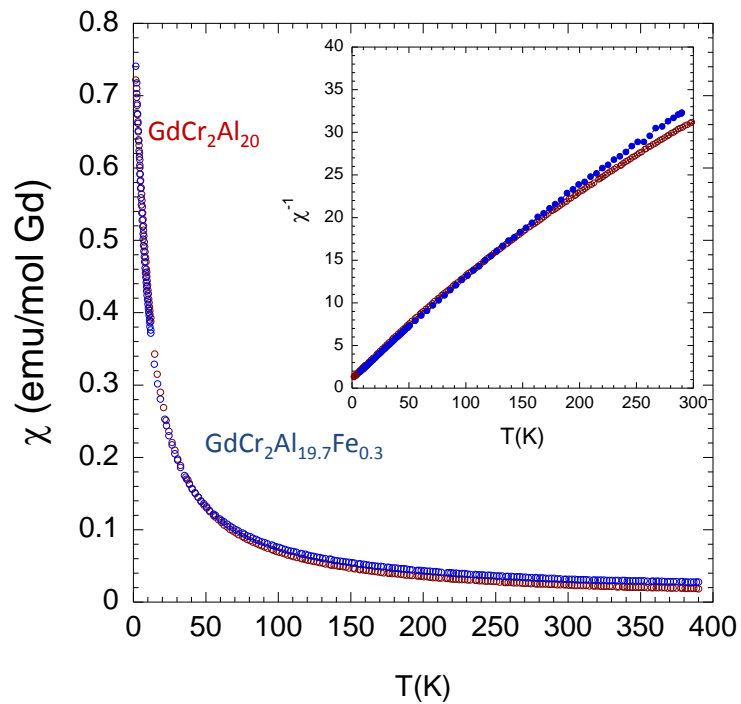


Figure 3.13. Temperature dependent magnetic susceptibility data for $\text{GdCr}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$.

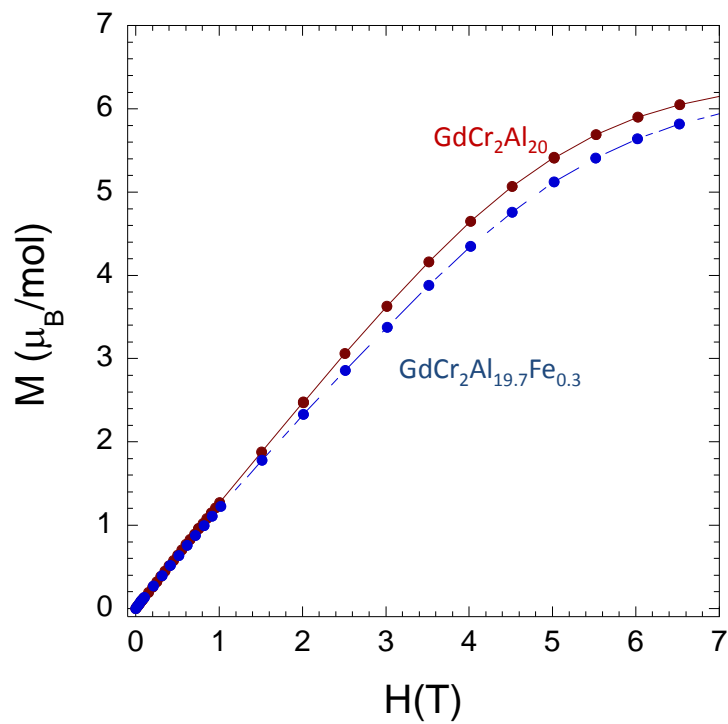


Figure 3.14. Field dependent magnetization data at 3 K are shown for $\text{GdCr}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$.

3.4 Conclusions

Single crystals of $\text{LnCr}_2\text{Al}_{20-x}\text{Fe}_x$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$) were grown with molten aluminum flux. ^{57}Fe Mössbauer spectroscopy was essential in determining which sites the iron atoms occupied and indicated that the iron atoms occupied two distinct crystallographic sites. Crystallographic models were refined with Fe occupying each pair of crystallographic sites, and the best agreement with the Mössbauer spectroscopy was achieved when the Fe atoms partially occupied the Al1 (96g) and Al2 (48f) sites. The iron occupancy of the Al2 site remained fairly constant between the doping levels, while the iron occupancy of the Al1 site increased from ~0.5% to ~1.3% for the larger doping level. Single crystal X-ray diffraction data of the Fe doped Gd-analogues showed that Fe prefers to substitute for Al as opposed to a transition metal. Given the volume change with Fe substitution and the difference in atomic radii of the elements, it is reasonable to conclude that our model is suitable. Based on the atomic radii of Cr (1.249) and Fe (1.241), if Fe substitutes onto the transition metal site, we would expect a negligible change in volume. However, in our experiments, the volume of $\text{GdCr}_2\text{Al}_{20}$ ($3023.5(11) \text{ \AA}^3$) shows a decrease in volume upon substitution ($3005.3(5) \text{ \AA}^3$). This trend is also consistent with the Fe-doped Yb compounds as well. Due to the results of ^{57}Fe Mössbauer spectroscopy and single crystal X-ray diffraction data, we have successfully characterized the first pseudo ternary intermetallic of the $\text{CeCr}_2\text{Al}_{20}$ structure type, where the Fe substitutes for the main group element. The results indicate that the latter transition metals ($\geq \text{Fe}$) do not form $\text{LnT}_2\text{Al}_{20}$ compounds adopting the $\text{CeCr}_2\text{Al}_{20}$ structure type, which can be rationalized by both atomic volume and valence electron count arguments.⁸⁰

Like $\text{YbCr}_2\text{Al}_{20}$, both $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$ and $\text{LaCr}_2\text{Al}_{20}$ compounds display temperature independent magnetism. Due to the relative size of Gd, Fe can only be substituted on the Al1 site

for $\text{GdCr}_2\text{Al}_{20-x}\text{Fe}_x$, unlike $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$ where the Fe substitutes on both the Al1 and Al2 sites. Single crystals of $\text{GdCr}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{19.7}\text{Fe}_{0.3}$ exhibit paramagnetic behavior down to 3 K with no magnetic ordering, while previously reported polycrystalline $\text{GdCr}_2\text{Al}_{20}$ displayed antiferromagnetic ordering at 3.90(5) K. This shows the importance of growing single crystals to determine the intrinsic magnetic properties of materials.

Chapter 4. Crystal growth and physical properties of Sm_{1.33}Pd₃Ga₈, a disordered variant of the Er₄Pt₉Al₂₄-structure type

4.1 Introduction

Over the last decade, there has been significant interest in the single crystal growth of highly correlated materials. Recently, we have reviewed and highlighted several highly correlated Ce-based intermetallics with unusual properties such as magnetically mediated superconductivity, unusual forms of magnetism, and heavy fermion behavior.²⁷ Heavy fermion compounds are materials whose conduction electrons interact strongly with the local magnetic moments.⁸⁹ This phenomenon results in the electrons behaving as if they have an increased mass and is identified by a large Sommerfeld coefficient, γ , where $C_p = \gamma T + bT^3$ ($\gamma > 200$ mJ/mol-K²). For example, the homologous series Ce_{*n*}MIn_{3*n*+2} ($n = 1, 2$; M = Co, Rh, Ir) is a family of heavy-fermion compounds that exhibit magnetism and superconductivity.^{2-4, 90, 91} The report of Ce_{*n*}MIn_{3*n*+2} ($n = 1, 2$; M = Co, Rh, Ir) and their interesting physical properties stimulated our investigation in the Ce-Pd-Ga-based single crystals, which led to the discovery of CePdGa₆⁹² and Ce₂PdGa₁₂.⁹³ Both materials were found to be tetragonal and composed of Ce-Ga and PdGa_{8/2} layers. Physical property measurements determined each to also be heavy fermion antiferromagnets with $\gamma \sim 300$ mJ/K² mol and $\gamma \sim 72$ mJ/K² mol, respectively, and exhibit metamagnetic transitions at 2 T and 2.5 T, respectively.

In addition, the search for rare earth intermetallics has led to the discovery of the quadrupolar Kondo effect in Pr- and Sm-based intermetallics adopting the CeCr₂Al₂₀ structure type.⁹⁴ PrM₂Al₂₀ (M = Ti, V, Cr) exhibits a decrease in electron scattering in resistivity below 5 K due to Kondo interactions with quadrupolar ordering.⁹⁵ It has been found that by increasing the conduction and *f*-electron hybridization (*c-f*) strength, magnetic ordering can be suppressed leading to greater Kondo interactions. For example, SmM₂Al₂₀ (M = Ti, V, Cr) exhibits a

systematic increase in both Kondo temperature and valence fluctuating temperature from $M = \text{Ti}$ to Cr , which is consistent with the enhancement of the c - f hybridization.^{95, 96} More Recently, $\text{SmTa}_2\text{Al}_{20}$ was reported to exhibit Kondo behavior and a suppressed effective magnetic moment of $0.09 \mu_B/\text{Sm}$ indicating strong c - f hybridization.⁹⁷

Due to the unusual physical properties of Sm-containing intermetallics and the discovery of the layered compounds CePdGa_6 and $\text{Ce}_2\text{PdGa}_{12}$, we were motivated to grow Sm-Pd-Ga-based single crystals that led to the discovery of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$. Several isostructural analogues $\text{R}_{1.33}\text{Pt}_3\text{Al}_8$ ($R = \text{Ce}, \text{Gd}$) have been reported.^{98, 99} $\text{Gd}_{1.33}\text{Pt}_3\text{Al}_8$ orders antiferromagnetically at 20 K, but upon doping with silicon to yield $\text{Gd}_{1.33}\text{Pt}_3(\text{Al}, \text{Si})_8$, the ordering temperature decreases to 7 K.⁹⁸ The structure of $\text{Ln}_{1.33}\text{Pt}_3\text{Al}_8$ ($\text{Ln} = \text{Ce}, \text{Gd}$) is composed of two dimensional layers consisting of a Pt_2Al_4 layer, R-Al disordered layer, and PtAl_2 layer stacked along c -direction. The Ln atoms are located in a 2- d triangular net with an interatomic distance of $\sim 4 \text{ \AA}$, resembling a Kagome network. Samarium intermetallics with similar rare-earth geometry have shown unusual magnetism such as spin glass and frustration as seen in SmNiGeAl_4 ¹⁰⁰ and SmPd_2Al_3 .^{101, 102} Herein, we report the synthesis, crystal structure, and physical properties of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$.

4.2 Experimental

4.2.1 Synthesis

The flux-growth method was selected to grow single crystals, which uses a low melting metal as a flux.²⁵⁻²⁷ Initially, we targeted $\text{Sm}_2\text{Pd}_3\text{Ga}_9$ due to our recent report of $\text{Yb}_2\text{Pd}_3\text{Ga}_9$.²⁷ Therefore, the elements Sm, Pd, and Ga were weighed in the same atomic ratios of 1:2:5 and loaded into an alumina crucible. The crucible was placed in a fused-silica tube topped with silica wool. The fused-silica tube was then evacuated (50-70 mTorr) and sealed. The vessel was heated to $1150 \text{ }^\circ\text{C}$ at a rate of $170 \text{ }^\circ\text{C/h}$, and dwelled for 2 h. The vessel was then cooled to $500 \text{ }^\circ\text{C}$ at a

rate of 150 °C/h, and subsequently cooled to 400 °C at a rate 8 °C/h, followed by centrifugation to remove the excess Ga. Hot water was used to separate the aggregate crystals from the gallium flux and 3M DMF/I₂ solution was employed to clean residual gallium on the surfaces of the single crystals. The single crystals dimensions were ~ 0.5 x 0.5 x 3 mm³.

4.2.2 Powder and Single Crystal X-ray Diffraction

Ground aggregates of crystals were characterized by X-ray powder diffraction using a Bruker AXS D8 Advance diffractometer with Cu K α ₁ radiation ($\lambda = 1.540562$ Å). The diffraction pattern is consistent with the calculated powder diffraction pattern of Sm_{1.33}Pd₃Ga₈. Single crystals of Sm_{1.33}Pd₃Ga₈ were cut to suitable sizes for data collection and mounted onto a glass fiber with epoxy. The fiber was then placed on a Nonius Kappa CCD diffractometer equipped with Mo K α radiation ($\lambda = 0.71073$ Å). Data was collected up to $\theta = 32^\circ$ at 298 K. The crystal structure was solved by direct methods with SIR92⁵⁸ and refined with SHELXL97.⁵⁹ The atomic positions, selected interatomic distances, and crystallographic parameters of Sm_{1.33}Pd₃Ga₈ are provided in Tables 4.1-4.3.

4.2.3 Structural Refinement

Following the initial refinement of Sm_{1.33}Pd₃Ga₈ using the previously reported atomic positions of Gd_{1.33}Pt₃Al₈, unusually large atomic displacement parameters (ADP) for Sm1 and Ga4 were observed possibly indicating that a lighter atom or no atom at all should occupy the site or disorder/partial occupancy is present. No other ADP values were found to be anomalous, and all refined sites were within ~ 1 % of fully occupied. A residual electron density of 127.24 e Å⁻³ and deepest minimum of -10.00 e Å⁻³ were observed. These Q peaks were located ~ 0.03 Å and 0.45 Å away from the Sm and Ga4 site, respectively. Because of the large atomic displacement parameters and the location of the Q peaks it was believed that the Sm and Ga4 site were partially

occupied. Therefore, to identify the occupancy of Sm and Ga4 sites, their occupancy were refined freely and found to be ~ 67 and 33 % occupancy, respectively.

Table 4.1. Atomic Positions

| Atom | <i>x</i> | <i>y</i> | <i>z</i> | Occ. | $U_{eq} (\text{\AA}^2)^a$ |
|------|-------------|-------------|--------------|----------|---------------------------|
| Sm1 | 0 | 0 | 0.269775(13) | 0.670(2) | 0.00699(19) |
| Pd1 | 0 | 0 | 0 | 1.00 | 0.00806(17) |
| Pd2 | 0 | 0 | 0.120867(13) | 1.00 | 0.00931(16) |
| Ga1 | 0 | 0 | 0.44354(2) | 1.00 | 0.01176(19) |
| Ga2 | 0 | 0 | 0.18643(2) | 1.00 | 0.0107(2) |
| Ga3 | 0 | 0 | 0.35195(2) | 1.00 | 0.00900(19) |
| Ga4 | 0.53713(19) | 0.46287(19) | 0.39464(3) | 0.330(2) | 0.01004(4) |

^a U_{eq} is defined as one-third of the trace of the orthogonalized U_{ij} tensor.

Table 4.2. Selected Interatomic Distance (\AA)

| Sm _{1.33} Pd ₃ Ga ₈ | |
|--|------------|
| Sm | |
| -Ga1 (x3) | 3.1020(4) |
| -Ga2 (x1) | 3.2488(7) |
| -Ga3 (x4) | 3.0635(4) |
| Pd1 | |
| -Ga3 (x6) | 2.7071(16) |
| -Ga4 (x2) | 2.6027(9) |
| Pd2 | |
| -Ga1 (x3) | 2.5473(6) |
| -Ga2 (x3) | 2.5556(5) |
| -Ga2 (x1) | 2.7104(5) |
| -Ga4 (x1) | 2.5202(4) |

Table 4.3. Crystallographic Parameters

| | |
|---|--------------------|
| Crystal System | Trigonal |
| Space Group | $R\bar{3}m$ |
| a (Å) | 4.353(5) |
| c (Å) | 38.98(4) |
| V (Å ³) | 639.70(12) |
| Z | 3 |
| Crystal dimensions (mm ³) | 0.02 x 0.02 x 0.03 |
| θ range (°) | 4.71 – 30.98 |
| μ (mm ⁻¹) | 37.651 |
| Data Collection | |
| Measured Reflections | 917 |
| Independent Reflections | 313 |
| Reflections with $I > 2\sigma(I)$ | 296 |
| R_{int} | 0.0245 |
| h | -6 to 6 |
| k | -4 to 4 |
| l | -55 to 52 |
| Refinement | |
| R_1 (F) ^a | 0.0178 |
| wR_2 ^b | 0.0396 |
| Reflections | 313 |
| Parameters | 27 |
| $\Delta\rho_{max}$ (e Å ⁻³) | 0.992 |
| $\Delta\rho_{min}$ (e Å ⁻³) | -1.736 |
| Extinction coefficient | 0.00108(10) |
| GOF | 1.194 |

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|$$

$$^b wR_2 = [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0123 P)^2 + 7.4140 P], [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}.$$

4.2.4 Physical Properties

Magnetic data were collected on grounded polycrystalline samples using a Quantum Design Magnetic Property Measurement System (MPMS). The temperature-dependent susceptibility was measured under zero-field conditions (ZFC) between 2 and 300 K with an applied magnetic field of 0.5 and 3 T. Field-dependent magnetization data was measured at 2 and 300 K with fields up to 7 T. The electrical resistivity measurement was performed on a single crystal by the standard four-probe AC technique.

4.3 Results and Discussion

4.3.1 Crystal Structure

$\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ crystallizes in the space group $R\bar{3}m$ with lattice parameters $a = 4.353(5)$ Å and $c = 38.98(4)$ Å and $V = 639.70(12)$ Å³. The crystal structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is shown in Figure 4.1. There are seven crystallographic positions in $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, including Sm, Pd1, Pd2, Ga1-3, and Ga4 occupying the $6c$, $3a$, $6c$, $6c$, and $18h$ sites, respectively. The crystal structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ can be viewed as a disordered variant of the triclinic $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ structure type which has cell dimensions $a = 7.462(2)$, $b = 12.940(2)$, and $c = 13.044(2)$ Å.³⁸ The rhombohedral dimensions can be related to the triclinic unit cell by the following relationships: $a_r = a_t/\sqrt{3}$ and $c_r = 3c_t$ (where r = rhombohedral and t = triclinic).

The structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, as shown in Figure 4.2, is composed of three distinct slabs: $\text{Pd}_2\text{Ga}_4 + 2 \times [\text{Sm}_{0.67}\text{Ga}] + \text{PdGa}_2$. The slabs stack in the c -direction in an ABCBABC'BA'BC''B sequence, where A is a Pd_2Ga_4 slab, B is a disordered $\text{Sm}_{0.67}\text{Ga}$ slab, and C is a PdGa_2 slab, and the position of the slabs with respect to each other is indicated by A', A''. Similarly, $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ is formed by three distinctive slabs leading to $2 \times [\text{Er}_2\text{Al}_3] + 3 \times [\text{PdAl}_2 + \text{Pd}_2\text{Al}_4]$ that stack in the c -direction. The $\text{Sm}_{0.67}\text{Ga}$ slab can be related to three superimposed Er_2Al_3 slabs offset by $a_t/\sqrt{3}$ as shown in Figure 4.3. Due to the partially occupied Ga4 site (~ 33 %) in the $\text{Sm}_{0.67}\text{Ga}$ slab, three superimposed Er_2Al_3 slabs must be used to account for the near tripling of the c -dimension of the $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ phase.

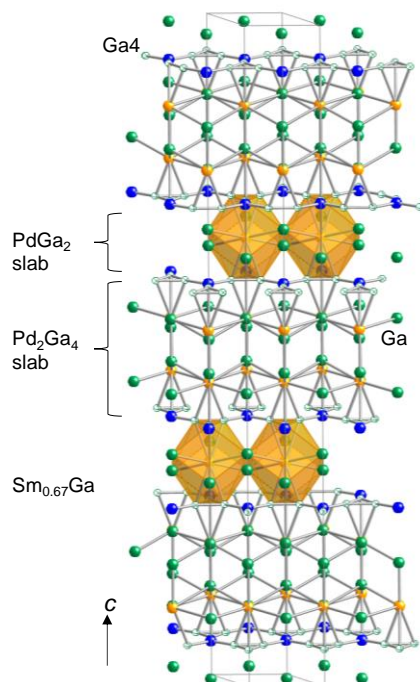


Figure 4.15. The crystal structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ viewed along the c -axis. Sm atoms are shown as blue spheres. Pd1 atoms are represented as orange polyhedra, and Pd2 atoms are orange spheres. Gallium atoms are shown as solid green spheres, while Ga4 atoms are represented as green hatch spheres.

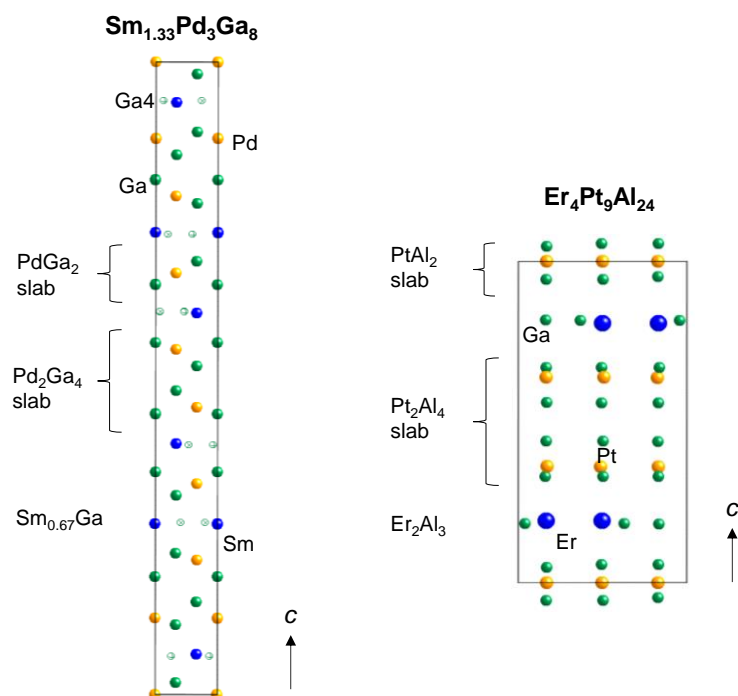


Figure 4.16. The unit cell projection of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ and $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ along the c -axis are shown.

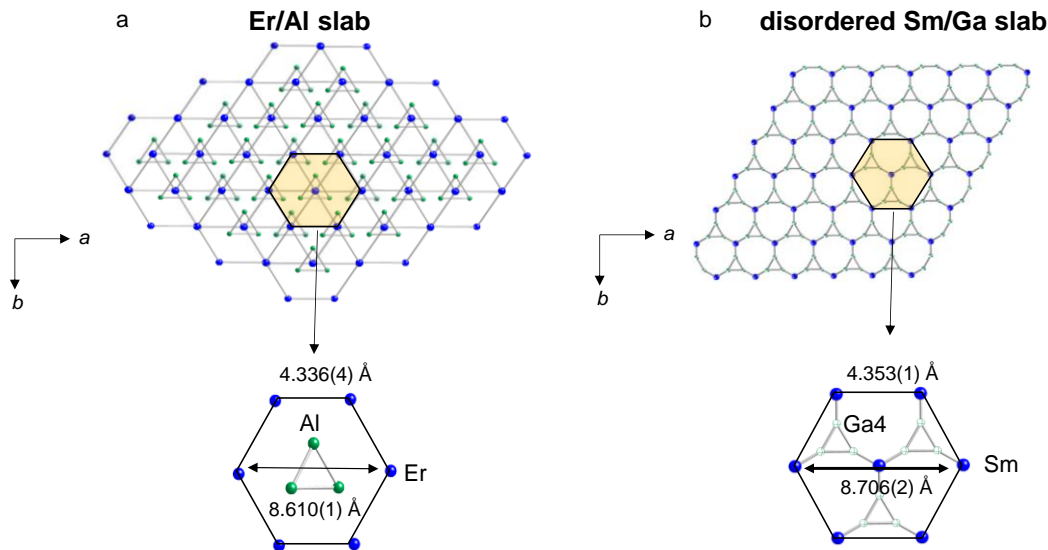


Figure 4.17. Projections of the $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ and $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ crystal structure down the c -plane are shown.

Figure 4.4 shows the $\text{Sm}_{0.67}\text{Ga}$ segment which consists of a triangular mesh of partially occupied Ga4 (33 %) atoms with the Sm (67 %) atoms residing in the center. The Sm-Ga distances are $1.539(2) \text{ \AA}$ and the Ga-Ga distances are $1.692(3) \text{ \AA}$, which are too close to be considered an interatomic distance given the sum of Sm and Ga atomic radii. As a result, Sm and Ga4 atomic sites were refined with partial occupancy. Similar contacts of $1.5381(7)$ and $1.5505(5) \text{ \AA}$ were also found in $\text{Gd}_{1.33}\text{Pt}_3\text{Al}_8$ and $\text{Ce}_{1.33}\text{Pt}_3\text{Al}_8$ ⁹⁹, respectively. Isostructural analogues $\text{Ln}_{1.33}\text{Pt}_3\text{Al}_8$ (Ln = Gd, Ce)^{98, 99} also yielded partial occupancy of Ln ~ 66 and Al ~ 33 % where $1/3$ of the Ln atoms are exchanged by Al-triangles. An attempt to explain the unique relationship between the disordered Ln-Al slab and the ordered Ln-Al slab was previously made between $\text{Gd}_{1.33}\text{Pt}_3\text{Al}_8$ and $\text{Er}_4\text{Pt}_9\text{Al}_{24}$.⁹⁸ The $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ -structure type is considered to be the supercell of the $\text{Gd}_{1.33}\text{Pd}_3\text{Al}_8$ -structure type. The partially occupied Gd and Al atoms allow the $\text{GdAl}_{0.67}$ slab to coincide in the c -direction retaining the 3-fold rotational symmetry, whereas in $\text{Er}_4\text{Pt}_9\text{Al}_{24}$, the Er/Al slabs do not coincide due to the Er and Al being fully occupied and ordered, destroying the 3-fold axis of rotation. The $\text{Ln}_{0.67}\text{X}$ (Ln = rare earth; X = Al, Si, Ga) slab is very robust, which is evident in that

it has been observed in various compounds such as $\text{Gd}_{0.67}\text{Pt}_2\text{Al}_5$ ⁹⁸ and $\text{La}_x\text{Ce}_{1.33-x}\text{Pt}_4\text{Ga}_{10}$,¹⁰³ where the Ln atoms are situated in a triangle mesh of X atoms (X = Ga or Al).

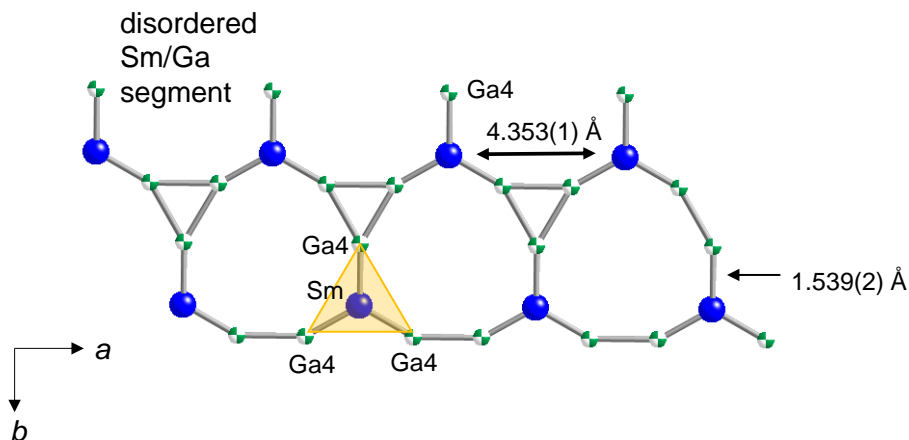


Figure 4.18. The Sm/Ga disordered slab viewed parallel to c -direction.

There are three distinct Sm-Sm distances in $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$: one Sm-Sm distance along the ab -plane and two Sm-Sm distances along the c -direction. The $(\text{Sm-Sm})_{ab}$ interatomic spacing is 4.353(5) Å, which is comparable to previously reported Sm-compounds and isostructural analogues $\text{Ln}_{1.33}\text{Pt}_3\text{Al}_8$ (Ln = Gd, Ce) with $(\text{Gd-Gd})_{ab}$ and $(\text{Ce-Ce})_{ab}$ interatomic spacing of 4.309(1) Å and 4.361(2) Å, respectively. The $(\text{Sm-Sm})_c$ distances are ~ 5.3391 Å parted by the PdGa_2 slab and ~ 8.1846 Å separated by the Pd_2Ga_4 slab, while $(\text{Gd-Gd})_c$ and $(\text{Ce-Ce})_c$ interatomic distances in $\text{Ln}_{1.33}\text{Pt}_3\text{Al}_8$ (Ln = Gd, Ce) are ~ 5.5197 and ~ 9.3528 and ~ 5.5989 and ~ 9.4522 Å. The three different Sm-Sm distances in $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ may lead to anisotropic magnetic behavior.

Figure 4.5a shows the PdGa_2 segment consisting of Pd1, Ga2, and Ga3 and can be described as hexagonal close-packed layers with the Pd atoms residing between the gallium networks. This arrangement has been found in $\text{Y}_2\text{Co}_3\text{Ga}_9$ and isostructural analogs¹⁰⁴⁻¹⁰⁶ as well as $\text{SmNiAl}_4\text{Ge}_2$ ¹⁰⁰, $\text{Yb}_2\text{Pd}_3\text{Ga}_9$,²⁷ CePdGa_6 ,⁹² and $\text{Ce}_2\text{PdGa}_{12}$.⁹³ Pd1 is surrounded by eight gallium atoms (six Ga4 partially occupied (33%) atoms), as shown in Figure 4.5b, with Pd-Ga

distances of 2.6027(9) and 2.7071(16) Å, which are slightly greater than the sum of the atomic radii of Ga (1.22 Å) and Pd (1.37 Å) as well as the interatomic distances in Pd-Ga binaries Pd_5Ga_2 ¹⁰⁷ and PdGa .¹⁰⁸ The Pd_2Ga_4 segment, as shown in Figure 4.5c, consists of Pd2, Ga1, Ga2, and Ga4 forming two PdGa_2 nets that are connected by Ga-Ga bonds. Pd2 is surrounded by a total of 8 gallium atoms (three Ga4 partially occupied (33%) atoms), as shown in Figure 4.5d, with Pd-Ga distances 2.5473(6), 2.5556(5), 2.7104(5), and 2.5202(4) Å.

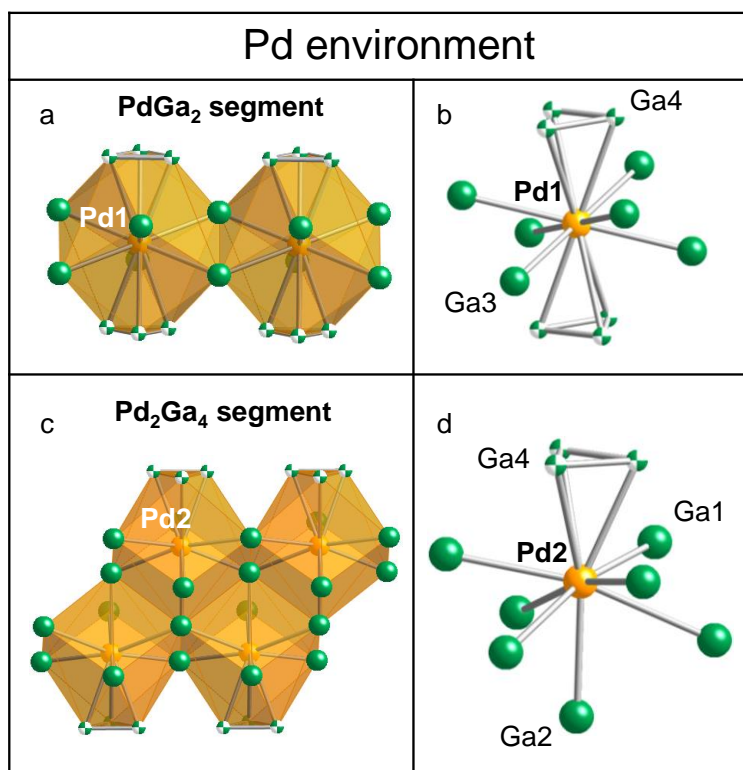


Figure 4.19. The PdGa_2 (a) and Pd_2Ga_4 (c) segments and the local environments of Pd1 (b) and Pd2 (d) are shown.

4.3.2 Magnetization and Electrical Transport

The temperature dependent magnetic susceptibility of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, not shown, is nearly temperature independent consistent with the presence of Sm^{2+} ions. The field-dependent magnetization measurements were measured at 3 K up to 9 T to characterize $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$. Anisotropic field dependent magnetization of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is shown in Figure 4.6. When the

applied field is parallel to the c -direction the magnetization initially increases until 0.5 T where there is a change in slope. Subsequently, the magnetization increases to $0.015 \mu_B/\text{mol Sm}$ at 9 T, which is below the expected value for free Sm^{3+} ions ($\mu_{\text{sat}} = 0.71 \mu_B/\text{mol}$). When the field is parallel to the ab -plane the magnetization displays linear behavior over the field measured up to $0.27 \mu_B/\text{mol Sm}$, well below the expected value for free Sm^{3+} ions ($\mu_{\text{sat}} = 0.71 \mu_B/\text{mol}$). The magnetization increases to $0.27 \mu_B/\text{mol Sm}$ at 9 T when the field is oriented ab -plane, which is two times greater than the magnetization when the field is oriented in the c -direction. Therefore, the magnetic correlation is stronger in the ab -direction.

The magnetic anisotropy observed in the field dependent magnetization coincides with differences in Sm-Sm distances in $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$. For the $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$, the Sm-Sm distances are $4.353(5) \text{ \AA}$ along the ab -plane, while the Sm-Sm distances are $\sim 5.3391 \text{ \AA}$ and 8.1846 \AA for the c -direction. In considering the differences in the Sm-Sm distances, the magnetic correlations in the ab -plane should be stronger than those along the c -axis. Similar behavior has been reported for CePdGa_6 ⁹² and $\text{Ce}_2\text{PdGa}_{12}$,⁹³ where there are two unique Ce-Ce distances in the ab - and c -direction. In CePdGa_6 , the Ce-Ce interatomic distances are $4.350(3) \text{ \AA}$ and $7.922(6) \text{ \AA}$ for the ab - and c -direction,⁹² while the Ce-Ce interatomic distances in the ab -plane are $4.318(6) \text{ \AA}$ and $7.664(5) \text{ \AA}$ and $7.882(6) \text{ \AA}$ for the c -direction in $\text{Ce}_2\text{PdGa}_{12}$.⁹³ The magnetic correlations are stronger in the ab -plane for CePdGa_6 and $\text{Ce}_2\text{PdGa}_{12}$ given the shorter Ce-Ce distances.^{92,93} Figure 4.7 shows the resistivity of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ as a function of temperature from 2 to 300 K. $\text{Sm}_{1.33}\text{Pd}_2\text{Ga}_8$ displays metallic behavior in the electrical resistivity.

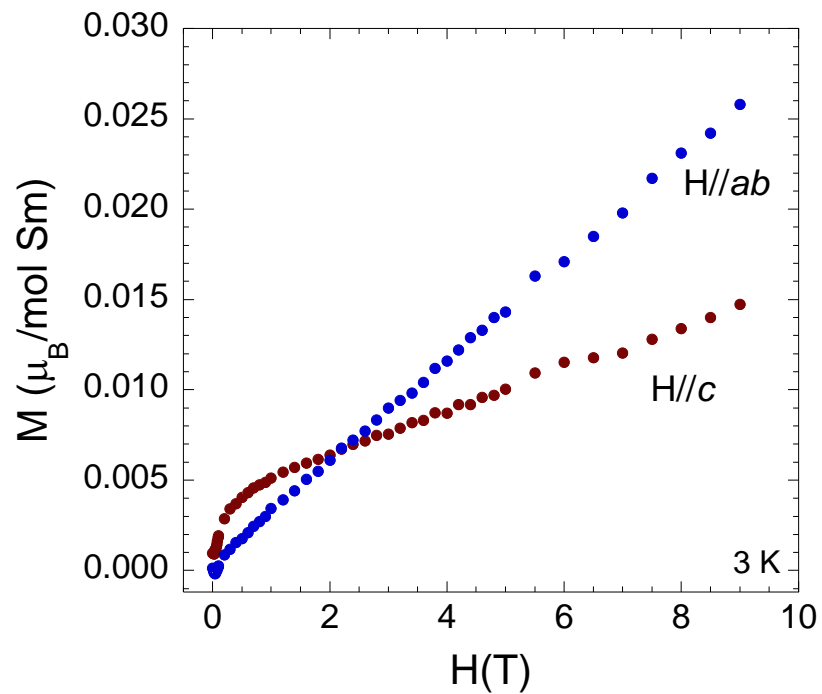


Figure 4.20. Magnetization as a function of applied field, measured at 3 K. Blue and red circles represent data collected for fields applied parallel to the crystallographic c - and ab -direction, respectively.

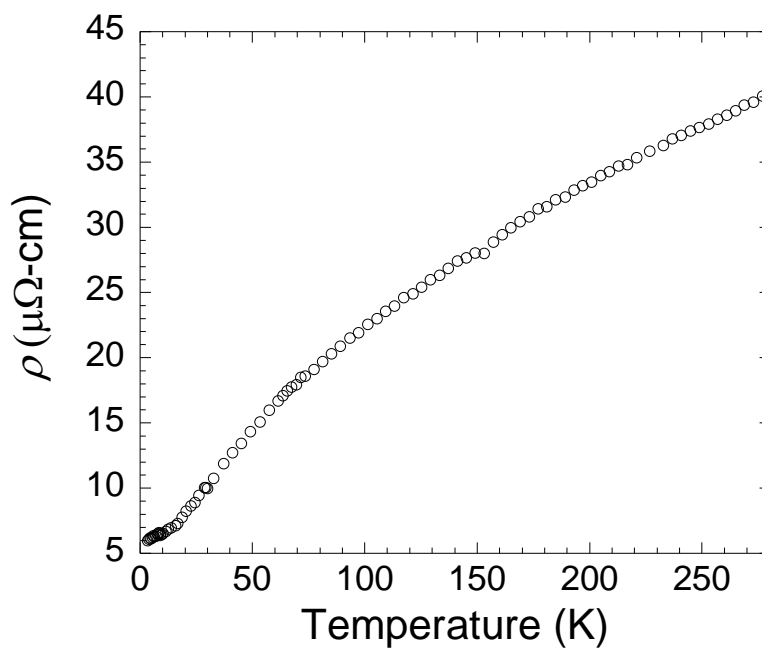


Figure 4.21. Electrical resistivity of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$.

4.4 Conclusion

The crystal structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ adopts a disordered variant of $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ -structure type with the building blocks: PdGa_2 , Pd_2Ga_4 , $\text{Sm}_{0.67}\text{Ga}$ slabs. The crystal structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is anisotropic given the lattice parameters and the magnetic behavior. Considering the structural motifs, unusual properties may exist in the compounds adopting the $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ phase. Further exploration to grow isostructural analogues are of interest to study the anisotropic and disorder effects.

Chapter 5. Investigation of Fe and Ni incorporation in CeCo₂Al₈

5.1 Introduction

The growth of single crystalline Ce and Yb intermetallic compounds has attracted our interest in recent years because of the possibility of magnetically mediated superconductivity and unusual magnetism.²⁷ Our effort to study materials with competing magnetic interactions such as RKKY and Kondo interactions¹⁰⁹ has led us to grow and characterize compounds with valence instability. In particular, compounds such as CeCo₂Al₈,¹¹⁰ an intermetallic phase adopting the CaCo₂Al₈ structure type,¹¹¹ follows Curie Weiss behavior with an effective moment consistent with Ce³⁺ with a $\theta = -136(1)$ K, while neither Ce or Fe carry a magnetic moment in CeFe₂Al₈.^{110, 112} The electrical resistivity of the cerium compounds are remarkably different, with the Co analogue showing a maxima near 45 K, while the Fe analogue near 200 K, which is consistent with the strongly hybridized Ce ion with conduction electrons.

FeS₂ an insulator with ~ 1 eV band gap and CoS₂ an itinerant ferromagnet was previously reported.¹¹³ Inspired by the carrier-doped magnetic semiconductor Fe_{1-x}Co_xS₂¹¹⁴ and compounds exhibiting insulator-to-metal transition, we set out to grow single crystals of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; $0 \leq x < 1$). Herein, we report the synthesis, crystal structure, magnetic and electrical properties of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; $0 \leq x < 1$).

5.2 Experimental

5.2.1 Synthesis

Single crystals of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; $0 \leq x < 1$) were prepared using the molten flux technique.^{26, 27} Ce (rod, 99.9 %), Co (powder, 99.9 %), M (Fe, Ni powder, 99.9 %), and Al (shots, 99.9 %) were used as received. For CeCo₂Al₈, the elements Ce:Co:Al in atomic ratios 1:2:20, respectively, were placed in an alumina crucible, topped with another crucible, and sealed in an evacuated (50-70 mTorr) fused silica tube filled with argon. The silica tube was heated to

1200 °C at a rate of 100 °C/h, and dwelled for 24 h. The ampoule was subsequently cooled to 900 °C at a rate of 4 °C/h, followed by centrifugation to separate crystals from the aluminum flux. Single crystals of CeCo₂Al₈ were etched in dilute NaOH (~ 0.1 M) and then cleaned with dilute HNO₃ (~ 0.1 M). The nominal ratios of the elements weighed to grow single crystals of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; 0 ≤ x < 1) are provided in Table 5.1.

5.2.2 Elemental Analysis

Elemental analysis was conducted via electron dispersive spectroscopy (EDS) using a FEI Quanta 200 scanning electron microscope equipped with an EDAX detector at an accelerating voltage of 20 kV. Spectra were integrated for 30 seconds and the results from 5 spots were averaged and normalized to Ln to determine the atomic percentage of each element. The compositions are Ce_{1.00(3)}Co_{1.48(6)}Fe_{0.29(1)}Al_{9.43(9)}, Ce_{1.00(7)}Co_{1.30(6)}Fe_{0.55(3)}Al_{8.42(15)}, Ce_{1.00(5)}Co_{1.14(11)}Fe_{1.06(10)}Al_{7.58(25)}, Ce_{1.00(3)}Co_{1.73(2)}Ni_{0.24(3)}Al_{9.52(5)}, and Ce_{1.00(3)}Co_{1.31(15)}Ni_{0.62(9)}Al_{8.48(18)}.

5.2.3 Single-Crystal X-ray Diffraction

Fragments of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; 0 ≤ x < 1) single crystals were cut to suitable sizes and glued onto glass fibers with epoxy. The fibers were mounted on a Nonius Kappa CCD X-ray diffractometer equipped with a Mo Kα radiation source (λ = 0.71073 Å) at room temperature. Also, fragments of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; 0 ≤ x < 1) single crystals were mounted on a Bruker D8 Quest Kappa single crystal X-ray diffractometer equipped with a IμS microfocus source (λ = 0.71073 Å) operating at 50 kV and 1 mA for multiple unit cell determinations. A starting model of the crystal structures was first obtained using SIR92⁵⁸ and refined with SHELXL97.⁵⁹ The atomic positions, Wyckoff symmetries, displacement parameters, site occupancies, and interatomic distances of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; 0 ≤ x < 1) are provided in Tables 5.2-5.7.

5.2.4 Structure Refinement

Because scattering factors of Fe, Co, and Ni are similar, the composition obtained from EDX data were fixed during refinement of single crystal X-ray data. In all refinements the dopant (M) was only modeled on the Co1 and Co2 sites, except for $\text{CeCo}_{2-x}\text{Fe}_x\text{Al}_8$ ($x = 0.33$) where Fe was only modeled on the Co1 site. For the refinement of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}; 0 \leq x < 1$), we used the atomic positions of CeCo_2Al_8 and observed that the atomic displacement parameters (ADP) of the Co1 site was greater than Co2 site. Therefore, the dopant M was first modeled on the Co1 site and subsequently on the Co2 site. The dopant M in all refined models favored the Co1 position over the Co2 site, which is different than the previously reported $\text{YbNi}_{2-x}\text{Fe}_x\text{Al}_8$ ($x = 0.91$).¹¹⁵ The structural refinement of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}; 0 \leq x < 1$) led to M composition provided in Table 5.1.

Table 5.1. Compositions of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}$)

| | Fe | | | Ni | | |
|-------------|---------|---------|----------|---------|---------|---------|
| Nominal (x) | 0.33 | 0.67 | 1.00 | 0.33 | 0.67 | 1.00 |
| XRD (x) | 0.23(7) | 0.52(6) | 0.70(4) | 0.29(5) | 0.60(8) | 0.80(7) |
| EDS (x) | 0.30(1) | 0.61(3) | 1.06(10) | 0.24(2) | 0.62(2) | 0.80(4) |

5.3 Results and Discussion

5.3.1 Crystal Structure

$\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}; 0 \leq x < 1$) adopts the CaCo_2Al_8 structure type¹¹¹ with the orthorhombic space group, *Pbam*. This structure type has also been reported for LnRu_2Ga_8 ($\text{Ln} = \text{Ce}, \text{Pr}$),¹¹⁶ PrCo_2Al_8 ,¹¹⁷ and $\text{YbNi}_{2-x}\text{Fe}_x\text{Al}_8$ ($x = 0.91$).¹¹⁵ There are 12 unique crystallographic positions in CeCo_2Al_8 consisting of one Ce, two Co, and nine Al atoms. The crystal structure of CeCo_2Al_8 is shown in Figure 5.1 and consists of Ce atoms encapsulated in channels created by the Co-sublattice.

Table 5.2. CeCo_{2-x}Fe_xAl₈ (0 ≤ x < 1) Crystallographic Parameters

| Compound | CeCo ₂ Al ₈ | CeCo _{1.77(7)} Fe _{0.23(7)} Al ₈ | CeCo _{1.48(4)} Fe _{0.52(6)} Al ₈ | CeCo _{1.30(4)} Fe _{0.70(4)} Al ₈ |
|--|-----------------------------------|---|---|---|
| Crystal System | Orthorhombic | Orthorhombic | Orthorhombic | Orthorhombic |
| Space Group | <i>Pbam</i> | <i>Pbam</i> | <i>Pbam</i> | <i>Pbam</i> |
| <i>a</i> (Å) | 12.4720(2) | 12.4770(5) | 12.4820(5) | 12.4591(5) |
| <i>b</i> (Å) | 14.3870(3) | 14.391(2) | 14.401(3) | 14.3798(6) |
| <i>c</i> (Å) | 4.0220(5) | 4.027(2) | 4.029(3) | 4.024(1) |
| <i>V</i> (Å ³) | 721.69(9) | 723.1(4) | 724.2(5) | 720.96(5) |
| <i>Z</i> | 4 | 4 | 4 | 4 |
| θ range (°) | 2.83 – 31.01 | 3.27 – 31.00 | 2.83 – 30.99 | 2.83 – 30.45 |
| μ (mm ⁻¹) | 11.613 | 11.303 | 11.285 | 10.828 |
| Data Collection | | | | |
| Measured Reflections | 2191 | 2194 | 2144 | 11930 |
| Independent Reflections | 1297 | 1300 | 1300 | 1237 |
| Reflections with I>2σ(I) | 1141 | 1033 | 1092 | 1137 |
| <i>R</i> _{int} | 0.0243 | 0.0284 | 0.0263 | 0.0422 |
| <i>h</i> | -17 to 17 | -17 to 18 | -17 to 18 | -17 to 18 |
| <i>k</i> | -20 to 20 | -20 to 20 | -20 to 20 | -20 to 20 |
| <i>l</i> | -5 to 5 | -5 to 5 | -5 to 5 | -5 to 5 |
| Refinement | | | | |
| <i>R</i> ₁ (F) ^a | 0.0256 | 0.0266 | 0.0298 | 0.0211 |
| w <i>R</i> ₂ ^b | 0.0564 | 0.0583 | 0.0696 | 0.0492 |
| Reflections | 1297 | 1300 | 1300 | 1237 |
| Parameters | 70 | 71 | 74 | 74 |
| Δρ _{max} (e Å ⁻³) | 1.119 | 2.459 | 1.318 | 1.417 |
| Δρ _{min} (e Å ⁻³) | -2.148 | -1.272 | -2.199 | -1.923 |
| Extinction coefficient | 0.0045(3) | 0.0076(3) | 0.0293(11) | 0.0225(6) |
| GOF | 1.179 | 1.039 | 1.163 | 1.248 |

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|$$

$$^b wR_2 = [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0243 P)^2 + 3.6274 P], [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.03119 P)^2 + 0.6661 P], [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0388 P)^2 + 3.0837 P], and [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0239 P)^2 + 0.5008 P], and [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2} for CeCo₂Al₈, CeCo_{1.72(2)}Fe_{0.28(2)}Al₈, CeCo_{1.37(4)}Fe_{0.63(4)}Al₈, and CeCo_{0.98(4)}Fe_{1.00(4)}Al₈, respectively.$$

Table 5.3. CeCo_{2-x}Ni_xAl₈ (0 < x < 1) Crystallographic Parameters

| Compound | CeCo _{1.71(5)} Ni _{0.29(5)} Al ₈ | CeCo _{1.40(8)} Ni _{0.60(8)} Al ₈ | CeCo _{1.20(8)} Ni _{0.80(7)} Al ₈ |
|--|---|---|---|
| Crystal System | Orthorhombic | Orthorhombic | Orthorhombic |
| Space Group | <i>Pbam</i> | <i>Pbam</i> | <i>Pbam</i> |
| <i>a</i> (Å) | 12.4770(10) | 12.4710(5) | 12.4654(5) |
| <i>b</i> (Å) | 14.393(4) | 14.386(2) | 14.3872(6) |
| <i>c</i> (Å) | 4.023(4) | 4.022(3) | 4.022(1) |
| <i>V</i> (Å ³) | 722.5(7) | 721.6(5) | 721.30(6) |
| <i>Z</i> | 4 | 4 | 4 |
| θ range (°) | 2.83 – 31.19 | 2.83 – 31.01 | 2.83 – 30.50 |
| μ (mm ⁻¹) | 11.91 | 11.925 | 11.93 |
| Data Collection | | | |
| Measured Reflections | 2149 | 2197 | 8692 |
| Independent Reflections | 1303 | 1297 | 1249 |
| Reflections with $I > 2\sigma(I)$ | 942 | 1053 | 1070 |
| <i>R</i> _{int} | 0.0488 | 0.0299 | 0.0279 |
| <i>h</i> | -17 to 18 | -17 to 17 | -17 to 17 |
| <i>k</i> | -20 to 20 | -20 to 20 | -20 to 20 |
| <i>l</i> | -5 to 5 | -5 to 5 | -5 to 5 |
| Refinement | | | |
| <i>R</i> ₁ (F) ^a | 0.0366 | 0.0298 | 0.0181 |
| <i>wR</i> ₂ ^b | 0.0628 | 0.0696 | 0.0308 |
| Reflections | 1303 | 1297 | 1249 |
| Parameters | 72 | 72 | 74 |
| $\Delta\rho_{\max}$ (e Å ⁻³) | 1.301 | 1.915 | 1.381 |
| $\Delta\rho_{\min}$ (e Å ⁻³) | -1.392 | -1.416 | -0.677 |
| Extinction coefficient | 0.00235(17) | 0.0050(3) | 0.00005(6) |
| GOF | 1.06 | 1.015 | 1.095 |

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|$$

$$^b wR_2 = [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0112 P)^2 + 7.2986 P], [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0382 P)^2 + 0.7057 P], [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.0136 P)^2 + 0.0005 P], and [\sum [w(F_o^2 - F_c^2)^2] / \sum [w(F_o^2)^2]]^{1/2} for CeCo_{1.71(3)}Ni_{0.29(3)}Al₈, CeCo_{1.38(3)}Ni_{0.60(3)}Al₈, CeCo_{1.26(3)}Ni_{0.73(3)}Al₈, respectively.$$

Table 5.4. CeCo_{2-x}M_xAl₈ (M = Fe, Ni; 0 ≤ x < 1) Atomic Positions

| Element | Symmetry | x | y | z | Occupancy | ^a U _{eq} (Å ²) |
|---|-------------|--------------|--------------|-----|-----------|--|
| CeCo ₂ Al ₈ | | | | | | |
| Ce1 | <i>m</i> | 0.34038(2) | 0.31841(2) | 0 | 1 | 0.00837(11) |
| Co1 | <i>m</i> | 0.03488(6) | 0.40566(5) | 0 | 1 | 0.00693(16) |
| Co2 | <i>m</i> | 0.15166(5) | 0.09643(5) | 0 | 1 | 0.00565(15) |
| Al1 | <i>m</i> | 0.09584(12) | 0.25276(10) | 0 | 1 | 0.0078(3) |
| Al2 | <i>m</i> | 0.33993(12) | 0.04446(11) | 0 | 1 | 0.0097(3) |
| Al3 | <i>m</i> | 0.15953(12) | 0.37939(11) | 1/2 | 1 | 0.0075(3) |
| Al4 | <i>m</i> | 0.45285(13) | 0.17938(10) | 1/2 | 1 | 0.0070(3) |
| Al5 | <i>m</i> | 0.23625(13) | 0.17238(10) | 1/2 | 1 | 0.0077(3) |
| Al6 | <i>m</i> | 0.33139(13) | 0.49140(11) | 1/2 | 1 | 0.0080(3) |
| Al7 | <i>m</i> | 0.02559(13) | 0.13168(11) | 1/2 | 1 | 0.0075(3) |
| Al8 | 2/ <i>m</i> | 0 | 1/2 | 1/2 | 1 | 0.0076(4) |
| Al9 | 2/ <i>m</i> | 0 | 0 | 0 | 1 | 0.0082(4) |
| CeCo _{1.77(7)} Fe _{0.23(7)} Al ₈ | | | | | | |
| Ce1 | <i>m</i> | 0.34072(2) | 0.318513(19) | 0 | 1 | 0.01055(11) |
| Co1 | <i>m</i> | 0.03456(5) | 0.40589(5) | 0 | 0.77(6) | 0.0092(2) |
| Co2 | <i>m</i> | 0.15116(5) | 0.09671(4) | 0 | 1 | 0.00808(15) |
| Al1 | <i>m</i> | 0.02558(12) | 0.13172(10) | 1/2 | 1 | 0.0097(3) |
| Al2 | <i>m</i> | 0.15961(12) | 0.37917(11) | 1/2 | 1 | 0.0095(3) |
| Al3 | <i>m</i> | 0.23606(12) | 0.17258(10) | 1/2 | 1 | 0.0096(3) |
| Al4 | <i>m</i> | 0.33146(12) | 0.49159(10) | 1/2 | 1 | 0.0106(3) |
| Al5 | <i>m</i> | 0.45250(12) | 0.17965(10) | 1/2 | 1 | 0.0095(3) |
| Al6 | <i>m</i> | 0.09581(12) | 0.25304(9) | 0 | 1 | 0.0096(3) |
| Al7 | <i>m</i> | 0.33940(12) | 0.04452(10) | 0 | 1 | 0.0111(3) |
| Al8 | 2/ <i>m</i> | 0 | 1/2 | 1/2 | 1 | 0.0096(4) |
| Al9 | 2/ <i>m</i> | 0 | 0 | 0 | 1 | 0.0104(4) |
| CeCo _{1.48(6)} Fe _{0.52(6)} Al ₈ | | | | | | |
| Ce1 | <i>m</i> | 0.34100(3) | 0.31861(2) | 0 | 1 | 0.01057(15) |
| Co1 | <i>m</i> | 0.03428(7) | 0.40657(6) | 0 | 0.79(7) | 0.0100(3) |
| Fe1 | <i>m</i> | 0.03428(7) | 0.40657(6) | 0 | 0.21(8) | 0.0100(3) |
| Co2 | <i>m</i> | 0.15082(6) | 0.09679(6) | 0 | 0.56(7) | 0.0088(3) |
| Fe2 | <i>m</i> | 0.15082(6) | 0.09679(6) | 0 | 0.46(8) | 0.0088(3) |
| Al1 | <i>m</i> | 0.02569(15) | 0.13175(13) | 1/2 | 1 | 0.0098(4) |
| Al2 | <i>m</i> | 0.15971(15) | 0.37927(14) | 1/2 | 1 | 0.0098(4) |
| Al3 | <i>m</i> | 0.23578(15) | 0.17252(13) | 1/2 | 1 | 0.0101(4) |
| Al4 | <i>m</i> | 0.33141(15) | 0.49210(13) | 1/2 | 1 | 0.0100(4) |
| Al5 | <i>m</i> | 0.45241(15) | 0.17966(13) | 1/2 | 1 | 0.0103(4) |
| Al6 | <i>m</i> | 0.09557(15) | 0.25327(12) | 0 | 1 | 0.0101(4) |
| Al7 | <i>m</i> | 0.33858(14) | 0.04441(14) | 0 | 1 | 0.0118(4) |
| Al8 | 2/ <i>m</i> | 0 | 1/2 | 1/2 | 1 | 0.0101(5) |
| Al9 | 2/ <i>m</i> | 0 | 0 | 0 | 1 | 0.0112(5) |
| CeCo _{1.30(4)} Fe _{0.70(4)} Al ₈ | | | | | | |
| | | | 0 | | | |
| Ce1 | <i>m</i> | 0.340544(12) | 0.318648(12) | 0 | 1 | 0.00855(9) |
| Co1 | <i>m</i> | 0.03460(3) | 0.40615(3) | 0 | 0.68(4) | 0.00687(15) |
| Fe1 | <i>m</i> | 0.03460(3) | 0.40615(3) | 0 | 0.30(4) | 0.00687(15) |
| Co2 | <i>m</i> | 0.15020(3) | 0.09724(3) | 0 | 0.29(5) | 0.00581(16) |
| Fe2 | <i>m</i> | 0.15020(3) | 0.09724(3) | 0 | 0.72(6) | 0.00581(16) |
| Al1 | <i>m</i> | 0.02542(7) | 0.13185(6) | 1/2 | 1 | 0.00673(17) |
| Al2 | <i>m</i> | 0.15966(6) | 0.37884(7) | 1/2 | 1 | 0.00741(19) |
| Al3 | <i>m</i> | 0.23543(7) | 0.17269(6) | 1/2 | 1 | 0.00767(18) |
| Al4 | <i>m</i> | 0.33146(7) | 0.49203(7) | 1/2 | 1 | 0.00750(18) |
| Al5 | <i>m</i> | 0.45229(7) | 0.17998(6) | 1/2 | 1 | 0.00733(18) |
| Al6 | <i>m</i> | 0.09522(6) | 0.25318(5) | 0 | 1 | 0.00754(18) |

(Table 5.4. continued)

| Element | Symmetry | x | y | z | Occupancy | ^a U _{eq} (Å ²) |
|---|------------|--------------|--------------|-----|------------|--|
| Al7 | <i>m</i> | 0.33860(6) | 0.04479(7) | 0 | 1 | 0.0094(2) |
| Al8 | <i>2/m</i> | 0 | 1/2 | 1/2 | 1 | 0.0071(2) |
| Al9 | <i>2/m</i> | 0 | 0 | 0 | 1 | 0.0077(2) |
| CeCo _{1.71(5)} Ni _{0.29(5)} Al ₈ | | | | | | |
| Ce1 | <i>m</i> | 0.34044(4) | 0.31848(3) | 0 | 1 | 0.01117(14) |
| Co1 | <i>m</i> | 0.03473(9) | 0.40571(8) | 0 | 0.91(11) | 0.0098(4) |
| Ni1 | <i>m</i> | 0.03473(9) | 0.40571(8) | 0 | 0.09(11) | 0.0098(4) |
| Co2 | <i>m</i> | 0.15175(9) | 0.09640(7) | 0 | 0.80(10) | 0.0087(4) |
| Ni2 | <i>m</i> | 0.15175(9) | 0.09640(7) | 0 | 0.20(10) | 0.0087(4) |
| Al1 | <i>m</i> | 0.0253(2) | 0.13172(17) | 1/2 | 1 | 0.0099(5) |
| Al2 | <i>m</i> | 0.1597(2) | 0.37958(17) | 1/2 | 1 | 0.0101(5) |
| Al3 | <i>m</i> | 0.2366(2) | 0.17235(18) | 1/2 | 1 | 0.0105(5) |
| Al4 | <i>m</i> | 0.3318(2) | 0.49155(16) | 1/2 | 1 | 0.0099(5) |
| Al5 | <i>m</i> | 0.4523(2) | 0.17948(18) | 1/2 | 1 | 0.0104(5) |
| Al6 | <i>m</i> | 0.0961(2) | 0.25286(18) | 0 | 1 | 0.0105(5) |
| Al7 | <i>m</i> | 0.3399(2) | 0.04426(17) | 0 | 1 | 0.0114(5) |
| Al8 | <i>2/m</i> | 0 | 1/2 | 1/2 | 1 | 0.0098(8) |
| Al9 | <i>2/m</i> | 0 | 0 | 0 | 1 | 0.0109(7) |
| CeCo _{1.40(8)} Ni _{0.60(8)} Al ₈ | | | | | | |
| Ce1 | <i>m</i> | 0.34035(2) | 0.31849(2) | 0 | 1 | 0.01152(11) |
| Co1 | <i>m</i> | 0.03469(5) | 0.40569(5) | 0 | 0.4858(17) | 0.0100(2) |
| Ni1 | <i>m</i> | 0.03469(5) | 0.40569(5) | 0 | 0.4858(17) | 0.0100(2) |
| Co2 | <i>m</i> | 0.15185(5) | 0.09639(5) | 0 | 0.89(8) | 0.0089(3) |
| Ni2 | <i>m</i> | 0.15185(5) | 0.09639(5) | 0 | 0.11(8) | 0.0089(3) |
| Al1 | <i>m</i> | 0.09608(12) | 0.25288(11) | 0 | 1 | 0.0110(3) |
| Al2 | <i>m</i> | 0.33977(12) | 0.04458(12) | 0 | 1 | 0.0122(3) |
| Al3 | <i>m</i> | 0.15972(12) | 0.37922(12) | 1/2 | 1 | 0.0107(3) |
| Al4 | <i>m</i> | 0.45256(13) | 0.17966(11) | 1/2 | 1 | 0.0109(3) |
| Al5 | <i>m</i> | 0.23631(13) | 0.17248(11) | 1/2 | 1 | 0.0110(3) |
| Al6 | <i>m</i> | 0.33148(13) | 0.49133(11) | 1/2 | 1 | 0.0109(3) |
| Al7 | <i>m</i> | 0.02525(13) | 0.13192(11) | 1/2 | 1 | 0.0109(3) |
| Al8 | <i>2/m</i> | 0 | 1/2 | 1/2 | 1 | 0.0110(4) |
| Al9 | <i>2/m</i> | 0 | 0 | 0 | 1 | 0.0111(4) |
| CeCo _{1.20(7)} Ni _{0.80(7)} Al ₈ | | | | | | |
| Ce1 | <i>m</i> | 0.340227(13) | 0.318594(11) | 0 | 1 | 0.00855(5) |
| Co1 | <i>m</i> | 0.03483(3) | 0.40579(3) | 0 | 0.66(4) | 0.00740(12) |
| Ni1 | <i>m</i> | 0.03483(3) | 0.40579(3) | 0 | 0.34(3) | 0.00740(12) |
| Co2 | <i>m</i> | 0.15196(3) | 0.09630(3) | 0 | 0.73(4) | 0.00634(12) |
| Ni2 | <i>m</i> | 0.15196(3) | 0.09630(3) | 0 | 0.27(4) | 0.00634(12) |
| Al1 | <i>m</i> | 0.09611(7) | 0.25282(6) | 0 | 1 | 0.00818(17) |
| Al2 | <i>m</i> | 0.33977(7) | 0.04459(6) | 0 | 1 | 0.01066(18) |

(Table 5.4. continued)

| Element | Symmetry | x | y | z | Occupancy | ^a U _{eq} (Å ²) |
|---------|-------------|------------|------------|-----|-----------|--|
| Al3 | <i>m</i> | 0.15982(7) | 0.37920(6) | 1/2 | 1 | 0.00797(17) |
| Al4 | <i>m</i> | 0.45238(7) | 0.17951(6) | 1/2 | 1 | 0.00779(17) |
| Al5 | <i>m</i> | 0.23642(7) | 0.17233(6) | 1/2 | 1 | 0.00835(18) |
| Al6 | <i>m</i> | 0.33142(7) | 0.49123(6) | 1/2 | 1 | 0.00814(17) |
| Al7 | <i>m</i> | 0.02547(7) | 0.13188(6) | 1/2 | 1 | 0.00757(17) |
| Al8 | 2/ <i>m</i> | 0 | 1/2 | 1/2 | 1 | 0.0077(2) |
| Al9 | 2/ <i>m</i> | 0 | 0 | 0 | 1 | 0.0081(2) |

^aU_{eq} is defined as one-third of the trace of the orthogonalized U_{ij} tensor

Table 5.5. CeCo_{2-x}Fe_xAl₈ (0 ≤ x < 1) Selected Interatomic Distances

| | CeCo ₂ Al ₈ | CeCo _{1.77(7)} Fe _{0.23(7)} Al ₈ | CeCo _{1.48(6)} Fe _{0.52(6)} Al ₈ | CeCo _{1.30(4)} Fe _{0.70(4)} Al ₈ |
|---------|-----------------------------------|---|---|---|
| Ce | | | | |
| Al1 x 2 | 3.1457(16) | 3.1443(14) | 3.1438(17) | 3.1402(7) |
| Al2 x 2 | 3.1467(14) | 3.1500(13) | 3.1531(17) | 3.1427(6) |
| Al3 x 2 | 3.1851(15) | 3.1891(13) | 3.1952(17) | 3.1889(7) |
| Al4 x 2 | 3.2017(16) | 3.2049(14) | 3.2116(17) | 3.2058(8) |
| Al5 x 2 | 3.1643(15) | 3.1611(13) | 3.1617(17) | 3.1564(7) |
| M1 | | | | |
| Al2 x 2 | 2.5698(14) | 2.5761(13) | 2.5814(16) | 2.5749(5) |
| Al5 x 2 | 2.5667(14) | 2.5726(12) | 2.5777(16) | 2.5756(6) |
| Al6 x 1 | 2.3275(16) | 2.3287(15) | 2.337(2) | 2.3257(9) |
| Al7 x 2 | 2.5349(17) | 2.5375(16) | 2.543(2) | 2.5438(10) |
| Al8 x 2 | 2.4649(17) | 2.4646(9) | 2.4600(11) | 2.4608(2) |
| M1 x 1 | 2.8505(13) | 2.8426(13) | 2.8236(17) | 2.8336(8) |
| M2 | | | | |
| Al1 x 2 | 2.6026(15) | 2.6005(13) | 2.5983(16) | 2.5909(6) |
| Al3 x 2 | 2.5201(14) | 2.5236(13) | 2.5243(16) | 2.5205(6) |
| Al4 x 2 | 2.5243(14) | 2.5278(13) | 2.5260(16) | 2.5277(6) |
| Al6 x 1 | 2.3543(16) | 2.3532(15) | 2.357(2) | 2.3447(9) |
| Al7 x 1 | 2.4643(17) | 2.4658(16) | 2.462(2) | 2.4655(9) |
| Al9 x 1 | 2.3457(7) | 2.3439(6) | 2.3424(8) | 2.3360(4) |

Table 5.6. CeCo_{2-x}Ni_xAl₈ (0 < x < 1) Selected Interatomic Distances

| | CeCo _{1.71(5)} Ni _{0.29(5)} Al ₈ | CeCo _{1.40(8)} Ni _{0.60(8)} Al ₈ | CeCo _{1.20(8)} Ni _{0.80(8)} Al ₈ |
|---------|---|---|---|
| Ce | | | |
| Al1 x 2 | 3.143(2) | 3.1417(16) | 3.1403(7) |
| Al2 x 2 | 3.148(3) | 3.1436(16) | 3.1438(6) |
| Al3 x 2 | 3.186(2) | 3.1843(16) | 3.1853(7) |
| Al4 x 2 | 3.204(2) | 3.1998(16) | 3.1977(7) |
| Al5 x 2 | 3.162(2) | 3.1609(16) | 3.1627(6) |
| M1 | | | |
| Al2 x 2 | 2.573(2) | 2.5730(16) | 2.5726(5) |
| Al5 x 2 | 2.570(2) | 2.5693(16) | 2.5702(6) |
| Al6 x 1 | 2.330(3) | 2.3278(17) | 2.3296(9) |
| Al7 x 2 | 2.535(3) | 2.5383(18) | 2.5360(9) |
| Al8 x 2 | 2.4646(18) | 2.4641(13) | 2.4636(2) |
| M1 x 1 | 2.849(2) | 2.8480(15) | 2.8465(7) |
| M2 | | | |
| Al1 x 2 | 2.607(2) | 2.6073(16) | 2.6062(6) |
| Al3 x 2 | 2.522(2) | 2.5203(16) | 2.5198(6) |
| Al4 x 2 | 2.522(2) | 2.5242(16) | 2.5242(6) |
| Al6 x 1 | 2.356(3) | 2.3563(17) | 2.3571(9) |
| Al7 x 1 | 2.465(3) | 2.4593(17) | 2.4565(9) |
| Al9 x 1 | 2.3437(12) | 2.3471(7) | 2.3468(4) |

Each Ce atom is located in a pentagonal prism of Al atoms with distances of ~ 3.1 Å. All the faces of the pentagonal prisms are capped by Al atoms with Ce-Al distances ranging from 3.3 to 4.0 Å. The transition metal sublattice of CeCo₂Al₈ forms a closed packed arrangement around the Ce atoms. The Co1 and Co2 environments are nine coordinate consisting of Al atoms forming monocapped rectangular prisms. The Co1 monocapped rectangular prisms are face-sharing with Co1 polyhedra forming dimers with Co1-Co1 distance of 2.8506(3) Å. The Co-Al distances in the [CoAl₈₊₁] prisms range from ~ 2.3 to 2.5 Å. The Co-Al distances in CeCo₂Al₈ are comparable to the sum of the covalent radii of Co (1.26) and Al (1.18),⁸³ which suggest strong atomic interactions. The Co-Al interatomic distances are comparable to the bond interaction in binary

Co_2Al_9 ,^{118, 119} with Co-Al distances ranging from 2.3 to 2.5 Å. The shortest Ce-Al distances and Co-Al distances in $[\text{CoAl}_{8+1}]$ prisms are comparable to the sum of the covalent radii (3.25 Å Ce+Al and 2.47 Å Co+Al). This suggests strong interactions are present in CeCo_2Al_8 . Previously, spin-polarized band structure calculations of isostructural EuRh_2Ga_8 revealed the formation of a 3D $[\text{Rh}_2\text{Ga}_8]$ polyanion by Ga-Ga and polar Ga-Rh bonds. The Eu atoms interact with the $[\text{Rh}_2\text{Ga}_8]$ polyanion by ionic and covalent interactions.¹²⁰

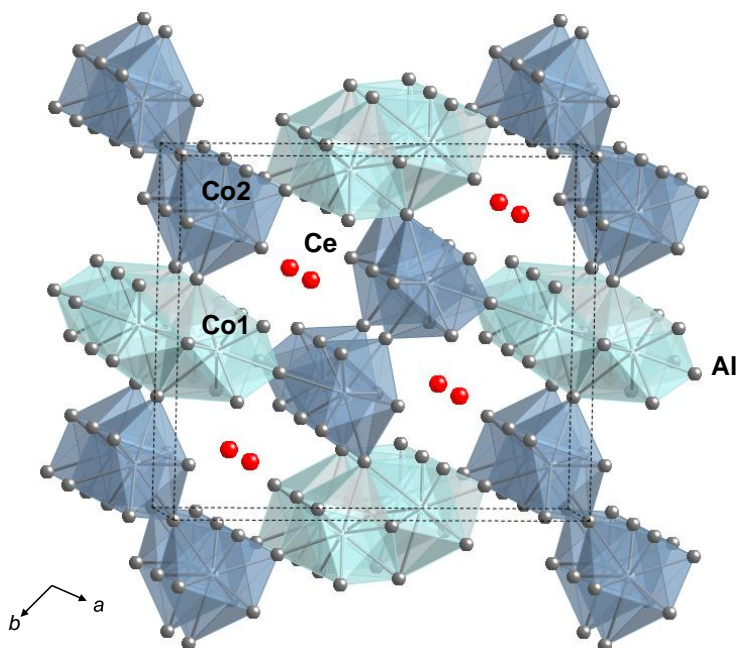


Figure 5.1. Crystal structure of CeCo_2Al_8 down the c -direction Co1 and Co2 are represented as light blue and dark blue polyhedra, respectively.

A plot of the volume as a function of dopant in $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}$; $0 \leq x < 1$) is shown in Figure 5.2. For the Fe-doped compounds, the volumes increase as a function of concentration until $x = 0.70(4)$ where the volume decreases. This behavior can be attributed to valence fluctuation of Ce caused by the substitution of Fe consistent with the valence fluctuating CeFe_2Al_8 . In the Ni-doped CeCo_2Al_8 , a slight increase in volume is observed for $x = 0.23(1)$, then followed by a decrease in volume as Ni concentration increases.

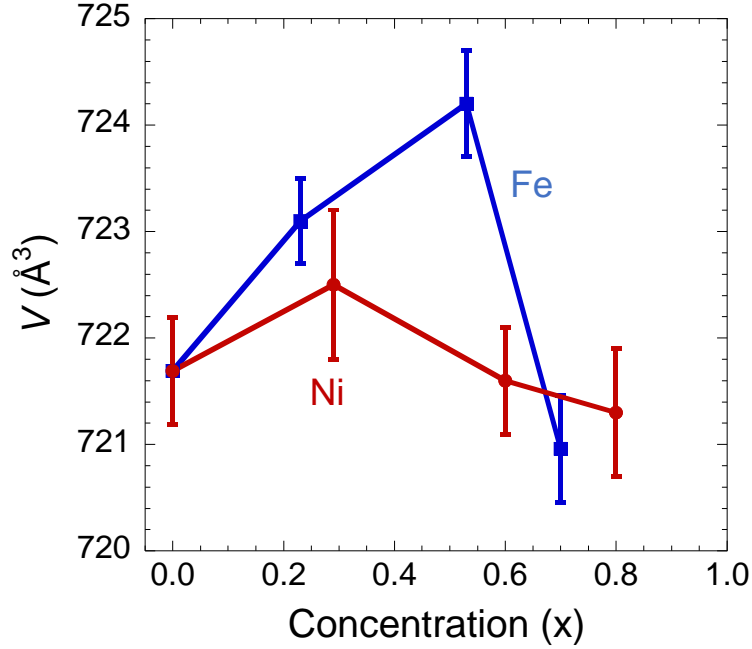


Figure 5.2. Volume $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}$; $0 \leq x < 1$) as function of concentration.

5.4 Conclusion

We have successfully grown single crystals of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}$; $0 \leq x < 1$). Hybridization between the 4*f*- and conduction electrons and the rare-earth valence state can change by applying chemical pressure to a strongly correlated intermetallic with an unstable ground state. By substituting and controlling the amount of dopant (M) in $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}$; $0 \leq x < 1$), we can systematically investigate the effects in substitution effect on the structural and physical properties of CeCo_2Al_8 . The expansion and contraction of the volume of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe}, \text{Ni}$; $0 \leq x < 1$) follows the expected trend given the respective dopant (M), except for $\text{CeCo}_{2-x}\text{Fe}_x\text{Al}_8$ ($x = 0.70(4)$) which marks the critical concentration of Fe needed to induce valence instability in the Ce 4*f*-electronic state. Considering the variation in Ce valence on the basis of the single crystal data indicates that the size of the substituting elements does not affect the 4*f*-electronic state of Ce.

Chapter 6. Conclusion and Future Work

6.1 Summary

Chemical substitution in rare earth intermetallics can affect the coupling between the conduction and $4f$ -electrons that can lead to the discovery of competing structural and physical properties in rare earth intermetallics. For example, YbNi_3Ga_9 exhibits intermediate valency, +2.46, with a high Kondo temperature of $T_K = 570$ K.¹²¹ Hole substitution studies, Co for Ni, led to $\text{Yb}(\text{Ni}_{1-x}\text{Co}_x)_3\text{Ga}_9$ causing a decrease in the Kondo temperature, $T_K = 540 - 220$ K for $0 \leq x \leq 0.3$, and an increase in the Sommerfeld coefficient, γ , indicating a mass enhancement.¹²² At ambient pressure, CeRhIn_5 orders antiferromagnetic at 3.8 K. Upon application of pressure, 19 kbar, CeRhIn_5 exhibits superconductivity suppressing the antiferromagnetic transition.² Sn substitution in CeRhIn_5 , led to $\text{CeRhIn}_{5-x}\text{Sn}_x$ and a suppression of the antiferromagnetic transition while inducing a quantum critical point at the critical concentration of $x = 0.35$.¹²³

The work in this dissertation illustrates the effects of substitution on the structural and physical properties in rare earth intermetallics with unique structural motifs and competing interactions. $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd}, \text{Yb}$) adopts the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ -structure type¹⁶ and can be describe as two interpenetrating networks of Ln and W atoms with the Ln atoms forming Kagome network in the ab -plane. $\text{Gd}_6\text{W}_4\text{Al}_{43}$ orders antiferromagnetically at $T_N = 15$ K with a $\theta = 13.62(7)$ K that suggests the presence of ferromagnetic exchange interactions.¹²⁴ The effect moment of $\text{Gd}_6\text{W}_4\text{Al}_{43}$ ($7.92(3) \mu_B$) is close to the magnetic moment for a free Gd^{3+} ion ($7.94 \mu_B$). $\text{Yb}_6\text{W}_4\text{Al}_{43}$ exhibits temperature independent paramagnetism with the Yb atoms adopting the nonmagnetic divalent configuration.¹²⁴ We aimed to substitute Mn and Fe in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd}, \text{Yb}$) because of the arrangement of the Ln atoms and the nonmagnetic nature of W. Only a relatively small amount of Mn or Fe ($x < 1.5$) was able to substitute in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ ($\text{Ln} = \text{Gd}, \text{Yb}$). Unexpectedly,

Mn and Fe prefers to substitute for Al only in $\text{Gd}_6\text{W}_4\text{Al}_{43}$.³⁷ However, Mn prefers to substitute for W and Al in $\text{Yb}_6\text{W}_4\text{Al}_{43}$, while Fe prefers to substitute for Al only. The site preference of Mn in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ (Ln = Gd, Yb) can be attributed to the difference in the cell volume of the parent analogues ($\text{Yb}_6\text{W}_4\text{Al}_{43}$ (1856.2(3) Å³) and $\text{Gd}_6\text{W}_4\text{Al}_{43}$ (1871.2(3) Å³)). The Gd-analogues order antiferromagnetically with the ordering temperatures decreasing from $\text{Gd}_6\text{W}_4\text{Al}_{43}$ ($T_N = 15$ K) > $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y$ ($T_N = 14$ K) > $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$ ($T_N = 13$ K). All three analogues show positive Weiss constant that decreases from $\text{Gd}_6\text{W}_4\text{Al}_{43}$ ($\theta = 13.62(7)$ K) > $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y$ ($\theta = 9.91(6)$ K) > $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$ ($\theta = 7.56(5)$ K).³⁷ The trend in magnetic behavior is unusually given the decrease in cell volumes, $\text{Gd}_6\text{W}_4\text{Al}_{43}$ (1871.1(3) Å³) > $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Mn}_y$ (1861.3(1) Å³) > $\text{Gd}_6\text{W}_4\text{Al}_{43-y}\text{Fe}_y$ (1855.1(4) Å³), and Gd-Gd interatomic distances that should lead to stronger magnetic interactions. A plausible explanation for the magnetic trend is the presence of competing interactions of the magnetic ions in the *ab*- and *c*-direction. Like $\text{Yb}_6\text{W}_4\text{Al}_{43}$, Mn and Fe substituted $\text{Yb}_6\text{W}_4\text{Al}_{43}$ exhibit temperature independent magnetism, which indicate that Mn and Fe are nonmagnetic.

Compounds of the $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ -¹⁶ and $\text{CeCr}_2\text{Al}_{20}$ -structure type¹⁷ share similar structural motifs such as interpenetrating rare earth and transition metal sublattices. In $\text{LnCr}_2\text{Al}_{20}$ (Ln = La, Gd, Yb) of the $\text{CeCr}_2\text{Al}_{20}$ structure type,¹⁷ the Ln ions are surrounded by 16 Al atoms forming Frank-Kasper cages that form triangular networks by corner sharing Al atoms. The Cr sublattice can be viewed as tetrahedral network of vertex sharing distorted icosahedra that is similar to the pyrochlore lattice. Polycrystalline $\text{GdCr}_2\text{Al}_{20}$ orders antiferromagnetically at 3.90(5) K.⁷⁷ Single crystals of $\text{LnCr}_2\text{Al}_{20}$ (Ln = La, Yb) are temperature independent paramagnets suggesting that the transition metal is nonmagnetic.⁷⁸ We targeted Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ (Ln = La, Gd, Yb) because of the arrangement of the Ln and Cr atoms and to induce unique magnetism. Based on

the similar atomic radii of Cr (1.249) and Fe (1.241), we expected the Fe to substitute for Cr in $\text{LnCr}_2\text{Al}_{20}$ (Ln = La, Gd, Yb). Through elemental analysis, we were able to determine that only a small amount of Fe, $x \sim 0.1$ and 0.2 , was substituted in $\text{LnCr}_2\text{Al}_{20}$ (Ln = Gd, Yb), while no Fe was substituted in $\text{LaCr}_2\text{Al}_{20}$. As a result of the small concentration of Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ (Ln = Gd, Yb), we were not able to identify the site presence of Fe solely by X-ray diffraction. Therefore, ^{57}Fe Mössbauer spectroscopy was used to determine the nature of Fe in our compounds. The refinement of the ^{57}Fe Mössbauer data suggested that Fe substituted on two Al sites. As a result, crystallographic models were refined with Fe occupying each pair of crystallographic Al sites, and the best agreement with the Mössbauer spectroscopy was achieved when the Fe atoms partially occupy the Al1 and Al2 sites. Based on the volume change between the undoped and doped compounds, we concluded that Fe substitutes for Al rather than Cr.³⁹ The results suggest that the latter transition metals do not adopt the $\text{CeCr}_2\text{Al}_{20}$ -structure type.¹⁷ Single crystals of $\text{GdCr}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{20-x}\text{Fe}_x$ exhibit paramagnetic behavior down to the lowest temperature measured with no magnetic ordering contrary to the previously reported polycrystalline $\text{GdCr}_2\text{Al}_{20}$ that display antiferromagnetic ordering at 3.90(5) K.⁷⁷ Like $\text{YbCr}_2\text{Al}_{20}$, both $\text{YbCr}_2\text{Al}_{20-x}\text{Fe}_x$ and $\text{LaCr}_2\text{Al}_{20}$ compounds display temperature independent magnetism which indicate that the small concentration of Fe did not change the magnetic behavior.³⁹

Because of the structural complexity in $\text{Yb}_2\text{Pd}_3\text{Ga}_9$,²⁷ we set out to target the samarium analogue due to the fact that Sm ions can exist in multiple electronic configuration ($4f^6$ and $4f^5$). However, with our flux growth conditions, we stabilized $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ that adopts a disordered variant of the $\text{Er}_4\text{Pt}_9\text{Al}_{24}$ -structure type.³⁸ The crystal structure of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ is composed of three distinct building block and is highly anisotropic. The temperature dependent susceptibility of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ display temperature independent paramagnetism, indicating Sm atoms adopting

the nonmagnetic divalent configuration. Field dependent magnetization of $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ exhibits anisotropic behavior. When the field is perpendicular to the c -direction $\text{Sm}_{1.33}\text{Pd}_3\text{Ga}_8$ exhibits a change in slope at 0.5 T, followed by an increase in magnetization to a maximum of $\sim 0.015 \mu_B/\text{mol Sm}$ at 9 T. The field dependent magnetization in the ab -direction is linear up to 9 T with a maximum of $\sim 0.028 \mu_B/\text{mol Sm}$. The magnetic anisotropy, observed in the field dependent magnetization, originates from the different Sm-Sm interatomic distances in the ab - and c -direction, which is similar to previously published CePdGa_6 ⁹² and $\text{Ce}_2\text{PdGa}_{12}$.⁹³

Strongly correlated Ce-intermetallic compounds exhibiting unusual behavior are highly dependent on the coupling of rare earth f -electrons and conduction electrons, which is greatly affected by substitution of transition metals.^{27, 125-127} We expect the properties of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe, Ni}; 0 \leq x < 1$) to change based on the dopant M and previously reported magnetic and electrical properties of CeM_2Al_8 ($\text{M} = \text{Fe, Co}$).¹¹⁰ Single crystal data of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe, Ni}; 0 \leq x < 1$) suggests Ce ground state changes as a function of Fe, which is evident by a deviation in the cell volume. However, the Ce ground state is stable as a function of Ni concentration given the consistent trend in the cell volume. This suggests that hole doping (Fe) or an increase in the cell volume plays a significant role in the oxidation state of Ce in CeCo_2Al_8 . Future work will include measuring the magnetization and the electrical resistivity. By measuring the properties of $\text{CeCo}_{2-x}\text{M}_x\text{Al}_8$ ($\text{M} = \text{Fe, Ni}; 0 \leq x < 1$), we will be able to investigate the ground state of Ce and determine how hole doping and electron doping effects the electrical resistivity. The results can lead to general conclusions on how the properties are affected by hole and electron doping, which in turn can be applied to future research with Yb-based compounds given their unstable ground state similar to Ce.

6.2 Future Work

The work presented in this dissertation illustrates how chemical substitution effects the structural and physical properties of rare earth intermetallics. Another way to influence the structure and magnetic properties of materials is to consider simple binary compounds and the insertion of guest atoms in the interstitial sites. A recent example of this strategy has been shown to be an effective method to discover new materials. Our research group recently reported Mn-insertion into the well-known AuCu_3 -structure type.¹²⁸ This structure type is of particular interest because of the CeIn_3 compound that orders antiferromagnetic at $T_N \sim 11$ K. Upon the application of pressure (25 kbar), the CeIn_3 compound exhibits superconductivity at ~ 0.2 K.¹ LnMn_xGa_3 ($\text{Ln} = \text{Ho-Tm}$; $x < 0.2$) adopts the stuffed variant of the AuCu_3 -structure type where Mn partially occupies the body center position of the unit cell.¹²⁸ Magnetic properties of LnGa_3 ($\text{Ln} = \text{Ho-Tm}$) change with the insertion of Mn. The Mn-containing Ho and Er analogues order antiferromagnetic at 7.7 K and 3.1 K, which is higher than the parent analogues that order at 6.2 K and 2.9 K.¹²⁸ This can be attributed to the increase in Ln-Ln distance due to the guest atom. The Mn containing TmGa_3 analogues exhibit paramagnetic behavior down to 3 K, however the TmGa_3 exhibits antiferromagnetic ordering at 4.2 K due to crystal electric field effects. DFT-chemical pressure analysis was performed to study the chemical pressure of LnMn_xGa_3 ($\text{Ln} = \text{Ho-Tm}$; $x < 0.2$). The results suggests that M guest atoms provide structural support when the Ln atoms are large so the Ga-Ga contacts of the AuCu_3 -structure type are significantly stretched.¹²⁸ Given the physical properties of LnMn_xGa_3 (Ho, Tm ; $x < 0.2$), it is of interest to study the effects of inserting Fe and Co in LnGa_3 ($\text{Ln} = \text{Ho-Tm}$). We have grown single crystals of ErM_xGa_3 (Fe, Co ; $x < 0.2$) and currently optimizing the single crystal growth of LnM_xGa_3 (Ho, Tm ; $\text{M} = \text{Fe, Co}$; $x < 0.2$) to investigate the chemical stability and magnetic behavior as a function of M.

The work in this dissertation illustrates that the geometry, magnetic ions interactions, elemental composition, and concentration of the substituting component is essential to achieve unique magnetic behavior. Substitution studies of the compounds reported led to the discovery of serendipitous as well as the desired pseudo ternary compounds. We have successfully grown and characterized Yb-containing compounds and performed substitution studies. There are relatively few studies of substitution effects in Yb-based compounds as compared to Ce-based compounds, due to the difficulty in growing Yb-based compounds because of the high vapor pressure of ytterbium. Unfortunately, we did not induce valence instability in Yb-based compounds which is most likely due to the low concentration of the substituting element; however mixed valent behavior in CeCo_2Al_8 was induced with high concentration of Fe. There is a lack in researchers' ability to predict how a substituting element will affect the magnetic properties of a host compound. Identification of structural motifs in materials that correlate with certain physical properties and how they are affected by substitution is a vital step to obtain a more profound understanding about the physics of materials. The most effective way to advance our understanding in the field of solid state chemistry is by continuing to search for new materials and perform substitution studies.

References

- (1) Mathur, N. D.; Grosche, F. M.; Julian, S. R.; Walker, I. R.; Freye, D. M.; Haselwimmer, R. K. W.; Lonzarich, G. G., Magnetically mediated superconductivity in heavy fermion compounds. *Nature* **1998**, *394*, 39-43.
- (2) Hegger, H.; Petrovic, C.; Moshopoulou, E. G.; Hundley, M. F.; Sarrao, J. L.; Fisk, Z.; Thompson, J. D., Pressure-induced superconductivity in quasi-2D CeRhIn₅. *Phys. Rev. Lett.* **2000**, *84*, 4986-4989.
- (3) Petrovic, C.; Pagliuso, P. G.; Hundley, M. F.; Movshovich, R.; Sarrao, J. L.; Thompson, J. D.; Fisk, Z.; Monthoux, P., Heavy-fermion superconductivity in CeCoIn₅ at 2.3 K. *J. Phys.: Condens. Matter* **2001**, *13*, L337.
- (4) Petrovic, C.; Movshovich, R.; Jaime, M.; Pagliuso, P. G.; Hundley, M. F.; Sarrao, J. L.; Fisk, Z.; Thompson, J. D., A new heavy-fermion superconductor CeIrIn₅: A relative of the cuprates? *Europhys. Lett.* **2001**, *53*, 354.
- (5) Bao, W.; Pagliuso, P. G.; Sarrao, J. L.; Thompson, J. D.; Fisk, Z.; Lynn, J. W., Magnetic structure of heavy-fermion Ce₂RhIn₈. *Phys. Rev. B* **2001**, *64*, 020401.
- (6) Macaluso, R. T.; Sarrao, J. L.; Moreno, N. O.; Pagliuso, P. G.; Thompson, J. D.; Fronczek, F. R.; Hundley, M. F.; Malinowski, A.; Chan, J. Y., Single-crystal growth of Ln₂MIn₈ (Ln = La, Ce; M = Rh, Ir): Implications for the heavy-fermion ground state. *Chem. Mater.* **2003**, *15*, 1394-1398.
- (7) Yamashita, T.; Ohara, S.; Sakamoto, I., Transport, thermal, and magnetic properties in heavy-fermion superconductor Ce₂CoIn₈. *Physica C* **2011**, *471*, 1655-1659.
- (8) Grin, Y.; Yarmolyuk, Y. P.; Gladyshevskii, E. I., Crystal structure of R₂CoGa₈ compounds (R = Sm, Gd, Tb, Dy, Er, Tm, Lu, Y) and RCoGa₅ compounds (R = Gd, Yb, Dy, Ho, Er, Tm, Lu, Y). *Sov. Phys. Crystallogr.* **1979**, *4*, 137.
- (9) Nagamatsu, J.; Nakagawa, N.; Muranaka, T.; Zenitani, Y.; Akimitsu, J., Superconductivity at 39 K in magnesium diboride. *Nature* **2001**, *410*, 63-64.
- (10) Kortus, J.; Mazin, I. I.; Belashchenko, K. D.; Antropov, V. P.; Boyer, L. L., Superconductivity of metallic boron in MgB₂. *Phys. Rev. Lett.* **2001**, *86*, 4656-4659.

- (11) Ramirez, A. P., Strongly geometrically frustrated magnets. *Annu. Rev. Mater. Sci.* **1994**, *24*, 453-480.
- (12) Greedan, J. E., Frustrated rare earth magnetism: Spin glasses, spin liquids and spin ices in pyrochlore oxides. *J. Alloys Comp.* **2006**, *408–412*, 444-455.
- (13) Greedan, J. E., Geometrically frustrated magnetic materials. *J. Mater. Chem.* **2001**, *11*, 37-53.
- (14) Sherrington, D.; Kirkpatrick, S., Solvable model of a spin-glass. *Phys. Rev. Lett.* **1975**, *35*, 1792-1796.
- (15) Tholence, J. L., On the frequency dependence of the transition temperature in spin glasses. *Solid State Commun.* **1980**, *35*, 113-117.
- (16) Niemann, S.; Jeitschko, W., ChemInform abstract: Ternary aluminides $A_6T_4Al_{43}$ with A: Y, Nd, Sm, Gd-Lu, Th, U and T: Cr, Mo, W. *ChemInform* **1994**, *25*.
- (17) Krypyakevich, P. I.; Zarechnyuk, O. S., The RCr_2Al_{20} compounds in the systems of the rare earth metals and calcium and their crystal structures. *Dopov. Akad. Nauk. Ukr., Ser A* **1968**, *30*, 364-366.
- (18) Ban, Z.; Sikirica, M., The crystal structure of ternary silicides ThM_2Si_2 (M = Cr, Mn, Fe, Co, Ni and Cu). *Acta Cryst.* **1965**, *18*, 594-599.
- (19) Niihara, K.; Shishido, T.; Yajima, S., The crystal data of ternary rare earth borides, RCO_2B_2 . *Bull. Chem. Soc. Jpn.* **1973**, *46*, 1137-1140.
- (20) Mizoguchi, H.; Kuroda, T.; Kamiya, T.; Hosono, H., $LaCo_2B_2$: A Co-based layered superconductor with a $ThCr_2Si_2$ -type structure. *Phys. Rev. Lett.* **2011**, *106*, 237001.
- (21) Matsumoto, Y.; Nakatsuji, S.; Kuga, K.; Karaki, Y.; Horie, N.; Shimura, Y.; Sakakibara, T.; Nevidomskyy, A. H.; Coleman, P., Quantum criticality without tuning in the mixed valence compound β - $YbAlB_4$. *Science* **2011**, *331*, 316-319.
- (22) Macaluso, R. T.; Nakatsuji, S.; Kuga, K.; Thomas, E. L.; Machida, Y.; Maeno, Y.; Fisk, Z.; Chan, J. Y., Crystal structure and physical properties of polymorphs of $LnAlB_4$ (Ln = Yb, Lu). *Chem. Mater.* **2007**, *19*, 1918-1922.

- (23) Kuga, K.; Morrison, G.; Treadwell, L.; Chan, J. Y.; Nakatsuji, S., Magnetic order induced by Fe substitution of Al site in the heavy-fermion systems α -YbAlB₄ and β -YbAlB₄. *Phys. Rev. B* **2012**, 86, 224413.
- (24) Fisk, Z.; Remeika, J. P., Chapter 81 Growth of single crystals from molten metal fluxes. In *Handbook on the Physics and Chemistry of Rare Earths*, Karl A. Gschneidner, Jr.; LeRoy, E., Eds. Elsevier: 1989; Vol. Volume 12, pp 53-70.
- (25) Canfield, P. C.; Fisher, I. R., High-temperature solution growth of intermetallic single crystals and quasicrystals. *J. Cryst. Growth* **2001**, 225, 155-161.
- (26) Kanatzidis, M. G.; Pöttgen, R.; Jeitschko, W., The metal flux: A preparative tool for the exploration of intermetallic compounds. *Angew. Chem., Int. Ed.* **2005**, 44, 6996-7023.
- (27) Phelan, W. A.; Menard, M. C.; Kangas, M. J.; McCandless, G. T.; Drake, B. L.; Chan, J. Y., Adventures in crystal growth: synthesis and characterization of single crystals of complex intermetallic compounds. *Chem. Mater.* **2012**, 24, 409-420.
- (28) Villars, P., *ASM Alloy Phase Diagram Database*. ASM International: Materials Park, OH, 1999.
- (29) West, A. R., *Basic Solid State Chemistry* 2nd ed.; John Wiley & Sons LTD: Chichester, England, 1999.
- (30) Bragg, W. L., The diffraction of short electromagnetic waves by a crystal. In *Proc. Camb. Philos. Soc.*, 1913; Vol. 17, pp 43-57.
- (31) Cullity, B. D., *Elements of X-ray Diffraction*. 2nd ed.; Addison-Wesley Publishing Company, Inc.: Reading, Massachusetts, 1978.
- (32) Carmelo, G.; Monaco, H. L.; Artioli, G.; Viterbo, D.; Milanesio, M.; Gilli, G.; Gilli, P.; Zanotti, G.; Ferraris, G., *Fundamentals of Crystallography*. 2nd ed.; Oxford University Press: Bari, Italy, 1992.
- (33) Hammond, C., *The Basics of Crystallography and Diffraction*. 3rd ed.; 2009.
- (34) Wertheim, G. K., *Mössbauer Effect: Principles and Application*. Academic Press INC.: 1964.

- (35) Gütlich, P., Fifty years of Mössbauer spectroscopy in solid state research – remarkable achievements, future perspectives. *Z. Anorg. Allg. Chem.* **2012**, 638, 15-43.
- (36) Mössbauer, R. L., Kernresonanzfluoreszenz von Gammastrahlung in Ir^{191} . *Z. Phys. A* **1958**, 151, 124-143.
- (37) Treadwell, L. J.; Watkins-Curry, P.; McAlpin, J. D.; Prestigiacomo, J.; Stadler, S.; Chan, J. Y., Substitution studies of Mn and Fe in $\text{Ln}_6\text{W}_4\text{Al}_{43}$ (Ln=Gd, Yb) and the structure of $\text{Yb}_6\text{Ti}_4\text{Al}_{43}$. *J. Solid State Chem.* **2014**, 210, 267-274.
- (38) Thiede, V. M. T.; Fehrmann, B.; Jeitschko, W., Ternary rare earth metal palladium and platinum aluminides $\text{R}_4\text{Pd}_9\text{Al}_{24}$ and $\text{R}_4\text{Pt}_9\text{Al}_{24}$. *Z. Anorg. Allg. Chem.* **1999**, 625, 1417-1425.
- (39) Treadwell, L. J.; McAlpin, J. D.; Schmitt, D. C.; Kangas, M. J.; Sougrati, M. T.; Haldolaarachchige, N.; Young, D. P.; Jumas, J.-C.; Chan, J. Y., Investigation of Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ (Ln = La, Gd, Yb) with ^{57}Fe Mössbauer and single crystal X-ray diffraction. *Inorg. Chem.* **2013**, 52, 5055-5062.
- (40) Ni, N.; Jia, S.; Samolyuk, G. D.; Kracher, A.; Sefat, A. S.; Bud'ko, S. L.; Canfield, P. C., Physical properties of $\text{GdFe}_2(\text{Al}_x\text{Zn}_{1-x})_{20}$. *Phys. Rev. B* **2011**, 83, 054416.
- (41) Sérgio, S.; Waerenborgh, J. C.; Almeida, M.; Godinho, M., ^{57}Fe Mössbauer spectroscopy and magnetization study of $\text{YFe}_x\text{Al}_{12-x}$ ($4.4 < x < 5$). *J. Magn. Magn. Mater.* **2003**, 265, 33-43.
- (42) Corsépius, S.; Lenkewitz, M.; Stewart, G. R., Ground state in CeAl_3 : a $\text{Ce}(\text{Al}_{1-x}\text{Mx})_3$ study with M=Ga, Si, Ge and Sn. *J. Alloys Comp.* **1997**, 259, 29-35.
- (43) Nishigori, S.; Fujiwara, K.; Ito, T., Specific heat study on dilute cerium alloys $\text{Ce}_x\text{La}_{1-x}\text{Pd}_2\text{Al}_3$. *Physica B* **1999**, 259–261, 397-398.
- (44) Kim, H. C.; Park, J. G.; Hauser, R.; Michor, H.; Bauer, E., Pressure studies on $(\text{Ce}_{1-x}\text{U}_x)\text{Al}_2$. *Physica B* **1999**, 259–261, 12-13.
- (45) Falkowski, M.; Kowalczyk, A., Magnetoresistivity of $\text{Ce}_{1-x}\text{La}_x\text{NiAl}_4$ compounds. *J. Appl. Phys.* **2013**, 113, 093704-5.

- (46) Tsujii, N.; Imai, M.; Yamaoka, H.; Jarrige, I.; Oohashi, H.; Tochio, T.; Handa, K.; Ide, J.; Atsuta, H.; Ito, Y.; Yoshikawa, H.; Kitazawa, H., Phase stability and superconducting properties of AlB_2 -type $\text{YbGa}_x\text{Si}_{2-x}$ ($1.12 \leq x \leq 1.49$). *Chem. Mater.* **2010**, *22*, 4690-4699.
- (47) Drake, B. L.; Kangas, M. J.; Capan, C.; Haldolaarachchige, N.; Xiong, Y.; Adams, P. W.; Young, D. P.; Chan, J. Y., Crystal growth, structure, and physical properties of $\text{Ln}(\text{Ag}, \text{Al}, \text{Si})_2$ ($\text{Ln} = \text{Ce}$ and Gd). *J. Phys.: Condens. Matter* **2010**, *22*, 426002.
- (48) Matsumoto, Y.; Kuga, K.; Horic, N.; Nakatsuji, S., Local moment behaviors of the valence fluctuating systems β - YbAlB_4 and α - YbAlB_4 . *J. Phys. Conf. Ser.* **2011**, *273*, 012006.
- (49) Nakatsuji, S.; Kuga, K.; Machida, Y.; Tayama, T.; Sakakibara, T.; Karaki, Y.; Ishimoto, H.; Yonezawa, S.; Maeno, Y.; Pearson, E.; Lonzarich, G. G.; Balicas, L.; Lee, H.; Fisk, Z., Superconductivity and quantum criticality in the heavy-fermion system β - YbAlB_4 . *Nat. Phys.* **2008**, *4*, 603-607.
- (50) Fulfer, B. W.; McAlpin, J. D.; Haldolaarachchige, N.; Young, D. P.; Chan, J. Y., Synthesis, structure, and magnetic and electrical properties of $\text{Yb}(\text{Mn}, \text{M})_x\text{Al}_{12-x}$ ($\text{M} = \text{Fe}, \text{Ru}$; $x \leq 2.5$) phases. *Cryst. Growth Des.* **2013**, *13*, 1543-1550.
- (51) Florio, J. V.; Rundle, R. E.; Snow, A. I., Compounds of thorium with transition metals. I. The thorium-manganese system. *Acta Cryst.* **1952**, *5*, 449-457.
- (52) Cordier, G.; Czech, E.; Ochmann, H.; Schäfer, H., Neue übergangsmetallaluminide des calciums. *J. Less-Common Met.* **1984**, *99*, 173-185.
- (53) Niemann, S.; Jeitschko, W., The crystal structure of $\text{YbFe}_2\text{Al}_{10}$, a combined substitution and stacking variant of the ThMn_{12} and CeMn_4Al_8 type structures. *Z. Kristallogr.* **1995**, *210*, 338-341.
- (54) Jia, S.; Ni, N.; Samolyuk, G. D.; Safa-Sefat, A.; Dennis, K.; Ko, H.; Miller, G. J.; Bud'ko, S. L.; Canfield, P. C., Variation of the magnetic ordering in $\text{GdT}_2\text{Zn}_{20}$ ($\text{T} = \text{Fe}, \text{Ru}, \text{Os}, \text{Co}, \text{Rh}$ and Ir) and its correlation with the electronic structure of isostructural $\text{YT}_2\text{Zn}_{20}$. *Phys. Rev. B* **2008**, *77*, 104408.
- (55) Tian, W.; Christianson, A. D.; Zarestky, J. L.; Jia, S.; Bud'ko, S. L.; Canfield, P. C.; Piccoli, P. M. B.; Schultz, A. J., Magnetic order in $\text{TbCo}_2\text{Zn}_{20}$ and $\text{TbFe}_2\text{Zn}_{20}$. *Phys. Rev. B* **2010**, *81*, 144409.

- (56) Canfield, P. C.; Jia, S.; Mun, E. D.; Bud'ko, S. L.; Samolyuk, G. D.; Torikachvili, M. S., Myriad of correlated electron effects found in the RT_2Zn_{20} family. *Physica B* **2008**, *403*, 844-846.
- (57) Condron, C. L.; Strand, J. D.; Canfield, P. C.; Miller, G. J., The intermetallic compound $Gd_6Ta_4Al_{43}$. *Acta Crystallogr., Sect. E: Struct. Rep. Online* **2003**, *59*, i147-i148.
- (58) Altomare, A.; Burla, M. C.; Camalli, M.; Cascarano, G. L.; Giacovazzo, C.; Guagliardi, A.; Moliterni, A. G. G.; Polidori, G.; Spagna, R., SIR97: a new tool for crystal structure determination and refinement. *J. Appl. Crystallogr.* **1999**, *32*, 115-119.
- (59) Sheldrick, G., A short history of SHELX. *Acta Crystallogr.* **2008**, *64*, 112-122.
- (60) Wollan, E. O.; Koehler, W. C., Neutron diffraction study of the magnetic properties of the series of Perovskite-type compounds $[(1-x)La, xCa]MnO_3$. *Phys. Rev.* **1955**, *100*, 545-563.
- (61) Shen, J.; Zhao, J.-L.; Hu, F.-X.; Wu, J.-F.; Gong, M.-Q.; Li, Y.-X.; Sun, J.-R.; Shen, B.-G., Magnetic properties and magnetocaloric effects in antiferromagnetic $ErTiSi$. *J. Appl. Phys.* **2010**, *107*, 09A931.
- (62) Hirose, K.; Doi, Y.; Hinatsu, Y., Magnetic properties of $EuLn_2O_4$ (Ln = rare earths). *J. Solid State Chem.* **2009**, *182*, 1624-1630.
- (63) Bajorek, A.; Chrobak, A.; Chełkowska, G.; Kwiecień, M., Influence of Fe substitution on the structure and magnetic properties in $Gd(Ni_{1-x}Fe_x)_3$ intermetallic compounds. *J. Alloys Comp.* **2009**, *485*, 6-12.
- (64) M. T. Thiede, V.; Ebel, T.; Jeitschko, W., Ternary aluminides LnT_2Al_{10} ($Ln=Y, La-Nd, Sm, Gd-Lu$ and $T=Fe, Ru, Os$) with $YbFe_2Al_{10}$ type structure and magnetic properties of the iron-containing series. *J. Mater. Chem.* **1998**, *8*, 125-130.
- (65) Kim, G.; Park, Y.; Han, M. J.; Yu, J.; Heo, C.; Lee, Y. H., Structure and magnetism of small Gd and Fe nanoclusters: calculations. *Solid State Commun.* **2009**, *149*, 2058-2060.
- (66) Engkagul, C.; Selim, R.; Mihalisin, T.; Schlottmann, P., $YbSi$: A nearly localized heavy-fermion antiferromagnet. *Phys. Rev. B* **1987**, *35*, 3686-3689.

- (67) Bonville, P.; Gonzalez-Jimenez, F.; Imbert, P.; Jaccard, D.; Jehannot, G.; Sierro, J., Magnetic ordering in the heavy-electron compound YbSi. *J. Phys.: Condens. Matter* **1989**, *1*, 8567.
- (68) Tsujii, N.; Kitazawa, H.; Aoyagi, T.; Kimura, T.; Kido, G., Non-Fermi liquid behavior in YbCu₂Si₂. *J. Magn. Magn. Mater.* **2007**, *310*, 349-351.
- (69) Ōnuki, Y.; Yasui, S.; Matsushita, M.; Yoshiuchi, S.; Ohya, M.; Hirose, Y.; Dung, N. D.; Honda, F.; Takeuchi, T.; Settai, R.; Sugiyama, K.; Yamamoto, E.; Matsuda, T. D.; Haga, Y.; Tanaka, T.; Kubo, Y.; Harima, H., Characteristic heavy fermion properties in YbCu₂Si₂ and YbT₂Zn₂₀ (T: Co, Rh, Ir). *J. Phys. Soc. Jpn.* **2011**, *80SA*, SA003.
- (70) Torikachvili, M. S.; Jia, S.; Mun, E. D.; Hannahs, S. T.; Black, R. C.; Neils, W. K.; Martien, D.; Bud'ko, S. L.; Canfield, P. C., Six closely related YbT₂Zn₂₀ (T = Fe, Co, Ru, Rh, Os, Ir) heavy fermion compounds with large local moment degeneracy. *Proc. Natl. Acad. Sci. U. S. A.* **2007**, *104*, 9960-9963.
- (71) Jia, S.; Ni, N.; Samolyuk, G. D.; Safa-Sefat, A.; Dennis, K.; Ko, H.; Miller, G. J.; Bud'ko, S. L.; Canfield, P. C., Variation of the magnetic ordering in GdT₂Zn₂₀ (T=Fe, Ru, Os, Co, Rh and Ir) and its correlation with the electronic structure of isostructural YT₂Zn₂₀. *Phys. Rev. B* **2008**, *77*, 104408.
- (72) Niemann, S.; Jeitschko, W., Ternary Aluminides AT₂Al₂₀ (A = Rare Earth Elements and Uranium; T = Ti, Nb, Ta, Mo, and W) with CeCr₂Al₂₀-Type Structure. *J. Solid State Chem.* **1995**, *114*, 337-341.
- (73) Sato, T. J.; Ibuka, S.; Nambu, Y.; Yamazaki, T.; Hong, T.; Sakai, A.; Nakatsuji, S., Ferroquadrupolar ordering in PrTi₂Al₂₀. *Phys. Rev. B* **2012**, *86*, 184419.
- (74) Koseki, M.; Nakanishi, Y.; Deto, K.; Koseki, G.; Kashiwazaki, R.; Shichinomiya, F.; Nakamura, M.; Yoshizawa, M.; Sakai, A.; Nakatsuji, S., Ultrasonic investigation on a cage structure compound PrTi₂Al₂₀. *J. Phys. Soc. Jpn.* **2011**, *80SA*, SA049.
- (75) Ito, T. U.; Higemoto, W.; Nimomiya, K.; Luetkens, H.; Baines, C.; Sakai, A.; Nakatsuji, S., μ SR Evidence of nonmagnetic order and ¹⁴¹Pr hyperfine enhanced nuclear magnetism in the cubic Γ_3 ground doublet system PrTi₂Al₂₀. *J. Phys. Soc. Jpn.* **2011**, *80*, 113703.
- (76) Sakai, A.; Nakatsuji, S., Strong valence fluctuation effects in SmTr₂Al₂₀ (Tr=Ti, V, Cr). *Phys. Rev. B: Condens. Matter Mater. Phys.* **2011**, *84*, 201106(R).

- (77) Verbovytsky, Y.; Latka, K.; Tomala, K., The crystal structure and magnetic properties of the $\text{GdV}_2\text{Al}_{20}$ and $\text{GdCr}_2\text{Al}_{20}$ ternary compounds. *J. Alloys Comp.* **2007**, 442, 334-336.
- (78) Kangas, M. J.; Schmitt, D. C.; Sakai, A.; Nakatsuji, S.; Chan, J. Y., Structure and physical properties of single crystal $\text{PrCr}_2\text{Al}_{20}$ and $\text{CeM}_2\text{Al}_{20}$ ($\text{M}=\text{V}, \text{Cr}$): A comparison of compounds adopting the $\text{CeCr}_2\text{Al}_{20}$ structure type. *J. Solid State Chem.* **2012**, 196, 274-281.
- (79) Moze, O.; Tung, L. D.; Franse, J. J. M.; Buschow, K. H. J., Crystal structure and magnetic properties of $\text{CeV}_2\text{Al}_{20}$ and $\text{CeCr}_2\text{Al}_{20}$. *J. Alloys Comp.* **1998**, 268, 39-41.
- (80) Thiede, V. M. T.; Jeitschko, W.; Niemann, S.; Ebel, T., $\text{EuTa}_2\text{Al}_{20}$, $\text{Ca}_6\text{W}_4\text{Al}_{43}$ and other compounds with $\text{CeCr}_2\text{Al}_{20}$ and $\text{Ho}_6\text{Mo}_4\text{Al}_{43}$ type structures and some magnetic properties of these compounds. *J. Alloys Comp.* **1998**, 267, 23-31.
- (81) Kangas, M. J.; Treadwell, L. J.; Haldolaarachchige, N.; McAlpin, J. D.; Young, D. P.; Chan, J. Y., Magnetic and electrical properties of flux grown single crystals of $\text{Ln}_6\text{M}_4\text{Al}_{43}$ ($\text{Ln}=\text{Gd}, \text{Yb}$; $\text{M}=\text{Cr}, \text{Mo}, \text{W}$). *J. Solid State Chem.* **2013**, 197, 523-531.
- (82) Niemann, S.; Jeitschko, W., The crystal structure of $\text{YbFe}_2\text{Al}_{10}$, a combined substitution and stacking variant of the ThMn_{12} and CeMn_4Al_8 type structures. *Z. Kristallogr.* **1995**, 210, 338-341.
- (83) Cordero, B.; Gomez, V.; Platero-Prats, A. E.; Reves, M.; Echeverria, J.; Cremades, E.; Barragan, F.; Alvarez, S., Covalent radii revisited. *Dalton Trans.* **2008**, 2832-2838.
- (84) Fazakas, E.; Kane, S.; Lazar, K.; Varga, L., Mössbauer study of rapidly solidified Al-Fe based amorphous alloys. *Hyperfine Interact.* **2009**, 189, 119-123.
- (85) Preston, R., Mössbauer study of the surface barrier to the diffusion of iron into aluminum. *Metall. Mater. Trans. B* **1972**, 3, 1831-1835.
- (86) Shabashov, V. A.; Brodova, I. G.; Mukoseev, A. G.; Sagaradze, V. V.; Litvinov, A. V., Deformation-induced phase transformations in the Al-Fe system under intensive plastic deformation. *J. Phys.: Condens. Matter* **2007**, 19, 386222.
- (87) Waerenborgh, J. C.; Salamakha, P.; Sologub, O.; Sérgio, S.; Godinho, M.; Gonçalves, A. P.; Almeida, M., Y-Fe-Al ternary system: partial isothermal section at 1070 K: Powder X-ray diffraction and Mössbauer spectroscopy study. *J. Alloys Comp.* **2001**, 323-324, 78-82.

- (88) Zaleskia, A.; Fedotova, J.; Ilyuschenkob, A.; Talakob, T.; Belyaevb, A.; A., L.; Stanekc, J., Mössbauer, XRD, and SEM Study of FeAl-based powder alloys with nanoinclusions. *Acta Phys. Pol. A* **2006**, *109*, 441-444.
- (89) Fisk, Z., A whiff of chemistry in heavy electron physics. *Science* **2007**, *318*, 1559-1560.
- (90) Chen, G.; Ohara, S.; Hedo, M.; Uwatoko, Y.; Sakamoto, I., Transport properties of the heavy-fermion superconductor Ce₂CoIn₈. *J. Phys.: Condens. Matter* **2003**, *15*, S2175.
- (91) Nicklas, M.; Sidorov, V. A.; Borges, H. A.; Pagliuso, P. G.; Petrovic, C.; Fisk, Z.; Sarrao, J. L.; Thompson, J. D., Magnetism and superconductivity in Ce₂RhIn₈. *Phys. Rev. B* **2003**, *67*, 020506.
- (92) Macaluso, R. T.; Nakatsuji, S.; Lee, H.; Fisk, Z.; Moldovan, M.; Young, D. P.; Chan, J. Y., Synthesis, structure, and magnetism of a new heavy-fermion antiferromagnet, CePdGa₆. *J. Solid State Chem.* **2003**, *174*, 296-301.
- (93) Macaluso, R. T.; Millican, J. N.; Nakatsuji, S.; Lee, H.-O.; Carter, B.; Moreno, N. O.; Fisk, Z.; Chan, J. Y., A comparison of the structure and localized magnetism in Ce₂PdGa₁₂ with the heavy fermion CePdGa₆. *J. Solid State Chem.* **2005**, *178*, 3547-3553.
- (94) Sakai, A.; Nakatsuji, S., Kondo effects and multipolar order in the cubic PrTr₂Al₂₀ (Tr=Ti, V). *J. Phys. Soc. Jpn.* **2011**, *80*, 063701.
- (95) Kangas, M. J.; Schmitt, D. C.; Sakai, A.; Nakatsuji, S.; Chan, J. Y., Structure and physical properties of single crystal PrCr₂Al₂₀ and CeM₂Al₂₀ (M = V, Cr): A comparison of compounds adopting the CeCr₂Al₂₀ structure type. *J. Solid State Chem.* **2012**, *196*, 274-281.
- (96) Sakai, A.; Nakatsuji, S., Strong valence fluctuation effects in SmT₂Al₂₀ (T = Ti, V, Cr). *Phys. Rev. B* **2011**, *84*, 201106.
- (97) Yamada, A.; Higashinaka, R.; Miyazaki, R.; Fushiya, K.; D. Matsuda, T.; Aoki, Y.; Fujita, W.; Harima, H.; Sato, H., Anomalously field-insensitive correlated electron behaviors in SmTa₂Al₂₀. *J. Phys. Soc. Jpn.* **2013**, *82*, 123710.
- (98) Lattur, S. E.; Kanatzidis, M. G., Gd_{1.33}Pt₃(Al,Si)₈ and Gd_{0.67}Pt₂(Al,Si)₅: Two structures containing a disordered Gd/Al layer grown in liquid aluminum. *Inorg. Chem.* **2002**, *41*, 5479-5486.

- (99) Murashova, E. V.; Tursina, A. I.; Bukhan'ko, N. G.; Gribanov, A. V.; Chernyshev, I. V.; Seropegin, Y. D., Ternary compounds $\text{Ce}_{0.67}\text{Pt}_2\text{Al}_5$ and $\text{Ce}_{1.33}\text{Pt}_3\text{Al}_8$. *J. Alloys Comp.* **2005**, *398*, 100-105.
- (100) Sieve, B.; Chen, X.; Cowen, J.; Larson, P.; Mahanti, S. D.; Kanatzidis, M. G., Multinary intermetallics from molten Al. Synthesis of $\text{SmNiAl}_4\text{Ge}_2$ and $\text{YNiAl}_4\text{Ge}_2$. Possible spin frustration in separated triangular Sm^{3+} Layers. *Chem. Mater.* **1999**, *11*, 2451-2455.
- (101) Kitazawa, H.; Mori, A.; Takano, S.; Yamadaya, T.; Matsushita, A.; Matsumoto, T., Physical properties of antiferromagnetic ternary compound SmPd_2Al_3 . *Physica B* **1993**, *186–188*, 661-663.
- (102) Pospíšil, J.; Nénert, G.; Miyashita, S.; Kitazawa, H.; Skourski, Y.; Diviš, M.; Prokleška, J.; Sechovský, V., Complex magnetic phase diagram of a geometrically frustrated Sm lattice: Magnetometry and neutron diffraction study of SmPd_2Al_3 . *Phys. Rev. B* **2013**, *87*, 214405.
- (103) Macaluso, R. T.; Shatruk, M.; Chai, P.; Hong, H.; Wangeline, C.; Ryan, K.; Holton, P.; Allaz, J.; Morrison, G.; Fulfer, B.; Fronczek, F.; Chan, J. Y., Synthesis, structure, and magnetic behavior of $(\text{La}_x\text{Ce}_{1-x})_{1.33}\text{Pt}_4\text{Ga}_{10}$ ($0 < x < 1$). *J. Alloys Comp.* **2014**, *600*, 193-198.
- (104) Buschinger, B.; Geibel, C.; Weiden, M.; Dietrich, C.; Cordier, G.; Olesch, G.; Köhler, J.; Steglich, F., Crystallographic and physical properties of new ternary $\text{R}_2\text{T}_3\text{X}_9$ ($\text{R}=\text{La, Ce, U, T}=\text{Rh, Ir, X}=\text{Al, Ga}$) compounds. *J. Alloys Comp.* **1997**, *260*, 44-49.
- (105) Tougait, O.; Noël, H., Crystal structures and magnetic properties of NdCoAl_4 , $\text{Nd}_2\text{Co}_3\text{Al}_9$ and $\text{Sm}_2\text{Co}_3\text{Al}_9$. *J. Alloys Comp.* **2006**, *417*, 1-6.
- (106) Troć, R.; Tougait, O.; Noël, H., Crystal structure and properties of $\text{U}_2\text{Co}_3\text{Al}_9$. *Intermetallics* **2007**, *15*, 1091-1095.
- (107) Khalaff, K.; Schubert, K., Kristallstruktur von Pd_5Ga_2 . *J. Less Common Met.* **1974**, *37*, 129-140.
- (108) Gille, P.; Ziemer, T.; Schmidt, M.; Kovnir, K.; Burkhardt, U.; Armbrüster, M., Growth of large PdGa single crystals from the melt. *Intermetallics* **2010**, *18*, 1663-1668.
- (109) Coleman, P., New approach to the mixed-valence problem. *Phys. Rev. B* **1984**, *29*, 3035-3044.

- (110) S.Ghosh; Strydom, A. M., Strongly correlated electron behaviour in CeT_2Al_8 ($\text{T} = \text{Fe}, \text{Co}$). *Acta Phys. Pol., A* **2011**, *121*, 1082-1084.
- (111) Czech, E.; Cordier, G.; Schäfer, H., Zur kenntnis von CaCo_2Al_8 . *J. Less Common Met.* **1983**, *95*, 205-211.
- (112) Tamura, I.; Mizushima, T.; Isikawa, Y.; Sakurai, J., Mössbauer effect and magnetization studies of CeFe_2Al_8 and LaFe_2Al_8 . *J. Magn. Magn. Mater.* **2000**, *220*, 31-38.
- (113) Jarrett, H. S.; Cloud, W. H.; Bouchard, R. J.; Butler, S. R.; Frederick, C. G.; Gillson, J. L., Evidence for itinerant d -electron ferromagnetism. *Phys. Rev. Lett.* **1968**, *21*, 617-620.
- (114) Guo, S.; Young, D. P.; Macaluso, R. T.; Browne, D. A.; Henderson, N. L.; Chan, J. Y.; Henry, L. L.; DiTusa, J. F., Discovery of the Griffiths phase in the itinerant magnetic semiconductor $\text{Fe}_{1-x}\text{Co}_x\text{S}_2$. *Phys. Rev. Lett.* **2008**, *100*, 017209.
- (115) Wu, X.; Francisco, M.; Rak, Z.; Bakas, T.; Mahanti, S. D.; Kanatzidis, M. G., Synthesis, magnetism and electronic structure of $\text{YbNi}_{2-x}\text{Fe}_x\text{Al}_8$ ($x = 0.91$) isolated from Al flux. *J. Solid State Chem.* **2008**, *181*, 3269-3277.
- (116) Schlüter, M.; Jeitschko, W., Ternary lanthanoid ruthenium gallides with a high gallium content: $\text{Ln}_2\text{Ru}_3\text{Ga}_{10}$ ($\text{Ln} = \text{Yb}, \text{Lu}$) with a new structure type and LnRu_2Ga_8 ($\text{Ln} = \text{La}-\text{Nd}$) with CaCo_2Al_8 -type structure. *Inorg. Chem.* **2001**, *40*, 6362-6368.
- (117) Tougait, O.; Kaczorowski, D.; Noël, H., PrCo_2Al_8 and $\text{Pr}_2\text{Co}_6\text{Al}_{19}$: Crystal structure and electronic properties. *J. Solid State Chem.* **2005**, *178*, 3639-3647.
- (118) Antonyshyn, I.; Prots, Y.; Margiolaki, I.; Schmidt, M. P.; Zhak, O.; Oryshchyn, S.; Grin, Y., Tetragonal-antiprismatic coordination of transition metals in intermetallic compounds: $\omega 1\text{-Mn}_6\text{Ga}_{29}$ and its structural relationships. *J. Solid State Chem.* **2013**, *199*, 141-148.
- (119) Pauling, L., Interatomic distances in Co_2Al_9 . *Acta Cryst.* **1951**, *4*, 138-140.
- (120) Sichevych, O.; Kohout, M.; Schnelle, W.; Borrmann, H.; Cardoso-Gil, R.; Schmidt, M.; Burkhardt, U.; Grin, Y., EuTM_2Ga_8 ($\text{TM} = \text{Co}, \text{Rh}, \text{Ir}$) — A contribution to the chemistry of the CeFe_2Al_8 -type compounds. *Inorg. Chem.* **2009**, *48*, 6261-6270.

- (121) Yamashita, T.; Miyazaki, R.; Aoki, Y.; Ohara, S., Transport, thermal, and magnetic properties of YbNi_3X_9 ($\text{X} = \text{Al}, \text{Ga}$): A newly synthesized Yb-based Kondo lattice system. *J. Phys. Soc. Jpn.* **2012**, *81*, 034705.
- (122) Tomoshisa, F.; Hiroshi, K.; Tetsuro, Y.; Yuji, M.; Shigeo, O.; Jyunichi, Y., Tuning of Kondo temperature in YbNi_3Ga_9 by Co-substitution. *JPS Conf. Proc.* **2014**, *3*, 011048.
- (123) Bauer, E. D.; Mixson, D.; Ronning, F.; Hur, N.; Movshovich, R.; Thompson, J. D.; Sarrao, J. L.; Hundley, M. F.; Tobash, P. H.; Bobev, S., Antiferromagnetic quantum critical point in $\text{CeRhIn}_{5-x}\text{Sn}_x$. *Physica B* **2006**, *378–380*, 142-143.
- (124) Kangas, M. J.; Treadwell, L. J.; Haldolaarachchige, N.; McAlpin, J. D.; Young, D. P.; Chan, J. Y., Magnetic and electrical properties of flux grown single crystals of $\text{Ln}_6\text{M}_4\text{Al}_{43}$ ($\text{Ln}=\text{Gd}, \text{Yb}$; $\text{M}=\text{Cr}, \text{Mo}, \text{W}$). *J. Solid State Chem.*
- (125) Fisk, Z., Searching for heavy fermion materials. *Physica B* **2006**, *378–380*, 13-16.
- (126) Yang, Y.-f.; Fisk, Z.; Lee, H.-O.; Thompson, J. D.; Pines, D., Scaling the Kondo lattice. *Nature* **2008**, *454*, 611-613.
- (127) Morosan, E.; Natelson, D.; Nevidomskyy, A. H.; Si, Q., Strongly correlated materials. *Adv. Mater.* **2012**, *24*, 4896-4923.
- (128) Fulfer, B. W.; McAlpin, J. D.; Engelkemier, J.; McCandless, G. T.; Prestigiacomo, J.; Stadler, S.; Fredrickson, D. C.; Chan, J. Y., Filling in the holes: structural and magnetic properties of the chemical pressure stabilized LnMn_xGa_3 ($\text{Ln} = \text{Ho–Tm}$; $x < 0.15$). *Chem. Mater.* **2013**, *26*, 1170-1179.

Appendix A. Investigating the chemical stability and physical properties of ErM_xGa_3 ($\text{M} = \text{Fe}, \text{Co}$; $x < 0.2$)

A.1 Objective

To investigate the chemical stability and physical properties of ErM_xGa_3 ($\text{M} = \text{Fe}, \text{Co}$; $x < 0.2$). Single crystals of ErM_xGa_3 ($\text{M} = \text{Fe}, \text{Co}$; $x < 0.2$) were grown.

A.2 Synthesis

Single crystals of ErM_xGa_3 ($\text{M} = \text{Fe}, \text{Co}$; $x < 0.2$) were grown using the flux growth method. The elements Er: M: Ga were weighed in atomic ratio of 1:0.1:20 and 1:0.2:20, respectively, to investigate the effect of varying M concentration. The respective elements Er: M: Ga were placed in an alumina crucibles, topped with another crucible, and sealed in an evacuated silica tubes. All vessels were heated to 1150 °C at a rate of 100 °C/h, and dwelled for 5 hr. Subsequently, the ampoules were cooled to 550 °C at a rate of 5 °C/h, and finally cooled to 300 °C at a rate of 100 °C/h. The samples were removed from the furnace and centrifuged to remove excess Ga flux. The excess Ga flux on the single crystals was removed by repeated sonication in hot water. Synthesis yielded large single crystals ~ 5 mm long.

A.3 Elemental Analysis

Elemental analysis of ErM_xGa_3 ($\text{M} = \text{Fe}, \text{Co}$; $x < 0.2$) single crystals was performed via energy-dispersive spectroscopy (EDS) using an EDAX detector with an accelerating voltage of 19 kV. Single crystals of ErM_xGa_3 ($\text{M} = \text{Fe}, \text{Co}$; $x < 0.2$) were polished prior to analysis in order to minimize the presence of possible surface impurities. Spectra were integrated for 60 seconds and results from 6 spots were averaged and normalized to Er. The compositions are $\text{Er}_{1.00(6)}\text{Fe}_{0.08(1)}\text{Ga}_{2.27(7)}$, $\text{Er}_{1.00(1)}\text{Fe}_{0.11(1)}\text{Ga}_{2.91(1)}$, and $\text{Er}_{1.00(1)}\text{Co}_{0.14(1)}\text{Ga}_{3.06(1)}$.

A.4 Physical Properties

Magnetic data were collected on single crystals of ErM_xGa_3 ($M = \text{Fe, Co}$; $x < 0.2$) using a Quantum Design Magnetic Property Measurement System (MPMS). The temperature-dependent susceptibility was measured under zero-field (ZFC) conditions between 3 and 300 K with an applied magnetic field of 0.01 T. Also, the field-dependent magnetization data were measured at 3 K with fields up to 7 T for all analogues.

A.5 Results and Discussion

Powder diffraction data was collected on ground single crystals of ErM_xGa_3 ($M = \text{Fe, Co}$; $x < 0.2$) using a Bruker D8 Advance X-ray diffractometer equipped with a Lynxeye detector with $\text{Cu K}\alpha$ radiation. The diffraction patterns were indexed to AuCu_3 -structure type. All diffraction patterns exhibit a shift in 2θ consistent with the insertion of the guest atom M. Fragments of ErM_xGa_3 ($M = \text{Fe, Co}$; $x < 0.2$) were cut to appropriate sizes and mounted on a Bruker D8 Quest Kappa single crystal X-ray diffractometer equipped with a $\text{I}\mu\text{S}$ microfocus source ($\lambda = 0.71073 \text{ \AA}$) operating at 50 kV and 1 mA for data collections. The single crystal diffraction data were indexed to a primitive cubic cell with dimension $a \sim 4.25 \text{ \AA}$, consistent with the AuCu_3 -structure type.¹ A starting model of the crystal structure was first obtained using SIR97² and was refined using SHELXL97.³ After implementing the atomic position that corresponds to the AuCu_3 -structure type, residual electron density was observed at $\sim 0.11 \frac{1}{2} \frac{1}{2}$, which is really close to the elongated Ga1 site. Therefore, the Ga site was split to a Ga and Ga' site. Subsequently, another Q peak at $\frac{1}{2} \frac{1}{2}$ was present corresponding to the middle of the unit cell. This position was modeled M with partial occupancy. The atomic positions, Wyckoff symmetries, displacement parameters, site occupancies, and interatomic distances of ErM_xGa_3 ($M = \text{Fe, Co}$; $x < 0.2$) are provided in Tables A.1-3.

Table A.1. Crystallographic Parameters of ErM_xGa_3 (M = Fe, Co; $x < 0.2$)

| Crystal data | | | | |
|---|---|---|---|--|
| Formula | ErFe _{0.06(1)} Ga ₃ | ErFe _{0.11(2)} Ga ₃ | ErCo _{0.06(2)} Ga ₃ | |
| Space group | <i>Pm</i> $\bar{3}$ <i>m</i> | <i>Pm</i> $\bar{3}$ <i>m</i> | <i>Pm</i> $\bar{3}$ <i>m</i> | |
| <i>a</i> (Å) | 4.2227(4) | 4.2263(5) | 4.2201(7) | |
| <i>V</i> (Å ³) | 75.296(12) | 75.489(15) | 75.16(2) | |
| <i>Z</i> | 1 | 1 | 1 | |
| Crystal size (mm ³) | 0.04 x 0.04 x 0.12 | 0.04 x 0.04 x 0.10 | 0.10 x 0.10 x 0.15 | |
| θ Range (°) | 4.83-30.33 | 4.82-30.30 | 4.83-30.35 | |
| μ (mm ⁻¹) | 58.423 | 58.274 | 59.223 | |
| <i>Data Collection and Refinement</i> | | | | |
| Collected reflections | 734 | 756 | 745 | |
| Unique reflections | 41 | 41 | 41 | |
| <i>R</i> _{int} | 0.0217 | 0.0226 | 0.0236 | |
| <i>h</i> | -4 ≤ <i>h</i> ≤ 6 | -6 ≤ <i>h</i> ≤ 4 | -5 ≤ <i>h</i> ≤ 5 | |
| <i>k</i> | -5 ≤ <i>k</i> ≤ 5 | -5 ≤ <i>k</i> ≤ 5 | -5 ≤ <i>k</i> ≤ 5 | |
| <i>l</i> | -6 ≤ <i>l</i> ≤ 5 | -5 ≤ <i>l</i> ≤ 6 | -5 ≤ <i>l</i> ≤ 5 | |
| $\Delta\rho_{\text{max}}$ (e Å ⁻³) | 0.895 | 1.026 | 1.226 | |
| $\Delta\rho_{\text{min}}$ (e Å ⁻³) | -0.681 | -1.845 | -1.102 | |
| GoF | 1.416 | 1.269 | 1.529 | |
| Extinction coefficient | 0.181(12) | 0.001(6) | 0.046(4) | |
| ^a <i>R</i> ₁ (<i>F</i>) for <i>F</i> _o ² > 2σ(<i>F</i> _o ²) | 0.0099 | 0.0184 | 0.0212 | |
| ^b <i>R</i> _w (<i>F</i> _o ²) | 0.0204 | 0.0392 | 0.0495 | |

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|$$

$$^b wR_2 = [\sum w(F_o^2 - F_c^2)^2 / \sum w(F_o^2)^2]^{1/2}; w = 1/[\sigma^2(F_o^2) + (0.00005 P)^2 + 0.0026 P], w = 1/[\sigma^2(F_o^2) + 0.6347 P], \text{ and } w = 1/[\sigma^2(F_o^2) + (0.0168 P)^2 + 0.5117 P]; P = (F_o^2 + 2 F_c^2)/3 \text{ for } \text{ErFe}_{0.06(1)}\text{Ga}_3, \text{ and } \text{ErFe}_{0.11(2)}\text{Ga}_3, \text{ and } \text{ErCo}_{0.06(2)}\text{Ga}_3 \text{ respectively.}$$

Table A.2. Atomic Positions of ErM_xGa_3 (M = Fe, Co; $x < 0.2$)

| Atom | Wyckoff position | Symmetry | x | y | z | Occupancy | ^a U _{eq} (Å ²) |
|--|------------------|-------------|----------|-----|-----|-----------|--|
| $\text{ErFe}_{0.06(1)}\text{Ga}_3$ | | | | | | | |
| Er | 1a | $m\bar{3}m$ | 0 | 0 | 0 | 1 | 0.0082(5) |
| Fe | 1b | $m\bar{3}m$ | 1/2 | 1/2 | 1/2 | 0.062(8) | 0.005(7) |
| Ga | 3c | 4/ mmm | 0 | 1/2 | 1/2 | 0.76(8) | 0.0110(14) |
| Ga' | 6f | 4mm | 0.082(2) | 1/2 | 1/2 | 0.171(10) | 0.0082(13) |
| $\text{ErFe}_{0.11(2)}\text{Ga}_{2.92(8)}$ | | | | | | | |
| Er | 1a | $m\bar{3}m$ | 0 | 0 | 0 | 1 | 0.0037(9) |
| Fe | 1b | $m\bar{3}m$ | 1/2 | 1/2 | 1/2 | 0.128(4) | 0.002(8) |
| Ga | 3c | 4/ mmm | 0 | 1/2 | 1/2 | 0.684(13) | 0.007(2) |
| Ga' | 6f | 4mm | 0.070(9) | 1/2 | 1/2 | 0.145(6) | 0.004(4) |
| $\text{ErCo}_{0.06(2)}\text{Ga}_{2.9(1)}$ | | | | | | | |
| Er | 1a | $m\bar{3}m$ | 0 | 0 | 0 | 1 | 0.0083(8) |
| Co | 1b | $m\bar{3}m$ | 1/2 | 1/2 | 1/2 | 0.104(5) | 0.02(3) |
| Ga | 3c | 4/ mmm | 0 | 1/2 | 1/2 | 0.678(16) | 0.010(2) |
| Ga' | 6f | 4mm | 0.080(2) | 1/2 | 1/2 | 0.141(8) | 0.015(11) |

Table A.3. Selected interatomic distances (Å) for ErM_xGa_3 (M = Fe, Co; $x < 0.2$)

| Interatomic distance | $\text{ErFe}_{0.06(1)}\text{Ga}_3$ | $\text{ErFe}_{0.11(2)}\text{Ga}_3$ | $\text{ErCo}_{0.06(2)}\text{Ga}_{2.9(1)}$ |
|----------------------|------------------------------------|------------------------------------|---|
| Ln-Ga (x12) | 2.9859(2) | 2.9884(4) | 2.9841(4) |
| Ln-Ga' (x12) | 2.9970(4) | 3.0031(8) | 2.0031(10) |
| Ln-M (x8) | 3.6570(2) | 3.6601(3) | 3.6547(4) |
| Ln-Ln (x6) | 4.2227(4) | 4.2263(5) | 4.2201(7) |
| M-Ga (x6) | 2.1114(2) | 2.1131(3) | 2.1100(4) |
| M-Ga' (x6) | 1.8538(2) | 1.8173(2) | 1.7724(3) |

Table A.4. Magnetic properties of ErM_xGa_3 (M = Fe, Co; $0 \leq x < 2$)

| Compound | T_N (K) | θ_W (K) | μ_{eff} ($\mu_B/\text{mol Er}$) |
|------------------------------------|-----------|----------------|--|
| ErGa_3 | 2.9 | -33.48(3) | 10.095(4) |
| $\text{ErFe}_{0.06(1)}\text{Ga}_3$ | 5.2 | -10.35(9) | 10.78(7) |
| $\text{ErFe}_{0.11(2)}\text{Ga}_3$ | 6.2 | -8.65(6) | 10.44(5) |
| $\text{ErCo}_{0.06(2)}\text{Ga}_3$ | 3.3 | -9.65(5) | 10.34(3) |

A.6 Crystal Structure

ErM_xGa_3 (M = Fe, Co; $x < 0.2$) crystallizes in the space group $\text{Pm}\bar{3}\text{m}$ with $a = \sim 4.2$ Å. The unit cell of $\text{ErFe}_{0.07}\text{Ga}_3$ is shown in Figure A.1. The crystal structure can be described as a variant of the AuCu_3 -structure type. The lanthanide atoms occupy the corners of the unit cell, while the Fe atom partially occupies the center of the unit cell. As a result of Fe insertion, the Ga atoms that reside on the face were elongated as shown in Figure A.1. Therefore, the Ga1 position was refined to two partially occupied positions, Ga and Ga'. Similar behavior was observed in $\text{Er}_4\text{Fe}_{0.67}\text{Ga}_{12}$ that adopts the $\text{Y}_4\text{PdGa}_{12}$ structure type, where two gallium positions were observed on the face of the cube and on an extended position due to Fe vacancies.⁴

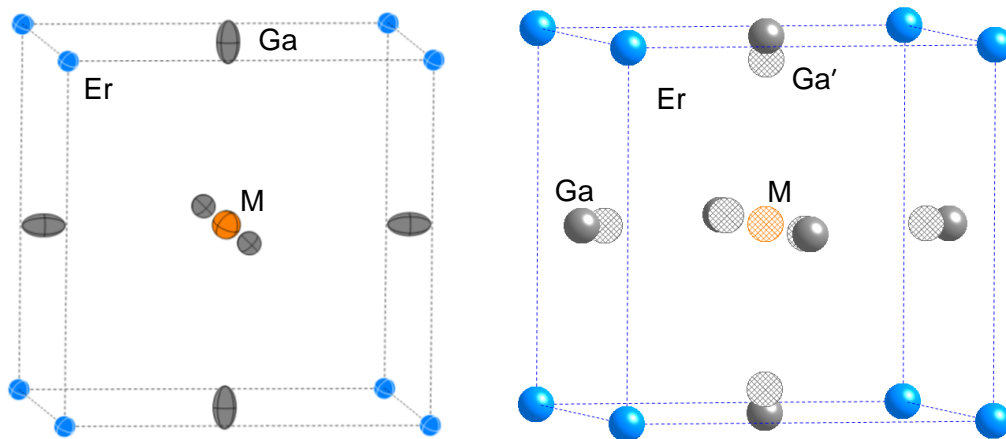


Figure A.1. a) Unit cell of $\text{ErFe}_{0.07}\text{Ga}_3$, where Er, Fe, and Ga atoms are blue, orange, and grey ellipsoids, (left) respectively. b) Unit cell of $\text{ErFe}_{0.07}\text{Ga}_3$, where Er, Fe, and Ga atoms are blue, orange, and grey spheres, (right) respectively.

A.7 Magnetism

The temperature dependent magnetic susceptibility of ErM_xGa_3 ($M = \text{Fe}, \text{Co}$) with an applied field of 0.1 T are shown in Figure A.2. The magnetic susceptibility increases with decreasing temperature until $T_N \sim 5.2, 6.2,$ and 3.3 K for $\text{Er}_{1.00(6)}\text{Fe}_{0.08(1)}\text{Ga}_{2.27(7)}$, $\text{Er}_{1.00(1)}\text{Fe}_{0.11(1)}\text{Ga}_{2.91(1)}$, and $\text{Er}_{1.00(1)}\text{Co}_{0.14(1)}\text{Ga}_{3.06(1)}$, respectively, followed by a decrease in magnetization. The Neél temperature are considerably different than the parent analogue ErGa_3 $T_N \sim 2.9$ K. The difference All compounds exhibit Curie-Weiss behavior above T_N and were fitted to a modified Curie-Weiss equation $\chi = \chi_0 + (C/(T-\theta))$, where χ_0 is the temperature independent contribution, θ is the Weiss constant, and C is the Curie constant. The constants from the Curie Weiss fit are provided in Table A.4. The magnetic moments are higher than the calculated magnetic moments of Er^{3+} ions (9.58 m_B), but it is comparable to the parent analogue ErGa_3 as shown in Table A.4. The Weiss constant of $\text{Er}_{1.00(6)}\text{Fe}_{0.08(1)}\text{Ga}_{2.27(7)}$, $\text{Er}_{1.00(1)}\text{Fe}_{0.11(1)}\text{Ga}_{2.91(1)}$, and $\text{Er}_{1.00(1)}\text{Co}_{0.14(1)}\text{Ga}_{3.06(1)}$ are significantly lower than ErGa_3 , which could be due to the decrease in the interaction strengthen between the Er atoms caused by the increase in Er-Er distance as a result of M insertion. Figure A.2 shows the field-dependent magnetization of ErM_xGa_3 ($M = \text{Fe}, \text{Co}$) at

3 K. The magnetization of all samples is linear at low fields followed by a curvature at ~ 2 T with no signs of saturation.

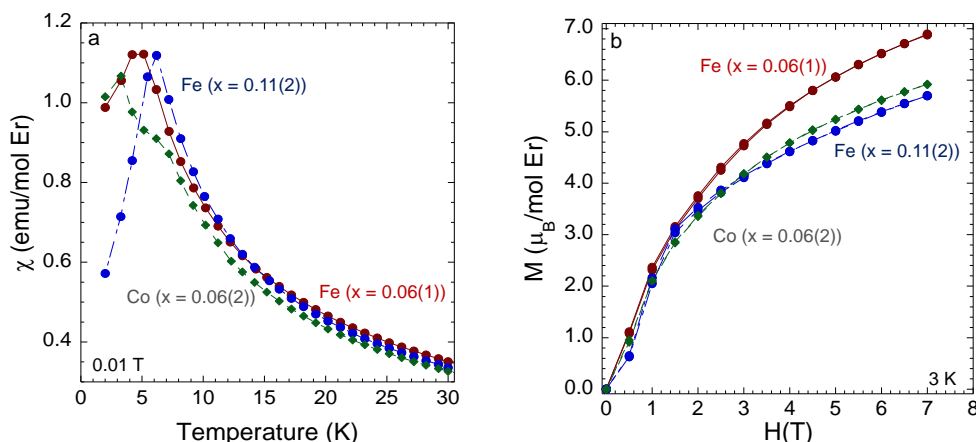


Figure A.1. Temperature (a) and field (b) dependent magnetization of ErM_xGa_3 (M = Fe, Co; $x < 0.2$).

A.8 References

- (1) le Blanc, M.; Richter, K.; Schiebold, E., Eine Pruefung der Tammannschen Theorie der Resistenzgrenzen am System Gold-Kupfer. Aufstellung neuer Gesichtspunkte. *Ann. Phys* **1928**, *86*, 929.
- (2) Altomare, A.; Burla, M. C.; Camalli, M.; Cascarano, G. L.; Giacovazzo, C.; Guagliardi, A.; Moliterni, A. G. G.; Polidori, G.; Spagna, R., SIR97: a new tool for crystal structure determination and refinement. *J. Appl. Crystallogr.* **1999**, *32*, 115-119.
- (3) Sheldrick, G., A short history of SHELX. *Acta Crystallogr.* **2008**, *64*, 112-122.
- (4) Drake, B. L.; Grandjean, F.; Kangas, M. J.; Okudzeto, E. K.; Karki, A. B.; Sougrati, M. T.; Young, D. P.; Long, G. J.; Chan, J. Y., Crystal growth, transport, and the structural and magnetic properties of $\text{Ln}_4\text{FeGa}_{12}$ with Ln = Y, Tb, Dy, Ho, and Er. *Inorg. Chem.* **2009**, *49*, 445-456.

Appendix B. Investigation of Ce and Yb intermetallics

B.1 Introduction

Discovering exotic properties based on structure-property relationship is an extensive research area in solid state chemistry. Ce and Yb – intermetallics can be used to study the magnetic properties as a function of a tunable parameter, such as disorder, coordination, and atomic size. The AlB_2 and ThSi_2 -structure types of Ce-analogues have been characterized structurally and magnetically based on the tunable parameter disorder.¹ CeGa_2 has been characterized as a Kondo lattice (Ce^{3+}) and exhibits multiple magnetic transitions between 8.4 and 11.4 K with a Sommerfeld parameter of approximately 32 mJ/mol K^2 .² The CeSi_2 has been reported as a mixed $\text{Ce}^{3+/4+}$ and heavy fermion compound ($\gamma \sim 100$ mJ/mol K^2) with strong ferromagnetic interactions ($\theta \sim 302$ K).³ The fully ordered phases of CeGa_2 and CeSi_2 have been magnetically tuned by doping in Ag to characterize their magnetic correlation based on a change in the electronic structure, which has been highlighted and extensively reviewed.^{1, 4} Our group has recently grown single crystals of $\text{CeAg}_y\text{Si}_x\text{Ga}_{2-x-y}$ adopting the AlB_2 and ThSi_2 -structure types. The ThSi_2 -structure type of $\text{CeAg}_y\text{Si}_x\text{Ga}_{2-x-y}$ behaves as a Ce^{3+} Kondo system with no ordering down to 3 K but is more metallic than ThSi_2 -structure type of $\text{Ce}(\text{Si},\text{Ga})_2$, which could be partly due to the addition of Ag.^{1, 4} The AlB_2 -structure type of $\text{CeAg}_y\text{Si}_x\text{Ga}_{2-x-y}$ exhibits a paramagnetic state down to 3 K and mix valent character.^{1, 4}

*Reprinted with permission from Morrison, G. W.; Menard, M. C.; Treadwell, L. J.; Haldolaarachchige, N.; Kendrick, K. C.; Young, D. P.; Chan, J. Y., Serendipitous growth of single crystals with silicon incorporation. *Philos. Mag.* **2012**, 92, 2524-2540. Copyright 2014 Elsevier.

Relative to Ce-based intermetallic compounds, there are very few Yb-based analogues. A summary of Yb(AgSiGa)₂ pseudo binary compounds adopting the AlB₂ and ThSi₂-structure types are shown in Figure 5. The AlB₂-structure type has been reported for YbGa_xSi_{2-x} (1.12 < x < 1.49) where Yb was determined to be mixed valent with an oxidation state of +2.23.^{5, 6} YbGa_xSi_{2-x} was observed to be superconducting as x varies from 1.12 - 1.49.^{5, 6} However, neither of the parent phases, YbGa₂ and YbSi_{2-x}, are superconducting at any temperature.^{7, 8} The Ga-containing parent compound YbGa₂ adopts the CaIn₂-structure type, unlike the Ce-analogue, CeGa₂, which adopts the AlB₂-structure type.² The Si-containing parent YbSi_{2-x} adopts the AlB₂-structure type, unlike the Ce-analogue that adopts the ThSi₂-structure type.³ By considering the previously reported superconductor, the AlB₂-type Yb(Si,Ga)₂,⁹ and the physical properties of the AlB₂ and ThSi₂-structure types of CeAg_{0.01(1)}Si_{0.1(1)}Ga_{1.9(1)}, we have focused our efforts on the growth of YbAg_ySi_xGa_{2-x-y} that adopts the ThSi₂ and AlB₂-structure types.

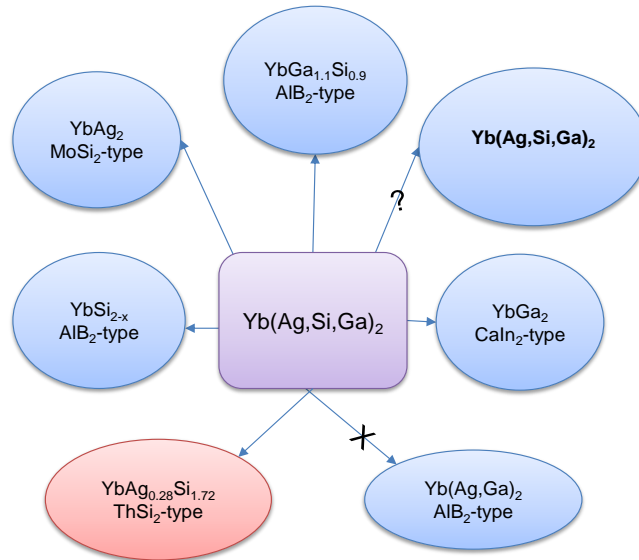


Figure B.1. This bubble diagram depicts a summary of Yb-Ag-Si-Ga pseudo binaries.

The self-flux growth method was attempted to synthesize the $\text{Yb}(\text{Ag},\text{Si},\text{Ga})_2$ adopting the AlB_2 and ThSi_2 -structure types. The initial reaction profile was similar to the reaction profile for the synthesis of $\text{CeAg}_y\text{Si}_x\text{Ga}_{2-x-y}$ that adopts the AlB_2 and ThSi_2 -structure types via different reaction ratio.^{1, 4} The $\text{Yb}:\text{Ag}:\text{Si}:\text{Ga}$ reaction ratios of 2:1:1:20 and 2:1:0.5:20 were attempted for the growth of pseudo-binaries of $\text{YbAg}_y\text{Si}_x\text{Ga}_{2-x-y}$ because these particular ratios were used in the growth of $\text{CeAg}_y\text{Si}_x\text{Ga}_{2-x-y}$. The elements were placed in alumina crucibles, topped with silica wool, and then sealed inside evacuated fused-silica tubes. Silica wool was placed on the brim of the alumina crucible to serve as a filter for excess flux during centrifugation. The initial reaction profile required heating the elements ($\text{Yb}:\text{Ag}:\text{Si}:\text{Ga}$) to 900 °C at a rate of 200 °C/h, dwelling for 24 h, then cooling to 650 °C at a rate of 150 °C/h, followed by dwelling for 2 days, and finally spinning to remove the excess flux. After the reaction, no single crystals were recovered. Subsequently, several attempts to grow pseudo binaries of $\text{YbAg}_y\text{Si}_x\text{Ga}_{2-x-y}$ by systematically varying the heating rate, dwelling time, and cooling rate were unsuccessful. The heating rate was decreased from 200 °C/h to 25 °C/h, to decrease the volatility of Yb. The dwell time at 900 °C was varied from 9 h, 12 h, and 120 h to allow mixing. The spin temperature was also varied from 750 °C, 650 °C, and 500 °C, and the dwell time at low temperature (500 °C) from 2 days to 5 days. In all the growths attempted, the only product that was identified was the $\text{Yb}(\text{AgGa})_4$, that adopts the BaAl_4 -structure type, which was identified by using powder X-ray diffraction and EDS. In another attempt to grow pseudo-binaries of $\text{YbAg}_y\text{Si}_x\text{Ga}_{2-x-y}$ the reaction ratios were changed to 6:1:1.5:20 and 6:1:2:20 to make sure that the silicon reacted with the other elements. The reactions were heated to 1000 °C at a rate of 25 °C/h, followed by a dwell for 24 h, and then cooling to 650 °C at a rate of 25 °C/h. The final synthesis yielded small crystals, which preliminary composition calculated from EDS measurements was $\text{YbAg}_{0.13(5)}\text{Si}_{0.03(2)}\text{Ga}_{2.0(5)}$. However, due to

low yield and poor crystal quality the structure could not be determined with these particular crystals. In order to grow the crystals with high yield and good crystal quality, the temperature profile was varied consisting of heating to 1000 °C at a rate of 25 °C/h, followed by a dwell for 96 h, and then cooling to 750 °C at a rate of 5 °C/h. Single crystals, in the shape of rods ~5 mm long, were obtained from this reaction. The rods were etched in diluted (~0.01 M) HCl and hot water to remove the excess gallium. X-ray powder diffraction technique was employed on the product, which is depicted in Figure 6. The X-ray powder diffraction pattern was compared to a calculated powder pattern of AlB₂-structure type of YbAg_ySi_xGa_{2-x-y}. The powder patterns match up well with each other indicating that the AlB₂-structure type was synthesized. Crystallographic parameters of YbAg_{0.10(2)}Si_{0.83(8)}Ga_{1.07(3)} were determined and provided in Appendix B.1. Crystal structures were solved by direct methods with SIR97 and refined with SHELXL97.^{10, 11} The atomic positions, Wyckoff symmetry, displacement parameters, and occupancies of atoms for YbAg_{0.10(2)}Si_{0.83(8)}Ga_{1.07(3)} are provided in Appendix B.2.

B.2 Results and Discussion

The hexagonal AlB₂-structure type, shown in Figure 7, has been well described for a vast number of intermetallics. The crystal structure can be described as honeycomb [Ga_{2-x-y}Si_xAg_y] planar nets stacked along the *c*-axis with Yb atoms located in hexagonal voids between them. The M-M interatomic distances are 2.39831(17) Å, consistent with covalently bonded M-M contacts of ~2.5 Å.

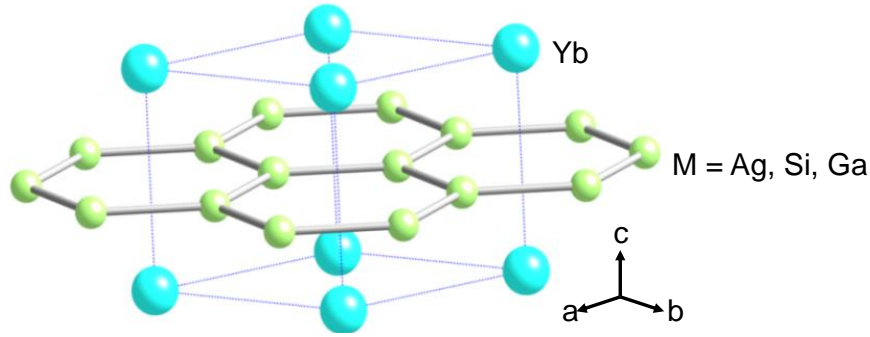


Figure B.2. Crystal structure of AlB₂-type of YbAg_xSi_yGa_{2-x-y} is along the *c*-axis, with the Yb atoms represented as blue spheres and the M-atoms represented as green spheres.

Table B.1. Crystallographic Parameters of YbAg_ySi_{2-x-y}Ga_x

| | |
|---|---|
| Crystal data | |
| Composition | CeAg _{0.01(1)} Si _{0.1(1)} Ga _{1.9(1)} |
| Crystal System | Hexagonal |
| Space group | <i>P6/mmm</i> |
| <i>a</i> (Å) | 4.1540(3) |
| <i>c</i> (Å) | 4.2500(2) |
| <i>V</i> (Å ³) | 63.511(7) |
| <i>Z</i> | 1 |
| Crystal dimensions (mm ³) | 0.05 x 0.05 x 0.05 |
| θ range (°) | 1.00-30.85 |
| μ (mm ⁻¹) | 34.530 |
| Data Collection | |
| Measured reflections | 648 |
| Independent reflections | 61 |
| Reflections with $I > 2\sigma(I)$ | 61 |
| R_{int} | 0.085 |
| <i>h</i> | -6 to 14 |
| <i>k</i> | -6 to 0 |
| <i>l</i> | -5 to 23 |
| R_I^a | 0.0158 |
| wR_2^b | 0.0332 |
| Parameters | 9 |
| $\Delta\rho_{max}$ (e Å ⁻³) | 1.759 |
| $\Delta\rho_{min}$ (e Å ⁻³) | -0.799 |
| Extinction coefficient | 0.19(2) |
| GOF | 1.09 |

^a $R_I = \sum ||F_o| - |F_c|| / \sum |F_o|$

^b $wR_2 = [\sum w(F_o^2 - F_c^2)^2 / \sum w(F_o^2)^2]^{1/2}$; $P = (F_o^2 + 2F_c^2)/3$; $w = 1/[\sigma^2(F_o^2) + 0.0182 P^2]$ for YbAg_xSi_yGa_{2-x-y}.

Table B.2. Atomic Positional & Displacement of AlB₂-type YbAg_ySi_yGa_{2-x-y} at 298 K

| Atom | Wyckoff position | <i>x</i> | <i>y</i> | <i>z</i> | Occ. ^a | U _{eq} (Å ²) ^b |
|---|------------------|----------|----------|----------|-------------------|--|
| YbAg _{0.01(1)} Si _{0.9(1)} Ga _{1.0(1)} | | | | | | |
| Ce | 1 <i>a</i> | 1 | 0 | 1 | 1.00 | 0.0127(4) |
| [†] <i>M</i> | 2 <i>d</i> | 1/3 | 2/3 | 1/2 | 1.00 | 0.0190(6) |

[†]*M* = Ag (0.5 %) + Si (45 %) + Ga (54.5 %)

^aOccupancy

^bU_{eq} is defined at one third of the trace of the orthogonalized U_{ij} tensor.

B.3 References

- (1) Morrison, G. W.; Menard, M. C.; Treadwell, L. J.; Haldolaarachchige, N.; Kendrick, K. C.; Young, D. P.; Chan, J. Y., Serendipitous growth of single crystals with silicon incorporation. *Philos. Mag.* **2012**, 92, 2524-2540.
- (2) Burlet, P.; Frémy, M. A.; Gignoux, D.; Lapertot, G.; Quezel, S.; Regnault, L. P.; Rossat-Mignod, J.; Roudaut, E., Magnetic properties of the Kondo lattice CeGa₂. *J. Magn. Mater.* **1987**, 63-64, 34-36.
- (3) Yashima, H.; Satoh, T.; Mori, H.; Watanabe, D.; Ohtsuka, T., Thermal and magnetic properties and crystal structures of CeGe₂ and CeSi₂. *Solid State Commun.* **1982**, 41, 1-4.
- (4) Morrison, G. W.; Menard, M. C.; Treadwell, L. J.; Haldolaarachchige, N.; Kendrick, K. C.; Young, D. P.; Chan, J. Y., Serendipitous growth of single crystals with silicon incorporation. *Philos. Mag. B* **2012**, *In press*.
- (5) Imai, M.; Sato, A.; Aoyagi, T.; Kimura, T.; Matsushita, Y.; Tsujii, N., Superconductivity in the AlB₂-type ternary rare-earth silicide YbGa_{1.1}Si_{0.9}. *J. Am. Chem. Soc.* **2008**, 130, 2886-2887.
- (6) Tsujii, N.; Imai, M.; Yamaoka, H.; Jarrige, I.; Ohashi, H.; Tochio, T.; Handa, K.; Ide, J.; Atsuta, H.; Ito, Y.; Yoshikawa, H.; Kitazawa, H., Phase stability and superconducting properties of AlB₂-type YbGa_xSi_{2-x} (1.12 ≤ *x* ≤ 1.49). *Chem. Mater.* **2010**, 22, 4690-4699.
- (7) Tillard, M.; Belin, C., Investigation in the binary system Yb–Ga: crystal structure of the Ga-rich compound YbGa_{3.34}. *Inorg. Chem.* **2009**, 48, 9250-9257.

- (8) Grytsiv, A.; Kaczorowski, D.; Leithe-Jasper, A.; Tran, V. H.; Pikul, A.; Rogl, P.; Potel, M.; Noël, H.; Bohn, M.; Velikanova, T., On the system silicon-Ytterbium: constitution, crystal chemistry, and physical properties. *J. Solid State Chem.* **2002**, *163*, 178-185.
- (9) Tsujii, N.; Imai, M.; Yamaoka, H.; Jarrige, I.; Oohashi, H.; Tochio, T.; Handa, K.; Ide, J.; Atsuta, H.; Ito, Y.; Yoshikawa, H.; Kitazawa, H., Phase stability and superconducting properties of AlB₂-type YbGa_xSi_{2-x} ($1.12 \leq x \leq 1.49$). *Chem. Mater.* **2010**, *22*, 4690-4699.
- (10) Altomare, A.; Burla, M. C.; Camalli, M.; Cascarano, G. L.; Giacovazzo, C.; Guagliardi, A.; Moliterni, A. G. G.; Polidori, G.; Spagna, R., SIR97: a new tool for crystal structure determination and refinement. *J. Appl. Crystallogr.* **1999**, *32*, 115-119.
- (11) Sheldrick, G., A short history of SHELX. *Acta Crystallogr.* **2008**, *64*, 112-122.

Appendix C. Letters of Permission

C.1 Elsevier

ELSEVIER LICENSE TERMS AND CONDITIONS

Jun 29, 2014

This is a License Agreement between LaRico J Treadwell ("You") and Elsevier ("Elsevier") provided by Copyright Clearance Center ("CCC"). The license consists of your order details, the terms and conditions provided by Elsevier, and the payment terms and conditions.

All payments must be made in full to CCC. For payment instructions, please see information listed at the bottom of this form.

| | |
|--------------------------------|---|
| Supplier | Elsevier Limited The Boulevard, Langford Lane Kidlington, Oxford, OX5 1GB, UK |
| Registered Company Number | 1982084 |
| Customer name | LaRico J Treadwell |
| Customer address | 219 Rachel Lane BATESVILLE, MS 38606 |
| License number | 3418011402183 |
| License date | Jun 29, 2014 |
| Licensed content publisher | Elsevier |
| Licensed content publication | Journal of Solid State Chemistry |
| Licensed content title | Substitution studies of Mn and Fe in $Ln_6W_4Al_{13}$ ($Ln = \text{Gd, Yb}$) and the structure of $Yb_6Ti_4Al_{13}$ |
| Licensed content author | LaRico J. Treadwell, Pilanda Watkins-Curry, Jacob D. McAlpin, Joseph Prestigiacomo, Shane Stadler, Julia Y. Chan |
| Licensed content date | February 2014 |
| Licensed content volume number | 210 |
| Licensed content issue number | 1 |
| Number of pages | 8 |
| Start Page | 267 |
| End Page | 274 |
| Type of Use | reuse in a thesis/dissertation |
| Portion | full article |

| | |
|--|---|
| Format | both print and electronic |
| Are you the author of this Elsevier article? | Yes |
| Will you be translating? | No |
| Title of your thesis/dissertation | Substitution and Disorder Effects in Ternary Intermetallics |
| Expected completion date | Sep 2014 |
| Estimated size (number of pages) | 120 |
| Elsevier VAT number | GB 494 6272 12 |
| Permissions price | 0.00 USD |
| VAT/Local Sales Tax | 0.00 USD / 0.00 GBP |
| Total | 0.00 USD |
| Terms and Conditions | |

INTRODUCTION

1. The publisher for this copyrighted material is Elsevier. By clicking "accept" in connection with completing this licensing transaction, you agree that the following terms and conditions apply to this transaction (along with the Billing and Payment terms and conditions established by Copyright Clearance Center, Inc. ("CCC"), at the time that you opened your Rightslink account and that are available at any time at <http://myaccount.copyright.com>).

GENERAL TERMS

2. Elsevier hereby grants you permission to reproduce the aforementioned material subject to the terms and conditions indicated.

3. Acknowledgement: If any part of the material to be used (for example, figures) has appeared in our publication with credit or acknowledgement to another source, permission must also be sought from that source. If such permission is not obtained then that material may not be included in your publication/copies. Suitable acknowledgement to the source must be made, either as a footnote or in a reference list at the end of your publication, as follows:

“Reprinted from Publication title, Vol /edition number, Author(s), Title of article / title of chapter, Pages No., Copyright (Year), with permission from Elsevier [OR APPLICABLE SOCIETY COPYRIGHT OWNER].” Also Lancet special credit - “Reprinted from The Lancet, Vol. number, Author(s), Title of article, Pages No., Copyright (Year), with permission from Elsevier.”

4. Reproduction of this material is confined to the purpose and/or media for which permission is hereby given.

5. Altering/Modifying Material: Not Permitted. However figures and illustrations may be altered/adapted minimally to serve your work. Any other abbreviations, additions, deletions and/or any other alterations shall be made only with prior written authorization of Elsevier Ltd. (Please contact Elsevier at permissions@elsevier.com)

6. If the permission fee for the requested use of our material is waived in this instance, please be advised that your future requests for Elsevier materials may attract a fee.

7. Reservation of Rights: Publisher reserves all rights not specifically granted in the combination of (i) the license details provided by you and accepted in the course of this licensing transaction, (ii) these terms and conditions and (iii) CCC's Billing and Payment terms and conditions.

8. License Contingent Upon Payment: While you may exercise the rights licensed immediately upon issuance of the license at the end of the licensing process for the transaction, provided that you have disclosed complete and accurate details of your proposed use, no license is finally effective unless and until full payment is received from you (either by publisher or by CCC) as provided in CCC's Billing and Payment terms and conditions. If full payment is not received on a timely basis, then any license preliminarily granted shall be deemed automatically revoked and shall be void as if never granted. Further, in the event that you breach any of these terms and conditions or any of CCC's Billing and Payment terms and conditions, the license is automatically revoked and shall be void as if never granted. Use of materials as described in a revoked license, as well as any use of the materials beyond the scope of an unrevoked license, may constitute copyright infringement and publisher reserves the right to take any and all action to protect its copyright in the materials.

9. Warranties: Publisher makes no representations or warranties with respect to the licensed material.

10. Indemnity: You hereby indemnify and agree to hold harmless publisher and CCC, and their respective officers, directors, employees and agents, from and against any and all claims arising out of your use of the licensed material other than as specifically authorized pursuant to this license.

11. No Transfer of License: This license is personal to you and may not be sublicensed, assigned, or transferred by you to any other person without publisher's written permission.

12. No Amendment Except in Writing: This license may not be amended except in a writing signed by both parties (or, in the case of publisher, by CCC on publisher's behalf).

13. Objection to Contrary Terms: Publisher hereby objects to any terms contained in any purchase order, acknowledgment, check endorsement or other writing prepared by you, which terms are inconsistent with these terms and conditions or CCC's Billing and Payment terms and conditions. These terms and conditions, together with CCC's Billing and Payment terms and conditions (which are incorporated herein), comprise the entire

agreement between you and publisher (and CCC) concerning this licensing transaction. In the event of any conflict between your obligations established by these terms and conditions and those established by CCC's Billing and Payment terms and conditions, these terms and conditions shall control.

14. **Revocation:** Elsevier or Copyright Clearance Center may deny the permissions described in this License at their sole discretion, for any reason or no reason, with a full refund payable to you. Notice of such denial will be made using the contact information provided by you. Failure to receive such notice will not alter or invalidate the denial. In no event will Elsevier or Copyright Clearance Center be responsible or liable for any costs, expenses or damage incurred by you as a result of a denial of your permission request, other than a refund of the amount(s) paid by you to Elsevier and/or Copyright Clearance Center for denied permissions.

LIMITED LICENSE

The following terms and conditions apply only to specific license types:

15. **Translation:** This permission is granted for non-exclusive world **English** rights only unless your license was granted for translation rights. If you licensed translation rights you may only translate this content into the languages you requested. A professional translator must perform all translations and reproduce the content word for word preserving the integrity of the article. If this license is to re-use 1 or 2 figures then permission is granted for non-exclusive world rights in all languages.

16. **Posting licensed content on any Website:** The following terms and conditions apply as follows: Licensing material from an Elsevier journal: All content posted to the web site must maintain the copyright information line on the bottom of each image; A hyper-text must be included to the Homepage of the journal from which you are licensing at <http://www.sciencedirect.com/science/journal/xxxxx> or the Elsevier homepage for books at <http://www.elsevier.com>; Central Storage: This license does not include permission for a scanned version of the material to be stored in a central repository such as that provided by Heron/XanEdu.

Licensing material from an Elsevier book: A hyper-text link must be included to the Elsevier homepage at <http://www.elsevier.com>. All content posted to the web site must maintain the copyright information line on the bottom of each image.

Posting licensed content on Electronic reserve: In addition to the above the following clauses are applicable: The web site must be password-protected and made available only to bona fide students registered on a relevant course. This permission is granted for 1 year only. You may obtain a new license for future website posting.

For journal authors: the following clauses are applicable in addition to the above:
Permission granted is limited to the author accepted manuscript version* of your paper.

***Accepted Author Manuscript (AAM) Definition:** An accepted author manuscript (AAM) is the author's version of the manuscript of an article that has been accepted for publication and which may include any author-incorporated changes suggested through the processes of submission processing, peer review, and editor-author communications. AAMs do not include other publisher value-added contributions such as copy-editing, formatting, technical enhancements and (if relevant) pagination.

You are not allowed to download and post the published journal article (whether PDF or HTML, proof or final version), nor may you scan the printed edition to create an electronic version. A hyper-text must be included to the Homepage of the journal from which you are licensing at <http://www.sciencedirect.com/science/journal/xxxxx>. As part of our normal production process, you will receive an e-mail notice when your article appears on Elsevier's online service ScienceDirect (www.sciencedirect.com). That e-mail will include the article's Digital Object Identifier (DOI). This number provides the electronic link to the published article and should be included in the posting of your personal version. We ask that you wait until you receive this e-mail and have the DOI to do any posting.

Posting to a repository: Authors may post their AAM immediately to their employer's institutional repository for internal use only and may make their manuscript publically available after the journal-specific embargo period has ended.

Please also refer to [Elsevier's Article Posting Policy](#) for further information.

18. **For book authors** the following clauses are applicable in addition to the above: Authors are permitted to place a brief summary of their work online only.. You are not allowed to download and post the published electronic version of your chapter, nor may you scan the printed edition to create an electronic version. **Posting to a repository:** Authors are permitted to post a summary of their chapter only in their institution's repository.

20. **Thesis/Dissertation:** If your license is for use in a thesis/dissertation your thesis may be submitted to your institution in either print or electronic form. Should your thesis be published commercially, please reapply for permission. These requirements include permission for the Library and Archives of Canada to supply single copies, on demand, of the complete thesis and include permission for UMI to supply single copies, on demand, of the complete thesis. Should your thesis be published commercially, please reapply for permission.

Elsevier Open Access Terms and Conditions

Elsevier publishes Open Access articles in both its Open Access journals and via its Open Access articles option in subscription journals.

Authors publishing in an Open Access journal or who choose to make their article Open Access in an Elsevier subscription journal select one of the following Creative Commons user licenses, which define how a reader may reuse their work: Creative Commons Attribution License (CC BY), Creative Commons Attribution – Non Commercial - ShareAlike (CC BY NC SA) and Creative Commons Attribution – Non Commercial – No Derivatives (CC BY NC ND)

Terms & Conditions applicable to all Elsevier Open Access articles:

Any reuse of the article must not represent the author as endorsing the adaptation of the article nor should the article be modified in such a way as to damage the author's honour or reputation.

The author(s) must be appropriately credited.

If any part of the material to be used (for example, figures) has appeared in our publication with credit or acknowledgement to another source it is the responsibility of the user to ensure their reuse complies with the terms and conditions determined by the rights holder.

Additional Terms & Conditions applicable to each Creative Commons user license:

CC BY: You may distribute and copy the article, create extracts, abstracts, and other revised versions, adaptations or derivative works of or from an article (such as a translation), to include in a collective work (such as an anthology), to text or data mine the article, including for commercial purposes without permission from Elsevier

CC BY NC SA: For non-commercial purposes you may distribute and copy the article, create extracts, abstracts and other revised versions, adaptations or derivative works of or from an article (such as a translation), to include in a collective work (such as an anthology), to text and data mine the article and license new adaptations or creations under identical terms without permission from Elsevier

CC BY NC ND: For non-commercial purposes you may distribute and copy the article and include it in a collective work (such as an anthology), provided you do not alter or modify the article, without permission from Elsevier

Any commercial reuse of Open Access articles published with a CC BY NC SA or CC BY NC ND license requires permission from Elsevier and will be subject to a fee.

Commercial reuse includes:

- Promotional purposes (advertising or marketing)

- Commercial exploitation (e.g. a product for sale or loan)
- Systematic distribution (for a fee or free of charge)

Please refer to [Elsevier's Open Access Policy](#) for further information.

21. Other Conditions:

v1.7

If you would like to pay for this license now, please remit this license along with your payment made payable to "COPYRIGHT CLEARANCE CENTER" otherwise you will be invoiced within 48 hours of the license date. Payment should be in the form of a check or money order referencing your account number and this invoice number 501339221.

Once you receive your invoice for this order, you may pay your invoice by credit card. Please follow instructions provided at that time.

**Make Payment To:
Copyright Clearance Center
Dept 001
P.O. Box 843006
Boston, MA 02284-3006**

For suggestions or comments regarding this order, contact RightsLink Customer Support: customercare@copyright.com or +1-877-622-5543 (toll free in the US) or +1-978-646-2777.

Gratis licenses (referencing \$0 in the Total field) are free. Please retain this printable license for your reference. No payment is required.

C.2 American Chemical Society



RightsLink®

Home

Account
Info

Help



ACS Publications
MOST TRUSTED. MOST CITED. MOST READ.

Title: Investigation of Fe incorporation in $\text{LnCr}_2\text{Al}_{20}$ ($\text{Ln} = \text{La}, \text{Gd}, \text{Yb}$) with ^{57}Fe Mössbauer and Single Crystal X-ray Diffraction

Author: LaRico J. Treadwell, Jacob D. McAlpin, Devin C. Schmitt, Michael J. Kangas, Moulay T. Sougrati, Neel Haldolaarachchige, David P. Young, Jean-Claude Jumas, and Julia Y. Chan

Publication: Inorganic Chemistry

Publisher: American Chemical Society

Date: May 1, 2013

Copyright © 2013, American Chemical Society

Logged in as:

LaRico Treadwell

Account #:
3000799896

LOGOUT

Quick Price Estimate

Permission for this particular request is granted for print and electronic formats, and translations, at no charge. Figures and tables may be modified. Appropriate credit should be given. Please print this page for your records and provide a copy to your publisher. Requests for up to 4 figures require only this record. Five or more figures will generate a printout of additional terms and conditions. Appropriate credit should read: "Reprinted with permission from {COMPLETE REFERENCE CITATION}. Copyright {YEAR} American Chemical Society." Insert appropriate information in place of the capitalized words.

I would like to...



Requestor Type



Portion



Format



Will you be

translating?



This service provides permission for reuse only. If you do not have a copy of the article you are using, you may copy and paste the content and reuse according to the terms of your agreement. Please be advised that obtaining the content you license is a separate transaction not involving Rightslink.

Select your
currency

Quick Price

Click
Quick
Price

QUICK PRICE

CONTINUE

To request permission for a type of use not listed, please contact [the publisher](#) directly.

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement.](#)
Comments? We would like to hear from you. E-mail us at customercare@copyright.com



RightsLink®

Home

Account
Info

Help



Title: Investigation of Fe
incorporation in LnCr₂Al₂₀
(Ln = La, Gd, Yb) with ⁵⁷Fe
Mössbauer and Single Crystal
X-ray Diffraction

Author: LaRico J. Treadwell, Jacob D.
McAlpin, Devin C. Schmitt,
Michael J. Kangas, Moulay T.
Sougrati, Neel
Haldolaarachchige, David P.
Young, Jean-Claude Jumas,
and Julia Y. Chan

Publication: Inorganic Chemistry

Publisher: American Chemical Society

Date: May 1, 2013

Copyright © 2013, American Chemical
Society

Logged in as:

LaRico Treadwell

Account #:
3000799896

LOGOUT

PERMISSION/LICENSE IS GRANTED FOR YOUR ORDER AT NO CHARGE

This type of permission/license, instead of the standard Terms & Conditions, is sent to you because no fee is being charged for your order. Please note the following:

- Permission is granted for your request in both print and electronic formats, and translations.
- If figures and/or tables were requested, they may be adapted or used in part.

- Please print this page for your records and send a copy of it to your publisher/graduate school.
- Appropriate credit for the requested material should be given as follows: "Reprinted (adapted) with permission from (COMPLETE REFERENCE CITATION). Copyright (YEAR) American Chemical Society." Insert appropriate information in place of the capitalized words.
- One-time permission is granted only for the use specified in your request. No additional uses are granted (such as derivative works or other editions). For any other uses, please submit a new request.

BACK

CLOSE WINDOW

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement](#).
Comments? We would like to hear from you. E-mail us at customercare@copyright.com

C.2 Taylor & Francis



RightsLink®

Home

Account
Info

Help

 Live Chat



Taylor & Francis
Taylor & Francis Group

Title: Serendipitous growth of single
crystals with silicon
incorporation
Author: Gregory W. Morrison, Melissa
C. Menard, LaRico J.
Treadwell, et al
Publication: Philosophical Magazine
Publisher: Taylor & Francis
Date: Jul 1, 2012
Copyright © 2012 Taylor & Francis

Logged in as:

LaRico Treadwell

LOGOUT

Thesis/Dissertation Reuse Request

Taylor & Francis is pleased to offer reuses of its content for a thesis or dissertation free of charge contingent on resubmission of permission request if work is published.

BACK

CLOSE WINDOW

Copyright © 2014 [Copyright Clearance Center, Inc.](#) All Rights Reserved. [Privacy statement.](#)
Comments? We would like to hear from you. E-mail us at customercare@copyright.com

Appendix D. CIF of Sm_{1.33}Pd₃Ga₈

data_shelx

_audit_creation_method SHELXL-97

_chemical_name_systematic

;

?

;

_chemical_name_common ?

_chemical_melting_point ?

_chemical_formula_moiety ?

_chemical_formula_sum

'Ga₈ Pd₃ Sm'

_chemical_formula_weight 1027.31

loop_

_atom_type_symbol

_atom_type_description

_atom_type_scatter_dispersion_real

_atom_type_scatter_dispersion_imag

_atom_type_scatter_source

'Sm' 'Sm' -0.1638 3.4418

'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

'Pd' 'Pd' -0.9988 1.0072

'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

'Ga' 'Ga' 0.2307 1.6083

'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

_symmetry_cell_setting ?

_symmetry_space_group_name_H-M ?

loop_

_symmetry_equiv_pos_as_xyz

'x, y, z'

'-y, x-y, z'

'-x+y, -x, z'

'x-y, -y, -z'

'-x, -x+y, -z'

'y, x, -z'

'x+2/3, y+1/3, z+1/3'

'-y+2/3, x-y+1/3, z+1/3'

'-x+y+2/3, -x+1/3, z+1/3'

'x-y+2/3, -y+1/3, -z+1/3'

'-x+2/3, -x+y+1/3, -z+1/3'

'y+2/3, x+1/3, -z+1/3'

'x+1/3, y+2/3, z+2/3'

'-y+1/3, x-y+2/3, z+2/3'

'-x+y+1/3, -x+2/3, z+2/3'

'x-y+1/3, -y+2/3, -z+2/3'

'-x+1/3, -x+y+2/3, -z+2/3'

'y+1/3, x+2/3, -z+2/3'

'-x, -y, -z'

'y, -x+y, -z'

'x-y, x, -z'

'-x+y, y, z'

'x, x-y, z'

'-y, -x, z'

'-x+2/3, -y+1/3, -z+1/3'

'y+2/3, -x+y+1/3, -z+1/3'

'x-y+2/3, x+1/3, -z+1/3'

'-x+y+2/3, y+1/3, z+1/3'

'x+2/3, x-y+1/3, z+1/3'

'-y+2/3, -x+1/3, z+1/3'

'-x+1/3, -y+2/3, -z+2/3'

'y+1/3, -x+y+2/3, -z+2/3'

'x-y+1/3, x+2/3, -z+2/3'

'-x+y+1/3, y+2/3, z+2/3'

'x+1/3, x-y+2/3, z+2/3'

'-y+1/3, -x+2/3, z+2/3'

_cell_length_a 4.353(5)

_cell_length_b 4.353(5)

_cell_length_c 38.98(4)

_cell_angle_alpha 90.00

_cell_angle_beta 90.00

_cell_angle_gamma 120.00

_cell_volume 639.7(12)

_cell_formula_units_Z 3

_cell_measurement_temperature 293(2)

_cell_measurement_reflns_used ?

_cell_measurement_theta_min ?

_cell_measurement_theta_max ?

_exptl_crystal_description ?

_exptl_crystal_colour ?

_exptl_crystal_size_max ?

_exptl_crystal_size_mid ?

_exptl_crystal_size_min ?

_exptl_crystal_density_meas ?

_exptl_crystal_density_diffn 8.001

_exptl_crystal_density_method 'not measured'

_exptl_crystal_F_000 1344

_exptl_absorpt_coefficient_mu 37.651

_exptl_absorpt_correction_type ?

_exptl_absorpt_correction_T_min ?

_exptl_absorpt_correction_T_max ?

_exptl_absorpt_process_details ?

_exptl_special_details

;

?

;

_diffn_ambient_temperature 293(2)

_diffn_radiation_wavelength 0.71073

_diffn_radiation_type MoK α

_diffn_radiation_source 'fine-focus sealed tube'

_diffn_radiation_monochromator graphite

_diffn_measurement_device_type ?

_diffn_measurement_method ?

_diffn_detector_area_resol_mean ?

_diffn_standards_number ?

_diffn_standards_interval_count ?

_diffn_standards_interval_time ?

_diffn_standards_decay_% ?

_diffn_reflns_number 917

_diffn_reflns_av_R_equivalents 0.0245

_diffn_reflns_av_sigmaI/netI 0.0228

```

_diffn_reflms_limit_h_min      -6
_diffn_reflms_limit_h_max      6
_diffn_reflms_limit_k_min      -4
_diffn_reflms_limit_k_max      4
_diffn_reflms_limit_l_min      -55
_diffn_reflms_limit_l_max      52
_diffn_reflms_theta_min        4.71
_diffn_reflms_theta_max        30.98
_reflms_number_total           313
_reflms_number_gt              296
_reflms_threshold_expression    >2sigma(I)

_computing_data_collection      ?
_computing_cell_refinement      ?
_computing_data_reduction       ?
_computing_structure_solution   'SHELXS-97 (Sheldrick,
1990)'
_computing_structure_refinement 'SHELXL-97
(Sheldrick, 1997)'
_computing_molecular_graphics   ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F2 against ALL reflections. The
weighted R-factor wR and
goodness of fit S are based on F2, conventional R-
factors R are based
on F, with F set to zero for negative F2. The threshold
expression of
F2 > 2sigma(F2) is used only for calculating R-
factors(gt) etc. and is
not relevant to the choice of reflections for refinement. R-
factors based
on F2 are statistically about twice as large as those based
on F, and R-
factors based on ALL data will be even larger.
;

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type          full
_refine_ls_weighting_scheme      calc
_refine_ls_weighting_details
'calc w=1/[s2(Fo2)+(0.0155P)2+4.5306P] where
P=(Fo2+2Fc2)/3'
_atom_sites_solution_primary     direct
_atom_sites_solution_secondary   difmap
_atom_sites_solution_hydrogens   geom
_refine_ls_hydrogen_treatment    mixed
_refine_ls_extinction_method     SHELXL
_refine_ls_extinction_coef        0.00108(10)
_refine_ls_extinction_expression
'Fc*=kFc[1+0.001xFc2/sin(2q)]-1/4'
_refine_ls_number_reflms        313
_refine_ls_number_parameters     27
_refine_ls_number_restraints     2
_refine_ls_R_factor_all          0.0194
_refine_ls_R_factor_gt           0.0178
_refine_ls_wR_factor_ref         0.0405
_refine_ls_wR_factor_gt          0.0397
_refine_ls_goodness_of_fit_ref   1.196
_refine_ls_restrained_S_all      1.203

_refine_ls_shift/su_max          0.000
_refine_ls_shift/su_mean         0.000

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Sm1 Sm 0.0000 0.0000 0.269775(13) 0.00706(19) Uani
0.652(2) 6 d SP . .
Pd1 Pd 0.0000 0.0000 0.0000 0.00803(17) Uani 1 12 d S . .
Pd2 Pd 0.0000 0.0000 0.120867(13) 0.00928(16) Uani 1 6
d S . .
Ga3 Ga 0.0000 0.0000 0.35195(2) 0.00897(19) Uani 1 6 d
S . .
Ga4 Ga 0.0000 0.0000 0.44354(2) 0.0117(2) Uani 1 6 d S .
.
Ga2 Ga 0.0000 0.0000 0.18643(2) 0.0106(2) Uani 1 6 d S .
.
Ga1 Ga 0.53714(19) 0.46286(19) 0.39464(3) 0.0101(4)
Uani 0.333(2) 2 d SP . .

loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12
Sm1 0.0073(2) 0.0073(2) 0.0066(3) 0.000 0.000
0.00365(11)
Pd1 0.0080(2) 0.0080(2) 0.0081(3) 0.000 0.000
0.00400(11)
Pd2 0.00994(19) 0.00994(19) 0.0080(3) 0.000 0.000
0.00497(10)
Ga3 0.0078(2) 0.0078(2) 0.0114(4) 0.000 0.000
0.00388(12)
Ga4 0.0097(2) 0.0097(2) 0.0157(4) 0.000 0.000
0.00487(12)
Ga2 0.0119(3) 0.0119(3) 0.0080(4) 0.000 0.000
0.00597(13)
Ga1 0.0114(6) 0.0114(6) 0.0072(6) 0.0003(2) -0.0003(2)
0.0054(6)

_geom_special_details
;
All esds (except the esd in the dihedral angle between two
l.s. planes)
are estimated using the full covariance matrix. The cell
esds are taken
into account individually in the estimation of esds in
distances, angles

```

and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

;

loop_

_geom_bond_atom_site_label_1

_geom_bond_atom_site_label_2

_geom_bond_distance

_geom_bond_site_symmetry_2

_geom_bond_publ_flag

Sm1 Ga1 1.539(2) 33_545 ?

Sm1 Ga1 1.539(2) 32_445 ?

Sm1 Ga1 1.539(2) 31 ?

Sm1 Ga3 3.064(3) 31 ?

Sm1 Ga3 3.064(3) 31_445 ?

Sm1 Ga3 3.064(3) 31_545 ?

Sm1 Ga4 3.102(3) 31_445 ?

Sm1 Ga4 3.102(3) 31 ?

Sm1 Ga4 3.102(3) 31_545 ?

Sm1 Ga1 3.120(4) 33_435 ?

Sm1 Ga1 3.120(4) 32 ?

Sm1 Ga1 3.120(4) 31_655 ?

Pd1 Ga1 2.581(3) 25 ?

Pd1 Ga1 2.581(3) 13_444 ?

Pd1 Ga1 2.581(3) 27_445 ?

Pd1 Ga1 2.581(3) 15_554 ?

Pd1 Ga1 2.581(3) 26_455 ?

Pd1 Ga1 2.581(3) 14_544 ?

Pd1 Ga3 2.616(3) 25_445 ?

Pd1 Ga3 2.616(3) 13_554 ?

Pd1 Ga3 2.616(3) 25 ?

Pd1 Ga3 2.616(3) 13_444 ?

Pd1 Ga3 2.616(3) 13_544 ?

Pd1 Ga3 2.616(3) 25_455 ?

Pd2 Ga1 2.519(3) 13_444 ?

Pd2 Ga1 2.519(3) 14_544 ?

Pd2 Ga1 2.519(3) 15_554 ?

Pd2 Ga4 2.547(3) 13_444 ?

Pd2 Ga4 2.547(3) 13_554 ?

Pd2 Ga4 2.547(3) 13_544 ?

Pd2 Ga2 2.555(3) . ?

Pd2 Ga2 2.711(3) 25 ?

Pd2 Ga2 2.711(3) 25_445 ?

Pd2 Ga2 2.711(3) 25_455 ?

Pd2 Sm1 3.362(3) 25_445 ?

Pd2 Sm1 3.362(3) 25 ?

Ga3 Pd1 2.616(3) 7_445 ?

Ga3 Pd1 2.616(3) 7 ?

Ga3 Pd1 2.616(3) 7_455 ?

Ga3 Ga1 2.754(2) . ?

Ga3 Ga1 2.754(2) 3_565 ?

Ga3 Ga1 2.754(2) 2 ?

Ga3 Ga1 2.754(2) 1_445 ?

Ga3 Ga1 2.754(2) 2_655 ?

Ga3 Ga1 2.754(2) 3 ?

Ga3 Ga3 2.902(3) 31_445 ?

Ga3 Ga3 2.902(3) 31 ?

Ga3 Ga3 2.902(3) 31_545 ?

Ga4 Pd2 2.547(3) 7 ?

Ga4 Pd2 2.547(3) 7_445 ?

Ga4 Pd2 2.547(3) 7_455 ?

Ga4 Ga2 2.892(3) 31 ?

Ga4 Ga2 2.892(3) 31_445 ?

Ga4 Ga2 2.892(3) 31_545 ?

Ga4 Ga1 2.907(2) 2 ?

Ga4 Ga1 2.907(2) 3_565 ?

Ga4 Ga1 2.907(2) 1_445 ?

Ga4 Ga1 2.907(2) 3 ?

Ga4 Ga1 2.907(2) 2_655 ?

Ga4 Ga1 2.907(2) . ?

Ga2 Pd2 2.711(3) 25 ?

Ga2 Pd2 2.711(3) 25_445 ?

Ga2 Pd2 2.711(3) 25_455 ?

Ga2 Ga4 2.892(3) 31 ?

Ga2 Ga4 2.892(3) 31_445 ?

Ga2 Ga4 2.892(3) 31_545 ?

Ga2 Ga2 2.948(3) 25_445 ?

Ga2 Ga2 2.948(3) 25 ?

Ga2 Ga2 2.948(3) 25_455 ?

Ga1 Sm1 1.539(2) 31 ?

Ga1 Ga1 1.692(3) 3_665 ?

Ga1 Ga1 1.692(3) 2_655 ?

Ga1 Pd2 2.519(3) 7 ?

Ga1 Pd1 2.581(3) 7 ?

Ga1 Ga1 2.661(4) 3_565 ?

Ga1 Ga1 2.661(4) 2_665 ?

Ga1 Ga3 2.754(2) 1_665 ?

Ga1 Ga4 2.907(2) 1_665 ?

Ga1 Sm1 3.120(4) 31_545 ?

loop_

_geom_angle_atom_site_label_1

_geom_angle_atom_site_label_2

_geom_angle_atom_site_label_3

_geom_angle

_geom_angle_site_symmetry_1

_geom_angle_site_symmetry_3

_geom_angle_publ_flag

Ga1 Sm1 Ga1 119.678(10) 33_545 32_445 ?

Ga1 Sm1 Ga1 119.678(10) 33_545 31 ?

Ga1 Sm1 Ga1 119.678(10) 32_445 31 ?

Ga1 Sm1 Ga3 63.76(3) 33_545 31 ?

Ga1 Sm1 Ga3 141.85(7) 32_445 31 ?

Ga1 Sm1 Ga3 63.76(3) 31 31 ?

Ga1 Sm1 Ga3 141.85(7) 33_545 31_445 ?

Ga1 Sm1 Ga3 63.76(3) 32_445 31_445 ?

Ga1 Sm1 Ga3 63.76(3) 31 31_445 ?

Ga3 Sm1 Ga3 90.54(6) 31 31_445 ?

Ga1 Sm1 Ga3 63.76(3) 33_545 31_545 ?

Ga1 Sm1 Ga3 63.76(3) 32_445 31_545 ?

Ga1 Sm1 Ga3 141.85(7) 31 31_545 ?

Ga3 Sm1 Ga3 90.54(6) 31 31_545 ?

Ga3 Sm1 Ga3 90.54(6) 31_445 31_545 ?

Ga1 Sm1 Ga4 147.38(7) 33_545 31_445 ?

Ga1 Sm1 Ga4 68.22(4) 32_445 31_445 ?

Ga1 Sm1 Ga4 68.22(4) 31 31_445 ?

Ga3 Sm1 Ga4 131.88(3) 31 31_445 ?

Ga3 Sm1 Ga4 70.77(9) 31_445 31_445 ?

Ga3 Sm1 Ga4 131.88(3) 31_545 31_445 ?

Ga1 Sm1 Ga4 68.22(4) 33_545 31 ?

Ga1 Sm1 Ga4 147.38(7) 32_445 31 ?
 Ga1 Sm1 Ga4 68.22(4) 31 31 ?
 Ga3 Sm1 Ga4 70.77(9) 31 31 ?
 Ga3 Sm1 Ga4 131.88(3) 31_445 31 ?
 Ga3 Sm1 Ga4 131.88(3) 31_545 31 ?
 Ga4 Sm1 Ga4 89.11(6) 31_445 31 ?
 Ga1 Sm1 Ga4 68.22(4) 33_545 31_545 ?
 Ga1 Sm1 Ga4 68.22(4) 32_445 31_545 ?
 Ga1 Sm1 Ga4 147.38(7) 31 31_545 ?
 Ga3 Sm1 Ga4 131.88(3) 31 31_545 ?
 Ga3 Sm1 Ga4 131.88(3) 31_445 31_545 ?
 Ga3 Sm1 Ga4 70.77(8) 31_545 31_545 ?
 Ga4 Sm1 Ga4 89.11(6) 31_445 31_545 ?
 Ga4 Sm1 Ga4 89.11(6) 31 31_545 ?
 Ga1 Sm1 Ga1 135.49(2) 33_545 33_435 ?
 Ga1 Sm1 Ga1 15.809(18) 32_445 33_435 ?
 Ga1 Sm1 Ga1 104.139(19) 31 33_435 ?
 Ga3 Sm1 Ga1 140.64(5) 31 33_435 ?
 Ga3 Sm1 Ga1 52.89(3) 31_445 33_435 ?
 Ga3 Sm1 Ga1 77.40(2) 31_545 33_435 ?
 Ga4 Sm1 Ga1 55.70(3) 31_445 33_435 ?
 Ga4 Sm1 Ga1 142.75(5) 31 33_435 ?
 Ga4 Sm1 Ga1 79.45(2) 31_545 33_435 ?
 Ga1 Sm1 Ga1 15.809(18) 33_545 32 ?
 Ga1 Sm1 Ga1 135.49(2) 32_445 32 ?
 Ga1 Sm1 Ga1 104.139(19) 31 32 ?
 Ga3 Sm1 Ga1 52.89(3) 31 32 ?
 Ga3 Sm1 Ga1 140.64(5) 31_445 32 ?
 Ga3 Sm1 Ga1 77.40(2) 31_545 32 ?
 Ga4 Sm1 Ga1 142.75(5) 31_445 32 ?
 Ga4 Sm1 Ga1 55.70(3) 31 32 ?
 Ga4 Sm1 Ga1 79.45(2) 31_545 32 ?
 Ga1 Sm1 Ga1 151.30(4) 33_435 32 ?
 Ga1 Sm1 Ga1 15.809(19) 33_545 31_655 ?
 Ga1 Sm1 Ga1 104.139(18) 32_445 31_655 ?
 Ga1 Sm1 Ga1 135.49(2) 31 31_655 ?
 Ga3 Sm1 Ga1 77.40(2) 31 31_655 ?
 Ga3 Sm1 Ga1 140.64(5) 31_445 31_655 ?
 Ga3 Sm1 Ga1 52.89(3) 31_545 31_655 ?
 Ga4 Sm1 Ga1 142.75(5) 31_445 31_655 ?
 Ga4 Sm1 Ga1 79.45(2) 31 31_655 ?
 Ga4 Sm1 Ga1 55.70(3) 31_545 31_655 ?
 Ga1 Sm1 Ga1 119.921(2) 33_435 31_655 ?
 Ga1 Sm1 Ga1 31.46(4) 32 31_655 ?
 Ga1 Pd1 Ga1 180.00(2) 25 13_444 ?
 Ga1 Pd1 Ga1 38.25(7) 25 27_445 ?
 Ga1 Pd1 Ga1 141.75(7) 13_444 27_445 ?
 Ga1 Pd1 Ga1 141.75(7) 25 15_554 ?
 Ga1 Pd1 Ga1 38.25(7) 13_444 15_554 ?
 Ga1 Pd1 Ga1 180.00(11) 27_445 15_554 ?
 Ga1 Pd1 Ga1 38.25(7) 25 26_455 ?
 Ga1 Pd1 Ga1 141.75(7) 13_444 26_455 ?
 Ga1 Pd1 Ga1 38.25(7) 27_445 26_455 ?
 Ga1 Pd1 Ga1 141.75(7) 15_554 26_455 ?
 Ga1 Pd1 Ga1 141.75(7) 25 14_544 ?
 Ga1 Pd1 Ga1 38.25(7) 13_444 14_544 ?
 Ga1 Pd1 Ga1 141.75(7) 27_445 14_544 ?
 Ga1 Pd1 Ga1 38.25(7) 15_554 14_544 ?
 Ga1 Pd1 Ga1 180.00(11) 26_455 14_544 ?
 Ga1 Pd1 Ga3 64.00(2) 25 25_445 ?
 Ga1 Pd1 Ga3 116.00(2) 13_444 25_445 ?
 Ga1 Pd1 Ga3 64.00(2) 27_445 25_445 ?

Ga1 Pd1 Ga3 116.00(2) 15_554 25_445 ?
 Ga1 Pd1 Ga3 96.13(6) 26_455 25_445 ?
 Ga1 Pd1 Ga3 83.87(6) 14_544 25_445 ?
 Ga1 Pd1 Ga3 116.00(2) 25 13_554 ?
 Ga1 Pd1 Ga3 64.00(2) 13_444 13_554 ?
 Ga1 Pd1 Ga3 116.00(2) 27_445 13_554 ?
 Ga1 Pd1 Ga3 64.00(2) 15_554 13_554 ?
 Ga1 Pd1 Ga3 83.87(6) 26_455 13_554 ?
 Ga1 Pd1 Ga3 96.13(6) 14_544 13_554 ?
 Ga3 Pd1 Ga3 180.00(4) 25_445 13_554 ?
 Ga1 Pd1 Ga3 64.00(2) 25 25 ?
 Ga1 Pd1 Ga3 116.00(2) 13_444 25 ?
 Ga1 Pd1 Ga3 96.13(6) 27_445 25 ?
 Ga1 Pd1 Ga3 83.87(6) 15_554 25 ?
 Ga1 Pd1 Ga3 64.00(2) 26_455 25 ?
 Ga1 Pd1 Ga3 116.00(2) 14_544 25 ?
 Ga3 Pd1 Ga3 112.62(3) 25_445 25 ?
 Ga3 Pd1 Ga3 67.38(3) 13_554 25 ?
 Ga1 Pd1 Ga3 116.00(2) 25 13_444 ?
 Ga1 Pd1 Ga3 64.00(2) 13_444 13_444 ?
 Ga1 Pd1 Ga3 83.87(6) 27_445 13_444 ?
 Ga1 Pd1 Ga3 96.13(6) 15_554 13_444 ?
 Ga1 Pd1 Ga3 116.00(2) 26_455 13_444 ?
 Ga1 Pd1 Ga3 64.00(2) 14_544 13_444 ?
 Ga3 Pd1 Ga3 67.38(3) 25_445 13_444 ?
 Ga3 Pd1 Ga3 112.62(3) 13_554 13_444 ?
 Ga3 Pd1 Ga3 180.00(4) 25 13_444 ?
 Ga1 Pd1 Ga3 83.87(6) 25 13_544 ?
 Ga1 Pd1 Ga3 96.13(6) 13_444 13_544 ?
 Ga1 Pd1 Ga3 116.00(2) 27_445 13_544 ?
 Ga1 Pd1 Ga3 64.00(2) 15_554 13_544 ?
 Ga1 Pd1 Ga3 116.00(2) 26_455 13_544 ?
 Ga1 Pd1 Ga3 64.00(2) 14_544 13_544 ?
 Ga3 Pd1 Ga3 67.38(3) 25_445 13_544 ?
 Ga3 Pd1 Ga3 112.62(3) 13_554 13_544 ?
 Ga3 Pd1 Ga3 67.38(3) 25 13_544 ?
 Ga3 Pd1 Ga3 112.62(3) 13_444 13_544 ?
 Ga1 Pd1 Ga3 96.13(6) 25 25_455 ?
 Ga1 Pd1 Ga3 83.87(6) 13_444 25_455 ?
 Ga1 Pd1 Ga3 64.00(2) 27_445 25_455 ?
 Ga1 Pd1 Ga3 116.00(2) 15_554 25_455 ?
 Ga1 Pd1 Ga3 64.00(2) 26_455 25_455 ?
 Ga1 Pd1 Ga3 116.00(2) 14_544 25_455 ?
 Ga3 Pd1 Ga3 112.62(3) 25_445 25_455 ?
 Ga3 Pd1 Ga3 67.38(3) 13_554 25_455 ?
 Ga3 Pd1 Ga3 112.62(3) 25 25_455 ?
 Ga3 Pd1 Ga3 67.38(3) 13_444 25_455 ?
 Ga3 Pd1 Ga3 180.00(4) 13_544 25_455 ?
 Ga1 Pd2 Ga1 39.24(8) 13_444 14_544 ?
 Ga1 Pd2 Ga1 39.24(8) 13_444 15_554 ?
 Ga1 Pd2 Ga1 39.24(8) 14_544 15_554 ?
 Ga1 Pd2 Ga4 70.02(2) 13_444 13_444 ?
 Ga1 Pd2 Ga4 70.02(2) 14_544 13_444 ?
 Ga1 Pd2 Ga4 103.42(6) 15_554 13_444 ?
 Ga1 Pd2 Ga4 70.02(2) 13_444 13_554 ?
 Ga1 Pd2 Ga4 103.42(6) 14_544 13_554 ?
 Ga1 Pd2 Ga4 70.02(2) 15_554 13_554 ?
 Ga4 Pd2 Ga4 117.393(14) 13_444 13_554 ?
 Ga1 Pd2 Ga4 103.42(6) 13_444 13_544 ?
 Ga1 Pd2 Ga4 70.02(2) 14_544 13_544 ?
 Ga1 Pd2 Ga4 70.02(2) 15_554 13_544 ?
 Ga4 Pd2 Ga4 117.392(14) 13_444 13_544 ?

Ga4 Pd2 Ga4 117.392(14) 13_554 13_544 ?
 Ga1 Pd2 Ga2 157.19(5) 13_444 . ?
 Ga1 Pd2 Ga2 157.19(5) 14_544 . ?
 Ga1 Pd2 Ga2 157.19(5) 15_554 . ?
 Ga4 Pd2 Ga2 99.39(3) 13_444 . ?
 Ga4 Pd2 Ga2 99.39(3) 13_554 . ?
 Ga4 Pd2 Ga2 99.39(3) 13_544 . ?
 Ga1 Pd2 Ga2 121.67(3) 13_444 25 ?
 Ga1 Pd2 Ga2 121.67(3) 14_544 25 ?
 Ga1 Pd2 Ga2 89.18(7) 15_554 25 ?
 Ga4 Pd2 Ga2 167.39(4) 13_444 25 ?
 Ga4 Pd2 Ga2 66.65(2) 13_554 25 ?
 Ga4 Pd2 Ga2 66.65(2) 13_544 25 ?
 Ga2 Pd2 Ga2 68.00(4) . 25 ?
 Ga1 Pd2 Ga2 121.67(3) 13_444 25_445 ?
 Ga1 Pd2 Ga2 89.18(7) 14_544 25_445 ?
 Ga1 Pd2 Ga2 121.67(3) 15_554 25_445 ?
 Ga4 Pd2 Ga2 66.65(2) 13_444 25_445 ?
 Ga4 Pd2 Ga2 167.39(4) 13_554 25_445 ?
 Ga4 Pd2 Ga2 66.65(2) 13_544 25_445 ?
 Ga2 Pd2 Ga2 68.00(4) . 25_445 ?
 Ga2 Pd2 Ga2 106.83(4) 25 25_445 ?
 Ga1 Pd2 Ga2 89.18(7) 13_444 25_455 ?
 Ga1 Pd2 Ga2 121.67(3) 14_544 25_455 ?
 Ga1 Pd2 Ga2 121.67(3) 15_554 25_455 ?
 Ga4 Pd2 Ga2 66.65(2) 13_444 25_455 ?
 Ga4 Pd2 Ga2 66.65(2) 13_554 25_455 ?
 Ga4 Pd2 Ga2 167.39(4) 13_544 25_455 ?
 Ga2 Pd2 Ga2 68.00(4) . 25_455 ?
 Ga2 Pd2 Ga2 106.83(4) 25 25_455 ?
 Ga2 Pd2 Ga2 106.83(4) 25_445 25_455 ?
 Ga1 Pd2 Sm1 62.13(7) 13_444 25_445 ?
 Ga1 Pd2 Sm1 25.56(4) 14_544 25_445 ?
 Ga1 Pd2 Sm1 62.13(7) 15_554 25_445 ?
 Ga4 Pd2 Sm1 61.504(15) 13_444 25_445 ?
 Ga4 Pd2 Sm1 128.98(6) 13_554 25_445 ?
 Ga4 Pd2 Sm1 61.505(15) 13_544 25_445 ?
 Ga2 Pd2 Sm1 131.63(4) . 25_445 ?
 Ga2 Pd2 Sm1 126.54(2) 25 25_445 ?
 Ga2 Pd2 Sm1 63.63(8) 25_445 25_445 ?
 Ga2 Pd2 Sm1 126.54(2) 25_455 25_445 ?
 Ga1 Pd2 Sm1 62.13(7) 13_444 25 ?
 Ga1 Pd2 Sm1 62.13(7) 14_544 25 ?
 Ga1 Pd2 Sm1 25.56(4) 15_554 25 ?
 Ga4 Pd2 Sm1 128.98(6) 13_444 25 ?
 Ga4 Pd2 Sm1 61.504(15) 13_554 25 ?
 Ga4 Pd2 Sm1 61.505(15) 13_544 25 ?
 Ga2 Pd2 Sm1 131.63(5) . 25 ?
 Ga2 Pd2 Sm1 63.63(8) 25 25 ?
 Ga2 Pd2 Sm1 126.54(2) 25_445 25 ?
 Ga2 Pd2 Sm1 126.54(2) 25_455 25 ?
 Sm1 Pd2 Sm1 80.68(7) 25_445 25 ?
 Pd1 Ga3 Pd1 112.62(3) 7_445 7 ?
 Pd1 Ga3 Pd1 112.62(3) 7_445 7_455 ?
 Pd1 Ga3 Pd1 112.62(3) 7 7_455 ?
 Pd1 Ga3 Ga1 140.92(3) 7_445 . ?
 Pd1 Ga3 Ga1 57.40(6) 7 . ?
 Pd1 Ga3 Ga1 105.38(4) 7_455 . ?
 Pd1 Ga3 Ga1 140.92(3) 7_445 3_565 ?
 Pd1 Ga3 Ga1 105.38(4) 7 3_565 ?
 Pd1 Ga3 Ga1 57.40(6) 7_455 3_565 ?
 Ga1 Ga3 Ga1 57.79(7) . 3_565 ?

Pd1 Ga3 Ga1 105.38(4) 7_445 2 ?
 Pd1 Ga3 Ga1 140.92(3) 7 2 ?
 Pd1 Ga3 Ga1 57.40(6) 7_455 2 ?
 Ga1 Ga3 Ga1 87.27(7) . 2 ?
 Ga1 Ga3 Ga1 35.77(6) 3_565 2 ?
 Pd1 Ga3 Ga1 57.40(6) 7_445 1_445 ?
 Pd1 Ga3 Ga1 140.92(3) 7 1_445 ?
 Pd1 Ga3 Ga1 105.38(4) 7_455 1_445 ?
 Ga1 Ga3 Ga1 104.43(10) . 1_445 ?
 Ga1 Ga3 Ga1 87.27(7) 3_565 1_445 ?
 Ga1 Ga3 Ga1 57.79(7) 2 1_445 ?
 Pd1 Ga3 Ga1 105.38(4) 7_445 2_655 ?
 Pd1 Ga3 Ga1 57.40(6) 7 2_655 ?
 Pd1 Ga3 Ga1 140.92(3) 7_455 2_655 ?
 Ga1 Ga3 Ga1 35.77(6) . 2_655 ?
 Ga1 Ga3 Ga1 87.27(7) 3_565 2_655 ?
 Ga1 Ga3 Ga1 104.43(10) 2 2_655 ?
 Ga1 Ga3 Ga1 87.27(7) 1_445 2_655 ?
 Pd1 Ga3 Ga1 57.40(6) 7_445 3 ?
 Pd1 Ga3 Ga1 105.38(4) 7 3 ?
 Pd1 Ga3 Ga1 140.92(3) 7_455 3 ?
 Ga1 Ga3 Ga1 87.27(7) . 3 ?
 Ga1 Ga3 Ga1 104.43(10) 3_565 3 ?
 Ga1 Ga3 Ga1 87.27(7) 2 3 ?
 Ga1 Ga3 Ga1 35.77(6) 1_445 3 ?
 Ga1 Ga3 Ga1 57.79(7) 2_655 3 ?
 Pd1 Ga3 Ga3 56.310(13) 7_445 31_445 ?
 Pd1 Ga3 Ga3 133.90(8) 7 31_445 ?
 Pd1 Ga3 Ga3 56.311(13) 7_455 31_445 ?
 Ga1 Ga3 Ga3 159.86(3) . 31_445 ?
 Ga1 Ga3 Ga3 102.36(5) 3_565 31_445 ?
 Ga1 Ga3 Ga3 75.73(7) 2 31_445 ?
 Ga1 Ga3 Ga3 75.73(7) 1_445 31_445 ?
 Ga1 Ga3 Ga3 159.86(4) 2_655 31_445 ?
 Ga1 Ga3 Ga3 102.36(5) 3 31_445 ?
 Pd1 Ga3 Ga3 133.90(8) 7_445 31 ?
 Pd1 Ga3 Ga3 56.310(13) 7 31 ?
 Pd1 Ga3 Ga3 56.311(13) 7_455 31 ?
 Ga1 Ga3 Ga3 75.73(7) . 31 ?
 Ga1 Ga3 Ga3 75.73(7) 3_565 31 ?
 Ga1 Ga3 Ga3 102.36(5) 2 31 ?
 Ga1 Ga3 Ga3 159.86(3) 1_445 31 ?
 Ga1 Ga3 Ga3 102.36(5) 2_655 31 ?
 Ga1 Ga3 Ga3 159.86(4) 3 31 ?
 Ga3 Ga3 Ga3 97.18(6) 31_445 31 ?
 Pd1 Ga3 Ga3 56.311(13) 7_445 31_545 ?
 Pd1 Ga3 Ga3 56.311(12) 7 31_545 ?
 Pd1 Ga3 Ga3 133.90(8) 7_455 31_545 ?
 Ga1 Ga3 Ga3 102.36(5) . 31_545 ?
 Ga1 Ga3 Ga3 159.86(3) 3_565 31_545 ?
 Ga1 Ga3 Ga3 159.86(3) 2 31_545 ?
 Ga1 Ga3 Ga3 102.36(5) 1_445 31_545 ?
 Ga1 Ga3 Ga3 75.73(7) 2_655 31_545 ?
 Ga1 Ga3 Ga3 75.73(7) 3 31_545 ?
 Ga3 Ga3 Ga3 97.18(6) 31_445 31_545 ?
 Ga3 Ga3 Ga3 97.18(6) 31 31_545 ?
 Pd2 Ga4 Pd2 117.393(15) 7 7_445 ?
 Pd2 Ga4 Pd2 117.392(15) 7 7_455 ?
 Pd2 Ga4 Pd2 117.392(15) 7_445 7_455 ?
 Pd2 Ga4 Ga2 59.374(10) 7 31 ?
 Pd2 Ga4 Ga2 140.96(6) 7_445 31 ?
 Pd2 Ga4 Ga2 59.375(10) 7_455 31 ?

Pd2 Ga4 Ga2 140.96(6) 7 31_445 ?
 Pd2 Ga4 Ga2 59.374(10) 7_445 31_445 ?
 Pd2 Ga4 Ga2 59.375(10) 7_455 31_445 ?
 Ga2 Ga4 Ga2 97.64(6) 31 31_445 ?
 Pd2 Ga4 Ga2 59.375(10) 7 31_545 ?
 Pd2 Ga4 Ga2 59.375(10) 7_445 31_545 ?
 Pd2 Ga4 Ga2 140.96(6) 7_455 31_545 ?
 Ga2 Ga4 Ga2 97.64(6) 31 31_545 ?
 Ga2 Ga4 Ga2 97.64(6) 31_445 31_545 ?
 Pd2 Ga4 Ga1 134.37(4) 7 2 ?
 Pd2 Ga4 Ga1 101.65(3) 7_445 2 ?
 Pd2 Ga4 Ga1 54.53(6) 7_455 2 ?
 Ga2 Ga4 Ga1 103.93(5) 31 2 ?
 Ga2 Ga4 Ga1 78.62(7) 31_445 2 ?
 Ga2 Ga4 Ga1 158.41(3) 31_545 2 ?
 Pd2 Ga4 Ga1 101.65(3) 7 3_565 ?
 Pd2 Ga4 Ga1 134.37(4) 7_445 3_565 ?
 Pd2 Ga4 Ga1 54.53(6) 7_455 3_565 ?
 Ga2 Ga4 Ga1 78.62(7) 31 3_565 ?
 Ga2 Ga4 Ga1 103.93(5) 31_445 3_565 ?
 Ga2 Ga4 Ga1 158.41(3) 31_545 3_565 ?
 Ga1 Ga4 Ga1 33.83(6) 2 3_565 ?
 Pd2 Ga4 Ga1 134.37(4) 7 1_445 ?
 Pd2 Ga4 Ga1 54.53(6) 7_445 1_445 ?
 Pd2 Ga4 Ga1 101.66(3) 7_455 1_445 ?
 Ga2 Ga4 Ga1 158.41(3) 31 1_445 ?
 Ga2 Ga4 Ga1 78.62(7) 31_445 1_445 ?
 Ga2 Ga4 Ga1 103.93(5) 31_545 1_445 ?
 Ga1 Ga4 Ga1 54.49(7) 2 1_445 ?
 Ga1 Ga4 Ga1 81.66(7) 3_565 1_445 ?
 Pd2 Ga4 Ga1 101.66(3) 7 3 ?
 Pd2 Ga4 Ga1 54.53(6) 7_445 3 ?
 Pd2 Ga4 Ga1 134.37(4) 7_455 3 ?
 Ga2 Ga4 Ga1 158.41(3) 31 3 ?
 Ga2 Ga4 Ga1 103.93(5) 31_445 3 ?
 Ga2 Ga4 Ga1 78.62(7) 31_545 3 ?
 Ga1 Ga4 Ga1 81.66(7) 2 3 ?
 Ga1 Ga4 Ga1 96.97(10) 3_565 3 ?
 Ga1 Ga4 Ga1 33.83(6) 1_445 3 ?
 Pd2 Ga4 Ga1 54.53(6) 7 2_655 ?
 Pd2 Ga4 Ga1 101.66(3) 7_445 2_655 ?
 Pd2 Ga4 Ga1 134.37(4) 7_455 2_655 ?
 Ga2 Ga4 Ga1 103.93(5) 31 2_655 ?
 Ga2 Ga4 Ga1 158.41(3) 31_445 2_655 ?
 Ga2 Ga4 Ga1 78.62(7) 31_545 2_655 ?
 Ga1 Ga4 Ga1 96.97(10) 2 2_655 ?
 Ga1 Ga4 Ga1 81.66(7) 3_565 2_655 ?
 Ga1 Ga4 Ga1 81.66(7) 1_445 2_655 ?
 Ga1 Ga4 Ga1 54.49(7) 3 2_655 ?
 Pd2 Ga4 Ga1 54.53(6) 7 . ?
 Pd2 Ga4 Ga1 134.37(4) 7_445 . ?
 Pd2 Ga4 Ga1 101.66(3) 7_455 . ?
 Ga2 Ga4 Ga1 78.62(7) 31 . ?
 Ga2 Ga4 Ga1 158.41(3) 31_445 . ?
 Ga2 Ga4 Ga1 103.93(5) 31_545 . ?
 Ga1 Ga4 Ga1 81.66(7) 2 . ?
 Ga1 Ga4 Ga1 54.49(7) 3_565 . ?
 Ga1 Ga4 Ga1 96.97(10) 1_445 . ?
 Ga1 Ga4 Ga1 81.66(7) 3 . ?
 Ga1 Ga4 Ga1 33.83(6) 2_655 . ?
 Pd2 Ga2 Pd2 112.00(4) . 25 ?
 Pd2 Ga2 Pd2 112.00(4) . 25_445 ?

Pd2 Ga2 Pd2 106.83(4) 25 25_445 ?
 Pd2 Ga2 Pd2 112.00(4) . 25_455 ?
 Pd2 Ga2 Pd2 106.83(4) 25 25_455 ?
 Pd2 Ga2 Pd2 106.83(4) 25_445 25_455 ?
 Pd2 Ga2 Ga4 119.65(4) . 31 ?
 Pd2 Ga2 Ga4 53.971(18) 25 31 ?
 Pd2 Ga2 Ga4 128.36(8) 25_445 31 ?
 Pd2 Ga2 Ga4 53.972(18) 25_455 31 ?
 Pd2 Ga2 Ga4 119.65(4) . 31_445 ?
 Pd2 Ga2 Ga4 128.36(8) 25 31_445 ?
 Pd2 Ga2 Ga4 53.971(17) 25_445 31_445 ?
 Pd2 Ga2 Ga4 53.972(18) 25_455 31_445 ?
 Ga4 Ga2 Ga4 97.64(6) 31 31_445 ?
 Pd2 Ga2 Ga4 119.65(4) . 31_545 ?
 Pd2 Ga2 Ga4 53.972(18) 25 31_545 ?
 Pd2 Ga2 Ga4 53.972(18) 25_445 31_545 ?
 Pd2 Ga2 Ga4 128.36(8) 25_455 31_545 ?
 Ga4 Ga2 Ga4 97.64(6) 31 31_545 ?
 Ga4 Ga2 Ga4 97.64(6) 31_445 31_545 ?
 Pd2 Ga2 Ga2 58.50(5) . 25_445 ?
 Pd2 Ga2 Ga2 126.228(17) 25 25_445 ?
 Pd2 Ga2 Ga2 53.50(7) 25_445 25_445 ?
 Pd2 Ga2 Ga2 126.227(17) 25_455 25_445 ?
 Ga4 Ga2 Ga2 178.15(4) 31 25_445 ?
 Ga4 Ga2 Ga2 83.57(5) 31_445 25_445 ?
 Ga4 Ga2 Ga2 83.57(5) 31_545 25_445 ?
 Pd2 Ga2 Ga2 58.50(5) . 25 ?
 Pd2 Ga2 Ga2 53.50(7) 25 25 ?
 Pd2 Ga2 Ga2 126.228(17) 25_445 25 ?
 Pd2 Ga2 Ga2 126.227(17) 25_455 25 ?
 Ga4 Ga2 Ga2 83.57(5) 31 25 ?
 Ga4 Ga2 Ga2 178.15(4) 31_445 25 ?
 Ga4 Ga2 Ga2 83.57(5) 31_545 25 ?
 Ga2 Ga2 Ga2 95.19(6) 25_445 25 ?
 Pd2 Ga2 Ga2 58.50(5) . 25_455 ?
 Pd2 Ga2 Ga2 126.227(17) 25 25_455 ?
 Pd2 Ga2 Ga2 126.227(17) 25_445 25_455 ?
 Pd2 Ga2 Ga2 53.50(7) 25_455 25_455 ?
 Ga4 Ga2 Ga2 83.57(5) 31 25_455 ?
 Ga4 Ga2 Ga2 83.57(5) 31_445 25_455 ?
 Ga4 Ga2 Ga2 178.15(4) 31_545 25_455 ?
 Ga2 Ga2 Ga2 95.19(6) 25_445 25_455 ?
 Ga2 Ga2 Ga2 95.19(6) 25 25_455 ?
 Pd2 Ga2 Sm1 180.0 . . ?
 Pd2 Ga2 Sm1 68.00(4) 25 . ?
 Pd2 Ga2 Sm1 68.00(4) 25_445 . ?
 Pd2 Ga2 Sm1 68.00(4) 25_455 . ?
 Ga4 Ga2 Sm1 60.35(4) 31 . ?
 Ga4 Ga2 Sm1 60.35(4) 31_445 . ?
 Ga4 Ga2 Sm1 60.35(4) 31_545 . ?
 Ga2 Ga2 Sm1 121.50(5) 25_445 . ?
 Ga2 Ga2 Sm1 121.50(5) 25 . ?
 Ga2 Ga2 Sm1 121.50(5) 25_455 . ?
 Sm1 Ga1 Ga1 149.839(7) 31 3_665 ?
 Sm1 Ga1 Ga1 149.839(7) 31 2_655 ?
 Ga1 Ga1 Ga1 59.999(1) 3_665 2_655 ?
 Sm1 Ga1 Pd2 109.54(8) 31 7 ?
 Ga1 Ga1 Pd2 70.38(4) 3_665 7 ?
 Ga1 Ga1 Pd2 70.38(4) 2_655 7 ?
 Sm1 Ga1 Pd1 115.50(7) 31 7 ?
 Ga1 Ga1 Pd1 70.88(4) 3_665 7 ?
 Ga1 Ga1 Pd1 70.88(4) 2_655 7 ?

Pd2 Ga1 Pd1 134.96(9) 7 7 ?
 Sm1 Ga1 Ga1 30.161(5) 31 3_565 ?
 Ga1 Ga1 Ga1 180.00(7) 3_665 3_565 ?
 Ga1 Ga1 Ga1 120.000(1) 2_655 3_565 ?
 Pd2 Ga1 Ga1 109.62(4) 7 3_565 ?
 Pd1 Ga1 Ga1 109.13(4) 7 3_565 ?
 Sm1 Ga1 Ga1 30.161(5) 31 2_665 ?
 Ga1 Ga1 Ga1 120.000(1) 3_665 2_665 ?
 Ga1 Ga1 Ga1 179.998(2) 2_655 2_665 ?
 Pd2 Ga1 Ga1 109.62(4) 7 2_665 ?
 Pd1 Ga1 Ga1 109.13(4) 7 2_665 ?
 Ga1 Ga1 Ga1 60.000(1) 3_565 2_665 ?
 Sm1 Ga1 Ga3 86.16(4) 31 . ?
 Ga1 Ga1 Ga3 118.89(3) 3_665 . ?
 Ga1 Ga1 Ga3 72.12(3) 2_655 . ?
 Pd2 Ga1 Ga3 126.61(5) 7 . ?
 Pd1 Ga1 Ga3 58.61(6) 7 . ?
 Ga1 Ga1 Ga3 61.11(4) 3_565 . ?
 Ga1 Ga1 Ga3 107.89(3) 2_665 . ?
 Sm1 Ga1 Ga3 86.16(4) 31 1_665 ?
 Ga1 Ga1 Ga3 72.12(3) 3_665 1_665 ?
 Ga1 Ga1 Ga3 118.89(3) 2_655 1_665 ?
 Pd2 Ga1 Ga3 126.61(5) 7 1_665 ?
 Pd1 Ga1 Ga3 58.61(6) 7 1_665 ?
 Ga1 Ga1 Ga3 107.88(3) 3_565 1_665 ?
 Ga1 Ga1 Ga3 61.11(4) 2_665 1_665 ?
 Ga3 Ga1 Ga3 104.43(10) . 1_665 ?
 Sm1 Ga1 Ga4 82.32(4) 31 . ?
 Ga1 Ga1 Ga4 117.24(3) 3_665 . ?
 Ga1 Ga1 Ga4 73.08(3) 2_655 . ?
 Pd2 Ga1 Ga4 55.45(6) 7 . ?
 Pd1 Ga1 Ga4 130.05(5) 7 . ?
 Ga1 Ga1 Ga4 62.75(3) 3_565 . ?
 Ga1 Ga1 Ga4 106.92(3) 2_665 . ?
 Ga3 Ga1 Ga4 78.15(9) . . ?
 Ga3 Ga1 Ga4 168.02(6) 1_665 . ?
 Sm1 Ga1 Ga4 82.32(4) 31 1_665 ?
 Ga1 Ga1 Ga4 73.08(3) 3_665 1_665 ?
 Ga1 Ga1 Ga4 117.24(3) 2_655 1_665 ?
 Pd2 Ga1 Ga4 55.45(6) 7 1_665 ?
 Pd1 Ga1 Ga4 130.05(5) 7 1_665 ?
 Ga1 Ga1 Ga4 106.91(3) 3_565 1_665 ?
 Ga1 Ga1 Ga4 62.75(3) 2_665 1_665 ?
 Ga3 Ga1 Ga4 168.02(6) . 1_665 ?
 Ga3 Ga1 Ga4 78.16(9) 1_665 1_665 ?
 Ga4 Ga1 Ga4 96.97(10) . 1_665 ?
 Sm1 Ga1 Sm1 135.49(2) 31 31_545 ?
 Ga1 Ga1 Sm1 74.269(17) 3_665 31_545 ?
 Ga1 Ga1 Sm1 14.35(2) 2_655 31_545 ?
 Pd2 Ga1 Sm1 72.33(4) 7 31_545 ?
 Pd1 Ga1 Sm1 75.83(4) 7 31_545 ?
 Ga1 Ga1 Sm1 105.73(2) 3_565 31_545 ?
 Ga1 Ga1 Sm1 165.648(17) 2_665 31_545 ?
 Ga3 Ga1 Sm1 62.51(3) . 31_545 ?
 Ga3 Ga1 Sm1 129.88(5) 1_665 31_545 ?
 Ga4 Ga1 Sm1 61.84(2) . 31_545 ?
 Ga4 Ga1 Sm1 124.95(6) 1_665 31_545 ?

 _diffn_measured_fraction_theta_max 0.994
 _diffn_reflns_theta_full 30.98
 _diffn_measured_fraction_theta_full 0.994
 _refine_diff_density_max 0.995
 _refine_diff_density_min -1.723
 _refine_diff_density_rms 0.273

Appendix E. CIF of CeCo_{2-x}M_xAl₈ (M = Fe, Ni; 0 ≤ x < 1)

```

data_shelxl
_audit_creation_method      SHELXL-97
_chemical_name_systematic
;
?
;
_chemical_name_common      ?
_chemical_melting_point    ?
_chemical_formula_moiety    ?
_chemical_formula_sum
'Al8 Ce Co Fe'
_chemical_formula_weight    470.74

loop_
_atom_type_symbol
_atom_type_description
_atom_type_scatter_dispersion_real
_atom_type_scatter_dispersion_imag
_atom_type_scatter_source
'Ce' 'Ce' -0.2486 2.6331
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Co' 'Co' 0.3494 0.9721
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Fe' 'Fe' 0.3463 0.8444
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Al' 'Al' 0.0645 0.0514
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

_symmetry_cell_setting      ?
_symmetry_space_group_name_H-M ?

loop_
_symmetry_equiv_pos_as_xyz
'x, y, z'
'-x, -y, z'
'x+1/2, -y+1/2, -z'
'-x+1/2, y+1/2, -z'
'-x, -y, -z'
'x, y, -z'
'-x-1/2, y-1/2, z'
'x-1/2, -y-1/2, z'

_cell_length_a              12.4770(5)
_cell_length_b              14.391(2)
_cell_length_c              4.027(2)
_cell_angle_alpha           90.00
_cell_angle_beta            90.00
_cell_angle_gamma           90.00
_cell_volume                723.1(4)
_cell_formula_units_Z        4
_cell_measurement_temperature 293(2)
_cell_measurement_reflns_used ?
_cell_measurement_theta_min ?
_cell_measurement_theta_max ?

_exptl_crystal_description  ?
_exptl_crystal_colour       ?
_exptl_crystal_size_max     ?

_exptl_crystal_size_mid     ?
_exptl_crystal_size_min     ?
_exptl_crystal_density_meas ?
_exptl_crystal_density_diffn 4.324
_exptl_crystal_density_method 'not measured'
_exptl_crystal_F_000        860
_exptl_absorpt_coefficient_mu 11.303
_exptl_absorpt_correction_type ?
_exptl_absorpt_correction_T_min ?
_exptl_absorpt_correction_T_max ?
_exptl_absorpt_process_details ?

_exptl_special_details
;
?
;

_diffn_ambient_temperature 293(2)
_diffn_radiation_wavelength 0.71073
_diffn_radiation_type       MoK\alpha
_diffn_radiation_source     'fine-focus sealed tube'
_diffn_radiation_monochromator graphite
_diffn_measurement_device_type ?
_diffn_measurement_method   ?
_diffn_detector_area_resol_mean ?
_diffn_standards_number     ?
_diffn_standards_interval_count ?
_diffn_standards_interval_time ?
_diffn_standards_decay_%    ?
_diffn_reflns_number        2194
_diffn_reflns_av_R_equivalents 0.0284
_diffn_reflns_av_sigmaI/netI 0.0333
_diffn_reflns_limit_h_min   -17
_diffn_reflns_limit_h_max    18
_diffn_reflns_limit_k_min    -20
_diffn_reflns_limit_k_max     20
_diffn_reflns_limit_l_min    -5
_diffn_reflns_limit_l_max     5
_diffn_reflns_theta_min      3.27
_diffn_reflns_theta_max      31.00
_reflns_number_total         1300
_reflns_number_gt            1033
_reflns_threshold_expression >2\sigma(I)

_computing_data_collection   ?
_computing_cell_refinement   ?
_computing_data_reduction    ?
_computing_structure_solution ?
_computing_structure_refinement 'SHELXL-97
(Sheldrick, 2008)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F2 against ALL reflections. The
weighted R-factor wR and
goodness of fit S are based on F2, conventional R-
factors R are based

```

on F, with F set to zero for negative F^2 . The threshold expression of $F^2 > 2\sigma(F^2)$ is used only for calculating R-factors(gt) etc. and is not relevant to the choice of reflections for refinement. R-factors based on F^2 are statistically about twice as large as those based on F, and R-factors based on ALL data will be even larger.

```
_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type full
_refine_ls_weighting_scheme calc
_refine_ls_weighting_details
'calc w=1/[\s^2^(Fo^2)+(0.0311P)^2+0.6661P] where
P=(Fo^2+2Fc^2)/3'
_atom_sites_solution_primary direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment mixed
_refine_ls_extinction_method SHELXL
_refine_ls_extinction_coef 0.0076(3)
_refine_ls_extinction_expression
'Fc^*=kFc[1+0.001xFc^2^l^3/sin(2q)]^-1/4^'
_refine_ls_number_reflns 1300
_refine_ls_number_parameters 71
_refine_ls_number_restraints 0
_refine_ls_R_factor_all 0.0404
_refine_ls_R_factor_gt 0.0266
_refine_ls_wR_factor_ref 0.0638
_refine_ls_wR_factor_gt 0.0583
_refine_ls_goodness_of_fit_ref 1.039
_refine_ls_restrained_S_all 1.039
_refine_ls_shift/su_max 0.000
_refine_ls_shift/su_mean 0.000
```

```
loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ce1 Ce 0.34072(2) 0.318513(19) 0.0000 0.01055(11) Uani
1 2 d S . .
Co2 Co 0.15116(5) 0.09671(4) 0.0000 0.00808(15) Uani 1
2 d S . .
Co1 Co 0.03456(5) 0.40589(5) 0.0000 0.0092(2) Uani
0.77(6) 2 d SP . .
Fe1 Fe 0.03456(5) 0.40589(5) 0.0000 0.0092(2) Uani
0.23(6) 2 d SP . .
Al8 Al 0.0000 0.5000 0.5000 0.0096(4) Uani 1 4 d S . .
Al9 Al 0.0000 0.0000 0.0000 0.0104(4) Uani 1 4 d S . .
```

```
Al2 Al 0.15961(12) 0.37917(11) 0.5000 0.0095(3) Uani 1 2
d S . .
Al5 Al 0.45250(12) 0.17965(10) 0.5000 0.0095(3) Uani 1 2
d S . .
Al3 Al 0.23606(12) 0.17258(10) 0.5000 0.0096(3) Uani 1 2
d S . .
Al4 Al 0.33146(12) 0.49159(10) 0.5000 0.0106(3) Uani 1 2
d S . .
Al1 Al 0.02558(12) 0.13172(10) 0.5000 0.0097(3) Uani 1 2
d S . .
Al7 Al 0.33940(12) 0.04452(10) 0.0000 0.0111(3) Uani 1 2
d S . .
Al6 Al 0.09581(12) 0.25304(9) 0.0000 0.0096(3) Uani 1 2
d S . .
```

```
loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12
Ce1 0.01005(15) 0.01325(16) 0.00835(15) 0.000 0.000 -
0.00098(11)
Co2 0.0082(3) 0.0082(3) 0.0078(3) 0.000 0.000 0.0000(2)
Co1 0.0105(4) 0.0088(4) 0.0084(4) 0.000 0.000 0.0007(3)
Fe1 0.0105(4) 0.0088(4) 0.0084(4) 0.000 0.000 0.0007(3)
Al8 0.0120(10) 0.0096(9) 0.0071(10) 0.000 0.000 -
0.0005(8)
Al9 0.0084(9) 0.0121(10) 0.0105(11) 0.000 0.000 -
0.0002(8)
Al2 0.0084(6) 0.0109(7) 0.0093(7) 0.000 0.000 -0.0009(5)
Al5 0.0088(7) 0.0089(7) 0.0108(7) 0.000 0.000 0.0006(5)
Al3 0.0086(7) 0.0114(7) 0.0089(7) 0.000 0.000 -0.0012(6)
Al4 0.0114(7) 0.0102(7) 0.0102(7) 0.000 0.000 -0.0017(6)
Al1 0.0093(6) 0.0108(7) 0.0090(7) 0.000 0.000 0.0005(6)
Al7 0.0083(7) 0.0139(7) 0.0109(8) 0.000 0.000 0.0019(6)
Al6 0.0100(7) 0.0086(6) 0.0102(7) 0.000 0.000 0.0007(6)
```

```
_geom_special_details
;
All s.u.'s (except the s.u. in the dihedral angle between two
l.s. planes)
are estimated using the full covariance matrix. The cell
s.u.'s are taken
into account individually in the estimation of s.u.'s in
distances, angles
and torsion angles; correlations between s.u.'s in cell
parameters are only
used when they are defined by crystal symmetry. An
approximate (isotropic)
treatment of cell s.u.'s is used for estimating s.u.'s
involving l.s. planes.
```

```
loop_
_geom_bond_atom_site_label_1
_geom_bond_atom_site_label_2
_geom_bond_distance
_geom_bond_site_symmetry_2
_geom_bond_publ_flag
```

Ce1 Al1 3.1443(14) 3_556 ?
 Ce1 Al1 3.1443(14) 3 ?
 Ce1 Al2 3.1500(13) 1_554 ?
 Ce1 Al2 3.1500(13) . ?
 Ce1 Al5 3.1611(13) 1_554 ?
 Ce1 Al5 3.1611(13) . ?
 Ce1 Al3 3.1891(13) 1_554 ?
 Ce1 Al3 3.1891(13) . ?
 Ce1 Al6 3.1977(15) . ?
 Ce1 Al4 3.2049(13) . ?
 Ce1 Al4 3.2049(14) 1_554 ?
 Ce1 Al9 3.2819(4) 3 ?
 Co2 Al9 2.3439(6) . ?
 Co2 Al6 2.3532(15) . ?
 Co2 Al7 2.4658(16) . ?
 Co2 Al3 2.5236(13) . ?
 Co2 Al3 2.5236(13) 1_554 ?
 Co2 Al4 2.5278(13) 7_654 ?
 Co2 Al4 2.5278(13) 7_655 ?
 Co2 Al1 2.6005(13) 1_554 ?
 Co2 Al1 2.6005(13) . ?
 Co1 Al6 2.3287(15) . ?
 Co1 Al8 2.4646(9) . ?
 Co1 Al8 2.4646(9) 1_554 ?
 Co1 Al7 2.5375(16) 3_455 ?
 Co1 Al7 2.5403(16) 7_665 ?
 Co1 Al5 2.5726(12) 3_455 ?
 Co1 Al5 2.5726(12) 3_456 ?
 Co1 Al2 2.5761(13) . ?
 Co1 Al2 2.5761(13) 1_554 ?
 Co1 Fe1 2.8426(13) 5_565 ?
 Co1 Co1 2.8426(13) 5_565 ?
 Al8 Fe1 2.4646(9) 5_566 ?
 Al8 Co1 2.4646(9) 5_566 ?
 Al8 Fe1 2.4646(9) 1_556 ?
 Al8 Co1 2.4646(9) 1_556 ?
 Al8 Fe1 2.4646(9) 5_565 ?
 Al8 Co1 2.4646(9) 5_565 ?
 Al8 Al2 2.6438(15) . ?
 Al8 Al2 2.6438(15) 5_566 ?
 Al8 Al5 2.6524(14) 7_665 ?
 Al8 Al5 2.6524(14) 3_456 ?
 Al9 Co2 2.3439(6) 5 ?
 Al9 Al1 2.7838(13) 5 ?
 Al9 Al1 2.7838(13) . ?
 Al9 Al1 2.7838(13) 5_556 ?
 Al9 Al1 2.7838(13) 1_554 ?
 Al9 Al4 2.9139(13) 3_455 ?
 Al9 Al4 2.9139(13) 7_655 ?
 Al9 Al4 2.9139(13) 3_456 ?
 Al9 Al4 2.9139(13) 7_654 ?
 Al9 Ce1 3.2819(4) 3_455 ?
 Al9 Ce1 3.2819(4) 7_655 ?
 Al2 Fe1 2.5761(13) 1_556 ?
 Al2 Co1 2.5761(13) 1_556 ?
 Al2 Al4 2.686(2) . ?
 Al2 Al5 2.719(2) 3_456 ?
 Al2 Al6 2.8254(16) . ?
 Al2 Al6 2.8254(16) 1_556 ?
 Al2 Ce1 3.1500(13) 1_556 ?
 Al5 Fe1 2.5726(13) 3 ?
 Al5 Co1 2.5726(13) 3 ?

Al5 Fe1 2.5726(13) 3_556 ?
 Al5 Co1 2.5726(13) 3_556 ?
 Al5 Al8 2.6524(14) 3_556 ?
 Al5 Al3 2.702(2) . ?
 Al5 Al2 2.719(2) 3_556 ?
 Al5 Al6 2.8618(16) 3_556 ?
 Al5 Al6 2.8618(16) 3 ?
 Al5 Al1 2.864(2) 3_556 ?
 Al5 Ce1 3.1611(13) 1_556 ?
 Al3 Co2 2.5236(13) 1_556 ?
 Al3 Al1 2.691(2) . ?
 Al3 Al4 2.737(2) 7_655 ?
 Al3 Al6 2.9081(16) . ?
 Al3 Al6 2.9081(16) 1_556 ?
 Al3 Ce1 3.1891(13) 1_556 ?
 Al4 Co2 2.5278(13) 7_666 ?
 Al4 Co2 2.5278(13) 7_665 ?
 Al4 Al1 2.692(2) 7_665 ?
 Al4 Al3 2.737(2) 7_665 ?
 Al4 Al9 2.9139(13) 3_556 ?
 Al4 Al9 2.9139(13) 3 ?
 Al4 Ce1 3.2049(14) 1_556 ?
 Al1 Co2 2.6005(13) 1_556 ?
 Al1 Al4 2.692(2) 7_655 ?
 Al1 Al9 2.7838(13) 1_556 ?
 Al1 Al6 2.8054(16) 1_556 ?
 Al1 Al6 2.8054(16) . ?
 Al1 Al5 2.864(2) 3_456 ?
 Al1 Ce1 3.1443(14) 3_455 ?
 Al1 Ce1 3.1443(14) 3_456 ?
 Al7 Fe1 2.5375(16) 3 ?
 Al7 Co1 2.5375(16) 3 ?
 Al7 Fe1 2.5403(16) 7_655 ?
 Al7 Co1 2.5403(16) 7_655 ?
 Al7 Al8 2.9121(12) 3_556 ?
 Al7 Al8 2.9121(12) 3 ?
 Al6 Al1 2.8054(16) 1_554 ?
 Al6 Al2 2.8254(16) 1_554 ?
 Al6 Al5 2.8618(16) 3_455 ?
 Al6 Al5 2.8618(16) 3_456 ?
 Al6 Al3 2.9081(16) 1_554 ?

loop_
 _geom_angle_atom_site_label_1
 _geom_angle_atom_site_label_2
 _geom_angle_atom_site_label_3
 _geom_angle
 _geom_angle_site_symmetry_1
 _geom_angle_site_symmetry_3
 _geom_angle_publ_flag
 Al1 Ce1 Al1 79.64(5) 3_556 3 ?
 Al1 Ce1 Al2 150.74(4) 3_556 1_554 ?
 Al1 Ce1 Al2 93.08(4) 3 1_554 ?
 Al1 Ce1 Al2 93.08(4) 3_556 . ?
 Al1 Ce1 Al2 150.74(4) 3 . ?
 Al2 Ce1 Al2 79.47(5) 1_554 . ?
 Al1 Ce1 Al5 103.19(4) 3_556 1_554 ?
 Al1 Ce1 Al5 54.02(4) 3 1_554 ?
 Al2 Ce1 Al5 94.85(4) 1_554 1_554 ?
 Al2 Ce1 Al5 154.01(4) . 1_554 ?
 Al1 Ce1 Al5 54.02(4) 3_556 . ?
 Al1 Ce1 Al5 103.19(4) 3 . ?

Al2 Ce1 Al5 154.01(4) 1_554 . ?
 Al2 Ce1 Al5 94.85(4) . . ?
 Al5 Ce1 Al5 79.13(4) 1_554 . ?
 Al1 Ce1 Al3 148.72(4) 3_556 1_554 ?
 Al1 Ce1 Al3 92.64(4) 3 1_554 ?
 Al2 Ce1 Al3 59.01(4) 1_554 1_554 ?
 Al2 Ce1 Al3 107.00(4) . 1_554 ?
 Al5 Ce1 Al3 50.37(4) 1_554 1_554 ?
 Al5 Ce1 Al3 99.58(4) . 1_554 ?
 Al1 Ce1 Al3 92.64(4) 3_556 . ?
 Al1 Ce1 Al3 148.72(4) 3 . ?
 Al2 Ce1 Al3 107.00(4) 1_554 . ?
 Al2 Ce1 Al3 59.01(4) . . ?
 Al5 Ce1 Al3 99.58(4) 1_554 . ?
 Al5 Ce1 Al3 50.37(4) . . ?
 Al3 Ce1 Al3 78.30(4) 1_554 . ?
 Al1 Ce1 Al6 140.18(2) 3_556 . ?
 Al1 Ce1 Al6 140.18(2) 3 . ?
 Al2 Ce1 Al6 52.85(3) 1_554 . ?
 Al2 Ce1 Al6 52.85(3) . . ?
 Al5 Ce1 Al6 103.61(3) 1_554 . ?
 Al5 Ce1 Al6 103.61(3) . . ?
 Al3 Ce1 Al6 54.17(3) 1_554 . ?
 Al3 Ce1 Al6 54.17(3) . . ?
 Al1 Ce1 Al4 56.44(4) 3_556 . ?
 Al1 Ce1 Al4 104.58(4) 3 . ?
 Al2 Ce1 Al4 99.23(4) 1_554 . ?
 Al2 Ce1 Al4 50.00(4) . . ?
 Al5 Ce1 Al4 155.15(4) 1_554 . ?
 Al5 Ce1 Al4 96.14(4) . . ?
 Al3 Ce1 Al4 153.34(4) 1_554 . ?
 Al3 Ce1 Al4 95.76(4) . . ?
 Al6 Ce1 Al4 101.22(3) . . ?
 Al1 Ce1 Al4 104.58(4) 3_556 1_554 ?
 Al1 Ce1 Al4 56.44(4) 3 1_554 ?
 Al2 Ce1 Al4 50.00(4) 1_554 1_554 ?
 Al2 Ce1 Al4 99.23(4) . 1_554 ?
 Al5 Ce1 Al4 96.14(4) 1_554 1_554 ?
 Al5 Ce1 Al4 155.15(4) . 1_554 ?
 Al3 Ce1 Al4 95.76(4) 1_554 1_554 ?
 Al3 Ce1 Al4 153.34(4) . 1_554 ?
 Al6 Ce1 Al4 101.22(3) . 1_554 ?
 Al4 Ce1 Al4 77.84(4) . 1_554 ?
 Al1 Ce1 Al9 51.29(3) 3_556 3 ?
 Al1 Ce1 Al9 51.29(3) 3 3 ?
 Al2 Ce1 Al9 102.35(3) 1_554 3 ?
 Al2 Ce1 Al9 102.35(3) . 3 ?
 Al5 Ce1 Al9 103.65(3) 1_554 3 ?
 Al5 Ce1 Al9 103.65(3) . 3 ?
 Al3 Ce1 Al9 140.54(2) 1_554 3 ?
 Al3 Ce1 Al9 140.54(2) . 3 ?
 Al6 Ce1 Al9 144.40(3) . 3 ?
 Al4 Ce1 Al9 53.37(3) . 3 ?
 Al4 Ce1 Al9 53.37(3) 1_554 3 ?
 Al9 Co2 Al6 109.36(4) . . ?
 Al9 Co2 Al7 125.84(5) . . ?
 Al6 Co2 Al7 124.80(6) . . ?
 Al9 Co2 Al3 126.49(3) . . ?
 Al6 Co2 Al3 73.12(4) . . ?
 Al7 Co2 Al3 74.45(4) . . ?
 Al9 Co2 Al3 126.49(3) . 1_554 ?
 Al6 Co2 Al3 73.12(4) . 1_554 ?

Al7 Co2 Al3 74.45(4) . 1_554 ?
 Al3 Co2 Al3 105.86(6) . 1_554 ?
 Al9 Co2 Al4 73.36(4) . 7_654 ?
 Al6 Co2 Al4 126.68(3) . 7_654 ?
 Al7 Co2 Al4 74.69(4) . 7_654 ?
 Al3 Co2 Al4 149.14(6) . 7_654 ?
 Al3 Co2 Al4 65.63(5) 1_554 7_654 ?
 Al9 Co2 Al4 73.36(4) . 7_655 ?
 Al6 Co2 Al4 126.68(3) . 7_655 ?
 Al7 Co2 Al4 74.69(4) . 7_655 ?
 Al3 Co2 Al4 65.63(5) . 7_655 ?
 Al3 Co2 Al4 149.14(6) 1_554 7_655 ?
 Al4 Co2 Al4 105.60(7) 7_654 7_655 ?
 Al9 Co2 Al1 68.30(4) . 1_554 ?
 Al6 Co2 Al1 68.78(4) . 1_554 ?
 Al7 Co2 Al1 129.26(3) . 1_554 ?
 Al3 Co2 Al1 141.89(5) . 1_554 ?
 Al3 Co2 Al1 63.34(5) 1_554 1_554 ?
 Al4 Co2 Al1 63.32(5) 7_654 1_554 ?
 Al4 Co2 Al1 141.66(5) 7_655 1_554 ?
 Al9 Co2 Al1 68.30(4) . . ?
 Al6 Co2 Al1 68.78(4) . . ?
 Al7 Co2 Al1 129.26(3) . . ?
 Al3 Co2 Al1 63.34(5) . . ?
 Al3 Co2 Al1 141.89(5) 1_554 . ?
 Al4 Co2 Al1 141.66(5) 7_654 . ?
 Al4 Co2 Al1 63.32(5) 7_655 . ?
 Al1 Co2 Al1 101.48(6) 1_554 . ?
 Al6 Co1 Al8 125.204(19) . . ?
 Al6 Co1 Al8 125.204(19) . 1_554 ?
 Al8 Co1 Al8 109.56(4) . 1_554 ?
 Al6 Co1 Al7 125.49(6) . 3_455 ?
 Al8 Co1 Al7 71.19(2) . 3_455 ?
 Al8 Co1 Al7 71.19(2) 1_554 3_455 ?
 Al6 Co1 Al7 122.59(6) . 7_665 ?
 Al8 Co1 Al7 71.14(2) . 7_665 ?
 Al8 Co1 Al7 71.14(2) 1_554 7_665 ?
 Al7 Co1 Al7 111.92(4) 3_455 7_665 ?
 Al6 Co1 Al5 71.25(4) . 3_455 ?
 Al8 Co1 Al5 146.38(4) . 3_455 ?
 Al8 Co1 Al5 63.51(4) 1_554 3_455 ?
 Al7 Co1 Al5 75.68(4) 3_455 3_455 ?
 Al7 Co1 Al5 128.48(3) 7_665 3_455 ?
 Al6 Co1 Al5 71.25(4) . 3_456 ?
 Al8 Co1 Al5 63.51(4) . 3_456 ?
 Al8 Co1 Al5 146.38(4) 1_554 3_456 ?
 Al7 Co1 Al5 75.68(4) 3_455 3_456 ?
 Al7 Co1 Al5 128.48(3) 7_665 3_456 ?
 Al5 Co1 Al5 103.01(6) 3_455 3_456 ?
 Al6 Co1 Al2 70.14(4) . . ?
 Al8 Co1 Al2 63.22(4) . . ?
 Al8 Co1 Al2 145.75(4) 1_554 . ?
 Al7 Co1 Al2 128.55(3) 3_455 . ?
 Al7 Co1 Al2 75.07(4) 7_665 . ?
 Al5 Co1 Al2 141.38(6) 3_455 . ?
 Al5 Co1 Al2 63.76(5) 3_456 . ?
 Al6 Co1 Al2 70.14(4) . 1_554 ?
 Al8 Co1 Al2 145.75(4) . 1_554 ?
 Al8 Co1 Al2 63.22(4) 1_554 1_554 ?
 Al7 Co1 Al2 128.55(3) 3_455 1_554 ?
 Al7 Co1 Al2 75.07(4) 7_665 1_554 ?
 Al5 Co1 Al2 63.76(5) 3_455 1_554 ?

Al5 Co1 Al2 141.38(6) 3_456 1_554 ?
 Al2 Co1 Al2 102.81(6) . 1_554 ?
 Al6 Co1 Fe1 178.50(6) . 5_565 ?
 Al8 Co1 Fe1 54.782(19) . 5_565 ?
 Al8 Co1 Fe1 54.782(19) 1_554 5_565 ?
 Al7 Co1 Fe1 56.00(4) 3_455 5_565 ?
 Al7 Co1 Fe1 55.91(4) 7_665 5_565 ?
 Al5 Co1 Fe1 109.59(4) 3_455 5_565 ?
 Al5 Co1 Fe1 109.59(4) 3_456 5_565 ?
 Al2 Co1 Fe1 109.03(4) . 5_565 ?
 Al2 Co1 Fe1 109.03(4) 1_554 5_565 ?
 Al6 Co1 Co1 178.50(6) . 5_565 ?
 Al8 Co1 Co1 54.782(19) . 5_565 ?
 Al8 Co1 Co1 54.782(19) 1_554 5_565 ?
 Al7 Co1 Co1 56.00(4) 3_455 5_565 ?
 Al7 Co1 Co1 55.91(4) 7_665 5_565 ?
 Al5 Co1 Co1 109.59(4) 3_455 5_565 ?
 Al5 Co1 Co1 109.59(4) 3_456 5_565 ?
 Al2 Co1 Co1 109.03(4) . 5_565 ?
 Al2 Co1 Co1 109.03(4) 1_554 5_565 ?
 Fe1 Co1 Co1 0.00(3) 5_565 5_565 ?
 Fe1 Al8 Co1 0.00(3) 5_566 5_566 ?
 Fe1 Al8 Co1 180.0 5_566 . ?
 Co1 Al8 Co1 180.0 5_566 . ?
 Fe1 Al8 Fe1 70.44(4) 5_566 1_556 ?
 Co1 Al8 Fe1 70.44(4) 5_566 1_556 ?
 Co1 Al8 Fe1 109.56(4) . 1_556 ?
 Fe1 Al8 Co1 70.44(4) 5_566 1_556 ?
 Co1 Al8 Co1 70.44(4) 5_566 1_556 ?
 Co1 Al8 Co1 109.56(4) . 1_556 ?
 Fe1 Al8 Co1 0.00(3) 1_556 1_556 ?
 Fe1 Al8 Fe1 109.56(4) 5_566 5_565 ?
 Co1 Al8 Fe1 109.56(4) 5_566 5_565 ?
 Co1 Al8 Fe1 70.44(4) . 5_565 ?
 Fe1 Al8 Fe1 180.0 1_556 5_565 ?
 Co1 Al8 Fe1 180.0 1_556 5_565 ?
 Fe1 Al8 Co1 109.56(4) 5_566 5_565 ?
 Co1 Al8 Co1 109.56(4) 5_566 5_565 ?
 Co1 Al8 Co1 70.44(4) . 5_565 ?
 Fe1 Al8 Co1 180.0 1_556 5_565 ?
 Co1 Al8 Co1 180.0 1_556 5_565 ?
 Fe1 Al8 Co1 0.00(4) 5_565 5_565 ?
 Fe1 Al8 Al2 119.55(2) 5_566 . ?
 Co1 Al8 Al2 119.55(2) 5_566 . ?
 Co1 Al8 Al2 60.45(2) . . ?
 Fe1 Al8 Al2 60.45(2) 1_556 . ?
 Co1 Al8 Al2 60.45(2) 1_556 . ?
 Fe1 Al8 Al2 119.55(2) 5_565 . ?
 Co1 Al8 Al2 119.55(2) 5_565 . ?
 Fe1 Al8 Al2 60.45(2) 5_566 5_566 ?
 Co1 Al8 Al2 60.45(2) 5_566 5_566 ?
 Co1 Al8 Al2 119.55(2) . 5_566 ?
 Fe1 Al8 Al2 119.55(2) 1_556 5_566 ?
 Co1 Al8 Al2 119.55(2) 1_556 5_566 ?
 Fe1 Al8 Al2 60.45(2) 5_565 5_566 ?
 Co1 Al8 Al2 60.45(2) 5_565 5_566 ?
 Al2 Al8 Al2 180.0 . 5_566 ?
 Fe1 Al8 Al5 60.23(2) 5_566 7_665 ?
 Co1 Al8 Al5 60.23(2) 5_566 7_665 ?
 Co1 Al8 Al5 119.77(2) . 7_665 ?
 Fe1 Al8 Al5 119.77(2) 1_556 7_665 ?
 Co1 Al8 Al5 119.77(2) 1_556 7_665 ?

Fe1 Al8 Al5 60.23(2) 5_565 7_665 ?
 Co1 Al8 Al5 60.23(2) 5_565 7_665 ?
 Al2 Al8 Al5 118.22(5) . 7_665 ?
 Al2 Al8 Al5 61.78(5) 5_566 7_665 ?
 Fe1 Al8 Al5 119.77(2) 5_566 3_456 ?
 Co1 Al8 Al5 119.77(2) 5_566 3_456 ?
 Co1 Al8 Al5 60.23(2) . 3_456 ?
 Fe1 Al8 Al5 60.23(2) 1_556 3_456 ?
 Co1 Al8 Al5 60.23(2) 1_556 3_456 ?
 Fe1 Al8 Al5 119.77(2) 5_565 3_456 ?
 Co1 Al8 Al5 119.77(2) 5_565 3_456 ?
 Al2 Al8 Al5 61.78(5) . 3_456 ?
 Al2 Al8 Al5 118.22(5) 5_566 3_456 ?
 Al5 Al8 Al5 180.0 7_665 3_456 ?
 Co2 Al9 Co2 180.00(3) 5 . ?
 Co2 Al9 Al1 60.22(3) 5 5 ?
 Co2 Al9 Al1 119.78(3) . 5 ?
 Co2 Al9 Al1 119.78(3) 5 . ?
 Co2 Al9 Al1 60.22(3) . . ?
 Al1 Al9 Al1 180.00(8) 5 . ?
 Co2 Al9 Al1 60.22(3) 5 5_556 ?
 Co2 Al9 Al1 119.78(3) . 5_556 ?
 Al1 Al9 Al1 92.66(5) 5 5_556 ?
 Al1 Al9 Al1 87.34(5) . 5_556 ?
 Co2 Al9 Al1 119.78(3) 5 1_554 ?
 Co2 Al9 Al1 60.22(3) . 1_554 ?
 Al1 Al9 Al1 87.34(5) 5 1_554 ?
 Al1 Al9 Al1 92.66(5) . 1_554 ?
 Al1 Al9 Al1 180.00(5) 5_556 1_554 ?
 Co2 Al9 Al4 56.22(3) 5 3_455 ?
 Co2 Al9 Al4 123.78(3) . 3_455 ?
 Al1 Al9 Al4 56.34(4) 5 3_455 ?
 Al1 Al9 Al4 123.66(4) . 3_455 ?
 Al1 Al9 Al4 116.45(4) 5_556 3_455 ?
 Al1 Al9 Al4 63.55(4) 1_554 3_455 ?
 Co2 Al9 Al4 123.78(3) 5 7_655 ?
 Co2 Al9 Al4 56.22(3) . 7_655 ?
 Al1 Al9 Al4 123.66(4) 5 7_655 ?
 Al1 Al9 Al4 56.34(4) . 7_655 ?
 Al1 Al9 Al4 63.55(4) 5_556 7_655 ?
 Al1 Al9 Al4 116.45(4) 1_554 7_655 ?
 Al4 Al9 Al4 180.00(4) 3_455 7_655 ?
 Co2 Al9 Al4 56.22(3) 5 3_456 ?
 Co2 Al9 Al4 123.78(3) . 3_456 ?
 Al1 Al9 Al4 116.45(4) 5 3_456 ?
 Al1 Al9 Al4 63.55(4) . 3_456 ?
 Al1 Al9 Al4 56.34(4) 5_556 3_456 ?
 Al1 Al9 Al4 123.66(4) 1_554 3_456 ?
 Al4 Al9 Al4 87.42(5) 3_455 3_456 ?
 Al4 Al9 Al4 92.58(5) 7_655 3_456 ?
 Co2 Al9 Al4 123.78(3) 5 7_654 ?
 Co2 Al9 Al4 56.22(3) . 7_654 ?
 Al1 Al9 Al4 63.55(4) 5 7_654 ?
 Al1 Al9 Al4 116.45(4) . 7_654 ?
 Al1 Al9 Al4 123.66(4) 5_556 7_654 ?
 Al1 Al9 Al4 56.34(4) 1_554 7_654 ?
 Al4 Al9 Al4 92.58(5) 3_455 7_654 ?
 Al4 Al9 Al4 87.42(5) 7_655 7_654 ?
 Al4 Al9 Al4 180.00(4) 3_456 7_654 ?
 Co2 Al9 Ce1 89.159(18) 5 3_455 ?
 Co2 Al9 Ce1 90.841(18) . 3_455 ?
 Al1 Al9 Ce1 118.20(3) 5 3_455 ?

Al1 Al9 Ce1 61.80(3) . 3_455 ?
 Al1 Al9 Ce1 118.20(3) 5_556 3_455 ?
 Al1 Al9 Ce1 61.80(3) 1_554 3_455 ?
 Al4 Al9 Ce1 61.96(3) 3_455 3_455 ?
 Al4 Al9 Ce1 118.04(3) 7_655 3_455 ?
 Al4 Al9 Ce1 61.96(3) 3_456 3_455 ?
 Al4 Al9 Ce1 118.04(3) 7_654 3_455 ?
 Co2 Al9 Ce1 90.841(18) 5 7_655 ?
 Co2 Al9 Ce1 89.159(18) . 7_655 ?
 Al1 Al9 Ce1 61.80(3) 5 7_655 ?
 Al1 Al9 Ce1 118.20(3) . 7_655 ?
 Al1 Al9 Ce1 61.80(3) 5_556 7_655 ?
 Al1 Al9 Ce1 118.20(3) 1_554 7_655 ?
 Al4 Al9 Ce1 118.04(3) 3_455 7_655 ?
 Al4 Al9 Ce1 61.96(3) 7_655 7_655 ?
 Al4 Al9 Ce1 118.04(3) 3_456 7_655 ?
 Al4 Al9 Ce1 61.96(3) 7_654 7_655 ?
 Ce1 Al9 Ce1 180.000(9) 3_455 7_655 ?
 Co1 Al2 Fe1 102.81(6) . 1_556 ?
 Co1 Al2 Co1 102.81(6) . 1_556 ?
 Fe1 Al2 Co1 0.00(2) 1_556 1_556 ?
 Co1 Al2 Al8 56.33(3) . . ?
 Fe1 Al2 Al8 56.33(3) 1_556 . ?
 Co1 Al2 Al8 56.33(3) 1_556 . ?
 Co1 Al2 Al4 113.18(5) . . ?
 Fe1 Al2 Al4 113.18(5) 1_556 . ?
 Co1 Al2 Al4 113.18(5) 1_556 . ?
 Al8 Al2 Al4 101.84(6) . . ?
 Co1 Al2 Al5 58.06(3) . 3_456 ?
 Fe1 Al2 Al5 58.06(3) 1_556 3_456 ?
 Co1 Al2 Al5 58.06(3) 1_556 3_456 ?
 Al8 Al2 Al5 59.26(4) . 3_456 ?
 Al4 Al2 Al5 161.10(8) . 3_456 ?
 Co1 Al2 Al6 50.82(4) . . ?
 Fe1 Al2 Al6 118.83(6) 1_556 . ?
 Co1 Al2 Al6 118.83(6) 1_556 . ?
 Al8 Al2 Al6 102.14(5) . . ?
 Al4 Al2 Al6 127.72(4) . . ?
 Al5 Al2 Al6 62.11(4) 3_456 . ?
 Co1 Al2 Al6 118.83(6) . 1_556 ?
 Fe1 Al2 Al6 50.82(4) 1_556 1_556 ?
 Co1 Al2 Al6 50.82(4) 1_556 1_556 ?
 Al8 Al2 Al6 102.14(5) . 1_556 ?
 Al4 Al2 Al6 127.72(4) . 1_556 ?
 Al5 Al2 Al6 62.11(4) 3_456 1_556 ?
 Al6 Al2 Al6 90.90(7) . 1_556 ?
 Co1 Al2 Ce1 167.28(5) . 1_556 ?
 Fe1 Al2 Ce1 88.64(3) 1_556 1_556 ?
 Co1 Al2 Ce1 88.64(3) 1_556 1_556 ?
 Al8 Al2 Ce1 136.27(3) . 1_556 ?
 Al4 Al2 Ce1 66.06(4) . 1_556 ?
 Al5 Al2 Ce1 126.55(4) 3_456 1_556 ?
 Al6 Al2 Ce1 118.66(6) . 1_556 ?
 Al6 Al2 Ce1 64.44(4) 1_556 1_556 ?
 Co1 Al2 Ce1 88.64(3) . . ?
 Fe1 Al2 Ce1 167.28(5) 1_556 . ?
 Co1 Al2 Ce1 167.28(5) 1_556 . ?
 Al8 Al2 Ce1 136.27(3) . . ?
 Al4 Al2 Ce1 66.06(4) . . ?
 Al5 Al2 Ce1 126.55(4) 3_456 . ?
 Al6 Al2 Ce1 64.44(4) . . ?
 Al6 Al2 Ce1 118.66(6) 1_556 . ?

Ce1 Al2 Ce1 79.47(5) 1_556 . ?
 Fe1 Al5 Co1 0.00(4) 3 3 ?
 Fe1 Al5 Fe1 103.01(6) 3 3_556 ?
 Co1 Al5 Fe1 103.01(6) 3 3_556 ?
 Fe1 Al5 Co1 103.01(6) 3 3_556 ?
 Co1 Al5 Co1 103.01(6) 3 3_556 ?
 Fe1 Al5 Co1 0.00(3) 3_556 3_556 ?
 Fe1 Al5 Al8 56.26(3) 3 3_556 ?
 Co1 Al5 Al8 56.26(3) 3 3_556 ?
 Fe1 Al5 Al8 56.26(3) 3_556 3_556 ?
 Co1 Al5 Al8 56.26(3) 3_556 3_556 ?
 Fe1 Al5 Al3 112.31(4) 3 . ?
 Co1 Al5 Al3 112.31(4) 3 . ?
 Fe1 Al5 Al3 112.31(4) 3_556 . ?
 Co1 Al5 Al3 112.31(4) 3_556 . ?
 Al8 Al5 Al3 100.75(6) 3_556 . ?
 Fe1 Al5 Al2 58.18(3) 3 3_556 ?
 Co1 Al5 Al2 58.18(3) 3 3_556 ?
 Fe1 Al5 Al2 58.18(3) 3_556 3_556 ?
 Co1 Al5 Al2 58.18(3) 3_556 3_556 ?
 Al8 Al5 Al2 58.95(4) 3_556 3_556 ?
 Al3 Al5 Al2 159.70(7) . 3_556 ?
 Fe1 Al5 Al6 117.64(6) 3 3_556 ?
 Co1 Al5 Al6 117.64(6) 3 3_556 ?
 Fe1 Al5 Al6 50.40(4) 3_556 3_556 ?
 Co1 Al5 Al6 50.40(4) 3_556 3_556 ?
 Al8 Al5 Al6 100.97(5) 3_556 3_556 ?
 Al3 Al5 Al6 129.58(4) . 3_556 ?
 Al2 Al5 Al6 60.76(4) 3_556 3_556 ?
 Fe1 Al5 Al6 50.40(4) 3 3 ?
 Co1 Al5 Al6 50.40(4) 3 3 ?
 Fe1 Al5 Al6 117.64(6) 3_556 3 ?
 Co1 Al5 Al6 117.64(6) 3_556 3 ?
 Al8 Al5 Al6 100.97(5) 3_556 3 ?
 Al3 Al5 Al6 129.58(4) . 3 ?
 Al2 Al5 Al6 60.76(4) 3_556 3 ?
 Al6 Al5 Al6 89.43(7) 3_556 3 ?
 Fe1 Al5 Al1 109.08(5) 3 3_556 ?
 Co1 Al5 Al1 109.08(5) 3 3_556 ?
 Fe1 Al5 Al1 109.08(5) 3_556 3_556 ?
 Co1 Al5 Al1 109.08(5) 3_556 3_556 ?
 Al8 Al5 Al1 148.52(7) 3_556 3_556 ?
 Al3 Al5 Al1 110.73(6) . 3_556 ?
 Al2 Al5 Al1 89.57(6) 3_556 3_556 ?
 Al6 Al5 Al1 58.68(4) 3_556 3_556 ?
 Al6 Al5 Al1 58.68(4) 3 3_556 ?
 Fe1 Al5 Ce1 167.59(4) 3 1_556 ?
 Co1 Al5 Ce1 167.59(4) 3 1_556 ?
 Fe1 Al5 Ce1 88.83(3) 3_556 1_556 ?
 Co1 Al5 Ce1 88.83(3) 3_556 1_556 ?
 Al8 Al5 Ce1 135.62(3) 3_556 1_556 ?
 Al3 Al5 Ce1 65.35(4) . 1_556 ?
 Al2 Al5 Ce1 128.03(4) 3_556 1_556 ?
 Al6 Al5 Ce1 67.27(4) 3_556 1_556 ?
 Al6 Al5 Ce1 120.65(6) 3 1_556 ?
 Al1 Al5 Ce1 62.69(3) 3_556 1_556 ?
 Fe1 Al5 Ce1 88.83(3) 3 . ?
 Co1 Al5 Ce1 88.83(3) 3 . ?
 Fe1 Al5 Ce1 167.59(4) 3_556 . ?
 Co1 Al5 Ce1 167.59(4) 3_556 . ?
 Al8 Al5 Ce1 135.62(3) 3_556 . ?
 Al3 Al5 Ce1 65.35(4) . . ?

Al2 Al5 Ce1 128.03(4) 3_556 . ?
 Al6 Al5 Ce1 120.65(6) 3_556 . ?
 Al6 Al5 Ce1 67.27(4) 3 . ?
 Al1 Al5 Ce1 62.69(3) 3_556 . ?
 Ce1 Al5 Ce1 79.13(4) 1_556 . ?
 Co2 Al3 Co2 105.86(6) . 1_556 ?
 Co2 Al3 Al1 59.72(4) . ?
 Co2 Al3 Al1 59.72(4) 1_556 . ?
 Co2 Al3 Al5 115.84(4) . ?
 Co2 Al3 Al5 115.84(4) 1_556 . ?
 Al1 Al3 Al5 169.54(8) . ?
 Co2 Al3 Al4 57.26(3) . 7_655 ?
 Co2 Al3 Al4 57.26(3) 1_556 7_655 ?
 Al1 Al3 Al4 59.46(6) . 7_655 ?
 Al5 Al3 Al4 110.08(7) . 7_655 ?
 Co2 Al3 Al6 50.74(4) . ?
 Co2 Al3 Al6 118.17(6) 1_556 . ?
 Al1 Al3 Al6 59.99(4) . ?
 Al5 Al3 Al6 125.89(5) . ?
 Al4 Al3 Al6 101.17(5) 7_655 . ?
 Co2 Al3 Al6 118.17(6) . 1_556 ?
 Co2 Al3 Al6 50.74(4) 1_556 1_556 ?
 Al1 Al3 Al6 59.99(4) . 1_556 ?
 Al5 Al3 Al6 125.89(5) . 1_556 ?
 Al4 Al3 Al6 101.17(5) 7_655 1_556 ?
 Al6 Al3 Al6 87.64(6) . 1_556 ?
 Co2 Al3 Ce1 163.85(5) . 1_556 ?
 Co2 Al3 Ce1 87.31(3) 1_556 1_556 ?
 Al1 Al3 Ce1 122.92(4) . 1_556 ?
 Al5 Al3 Ce1 64.28(4) . 1_556 ?
 Al4 Al3 Ce1 138.82(3) 7_655 1_556 ?
 Al6 Al3 Ce1 114.92(5) . 1_556 ?
 Al6 Al3 Ce1 63.07(4) 1_556 1_556 ?
 Co2 Al3 Ce1 87.31(3) . ?
 Co2 Al3 Ce1 163.85(5) 1_556 . ?
 Al1 Al3 Ce1 122.92(4) . ?
 Al5 Al3 Ce1 64.28(4) . ?
 Al4 Al3 Ce1 138.82(3) 7_655 . ?
 Al6 Al3 Ce1 63.07(4) . ?
 Al6 Al3 Ce1 114.92(5) 1_556 . ?
 Ce1 Al3 Ce1 78.30(4) 1_556 . ?
 Co2 Al4 Co2 105.60(7) 7_666 7_665 ?
 Co2 Al4 Al2 115.40(5) 7_666 . ?
 Co2 Al4 Al2 115.40(5) 7_665 . ?
 Co2 Al4 Al1 59.66(4) 7_666 7_665 ?
 Co2 Al4 Al1 59.66(4) 7_665 7_665 ?
 Al2 Al4 Al1 168.53(8) . 7_665 ?
 Co2 Al4 Al3 57.11(4) 7_666 7_665 ?
 Co2 Al4 Al3 57.11(4) 7_665 7_665 ?
 Al2 Al4 Al3 109.11(7) . 7_665 ?
 Al1 Al4 Al3 59.42(5) 7_665 7_665 ?
 Co2 Al4 Al9 50.42(3) 7_666 3_556 ?
 Co2 Al4 Al9 117.62(6) 7_665 3_556 ?
 Al2 Al4 Al9 126.95(4) . 3_556 ?
 Al1 Al4 Al9 59.39(4) 7_665 3_556 ?
 Al3 Al4 Al9 100.52(4) 7_665 3_556 ?
 Co2 Al4 Al9 117.62(6) 7_666 3 ?
 Co2 Al4 Al9 50.42(3) 7_665 3 ?
 Al2 Al4 Al9 126.95(4) . 3 ?
 Al1 Al4 Al9 59.39(4) 7_665 3 ?
 Al3 Al4 Al9 100.52(4) 7_665 3 ?
 Al9 Al4 Al9 87.42(5) 3_556 3 ?

Co2 Al4 Ce1 164.25(5) 7_666 . ?
 Co2 Al4 Ce1 87.80(3) 7_665 . ?
 Al2 Al4 Ce1 63.94(4) . ?
 Al1 Al4 Ce1 123.93(5) 7_665 . ?
 Al3 Al4 Ce1 138.64(3) 7_665 . ?
 Al9 Al4 Ce1 116.13(5) 3_556 . ?
 Al9 Al4 Ce1 64.67(3) 3 . ?
 Co2 Al4 Ce1 87.80(3) 7_666 1_556 ?
 Co2 Al4 Ce1 164.25(5) 7_665 1_556 ?
 Al2 Al4 Ce1 63.94(4) . 1_556 ?
 Al1 Al4 Ce1 123.93(5) 7_665 1_556 ?
 Al3 Al4 Ce1 138.64(3) 7_665 1_556 ?
 Al9 Al4 Ce1 64.67(3) 3_556 1_556 ?
 Al9 Al4 Ce1 116.13(5) 3 1_556 ?
 Ce1 Al4 Ce1 77.84(4) . 1_556 ?
 Co2 Al1 Co2 101.48(6) 1_556 . ?
 Co2 Al1 Al3 56.93(3) 1_556 . ?
 Co2 Al1 Al3 56.93(3) . ?
 Co2 Al1 Al4 57.03(4) 1_556 7_655 ?
 Co2 Al1 Al4 57.03(4) . 7_655 ?
 Al3 Al1 Al4 61.13(6) . 7_655 ?
 Co2 Al1 Al9 119.81(6) 1_556 . ?
 Co2 Al1 Al9 51.47(3) . ?
 Al3 Al1 Al9 105.11(5) . ?
 Al4 Al1 Al9 64.27(4) 7_655 . ?
 Co2 Al1 Al9 51.47(3) 1_556 1_556 ?
 Co2 Al1 Al9 119.81(6) . 1_556 ?
 Al3 Al1 Al9 105.11(5) . 1_556 ?
 Al4 Al1 Al9 64.27(4) 7_655 1_556 ?
 Al9 Al1 Al9 92.66(5) . 1_556 ?
 Co2 Al1 Al6 51.44(4) 1_556 1_556 ?
 Co2 Al1 Al6 119.21(6) . 1_556 ?
 Al3 Al1 Al6 63.85(5) . 1_556 ?
 Al4 Al1 Al6 105.02(5) 7_655 1_556 ?
 Al9 Al1 Al6 168.16(7) . 1_556 ?
 Al9 Al1 Al6 86.59(4) 1_556 1_556 ?
 Co2 Al1 Al6 119.21(6) 1_556 . ?
 Co2 Al1 Al6 51.44(4) . ?
 Al3 Al1 Al6 63.85(5) . ?
 Al4 Al1 Al6 105.02(5) 7_655 . ?
 Al9 Al1 Al6 86.59(4) . ?
 Al9 Al1 Al6 168.16(7) 1_556 . ?
 Al6 Al1 Al6 91.73(7) 1_556 . ?
 Co2 Al1 Al5 112.05(4) 1_556 3_456 ?
 Co2 Al1 Al5 112.05(4) . 3_456 ?
 Al3 Al1 Al5 95.95(7) . 3_456 ?
 Al4 Al1 Al5 157.08(8) 7_655 3_456 ?
 Al9 Al1 Al5 127.52(4) . 3_456 ?
 Al9 Al1 Al5 127.52(4) 1_556 3_456 ?
 Al6 Al1 Al5 60.63(4) 1_556 3_456 ?
 Al6 Al1 Al5 60.63(4) . 3_456 ?
 Co2 Al1 Ce1 169.07(5) 1_556 3_455 ?
 Co2 Al1 Ce1 89.44(3) . 3_455 ?
 Al3 Al1 Ce1 131.76(4) . 3_455 ?
 Al4 Al1 Ce1 131.04(4) 7_655 3_455 ?
 Al9 Al1 Ce1 66.91(3) . 3_455 ?
 Al9 Al1 Ce1 122.29(5) 1_556 3_455 ?
 Al6 Al1 Ce1 123.16(6) 1_556 3_455 ?
 Al6 Al1 Ce1 68.15(4) . 3_455 ?
 Al5 Al1 Ce1 63.29(3) 3_456 3_455 ?
 Co2 Al1 Ce1 89.44(3) 1_556 3_456 ?
 Co2 Al1 Ce1 169.07(5) . 3_456 ?

Al3 Al1 Ce1 131.76(4) . 3_456 ?
 Al4 Al1 Ce1 131.04(4) 7_655 3_456 ?
 Al9 Al1 Ce1 122.29(5) . 3_456 ?
 Al9 Al1 Ce1 66.91(3) 1_556 3_456 ?
 Al6 Al1 Ce1 68.15(4) 1_556 3_456 ?
 Al6 Al1 Ce1 123.16(6) . 3_456 ?
 Al5 Al1 Ce1 63.29(4) 3_456 3_456 ?
 Ce1 Al1 Ce1 79.64(5) 3_455 3_456 ?
 Co2 Al7 Fe1 145.93(7) . 3 ?
 Co2 Al7 Co1 145.93(7) . 3 ?
 Fe1 Al7 Co1 0.00(3) 3 3 ?
 Co2 Al7 Fe1 145.98(7) . 7_655 ?
 Fe1 Al7 Fe1 68.08(4) 3 7_655 ?
 Co1 Al7 Fe1 68.08(4) 3 7_655 ?
 Co2 Al7 Co1 145.98(7) . 7_655 ?
 Fe1 Al7 Co1 68.08(4) 3 7_655 ?
 Co1 Al7 Co1 68.08(4) 3 7_655 ?
 Fe1 Al7 Co1 0.00(3) 7_655 7_655 ?
 Co2 Al7 Al8 136.26(2) . 3_556 ?
 Fe1 Al7 Al8 53.24(3) 3 3_556 ?
 Co1 Al7 Al8 53.24(3) 3 3_556 ?
 Fe1 Al7 Al8 53.22(3) 7_655 3_556 ?
 Co1 Al7 Al8 53.22(3) 7_655 3_556 ?
 Co2 Al7 Al8 136.26(2) . 3 ?
 Fe1 Al7 Al8 53.24(3) 3 3 ?
 Co1 Al7 Al8 53.24(3) 3 3 ?
 Fe1 Al7 Al8 53.22(3) 7_655 3 ?
 Co1 Al7 Al8 53.22(3) 7_655 3 ?
 Al8 Al7 Al8 87.49(5) 3_556 3 ?
 Co1 Al6 Co2 177.90(8) . . ?
 Co1 Al6 Al1 119.04(5) . 1_554 ?
 Co2 Al6 Al1 59.78(4) . 1_554 ?
 Co1 Al6 Al1 119.04(5) . . ?
 Co2 Al6 Al1 59.78(4) . . ?
 Al1 Al6 Al1 91.73(7) 1_554 . ?
 Co1 Al6 Al2 59.04(4) . . ?
 Co2 Al6 Al2 122.11(5) . . ?
 Al1 Al6 Al2 177.88(7) 1_554 . ?
 Al1 Al6 Al2 88.64(4) . . ?
 Co1 Al6 Al2 59.04(4) . 1_554 ?
 Co2 Al6 Al2 122.11(5) . 1_554 ?
 Al1 Al6 Al2 88.64(4) 1_554 1_554 ?
 Al1 Al6 Al2 177.88(7) . 1_554 ?
 Al2 Al6 Al2 90.90(7) . 1_554 ?
 Co1 Al6 Al5 58.35(4) . 3_455 ?
 Co2 Al6 Al5 120.46(5) . 3_455 ?
 Al1 Al6 Al5 60.69(4) 1_554 3_455 ?
 Al1 Al6 Al5 121.36(7) . 3_455 ?
 Al2 Al6 Al5 117.39(6) . 3_455 ?
 Al2 Al6 Al5 57.12(4) 1_554 3_455 ?
 Co1 Al6 Al5 58.35(4) . 3_456 ?
 Co2 Al6 Al5 120.46(5) . 3_456 ?
 Al1 Al6 Al5 121.36(7) 1_554 3_456 ?
 Al1 Al6 Al5 60.69(4) . 3_456 ?
 Al2 Al6 Al5 57.12(4) . 3_456 ?
 Al2 Al6 Al5 117.39(6) 1_554 3_456 ?
 Al5 Al6 Al5 89.43(7) 3_455 3_456 ?
 Co1 Al6 Al3 125.00(4) . . ?
 Co2 Al6 Al3 56.14(4) . . ?
 Al1 Al6 Al3 115.92(6) 1_554 . ?
 Al1 Al6 Al3 56.17(4) . . ?
 Al2 Al6 Al3 65.97(4) . . ?

Al2 Al6 Al3 125.43(7) 1_554 . ?
 Al5 Al6 Al3 176.28(7) 3_455 . ?
 Al5 Al6 Al3 91.35(4) 3_456 . ?
 Co1 Al6 Al3 125.00(4) . 1_554 ?
 Co2 Al6 Al3 56.14(4) . 1_554 ?
 Al1 Al6 Al3 56.17(4) 1_554 1_554 ?
 Al1 Al6 Al3 115.92(6) . 1_554 ?
 Al2 Al6 Al3 125.43(7) . 1_554 ?
 Al2 Al6 Al3 65.97(4) 1_554 1_554 ?
 Al5 Al6 Al3 91.35(4) 3_455 1_554 ?
 Al5 Al6 Al3 176.28(7) 3_456 1_554 ?
 Al3 Al6 Al3 87.64(6) . 1_554 ?
 Co1 Al6 Ce1 92.02(5) . . ?
 Co2 Al6 Ce1 90.07(5) . . ?
 Al1 Al6 Ce1 118.81(4) 1_554 . ?
 Al1 Al6 Ce1 118.81(4) . . ?
 Al2 Al6 Ce1 62.71(4) . . ?
 Al2 Al6 Ce1 62.71(4) 1_554 . ?
 Al5 Al6 Ce1 119.82(4) 3_455 . ?
 Al5 Al6 Ce1 119.82(4) 3_456 . ?
 Al3 Al6 Ce1 62.76(4) . . ?
 Al3 Al6 Ce1 62.76(4) 1_554 . ?

_diffn_measured_fraction_theta_max 0.998
 _diffn_reflns_theta_full 31.00
 _diffn_measured_fraction_theta_full 0.998
 _refine_diff_density_max 2.459
 _refine_diff_density_min -1.272
 _refine_diff_density_rms 0.251

data_shelxl

_audit_creation_method SHELXL-97
 _chemical_name_systematic
 ;
 ?
 ;
 _chemical_name_common ?
 _chemical_melting_point ?
 _chemical_formula_moiety ?
 _chemical_formula_sum
 'Al8 Ce Co Fe'
 _chemical_formula_weight 470.74

 loop_
 _atom_type_symbol
 _atom_type_description
 _atom_type_scatter_dispersion_real
 _atom_type_scatter_dispersion_imag
 _atom_type_scatter_source
 'Ce' 'Ce' -0.2486 2.6331
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
 'Fe' 'Fe' 0.3463 0.8444
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
 'Co' 'Co' 0.3494 0.9721
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
 'Al' 'Al' 0.0645 0.0514
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

 _symmetry_cell_setting ?
 _symmetry_space_group_name_H-M ?

```

loop_
_symmetry_equiv_pos_as_xyz
'x, y, z'
'-x, -y, z'
'x+1/2, -y+1/2, -z'
'-x+1/2, y+1/2, -z'
'-x, -y, -z'
'x, y, -z'
'-x-1/2, y-1/2, z'
'x-1/2, -y-1/2, z'

_cell_length_a      12.4820(5)
_cell_length_b      14.401(3)
_cell_length_c      4.029(3)
_cell_angle_alpha   90.00
_cell_angle_beta    90.00
_cell_angle_gamma   90.00
_cell_volume        724.2(5)
_cell_formula_units_Z 4
_cell_measurement_temperature 293(2)
_cell_measurement_reflns_used ?
_cell_measurement_theta_min ?
_cell_measurement_theta_max ?

_exptl_crystal_description ?
_exptl_crystal_colour ?
_exptl_crystal_size_max ?
_exptl_crystal_size_mid ?
_exptl_crystal_size_min ?
_exptl_crystal_density_meas ?
_exptl_crystal_density_diffn 4.317
_exptl_crystal_density_method 'not measured'
_exptl_crystal_F_000 860
_exptl_absorpt_coefficient_mu 11.285
_exptl_absorpt_correction_type ?
_exptl_absorpt_correction_T_min ?
_exptl_absorpt_correction_T_max ?
_exptl_absorpt_process_details ?

_exptl_special_details
;
?
;

_diffn_ambient_temperature 293(2)
_diffn_radiation_wavelength 0.71073
_diffn_radiation_type MoK\alpha
_diffn_radiation_source 'fine-focus sealed tube'
_diffn_radiation_monochromator graphite
_diffn_measurement_device_type ?
_diffn_measurement_method ?
_diffn_detector_area_resol_mean ?
_diffn_standards_number ?
_diffn_standards_interval_count ?
_diffn_standards_interval_time ?
_diffn_standards_decay_% ?
_diffn_reflns_number 2144
_diffn_reflns_av_R_equivalents 0.0263
_diffn_reflns_av_sigma/netI 0.0325
_diffn_reflns_limit_h_min -17
_diffn_reflns_limit_h_max 18

```

```

_diffn_reflns_limit_k_min -20
_diffn_reflns_limit_k_max 20
_diffn_reflns_limit_l_min -5
_diffn_reflns_limit_l_max 5
_diffn_reflns_theta_min 2.83
_diffn_reflns_theta_max 30.99
_reflns_number_total 1300
_reflns_number_gt 1092
_reflns_threshold_expression >2\sigma(I)

_computing_data_collection ?
_computing_cell_refinement ?
_computing_data_reduction ?
_computing_structure_solution ?
_computing_structure_refinement 'SHELXL-97
(Sheldrick, 2008)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F2 against ALL reflections. The
weighted R-factor wR and
goodness of fit S are based on F2, conventional R-
factors R are based
on F, with F set to zero for negative F2. The threshold
expression of
F2 > 2\sigma(F2) is used only for calculating R-factors(gt)
etc. and is
not relevant to the choice of reflections for refinement. R-
factors based
on F2 are statistically about twice as large as those based
on F, and R-
factors based on ALL data will be even larger.
;

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type full
_refine_ls_weighting_scheme calc
_refine_ls_weighting_details
'calc w=1/[\sigma2(Fo2)+(0.0388P)2+3.0837P] where
P=(Fo2+2Fc2)/3'
_atom_sites_solution_primary direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment mixed
_refine_ls_extinction_method SHELXL
_refine_ls_extinction_coef 0.0293(11)
_refine_ls_extinction_expression
'Fc*=kFc[1+0.001xFc2l3/sin(2\theta)]-1/4'
_refine_ls_number_reflns 1300
_refine_ls_number_parameters 74
_refine_ls_number_restraints 1
_refine_ls_R_factor_all 0.0388
_refine_ls_R_factor_gt 0.0298
_refine_ls_wR_factor_ref 0.0864
_refine_ls_wR_factor_gt 0.0696
_refine_ls_goodness_of_fit_ref 1.163
_refine_ls_restrained_S_all 1.163
_refine_ls_shift/su_max 0.001
_refine_ls_shift/su_mean 0.000

```

```

loop_
  _atom_site_label
  _atom_site_type_symbol
  _atom_site_fract_x
  _atom_site_fract_y
  _atom_site_fract_z
  _atom_site_U_iso_or_equiv
  _atom_site_adp_type
  _atom_site_occupancy
  _atom_site_symmetry_multiplicity
  _atom_site_calc_flag
  _atom_site_refinement_flags
  _atom_site_disorder_assembly
  _atom_site_disorder_group
Ce1 Ce 0.34100(3) 0.31861(2) 0.0000 0.01057(15) Uani 1
2 d S . .
Co2 Co 0.15082(6) 0.09679(6) 0.0000 0.0088(3) Uani
0.56(7) 2 d SP . .
Fe2 Fe 0.15082(6) 0.09679(6) 0.0000 0.0088(3) Uani
0.46(8) 2 d SP . .
Co1 Co 0.03428(7) 0.40657(6) 0.0000 0.0100(3) Uani
0.79(7) 2 d SP . .
Fe1 Fe 0.03428(7) 0.40657(6) 0.0000 0.0100(3) Uani
0.21(8) 2 d SP . .
Al8 Al 0.0000 0.5000 0.5000 0.0101(5) Uani 1 4 d S . .
Al9 Al 0.0000 0.0000 0.0000 0.0112(5) Uani 1 4 d S . .
Al2 Al 0.15971(15) 0.37927(14) 0.5000 0.0098(4) Uani 1 2
d S . .
Al5 Al 0.45241(15) 0.17966(13) 0.5000 0.0103(4) Uani 1 2
d S . .
Al3 Al 0.23578(15) 0.17252(13) 0.5000 0.0101(4) Uani 1 2
d S . .
Al4 Al 0.33141(15) 0.49210(13) 0.5000 0.0100(4) Uani 1 2
d S . .
Al1 Al 0.02569(15) 0.13175(13) 0.5000 0.0098(4) Uani 1 2
d S . .
Al7 Al 0.33858(14) 0.04441(14) 0.0000 0.0118(4) Uani 1 2
d S . .
Al6 Al 0.09557(15) 0.25327(12) 0.0000 0.0101(4) Uani 1 2
d S . .

loop_
  _atom_site_aniso_label
  _atom_site_aniso_U_11
  _atom_site_aniso_U_22
  _atom_site_aniso_U_33
  _atom_site_aniso_U_23
  _atom_site_aniso_U_13
  _atom_site_aniso_U_12
Ce1 0.0102(2) 0.0139(2) 0.0076(2) 0.000 0.000 -
0.00091(12)
Co2 0.0089(4) 0.0098(5) 0.0077(4) 0.000 0.000 0.0001(3)
Fe2 0.0089(4) 0.0098(5) 0.0077(4) 0.000 0.000 0.0001(3)
Co1 0.0112(4) 0.0102(5) 0.0085(4) 0.000 0.000 0.0005(3)
Fe1 0.0112(4) 0.0102(5) 0.0085(4) 0.000 0.000 0.0005(3)
Al8 0.0128(12) 0.0080(11) 0.0095(12) 0.000 0.000
0.0008(9)
Al9 0.0100(12) 0.0112(12) 0.0125(12) 0.000 0.000 -
0.0009(9)
Al2 0.0084(8) 0.0116(9) 0.0095(9) 0.000 0.000 0.0000(6)
Al5 0.0092(8) 0.0118(9) 0.0099(8) 0.000 0.000 0.0013(6)
Al3 0.0103(9) 0.0123(9) 0.0077(8) 0.000 0.000 -0.0016(6)

```

```

Al4 0.0112(8) 0.0091(8) 0.0097(8) 0.000 0.000 -0.0020(6)
Al1 0.0095(8) 0.0106(8) 0.0093(8) 0.000 0.000 0.0005(6)
Al7 0.0085(8) 0.0167(10) 0.0102(9) 0.000 0.000 0.0016(7)
Al6 0.0107(9) 0.0087(8) 0.0111(8) 0.000 0.000 -0.0003(6)

```

```

_geom_special_details
;
All s.u.'s (except the s.u. in the dihedral angle between two
l.s. planes)
are estimated using the full covariance matrix. The cell
s.u.'s are taken
into account individually in the estimation of s.u.'s in
distances, angles
and torsion angles; correlations between s.u.'s in cell
parameters are only
used when they are defined by crystal symmetry. An
approximate (isotropic)
treatment of cell s.u.'s is used for estimating s.u.'s
involving l.s. planes.
;

```

```

loop_
  _geom_bond_atom_site_label_1
  _geom_bond_atom_site_label_2
  _geom_bond_distance
  _geom_bond_site_symmetry_2
  _geom_bond_publ_flag
Ce1 Al1 3.1438(17) 3_556 ?
Ce1 Al1 3.1438(17) 3 ?
Ce1 Al2 3.1531(17) 1_554 ?
Ce1 Al2 3.1531(17) . ?
Ce1 Al5 3.1617(17) 1_554 ?
Ce1 Al5 3.1617(17) . ?
Ce1 Al3 3.1952(17) 1_554 ?
Ce1 Al3 3.1952(17) . ?
Ce1 Al6 3.2047(19) . ?
Ce1 Al4 3.2116(17) . ?
Ce1 Al4 3.2116(17) 1_554 ?
Ce1 Al9 3.2806(5) 3 ?
Co2 Al9 2.3424(8) . ?
Co2 Al6 2.357(2) . ?
Co2 Al7 2.462(2) . ?
Co2 Al3 2.5243(16) . ?
Co2 Al3 2.5243(16) 1_554 ?
Co2 Al4 2.5260(16) 7_654 ?
Co2 Al4 2.5260(16) 7_655 ?
Co2 Al1 2.5983(16) 1_554 ?
Co2 Al1 2.5983(16) . ?
Co1 Al6 2.337(2) . ?
Co1 Al8 2.4600(11) . ?
Co1 Al8 2.4600(11) 1_554 ?
Co1 Al7 2.541(2) 7_665 ?
Co1 Al7 2.543(2) 3_455 ?
Co1 Al5 2.5777(16) 3_455 ?
Co1 Al5 2.5777(16) 3_456 ?
Co1 Al2 2.5814(16) . ?
Co1 Al2 2.5814(16) 1_554 ?
Co1 Co1 2.8236(17) 5_565 ?
Co1 Fe1 2.8236(17) 5_565 ?
Al8 Fe1 2.4600(11) 5_566 ?
Al8 Co1 2.4600(11) 5_566 ?
Al8 Fe1 2.4600(11) 5_565 ?

```

Al8 Co1 2.4600(11) 5_565 ?
 Al8 Co1 2.4600(11) 1_556 ?
 Al8 Fe1 2.4600(11) 1_556 ?
 Al8 Al2 2.6451(19) 5_566 ?
 Al8 Al2 2.6451(19) . ?
 Al8 Al5 2.6546(19) 7_665 ?
 Al8 Al5 2.6546(19) 3_456 ?
 Al9 Fe2 2.3424(8) 5 ?
 Al9 Co2 2.3424(8) 5 ?
 Al9 Al1 2.7858(16) 5 ?
 Al9 Al1 2.7858(16) . ?
 Al9 Al1 2.7858(16) 5_556 ?
 Al9 Al1 2.7858(16) 1_554 ?
 Al9 Al4 2.9153(16) 3_455 ?
 Al9 Al4 2.9153(16) 7_655 ?
 Al9 Al4 2.9153(16) 3_456 ?
 Al9 Al4 2.9153(16) 7_654 ?
 Al2 Fe1 2.5814(16) 1_556 ?
 Al2 Co1 2.5814(16) 1_556 ?
 Al2 Al4 2.689(3) . ?
 Al2 Al5 2.723(3) 3_456 ?
 Al2 Al6 2.827(2) . ?
 Al2 Al6 2.827(2) 1_556 ?
 Al2 Ce1 3.1531(17) 1_556 ?
 Al5 Fe1 2.5777(16) 3 ?
 Al5 Co1 2.5777(16) 3 ?
 Al5 Fe1 2.5777(16) 3_556 ?
 Al5 Co1 2.5777(16) 3_556 ?
 Al5 Al8 2.6546(19) 3_556 ?
 Al5 Al3 2.706(3) . ?
 Al5 Al2 2.723(3) 3_556 ?
 Al5 Al6 2.861(2) 3_556 ?
 Al5 Al6 2.861(2) 3 ?
 Al5 Al1 2.866(3) 3_556 ?
 Al5 Ce1 3.1617(17) 1_556 ?
 Al3 Fe2 2.5243(16) 1_556 ?
 Al3 Co2 2.5243(16) 1_556 ?
 Al3 Al1 2.687(3) . ?
 Al3 Al4 2.730(3) 7_655 ?
 Al3 Al6 2.911(2) . ?
 Al3 Al6 2.911(2) 1_556 ?
 Al3 Ce1 3.1952(17) 1_556 ?
 Al4 Fe2 2.5260(16) 7_666 ?
 Al4 Co2 2.5260(16) 7_666 ?
 Al4 Fe2 2.5260(16) 7_665 ?
 Al4 Co2 2.5260(16) 7_665 ?
 Al4 Al1 2.688(3) 7_665 ?
 Al4 Al3 2.730(3) 7_665 ?
 Al4 Al9 2.9153(16) 3_556 ?
 Al4 Al9 2.9153(16) 3 ?
 Al4 Ce1 3.2116(17) 1_556 ?
 Al1 Fe2 2.5983(16) 1_556 ?
 Al1 Co2 2.5983(16) 1_556 ?
 Al1 Al4 2.688(3) 7_655 ?
 Al1 Al9 2.7858(16) 1_556 ?
 Al1 Al6 2.807(2) 1_556 ?
 Al1 Al6 2.807(2) . ?
 Al1 Al5 2.866(3) 3_456 ?
 Al1 Ce1 3.1438(17) 3_455 ?
 Al7 Fe1 2.541(2) 7_655 ?
 Al7 Co1 2.541(2) 7_655 ?
 Al7 Co1 2.543(2) 3 ?

Al7 Fe1 2.543(2) 3 ?
 Al7 Al8 2.9201(16) 3_556 ?
 Al7 Al8 2.9201(16) 3 ?
 Al6 Al1 2.807(2) 1_554 ?
 Al6 Al2 2.827(2) 1_554 ?
 Al6 Al5 2.861(2) 3_455 ?
 Al6 Al5 2.861(2) 3_456 ?
 Al6 Al3 2.911(2) 1_554 ?
 loop_
 _geom_angle_atom_site_label_1
 _geom_angle_atom_site_label_2
 _geom_angle_atom_site_label_3
 _geom_angle
 _geom_angle_site_symmetry_1
 _geom_angle_site_symmetry_3
 _geom_angle_publ_flag
 Al1 Ce1 Al1 79.70(6) 3_556 3 ?
 Al1 Ce1 Al2 150.77(5) 3_556 1_554 ?
 Al1 Ce1 Al2 93.09(5) 3 1_554 ?
 Al1 Ce1 Al2 93.09(5) 3_556 . ?
 Al1 Ce1 Al2 150.77(5) 3 . ?
 Al2 Ce1 Al2 79.42(6) 1_554 . ?
 Al1 Ce1 Al5 103.28(5) 3_556 1_554 ?
 Al1 Ce1 Al5 54.06(5) 3 1_554 ?
 Al2 Ce1 Al5 94.82(5) 1_554 1_554 ?
 Al2 Ce1 Al5 153.91(5) . 1_554 ?
 Al1 Ce1 Al5 54.06(5) 3_556 . ?
 Al1 Ce1 Al5 103.28(5) 3 . ?
 Al2 Ce1 Al5 153.91(5) 1_554 . ?
 Al2 Ce1 Al5 94.82(5) . ?
 Al5 Ce1 Al5 79.16(6) 1_554 . ?
 Al1 Ce1 Al3 148.77(5) 3_556 1_554 ?
 Al1 Ce1 Al3 92.70(5) 3 1_554 ?
 Al2 Ce1 Al3 58.98(5) 1_554 1_554 ?
 Al2 Ce1 Al3 106.87(5) . 1_554 ?
 Al5 Ce1 Al3 50.38(5) 1_554 1_554 ?
 Al5 Ce1 Al3 99.54(5) . 1_554 ?
 Al1 Ce1 Al3 92.70(5) 3_556 . ?
 Al1 Ce1 Al3 148.77(5) 3 . ?
 Al2 Ce1 Al3 106.87(5) 1_554 . ?
 Al2 Ce1 Al3 58.98(5) . ?
 Al5 Ce1 Al3 99.54(5) 1_554 . ?
 Al5 Ce1 Al3 50.38(5) . ?
 Al3 Ce1 Al3 78.17(6) 1_554 . ?
 Al1 Ce1 Al6 140.15(3) 3_556 . ?
 Al1 Ce1 Al6 140.15(3) 3 . ?
 Al2 Ce1 Al6 52.79(4) 1_554 . ?
 Al2 Ce1 Al6 52.79(4) . ?
 Al5 Ce1 Al6 103.57(4) 1_554 . ?
 Al5 Ce1 Al6 103.57(4) . ?
 Al3 Ce1 Al6 54.11(4) 1_554 . ?
 Al3 Ce1 Al6 54.11(4) . ?
 Al1 Ce1 Al4 56.53(5) 3_556 . ?
 Al1 Ce1 Al4 104.62(5) 3 . ?
 Al2 Ce1 Al4 99.12(5) 1_554 . ?
 Al2 Ce1 Al4 49.98(5) . ?
 Al5 Ce1 Al4 155.28(5) 1_554 . ?
 Al5 Ce1 Al4 96.26(5) . ?
 Al3 Ce1 Al4 153.17(5) 1_554 . ?
 Al3 Ce1 Al4 95.82(5) . ?
 Al6 Ce1 Al4 101.12(4) . ?

Al1 Ce1 Al4 104.62(5) 3_556 1_554 ?
 Al1 Ce1 Al4 56.53(5) 3 1_554 ?
 Al2 Ce1 Al4 49.98(5) 1_554 1_554 ?
 Al2 Ce1 Al4 99.12(5) . 1_554 ?
 Al5 Ce1 Al4 96.26(5) 1_554 1_554 ?
 Al5 Ce1 Al4 155.28(5) . 1_554 ?
 Al3 Ce1 Al4 95.82(5) 1_554 1_554 ?
 Al3 Ce1 Al4 153.17(5) . 1_554 ?
 Al6 Ce1 Al4 101.12(4) . 1_554 ?
 Al4 Ce1 Al4 77.70(6) . 1_554 ?
 Al1 Ce1 Al9 51.34(3) 3_556 3 ?
 Al1 Ce1 Al9 51.34(3) 3 3 ?
 Al2 Ce1 Al9 102.33(4) . 1_554 3 ?
 Al2 Ce1 Al9 102.33(4) . 3 ?
 Al5 Ce1 Al9 103.76(4) 1_554 3 ?
 Al5 Ce1 Al9 103.76(4) . 3 ?
 Al3 Ce1 Al9 140.62(3) 1_554 3 ?
 Al3 Ce1 Al9 140.62(3) . 3 ?
 Al6 Ce1 Al9 144.30(3) . 3 ?
 Al4 Ce1 Al9 53.35(3) . 3 ?
 Al4 Ce1 Al9 53.35(3) 1_554 3 ?
 Al9 Co2 Al6 109.50(6) . . ?
 Al9 Co2 Al7 125.64(6) . . ?
 Al6 Co2 Al7 124.86(8) . . ?
 Al9 Co2 Al3 126.49(4) . . ?
 Al6 Co2 Al3 73.13(5) . . ?
 Al7 Co2 Al3 74.48(5) . . ?
 Al9 Co2 Al3 126.49(4) . 1_554 ?
 Al6 Co2 Al3 73.13(5) . 1_554 ?
 Al7 Co2 Al3 74.48(5) . 1_554 ?
 Al3 Co2 Al3 105.89(8) . 1_554 ?
 Al9 Co2 Al4 73.46(5) . 7_654 ?
 Al6 Co2 Al4 126.62(4) . 7_654 ?
 Al7 Co2 Al4 74.55(6) . 7_654 ?
 Al3 Co2 Al4 149.03(7) . 7_654 ?
 Al3 Co2 Al4 65.45(6) 1_554 7_654 ?
 Al9 Co2 Al4 73.46(5) . 7_655 ?
 Al6 Co2 Al4 126.62(4) . 7_655 ?
 Al7 Co2 Al4 74.55(6) . 7_655 ?
 Al3 Co2 Al4 65.45(6) . 7_655 ?
 Al3 Co2 Al4 149.03(7) 1_554 7_655 ?
 Al4 Co2 Al4 105.79(8) 7_654 7_655 ?
 Al9 Co2 Al1 68.42(4) . 1_554 ?
 Al6 Co2 Al1 68.83(5) . 1_554 ?
 Al7 Co2 Al1 129.17(4) . 1_554 ?
 Al3 Co2 Al1 141.96(7) . 1_554 ?
 Al3 Co2 Al1 63.26(6) 1_554 1_554 ?
 Al4 Co2 Al1 63.26(6) 7_654 1_554 ?
 Al4 Co2 Al1 141.88(7) 7_655 1_554 ?
 Al9 Co2 Al1 68.42(4) . . ?
 Al6 Co2 Al1 68.83(5) . . ?
 Al7 Co2 Al1 129.17(4) . . ?
 Al3 Co2 Al1 63.26(6) . . ?
 Al3 Co2 Al1 141.96(7) 1_554 . ?
 Al4 Co2 Al1 141.88(7) 7_654 . ?
 Al4 Co2 Al1 63.26(6) 7_655 . ?
 Al1 Co2 Al1 101.67(8) 1_554 . ?
 Al6 Co1 Al8 125.01(2) . . ?
 Al6 Co1 Al8 125.01(2) . 1_554 ?
 Al8 Co1 Al8 109.95(5) . 1_554 ?
 Al6 Co1 Al7 122.24(7) . 7_665 ?
 Al8 Co1 Al7 71.42(3) . 7_665 ?

Al8 Co1 Al7 71.42(3) 1_554 7_665 ?
 Al6 Co1 Al7 125.23(7) . 3_455 ?
 Al8 Co1 Al7 71.40(3) . 3_455 ?
 Al8 Co1 Al7 71.40(3) 1_554 3_455 ?
 Al7 Co1 Al7 112.52(6) 7_665 3_455 ?
 Al6 Co1 Al5 71.01(5) . 3_455 ?
 Al8 Co1 Al5 146.57(6) . 3_455 ?
 Al8 Co1 Al5 63.55(5) 1_554 3_455 ?
 Al7 Co1 Al5 128.60(4) 7_665 3_455 ?
 Al7 Co1 Al5 75.70(5) 3_455 3_455 ?
 Al6 Co1 Al5 71.01(5) . 3_456 ?
 Al8 Co1 Al5 63.55(5) . 3_456 ?
 Al8 Co1 Al5 146.57(6) 1_554 3_456 ?
 Al7 Co1 Al5 128.60(4) 7_665 3_456 ?
 Al7 Co1 Al5 75.70(5) 3_455 3_456 ?
 Al5 Co1 Al5 102.80(8) 3_455 3_456 ?
 Al6 Co1 Al2 69.97(5) . . ?
 Al8 Co1 Al2 63.24(5) . . ?
 Al8 Co1 Al2 145.88(6) 1_554 . ?
 Al7 Co1 Al2 74.94(5) 7_665 . ?
 Al7 Co1 Al2 128.68(4) 3_455 . ?
 Al5 Co1 Al2 140.98(7) 3_455 . ?
 Al5 Co1 Al2 63.72(6) 3_456 . ?
 Al6 Co1 Al2 69.97(5) . 1_554 ?
 Al8 Co1 Al2 145.88(6) . 1_554 ?
 Al8 Co1 Al2 63.24(5) 1_554 1_554 ?
 Al7 Co1 Al2 74.94(5) 7_665 1_554 ?
 Al7 Co1 Al2 128.68(4) 3_455 1_554 ?
 Al5 Co1 Al2 63.72(6) 3_455 1_554 ?
 Al5 Co1 Al2 140.98(7) 3_456 1_554 ?
 Al2 Co1 Al2 102.59(8) . 1_554 ?
 Al6 Co1 Co1 178.53(7) . 5_565 ?
 Al8 Co1 Co1 54.98(2) . 5_565 ?
 Al8 Co1 Co1 54.98(2) 1_554 5_565 ?
 Al7 Co1 Co1 56.29(5) 7_665 5_565 ?
 Al7 Co1 Co1 56.24(5) 3_455 5_565 ?
 Al5 Co1 Co1 109.81(5) 3_455 5_565 ?
 Al5 Co1 Co1 109.81(5) 3_456 5_565 ?
 Al2 Co1 Co1 109.20(5) . 5_565 ?
 Al2 Co1 Co1 109.20(5) 1_554 5_565 ?
 Al6 Co1 Fe1 178.53(7) . 5_565 ?
 Al8 Co1 Fe1 54.98(2) . 5_565 ?
 Al8 Co1 Fe1 54.98(2) 1_554 5_565 ?
 Al7 Co1 Fe1 56.29(5) 7_665 5_565 ?
 Al7 Co1 Fe1 56.24(5) 3_455 5_565 ?
 Al5 Co1 Fe1 109.81(5) 3_455 5_565 ?
 Al5 Co1 Fe1 109.81(5) 3_456 5_565 ?
 Al2 Co1 Fe1 109.20(5) . 5_565 ?
 Al2 Co1 Fe1 109.20(5) 1_554 5_565 ?
 Co1 Co1 Fe1 0.00(3) 5_565 5_565 ?
 Co1 Al8 Fe1 180.0 . 5_566 ?
 Co1 Al8 Co1 180.0 . 5_566 ?
 Fe1 Al8 Co1 0.00(4) 5_566 5_566 ?
 Co1 Al8 Fe1 70.05(5) . 5_565 ?
 Fe1 Al8 Fe1 109.95(5) 5_566 5_565 ?
 Co1 Al8 Fe1 109.95(5) 5_566 5_565 ?
 Co1 Al8 Co1 70.05(5) . 5_565 ?
 Fe1 Al8 Co1 109.95(5) 5_566 5_565 ?
 Co1 Al8 Co1 109.95(5) 5_566 5_565 ?
 Fe1 Al8 Co1 0.00(5) 5_565 5_565 ?
 Co1 Al8 Co1 109.95(5) . 1_556 ?
 Fe1 Al8 Co1 70.05(5) 5_566 1_556 ?

Co1 Al8 Co1 70.05(5) 5_566 1_556 ?
 Fe1 Al8 Co1 180.00(3) 5_565 1_556 ?
 Co1 Al8 Co1 180.00(3) 5_565 1_556 ?
 Co1 Al8 Fe1 109.95(5) . 1_556 ?
 Fe1 Al8 Fe1 70.05(5) 5_566 1_556 ?
 Co1 Al8 Fe1 70.05(5) 5_566 1_556 ?
 Fe1 Al8 Fe1 180.00(3) 5_565 1_556 ?
 Co1 Al8 Fe1 180.00(3) 5_565 1_556 ?
 Co1 Al8 Fe1 0.00(3) 1_556 1_556 ?
 Co1 Al8 Al2 119.38(3) . 5_566 ?
 Fe1 Al8 Al2 60.62(3) 5_566 5_566 ?
 Co1 Al8 Al2 60.62(3) 5_566 5_566 ?
 Fe1 Al8 Al2 60.62(3) 5_565 5_566 ?
 Co1 Al8 Al2 60.62(3) 5_565 5_566 ?
 Co1 Al8 Al2 119.38(3) 1_556 5_566 ?
 Fe1 Al8 Al2 119.38(3) 1_556 5_566 ?
 Co1 Al8 Al2 60.62(3) . . ?
 Fe1 Al8 Al2 119.38(3) 5_566 . ?
 Co1 Al8 Al2 119.38(3) 5_566 . ?
 Fe1 Al8 Al2 119.38(3) 5_565 . ?
 Co1 Al8 Al2 119.38(3) 5_565 . ?
 Co1 Al8 Al2 60.62(3) 1_556 . ?
 Fe1 Al8 Al2 60.62(3) 1_556 . ?
 Al2 Al8 Al2 180.0 5_566 . ?
 Co1 Al8 Al5 119.61(3) . 7_665 ?
 Fe1 Al8 Al5 60.39(3) 5_566 7_665 ?
 Co1 Al8 Al5 60.39(3) 5_566 7_665 ?
 Fe1 Al8 Al5 60.39(3) 5_565 7_665 ?
 Co1 Al8 Al5 60.39(3) 5_565 7_665 ?
 Co1 Al8 Al5 119.61(3) 1_556 7_665 ?
 Fe1 Al8 Al5 119.61(3) 1_556 7_665 ?
 Al2 Al8 Al5 61.84(6) 5_566 7_665 ?
 Al2 Al8 Al5 118.16(6) . 7_665 ?
 Co1 Al8 Al5 60.39(3) . 3_456 ?
 Fe1 Al8 Al5 119.61(3) 5_566 3_456 ?
 Co1 Al8 Al5 119.61(3) 5_566 3_456 ?
 Fe1 Al8 Al5 119.61(3) 5_565 3_456 ?
 Co1 Al8 Al5 119.61(3) 5_565 3_456 ?
 Co1 Al8 Al5 60.39(3) 1_556 3_456 ?
 Fe1 Al8 Al5 60.39(3) 1_556 3_456 ?
 Al2 Al8 Al5 118.16(6) 5_566 3_456 ?
 Al2 Al8 Al5 61.84(6) . 3_456 ?
 Al5 Al8 Al5 180.0 7_665 3_456 ?
 Fe2 Al9 Co2 0.00(4) 5 5 ?
 Fe2 Al9 Co2 180.00(4) 5 . ?
 Co2 Al9 Co2 180.00(4) 5 . ?
 Fe2 Al9 Al1 60.15(4) 5 5 ?
 Co2 Al9 Al1 60.15(4) 5 5 ?
 Co2 Al9 Al1 119.85(4) . 5 ?
 Fe2 Al9 Al1 119.85(4) 5 . ?
 Co2 Al9 Al1 119.85(4) 5 . ?
 Co2 Al9 Al1 60.15(4) . . ?
 Al1 Al9 Al1 180.00(10) 5 . ?
 Fe2 Al9 Al1 60.15(4) 5 5_556 ?
 Co2 Al9 Al1 60.15(4) 5 5_556 ?
 Co2 Al9 Al1 119.85(4) . 5_556 ?
 Al1 Al9 Al1 92.63(7) 5 5_556 ?
 Al1 Al9 Al1 87.37(7) . 5_556 ?
 Fe2 Al9 Al1 119.85(4) 5 1_554 ?
 Co2 Al9 Al1 119.85(4) 5 1_554 ?
 Co2 Al9 Al1 60.15(4) . 1_554 ?
 Al1 Al9 Al1 87.37(7) 5 1_554 ?

Al1 Al9 Al1 92.63(7) . 1_554 ?
 Al1 Al9 Al1 180.00(6) 5_556 1_554 ?
 Fe2 Al9 Al4 56.16(4) 5 3_455 ?
 Co2 Al9 Al4 56.16(4) 5 3_455 ?
 Co2 Al9 Al4 123.84(4) . 3_455 ?
 Al1 Al9 Al4 56.21(5) 5 3_455 ?
 Al1 Al9 Al4 123.79(5) . 3_455 ?
 Al1 Al9 Al4 116.31(5) 5_556 3_455 ?
 Al1 Al9 Al4 63.69(5) 1_554 3_455 ?
 Fe2 Al9 Al4 123.84(4) 5 7_655 ?
 Co2 Al9 Al4 123.84(4) 5 7_655 ?
 Co2 Al9 Al4 56.16(4) . 7_655 ?
 Al1 Al9 Al4 123.79(5) 5 7_655 ?
 Al1 Al9 Al4 56.21(5) . 7_655 ?
 Al1 Al9 Al4 63.69(5) 5_556 7_655 ?
 Al1 Al9 Al4 116.31(5) 1_554 7_655 ?
 Al4 Al9 Al4 180.00(9) 3_455 7_655 ?
 Fe2 Al9 Al4 56.16(4) 5 3_456 ?
 Co2 Al9 Al4 56.16(4) 5 3_456 ?
 Co2 Al9 Al4 123.84(4) . 3_456 ?
 Al1 Al9 Al4 116.31(5) 5 3_456 ?
 Al1 Al9 Al4 63.69(5) . 3_456 ?
 Al1 Al9 Al4 56.21(5) 5_556 3_456 ?
 Al1 Al9 Al4 123.79(5) 1_554 3_456 ?
 Al4 Al9 Al4 87.42(6) 3_455 3_456 ?
 Al4 Al9 Al4 92.58(6) 7_655 3_456 ?
 Fe2 Al9 Al4 123.84(4) 5 7_654 ?
 Co2 Al9 Al4 123.84(4) 5 7_654 ?
 Co2 Al9 Al4 56.16(4) . 7_654 ?
 Al1 Al9 Al4 63.69(5) 5 7_654 ?
 Al1 Al9 Al4 116.31(5) . 7_654 ?
 Al1 Al9 Al4 123.79(5) 5_556 7_654 ?
 Al1 Al9 Al4 56.21(5) 1_554 7_654 ?
 Al4 Al9 Al4 92.58(6) 3_455 7_654 ?
 Al4 Al9 Al4 87.42(6) 7_655 7_654 ?
 Al4 Al9 Al4 180.00(5) 3_456 7_654 ?
 Co1 Al2 Fe1 102.59(8) . 1_556 ?
 Co1 Al2 Co1 102.59(8) . 1_556 ?
 Fe1 Al2 Co1 0.00(3) 1_556 1_556 ?
 Co1 Al2 Al8 56.14(4) . . ?
 Fe1 Al2 Al8 56.14(4) 1_556 . ?
 Co1 Al2 Al8 56.14(4) 1_556 . ?
 Co1 Al2 Al4 113.03(6) . . ?
 Fe1 Al2 Al4 113.03(6) 1_556 . ?
 Co1 Al2 Al4 113.03(6) 1_556 . ?
 Al8 Al2 Al4 101.74(8) . . ?
 Co1 Al2 Al5 58.08(4) . 3_456 ?
 Fe1 Al2 Al5 58.08(4) 1_556 3_456 ?
 Co1 Al2 Al5 58.08(4) 1_556 3_456 ?
 Al8 Al2 Al5 59.25(6) . 3_456 ?
 Al4 Al2 Al5 160.99(10) . 3_456 ?
 Co1 Al2 Al6 50.94(5) . . ?
 Fe1 Al2 Al6 118.82(8) 1_556 . ?
 Co1 Al2 Al6 118.82(8) 1_556 . ?
 Al8 Al2 Al6 102.03(6) . . ?
 Al4 Al2 Al6 127.84(5) . . ?
 Al5 Al2 Al6 62.02(6) 3_456 . ?
 Co1 Al2 Al6 118.82(8) . 1_556 ?
 Fe1 Al2 Al6 50.94(5) 1_556 1_556 ?
 Co1 Al2 Al6 50.94(5) 1_556 1_556 ?
 Al8 Al2 Al6 102.03(6) . 1_556 ?
 Al4 Al2 Al6 127.84(5) . 1_556 ?

Al5 Al2 Al6 62.02(6) 3_456 1_556 ?
 Al6 Al2 Al6 90.89(8) . 1_556 ?
 Co1 Al2 Ce1 167.43(6) . 1_556 ?
 Fe1 Al2 Ce1 88.79(4) 1_556 1_556 ?
 Co1 Al2 Ce1 88.79(4) 1_556 1_556 ?
 Al8 Al2 Ce1 136.30(4) . 1_556 ?
 Al4 Al2 Ce1 66.14(5) . 1_556 ?
 Al5 Al2 Ce1 126.55(6) 3_456 1_556 ?
 Al6 Al2 Ce1 118.73(8) . 1_556 ?
 Al6 Al2 Ce1 64.54(5) 1_556 1_556 ?
 Co1 Al2 Ce1 88.79(4) . . ?
 Fe1 Al2 Ce1 167.43(6) 1_556 . ?
 Co1 Al2 Ce1 167.43(6) 1_556 . ?
 Al8 Al2 Ce1 136.30(4) . . ?
 Al4 Al2 Ce1 66.14(5) . . ?
 Al5 Al2 Ce1 126.55(6) 3_456 . ?
 Al6 Al2 Ce1 64.54(5) . . ?
 Al6 Al2 Ce1 118.73(8) 1_556 . ?
 Ce1 Al2 Ce1 79.42(6) 1_556 . ?
 Fe1 Al5 Co1 0.00(5) 3 3 ?
 Fe1 Al5 Fe1 102.80(8) 3 3_556 ?
 Co1 Al5 Fe1 102.80(8) 3 3_556 ?
 Fe1 Al5 Co1 102.80(8) 3 3_556 ?
 Co1 Al5 Co1 102.80(8) 3 3_556 ?
 Fe1 Al5 Co1 0.00(3) 3_556 3_556 ?
 Fe1 Al5 Al8 56.06(4) 3 3_556 ?
 Co1 Al5 Al8 56.06(4) 3 3_556 ?
 Fe1 Al5 Al8 56.06(4) 3_556 3_556 ?
 Co1 Al5 Al8 56.06(4) 3_556 3_556 ?
 Fe1 Al5 Al3 112.20(6) 3 . ?
 Co1 Al5 Al3 112.20(6) 3 . ?
 Fe1 Al5 Al3 112.20(6) 3_556 . ?
 Co1 Al5 Al3 112.20(6) 3_556 . ?
 Al8 Al5 Al3 100.75(7) 3_556 . ?
 Fe1 Al5 Al2 58.21(5) 3 3_556 ?
 Co1 Al5 Al2 58.21(5) 3 3_556 ?
 Fe1 Al5 Al2 58.21(5) 3_556 3_556 ?
 Co1 Al5 Al2 58.21(5) 3_556 3_556 ?
 Al8 Al5 Al2 58.91(6) 3_556 3_556 ?
 Al3 Al5 Al2 159.66(9) . 3_556 ?
 Fe1 Al5 Al6 117.73(8) 3 3_556 ?
 Co1 Al5 Al6 117.73(8) 3 3_556 ?
 Fe1 Al5 Al6 50.56(5) 3_556 3_556 ?
 Co1 Al5 Al6 50.56(5) 3_556 3_556 ?
 Al8 Al5 Al6 100.91(6) 3_556 3_556 ?
 Al3 Al5 Al6 129.57(5) . 3_556 ?
 Al2 Al5 Al6 60.77(6) 3_556 3_556 ?
 Fe1 Al5 Al6 50.56(5) 3 3 ?
 Co1 Al5 Al6 50.56(5) 3 3 ?
 Fe1 Al5 Al6 117.73(8) 3_556 3 ?
 Co1 Al5 Al6 117.73(8) 3_556 3 ?
 Al8 Al5 Al6 100.91(6) 3_556 3 ?
 Al3 Al5 Al6 129.57(5) . 3 ?
 Al2 Al5 Al6 60.77(6) 3_556 3 ?
 Al6 Al5 Al6 89.53(8) 3_556 3 ?
 Fe1 Al5 Al1 109.27(6) 3 3_556 ?
 Co1 Al5 Al1 109.27(6) 3 3_556 ?
 Fe1 Al5 Al1 109.27(6) 3_556 3_556 ?
 Co1 Al5 Al1 109.27(6) 3_556 3_556 ?
 Al8 Al5 Al1 148.46(9) 3_556 3_556 ?
 Al3 Al5 Al1 110.79(8) . 3_556 ?
 Al2 Al5 Al1 89.55(8) 3_556 3_556 ?

Al6 Al5 Al1 58.71(5) 3_556 3_556 ?
 Al6 Al5 Al1 58.71(5) 3 3_556 ?
 Fe1 Al5 Ce1 167.75(6) 3 1_556 ?
 Co1 Al5 Ce1 167.75(6) 3 1_556 ?
 Fe1 Al5 Ce1 88.93(4) 3_556 1_556 ?
 Co1 Al5 Ce1 88.93(4) 3_556 1_556 ?
 Al8 Al5 Ce1 135.67(4) 3_556 1_556 ?
 Al3 Al5 Ce1 65.45(5) . 1_556 ?
 Al2 Al5 Ce1 127.97(5) 3_556 1_556 ?
 Al6 Al5 Ce1 67.19(5) 3_556 1_556 ?
 Al6 Al5 Ce1 120.64(7) 3 1_556 ?
 Al1 Al5 Ce1 62.65(4) 3_556 1_556 ?
 Fe1 Al5 Ce1 88.93(4) 3 . ?
 Co1 Al5 Ce1 88.93(4) 3 . ?
 Fe1 Al5 Ce1 167.75(6) 3_556 . ?
 Co1 Al5 Ce1 167.75(6) 3_556 . ?
 Al8 Al5 Ce1 135.67(4) 3_556 . ?
 Al3 Al5 Ce1 65.45(5) . . ?
 Al2 Al5 Ce1 127.97(5) 3_556 . ?
 Al6 Al5 Ce1 120.64(7) 3_556 . ?
 Al6 Al5 Ce1 67.19(5) 3 . ?
 Al1 Al5 Ce1 62.65(4) 3_556 . ?
 Ce1 Al5 Ce1 79.16(6) 1_556 . ?
 Co2 Al3 Fe2 105.89(8) . 1_556 ?
 Co2 Al3 Co2 105.89(8) . 1_556 ?
 Fe2 Al3 Co2 0.00(5) 1_556 1_556 ?
 Co2 Al3 Al1 59.71(5) . . ?
 Fe2 Al3 Al1 59.71(5) 1_556 . ?
 Co2 Al3 Al1 59.71(5) 1_556 . ?
 Co2 Al3 Al5 115.86(5) . . ?
 Fe2 Al3 Al5 115.86(5) 1_556 . ?
 Co2 Al3 Al5 115.86(5) 1_556 . ?
 Al1 Al3 Al5 169.56(10) . . ?
 Co2 Al3 Al4 57.30(4) . 7_655 ?
 Fe2 Al3 Al4 57.30(4) 1_556 7_655 ?
 Co2 Al3 Al4 57.30(4) 1_556 7_655 ?
 Al1 Al3 Al4 59.49(7) . 7_655 ?
 Al5 Al3 Al4 110.07(8) . 7_655 ?
 Co2 Al3 Al6 50.78(5) . . ?
 Fe2 Al3 Al6 118.18(8) 1_556 . ?
 Co2 Al3 Al6 118.18(8) 1_556 . ?
 Al1 Al3 Al6 60.04(5) . . ?
 Al5 Al3 Al6 125.85(6) . . ?
 Al4 Al3 Al6 101.27(7) 7_655 . ?
 Co2 Al3 Al6 118.18(8) . 1_556 ?
 Fe2 Al3 Al6 50.78(5) 1_556 1_556 ?
 Co2 Al3 Al6 50.78(5) 1_556 1_556 ?
 Al1 Al3 Al6 60.04(5) . 1_556 ?
 Al5 Al3 Al6 125.85(6) . 1_556 ?
 Al4 Al3 Al6 101.27(7) 7_655 1_556 ?
 Al6 Al3 Al6 87.59(8) . 1_556 ?
 Co2 Al3 Ce1 163.80(6) . 1_556 ?
 Fe2 Al3 Ce1 87.36(4) 1_556 1_556 ?
 Co2 Al3 Ce1 87.36(4) 1_556 1_556 ?
 Al1 Al3 Ce1 123.02(6) . 1_556 ?
 Al5 Al3 Ce1 64.17(4) . 1_556 ?
 Al4 Al3 Ce1 138.84(4) 7_655 1_556 ?
 Al6 Al3 Ce1 114.86(7) . 1_556 ?
 Al6 Al3 Ce1 63.11(4) 1_556 1_556 ?
 Co2 Al3 Ce1 87.36(4) . . ?
 Fe2 Al3 Ce1 163.80(6) 1_556 . ?
 Co2 Al3 Ce1 163.80(6) 1_556 . ?

Al1 Al3 Ce1 123.02(6) . . ?
 Al5 Al3 Ce1 64.17(4) . . ?
 Al4 Al3 Ce1 138.84(4) 7_655 . ?
 Al6 Al3 Ce1 63.11(4) . . ?
 Al6 Al3 Ce1 114.86(7) 1_556 . ?
 Ce1 Al3 Ce1 78.17(6) 1_556 . ?
 Fe2 Al4 Co2 0.0 7_666 7_666 ?
 Fe2 Al4 Fe2 105.79(8) 7_666 7_665 ?
 Co2 Al4 Fe2 105.79(8) 7_666 7_665 ?
 Fe2 Al4 Co2 105.79(8) 7_666 7_665 ?
 Co2 Al4 Co2 105.79(8) 7_666 7_665 ?
 Fe2 Al4 Co2 0.00(3) 7_665 7_665 ?
 Fe2 Al4 Al1 59.68(5) 7_666 7_665 ?
 Co2 Al4 Al1 59.68(5) 7_666 7_665 ?
 Fe2 Al4 Al1 59.68(5) 7_665 7_665 ?
 Co2 Al4 Al1 59.68(5) 7_665 7_665 ?
 Fe2 Al4 Al2 115.50(6) 7_666 . ?
 Co2 Al4 Al2 115.50(6) 7_666 . ?
 Fe2 Al4 Al2 115.50(6) 7_665 . ?
 Co2 Al4 Al2 115.50(6) 7_665 . ?
 Al1 Al4 Al2 168.74(10) 7_665 . ?
 Fe2 Al4 Al3 57.25(5) 7_666 7_665 ?
 Co2 Al4 Al3 57.25(5) 7_666 7_665 ?
 Fe2 Al4 Al3 57.25(5) 7_665 7_665 ?
 Co2 Al4 Al3 57.25(5) 7_665 7_665 ?
 Al1 Al4 Al3 59.46(7) 7_665 7_665 ?
 Al2 Al4 Al3 109.28(9) . 7_665 ?
 Fe2 Al4 Al9 50.38(3) 7_666 3_556 ?
 Co2 Al4 Al9 50.38(3) 7_666 3_556 ?
 Fe2 Al4 Al9 117.67(7) 7_665 3_556 ?
 Co2 Al4 Al9 117.67(7) 7_665 3_556 ?
 Al1 Al4 Al9 59.46(4) 7_665 3_556 ?
 Al2 Al4 Al9 126.78(5) . 3_556 ?
 Al3 Al4 Al9 100.64(6) 7_665 3_556 ?
 Fe2 Al4 Al9 117.67(7) 7_666 3 ?
 Co2 Al4 Al9 117.67(7) 7_666 3 ?
 Fe2 Al4 Al9 50.38(3) 7_665 3 ?
 Co2 Al4 Al9 50.38(3) 7_665 3 ?
 Al1 Al4 Al9 59.46(4) 7_665 3 ?
 Al2 Al4 Al9 126.78(5) . 3 ?
 Al3 Al4 Al9 100.64(6) 7_665 3 ?
 Al9 Al4 Al9 87.42(6) 3_556 3 ?
 Fe2 Al4 Ce1 164.01(7) 7_666 . ?
 Co2 Al4 Ce1 164.01(7) 7_666 . ?
 Fe2 Al4 Ce1 87.75(4) 7_665 . ?
 Co2 Al4 Ce1 87.75(4) 7_665 . ?
 Al1 Al4 Ce1 123.87(6) 7_665 . ?
 Al2 Al4 Ce1 63.88(5) . . ?
 Al3 Al4 Ce1 138.74(4) 7_665 . ?
 Al9 Al4 Ce1 115.91(7) 3_556 . ?
 Al9 Al4 Ce1 64.53(3) 3 . ?
 Fe2 Al4 Ce1 87.75(4) 7_666 1_556 ?
 Co2 Al4 Ce1 87.75(4) 7_666 1_556 ?
 Fe2 Al4 Ce1 164.01(7) 7_665 1_556 ?
 Co2 Al4 Ce1 164.01(7) 7_665 1_556 ?
 Al1 Al4 Ce1 123.87(6) 7_665 1_556 ?
 Al2 Al4 Ce1 63.88(5) . 1_556 ?
 Al3 Al4 Ce1 138.74(4) 7_665 1_556 ?
 Al9 Al4 Ce1 64.53(3) 3_556 1_556 ?
 Al9 Al4 Ce1 115.91(7) 3 1_556 ?
 Ce1 Al4 Ce1 77.70(6) . 1_556 ?
 Fe2 Al1 Co2 0.00(4) 1_556 1_556 ?

Fe2 Al1 Co2 101.67(8) 1_556 . ?
 Co2 Al1 Co2 101.67(8) 1_556 . ?
 Fe2 Al1 Al3 57.03(4) 1_556 . ?
 Co2 Al1 Al3 57.03(4) 1_556 . ?
 Co2 Al1 Al3 57.03(4) . . ?
 Fe2 Al1 Al4 57.06(5) 1_556 7_655 ?
 Co2 Al1 Al4 57.06(5) 1_556 7_655 ?
 Co2 Al1 Al4 57.06(5) . 7_655 ?
 Al3 Al1 Al4 61.05(7) . 7_655 ?
 Fe2 Al1 Al9 119.86(8) 1_556 . ?
 Co2 Al1 Al9 119.86(8) 1_556 . ?
 Co2 Al1 Al9 51.43(3) . . ?
 Al3 Al1 Al9 105.14(6) . . ?
 Al4 Al1 Al9 64.33(5) 7_655 . ?
 Fe2 Al1 Al9 51.43(3) 1_556 1_556 ?
 Co2 Al1 Al9 51.43(3) 1_556 1_556 ?
 Co2 Al1 Al9 119.86(8) . 1_556 ?
 Al3 Al1 Al9 105.14(6) . 1_556 ?
 Al4 Al1 Al9 64.33(5) 7_655 1_556 ?
 Al9 Al1 Al9 92.63(7) . 1_556 ?
 Fe2 Al1 Al6 51.51(5) 1_556 1_556 ?
 Co2 Al1 Al6 51.51(5) 1_556 1_556 ?
 Co2 Al1 Al6 119.36(8) . 1_556 ?
 Al3 Al1 Al6 63.93(6) . 1_556 ?
 Al4 Al1 Al6 105.08(7) 7_655 1_556 ?
 Al9 Al1 Al6 168.29(9) . 1_556 ?
 Al9 Al1 Al6 86.64(4) 1_556 1_556 ?
 Fe2 Al1 Al6 119.36(8) 1_556 . ?
 Co2 Al1 Al6 119.36(8) 1_556 . ?
 Co2 Al1 Al6 51.51(5) . . ?
 Al3 Al1 Al6 63.93(6) . . ?
 Al4 Al1 Al6 105.08(7) 7_655 . ?
 Al9 Al1 Al6 86.64(4) . . ?
 Al9 Al1 Al6 168.29(9) 1_556 . ?
 Al6 Al1 Al6 91.71(8) 1_556 . ?
 Fe2 Al1 Al5 112.05(6) 1_556 3_456 ?
 Co2 Al1 Al5 112.05(6) 1_556 3_456 ?
 Co2 Al1 Al5 112.05(6) . 3_456 ?
 Al3 Al1 Al5 95.99(8) . 3_456 ?
 Al4 Al1 Al5 157.04(9) 7_655 3_456 ?
 Al9 Al1 Al5 127.50(5) . 3_456 ?
 Al9 Al1 Al5 127.50(5) 1_556 3_456 ?
 Al6 Al1 Al5 60.56(5) 1_556 3_456 ?
 Al6 Al1 Al5 60.56(5) . 3_456 ?
 Fe2 Al1 Ce1 169.01(6) 1_556 3_455 ?
 Co2 Al1 Ce1 169.01(6) 1_556 3_455 ?
 Co2 Al1 Ce1 89.31(4) . 3_455 ?
 Al3 Al1 Ce1 131.75(5) . 3_455 ?
 Al4 Al1 Ce1 131.05(5) 7_655 3_455 ?
 Al9 Al1 Ce1 66.86(3) . 3_455 ?
 Al9 Al1 Ce1 122.26(7) 1_556 3_455 ?
 Al6 Al1 Ce1 123.09(7) 1_556 3_455 ?
 Al6 Al1 Ce1 68.06(5) . 3_455 ?
 Al5 Al1 Ce1 63.29(4) 3_456 3_455 ?
 Co2 Al7 Fe1 146.49(9) . 7_655 ?
 Co2 Al7 Co1 146.49(9) . 7_655 ?
 Fe1 Al7 Co1 0.00(4) 7_655 7_655 ?
 Co2 Al7 Co1 146.04(10) . 3 ?
 Fe1 Al7 Co1 67.48(6) 7_655 3 ?
 Co1 Al7 Co1 67.48(6) 7_655 3 ?
 Co2 Al7 Fe1 146.04(10) . 3 ?
 Fe1 Al7 Fe1 67.48(6) 7_655 3 ?

Co1 Al7 Fe1 67.48(6) 7_655 3 ?
 Co1 Al7 Fe1 0.00(4) 3 3 ?
 Co2 Al7 Al8 136.38(3) . 3_556 ?
 Fe1 Al7 Al8 52.99(4) 7_655 3_556 ?
 Co1 Al7 Al8 52.99(4) 7_655 3_556 ?
 Co1 Al7 Al8 52.98(3) 3 3_556 ?
 Fe1 Al7 Al8 52.98(3) 3 3_556 ?
 Co2 Al7 Al8 136.38(3) . 3 ?
 Fe1 Al7 Al8 52.99(4) 7_655 3 ?
 Co1 Al7 Al8 52.99(4) 7_655 3 ?
 Co1 Al7 Al8 52.98(3) 3 3 ?
 Fe1 Al7 Al8 52.98(3) 3 3 ?
 Al8 Al7 Al8 87.24(6) 3_556 3 ?
 Co1 Al6 Co2 177.90(9) . . ?
 Co1 Al6 Al1 119.16(6) . 1_554 ?
 Co2 Al6 Al1 59.66(5) . 1_554 ?
 Co1 Al6 Al1 119.16(6) . . ?
 Co2 Al6 Al1 59.66(5) . . ?
 Al1 Al6 Al1 91.71(8) 1_554 . ?
 Co1 Al6 Al2 59.08(5) . . ?
 Co2 Al6 Al2 122.07(6) . . ?
 Al1 Al6 Al2 178.08(9) 1_554 . ?
 Al1 Al6 Al2 88.67(6) . . ?
 Co1 Al6 Al2 59.08(5) . 1_554 ?
 Co2 Al6 Al2 122.07(6) . 1_554 ?
 Al1 Al6 Al2 88.67(6) 1_554 1_554 ?
 Al1 Al6 Al2 178.08(9) . 1_554 ?
 Al2 Al6 Al2 90.89(8) . 1_554 ?
 Co1 Al6 Al5 58.43(5) . 3_455 ?
 Co2 Al6 Al5 120.37(6) . 3_455 ?
 Al1 Al6 Al5 60.73(6) 1_554 3_455 ?
 Al1 Al6 Al5 121.45(8) . 3_455 ?
 Al2 Al6 Al5 117.51(8) . 3_455 ?
 Al2 Al6 Al5 57.21(6) 1_554 3_455 ?
 Co1 Al6 Al5 58.43(5) . 3_456 ?
 Co2 Al6 Al5 120.37(6) . 3_456 ?
 Al1 Al6 Al5 121.45(8) 1_554 3_456 ?
 Al1 Al6 Al5 60.73(6) . 3_456 ?
 Al2 Al6 Al5 57.21(6) . 3_456 ?
 Al2 Al6 Al5 117.51(8) 1_554 3_456 ?
 Al5 Al6 Al5 89.53(8) 3_455 3_456 ?
 Co1 Al6 Al3 125.05(6) . . ?
 Co2 Al6 Al3 56.09(5) . . ?
 Al1 Al6 Al3 115.75(8) 1_554 . ?
 Al1 Al6 Al3 56.03(6) . . ?
 Al2 Al6 Al3 65.98(6) . . ?
 Al2 Al6 Al3 125.40(8) 1_554 . ?
 Al5 Al6 Al3 176.15(8) 3_455 . ?
 Al5 Al6 Al3 91.32(5) 3_456 . ?
 Co1 Al6 Al3 125.05(6) . 1_554 ?
 Co2 Al6 Al3 56.09(5) . 1_554 ?
 Al1 Al6 Al3 56.03(6) 1_554 1_554 ?
 Al1 Al6 Al3 115.75(8) . 1_554 ?
 Al2 Al6 Al3 125.40(8) . 1_554 ?
 Al2 Al6 Al3 65.98(6) 1_554 1_554 ?
 Al5 Al6 Al3 91.32(5) 3_455 1_554 ?
 Al5 Al6 Al3 176.15(8) 3_456 1_554 ?
 Al3 Al6 Al3 87.59(8) . 1_554 ?

 _diffn_measured_fraction_theta_max 0.998
 _diffn_reflns_theta_full 30.99
 _diffn_measured_fraction_theta_full 0.998

_refine_diff_density_max 1.318
 _refine_diff_density_min -2.199
 _refine_diff_density_rms 0.326

 data_scd0003

 _audit_creation_method SHELXL-97
 _chemical_name_systematic
 ;
 ?
 ;
 _chemical_name_common ?
 _chemical_melting_point ?
 _chemical_formula_moiety ?
 _chemical_formula_sum
 'Al4 Ce Co Fe'
 _chemical_formula_weight 362.82

 loop_
 _atom_type_symbol
 _atom_type_description
 _atom_type_scatter_dispersion_real
 _atom_type_scatter_dispersion_imag
 _atom_type_scatter_source
 'Al' 'Al' 0.0645 0.0514
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
 'Fe' 'Fe' 0.3463 0.8444
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
 'Co' 'Co' 0.3494 0.9721
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
 'Ce' 'Ce' -0.2486 2.6331
 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

 _symmetry_cell_setting ?
 _symmetry_space_group_name_H-M ?

 loop_
 _symmetry_equiv_pos_as_xyz
 'x, y, z'
 '-x, -y, z'
 '-x+1/2, y+1/2, -z'
 'x+1/2, -y+1/2, -z'
 '-x, -y, -z'
 'x, y, -z'
 'x-1/2, -y-1/2, z'
 '-x-1/2, y-1/2, z'

 _cell_length_a 12.4591(5)
 _cell_length_b 14.3798(6)
 _cell_length_c 4.02410(10)
 _cell_angle_alpha 90.00
 _cell_angle_beta 90.00
 _cell_angle_gamma 90.00
 _cell_volume 720.96(5)
 _cell_formula_units_Z 4
 _cell_measurement_temperature 298(2)
 _cell_measurement_reflns_used ?
 _cell_measurement_theta_min ?
 _cell_measurement_theta_max ?

 _exptl_crystal_description ?

```

_exptl_crystal_colour      ?
_exptl_crystal_size_max    0.12
_exptl_crystal_size_mid    0.09
_exptl_crystal_size_min    0.06
_exptl_crystal_density_meas      ?
_exptl_crystal_density_diffn    3.343
_exptl_crystal_density_method  'not measured'
_exptl_crystal_F_000         652
_exptl_absorpt_coefficient_mu   10.828
_exptl_absorpt_correction_type  ?
_exptl_absorpt_correction_T_min 0.3565
_exptl_absorpt_correction_T_max 0.5627
_exptl_absorpt_process_details ?

_exptl_special_details
;
?
;

_diffn_ambient_temperature 298(2)
_diffn_radiation_wavelength 0.71073
_diffn_radiation_type       MoK\alpha
_diffn_radiation_source     'fine-focus sealed tube'
_diffn_radiation_monochromator graphite
_diffn_measurement_device_type ?
_diffn_measurement_method   ?
_diffn_detector_area_resol_mean ?
_diffn_standards_number     ?
_diffn_standards_interval_count ?
_diffn_standards_interval_time ?
_diffn_standards_decay_%    ?
_diffn_reflns_number        11930
_diffn_reflns_av_R_equivalents 0.0422
_diffn_reflns_av_sigma/netI 0.0235
_diffn_reflns_limit_h_min    -17
_diffn_reflns_limit_h_max    17
_diffn_reflns_limit_k_min    -20
_diffn_reflns_limit_k_max    20
_diffn_reflns_limit_l_min    -5
_diffn_reflns_limit_l_max    5
_diffn_reflns_theta_min      2.83
_diffn_reflns_theta_max      30.45
_reflns_number_total         1237
_reflns_number_gt            1137
_reflns_threshold_expression  >2\sigma(I)

_computing_data_collection    ?
_computing_cell_refinement    ?
_computing_data_reduction     ?
_computing_structure_solution ?
_computing_structure_refinement 'SHELXL-97
(Sheldrick, 2008)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F2 against ALL reflections. The
weighted R-factor wR and
goodness of fit S are based on F2, conventional R-
factors R are based

```

on F, with F set to zero for negative F². The threshold expression of $F^2 > 2\sigma(F^2)$ is used only for calculating R-factors(gt) etc. and is not relevant to the choice of reflections for refinement. R-factors based on F² are statistically about twice as large as those based on F, and R-factors based on ALL data will be even larger.

```

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type          full
_refine_ls_weighting_scheme     calc
_refine_ls_weighting_details
'calc w=1/[\sigma^2(Fo^2)+(0.0239P)^2+0.5008P] where
P=(Fo^2+2Fc^2)/3'
_atom_sites_solution_primary    direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment  mixed
_refine_ls_extinction_method    SHELXL
_refine_ls_extinction_coef      0.0225(6)
_refine_ls_extinction_expression
'Fc^*=kFc[1+0.001xFc^2\lambda^3/sin(2\theta)]^-1/4^'
_refine_ls_number_reflns       1237
_refine_ls_number_parameters    74
_refine_ls_number_restraints    0
_refine_ls_R_factor_all         0.0244
_refine_ls_R_factor_gt          0.0211
_refine_ls_wR_factor_ref        0.0512
_refine_ls_wR_factor_gt         0.0492
_refine_ls_goodness_of_fit_ref  1.247
_refine_ls_restrained_S_all     1.247
_refine_ls_shift/su_max         0.007
_refine_ls_shift/su_mean        0.000

```

```

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ce1 Ce 0.340544(12) 0.318648(12) 0.0000 0.00855(9)
Uani 1 2 d S . .
Co2 Co 0.15020(3) 0.09724(3) 0.0000 0.00581(16) Uani
0.29(5) 2 d SP . .
Fe2 Fe 0.15020(3) 0.09724(3) 0.0000 0.00581(16) Uani
0.72(6) 2 d SP . .
Co1 Co 0.03460(3) 0.40615(3) 0.0000 0.00687(15) Uani
0.68(4) 2 d SP . .
Fe1 Fe 0.03460(3) 0.40615(3) 0.0000 0.00687(15) Uani
0.30(4) 2 d SP . .
Al8 Al 0.0000 0.5000 0.5000 0.0071(2) Uani 1 4 d S . .

```

Al9 Al 0.0000 0.0000 0.0000 0.0077(2) Uani 1 4 d S . .
 Al2 Al 0.15966(6) 0.37884(7) 0.5000 0.00741(19) Uani 1 2
 d S . .
 Al5 Al 0.45229(7) 0.17998(6) 0.5000 0.00733(18) Uani 1 2
 d S . .
 Al3 Al 0.23543(7) 0.17269(6) 0.5000 0.00767(18) Uani 1 2
 d S . .
 Al4 Al 0.33146(7) 0.49203(7) 0.5000 0.00750(18) Uani 1 2
 d S . .
 Al1 Al 0.02542(7) 0.13185(6) 0.5000 0.00673(17) Uani 1 2
 d S . .
 Al7 Al 0.33860(6) 0.04479(7) 0.0000 0.0094(2) Uani 1 2 d
 S . .
 Al6 Al 0.09522(6) 0.25318(5) 0.0000 0.00754(18) Uani 1 2
 d S . .

loop_

_atom_site_aniso_label
 _atom_site_aniso_U_11
 _atom_site_aniso_U_22
 _atom_site_aniso_U_33
 _atom_site_aniso_U_23
 _atom_site_aniso_U_13
 _atom_site_aniso_U_12
 Ce1 0.00800(12) 0.01196(13) 0.00568(12) 0.000 0.000 -
 0.00107(5)
 Co2 0.0059(2) 0.0069(3) 0.0047(2) 0.000 0.000
 0.00010(13)
 Fe2 0.0059(2) 0.0069(3) 0.0047(2) 0.000 0.000
 0.00010(13)
 Co1 0.0079(2) 0.0074(2) 0.0054(2) 0.000 0.000
 0.00052(14)
 Fe1 0.0079(2) 0.0074(2) 0.0054(2) 0.000 0.000
 0.00052(14)
 Al8 0.0093(5) 0.0065(6) 0.0057(5) 0.000 0.000 0.0010(4)
 Al9 0.0069(5) 0.0077(6) 0.0085(5) 0.000 0.000 -0.0025(4)
 Al2 0.0056(4) 0.0097(5) 0.0069(4) 0.000 0.000 -0.0001(3)
 Al5 0.0065(4) 0.0075(4) 0.0080(4) 0.000 0.000 0.0012(3)
 Al3 0.0061(4) 0.0102(5) 0.0067(4) 0.000 0.000 -0.0016(3)
 Al4 0.0083(4) 0.0067(4) 0.0075(4) 0.000 0.000 -0.0015(3)
 Al1 0.0066(4) 0.0071(4) 0.0065(4) 0.000 0.000 0.0008(3)
 Al7 0.0062(4) 0.0136(5) 0.0085(5) 0.000 0.000 0.0024(3)
 Al6 0.0084(4) 0.0062(4) 0.0080(4) 0.000 0.000 0.0007(3)

_geom_special_details

;
 All s.u.'s (except the s.u. in the dihedral angle between two
 l.s. planes)
 are estimated using the full covariance matrix. The cell
 s.u.'s are taken
 into account individually in the estimation of s.u.'s in
 distances, angles
 and torsion angles; correlations between s.u.'s in cell
 parameters are only
 used when they are defined by crystal symmetry. An
 approximate (isotropic)
 treatment of cell s.u.'s is used for estimating s.u.'s
 involving l.s. planes.
 ;

loop_

_geom_bond_atom_site_label_1

_geom_bond_atom_site_label_2
 _geom_bond_distance
 _geom_bond_site_symmetry_2
 _geom_bond_publ_flag
 Ce1 Al1 3.1402(7) 7_665 ?
 Ce1 Al1 3.1402(7) 7_664 ?
 Ce1 Al2 3.1427(6) 1_554 ?
 Ce1 Al2 3.1427(6) . ?
 Ce1 Al5 3.1564(7) 1_554 ?
 Ce1 Al5 3.1564(7) . ?
 Ce1 Al3 3.1889(7) 1_554 ?
 Ce1 Al3 3.1889(7) . ?
 Ce1 Al6 3.1982(8) . ?
 Ce1 Al4 3.2058(8) . ?
 Ce1 Al4 3.2058(8) 1_554 ?
 Ce1 Al9 3.27835(18) 3 ?
 Co2 Al9 2.3360(4) . ?
 Co2 Al6 2.3447(9) . ?
 Co2 Al7 2.4655(9) . ?
 Co2 Al3 2.5205(6) . ?
 Co2 Al3 2.5205(6) 1_554 ?
 Co2 Al4 2.5277(6) 3_545 ?
 Co2 Al4 2.5277(6) 3_546 ?
 Co2 Al1 2.5909(6) 1_554 ?
 Co2 Al1 2.5909(6) . ?
 Co1 Al6 2.3257(9) . ?
 Co1 Al8 2.4608(2) . ?
 Co1 Al8 2.4608(2) 1_554 ?
 Co1 Al7 2.5418(9) 7_565 ?
 Co1 Al7 2.5438(10) 3 ?
 Co1 Al2 2.5749(5) . ?
 Co1 Al2 2.5749(5) 1_554 ?
 Co1 Al5 2.5756(6) 7_564 ?
 Co1 Al5 2.5756(6) 7_565 ?
 Co1 Co1 2.8336(8) 5_565 ?
 Co1 Fe1 2.8336(8) 5_565 ?
 Al8 Fe1 2.4608(2) 5_566 ?
 Al8 Co1 2.4608(2) 5_566 ?
 Al8 Fe1 2.4608(2) 5_565 ?
 Al8 Co1 2.4608(2) 5_565 ?
 Al8 Co1 2.4608(2) 1_556 ?
 Al8 Fe1 2.4608(2) 1_556 ?
 Al8 Al2 2.6443(9) 5_566 ?
 Al8 Al2 2.6443(9) . ?
 Al8 Al5 2.6554(8) 7_565 ?
 Al8 Al5 2.6554(8) 3_556 ?
 Al9 Fe2 2.3360(4) 5 ?
 Al9 Co2 2.3360(4) 5 ?
 Al9 Al1 2.7827(6) . ?
 Al9 Al1 2.7827(6) 5 ?
 Al9 Al1 2.7827(6) 1_554 ?
 Al9 Al1 2.7827(6) 5_556 ?
 Al9 Al4 2.9104(6) 7_564 ?
 Al9 Al4 2.9104(6) 3_546 ?
 Al9 Al4 2.9104(6) 7_565 ?
 Al9 Al4 2.9104(6) 3_545 ?
 Al2 Fe1 2.5749(5) 1_556 ?
 Al2 Co1 2.5749(5) 1_556 ?
 Al2 Al4 2.6891(13) . ?
 Al2 Al5 2.7185(12) 7_565 ?
 Al2 Al6 2.8210(9) . ?
 Al2 Al6 2.8210(9) 1_556 ?

Al2 Ce1 3.1427(6) 1_556 ?
 Al5 Fe1 2.5756(6) 7_665 ?
 Al5 Co1 2.5756(6) 7_665 ?
 Al5 Fe1 2.5756(6) 7_666 ?
 Al5 Co1 2.5756(6) 7_666 ?
 Al5 Al8 2.6554(8) 3_546 ?
 Al5 Al3 2.7039(14) . ?
 Al5 Al2 2.7185(12) 7_665 ?
 Al5 Al6 2.8537(8) 7_666 ?
 Al5 Al6 2.8537(8) 7_665 ?
 Al5 Al1 2.8551(12) 7_665 ?
 Al5 Ce1 3.1564(7) 1_556 ?
 Al3 Fe2 2.5205(6) 1_556 ?
 Al3 Co2 2.5205(6) 1_556 ?
 Al3 Al1 2.6816(13) . ?
 Al3 Al4 2.7282(13) 3_546 ?
 Al3 Al6 2.9051(8) . ?
 Al3 Al6 2.9051(8) 1_556 ?
 Al3 Ce1 3.1889(7) 1_556 ?
 Al4 Fe2 2.5277(6) 3_556 ?
 Al4 Co2 2.5277(6) 3_556 ?
 Al4 Fe2 2.5277(6) 3 ?
 Al4 Co2 2.5277(6) 3 ?
 Al4 Al1 2.6874(13) 3_556 ?
 Al4 Al3 2.7282(13) 3_556 ?
 Al4 Al9 2.9104(6) 3_556 ?
 Al4 Al9 2.9104(6) 3 ?
 Al4 Ce1 3.2058(8) 1_556 ?
 Al1 Fe2 2.5909(6) 1_556 ?
 Al1 Co2 2.5909(6) 1_556 ?
 Al1 Al4 2.6874(13) 3_546 ?
 Al1 Al9 2.7827(6) 1_556 ?
 Al1 Al6 2.8015(8) 1_556 ?
 Al1 Al6 2.8015(8) . ?
 Al1 Al5 2.8551(12) 7_565 ?
 Al1 Ce1 3.1402(7) 7_565 ?
 Al7 Fe1 2.5418(9) 7_665 ?
 Al7 Co1 2.5418(9) 7_665 ?
 Al7 Co1 2.5438(10) 3_545 ?
 Al7 Fe1 2.5438(10) 3_545 ?
 Al7 Al8 2.9167(6) 3_546 ?
 Al7 Al8 2.9167(6) 3_545 ?
 Al6 Al1 2.8015(8) 1_554 ?
 Al6 Al2 2.8210(9) 1_554 ?
 Al6 Al5 2.8537(8) 7_564 ?
 Al6 Al5 2.8537(8) 7_565 ?
 Al6 Al3 2.9051(8) 1_554 ?

loop_

_geom_angle_atom_site_label_1
 _geom_angle_atom_site_label_2
 _geom_angle_atom_site_label_3
 _geom_angle
 _geom_angle_site_symmetry_1
 _geom_angle_site_symmetry_3
 _geom_angle_publ_flag
 Al1 Ce1 Al1 79.69(2) 7_665 7_664 ?
 Al1 Ce1 Al2 150.90(3) 7_665 1_554 ?
 Al1 Ce1 Al2 93.060(18) 7_664 1_554 ?
 Al1 Ce1 Al2 93.060(18) 7_665 . ?
 Al1 Ce1 Al2 150.90(3) 7_664 . ?
 Al2 Ce1 Al2 79.62(2) 1_554 . ?

Al1 Ce1 Al5 103.18(2) 7_665 1_554 ?
 Al1 Ce1 Al5 53.93(2) 7_664 1_554 ?
 Al2 Ce1 Al5 94.716(17) 1_554 1_554 ?
 Al2 Ce1 Al5 153.95(2) . 1_554 ?
 Al1 Ce1 Al5 53.93(2) 7_665 . ?
 Al1 Ce1 Al5 103.18(2) 7_664 . ?
 Al2 Ce1 Al5 153.95(2) 1_554 . ?
 Al2 Ce1 Al5 94.716(17) . . ?
 Al5 Ce1 Al5 79.20(2) 1_554 . ?
 Al1 Ce1 Al3 148.73(2) 7_665 1_554 ?
 Al1 Ce1 Al3 92.646(17) 7_664 1_554 ?
 Al2 Ce1 Al3 58.86(2) 1_554 1_554 ?
 Al2 Ce1 Al3 106.90(2) . 1_554 ?
 Al5 Ce1 Al3 50.44(2) 1_554 1_554 ?
 Al5 Ce1 Al3 99.64(2) . 1_554 ?
 Al1 Ce1 Al3 92.646(17) 7_665 . ?
 Al1 Ce1 Al3 148.73(2) 7_664 . ?
 Al2 Ce1 Al3 106.90(2) 1_554 . ?
 Al2 Ce1 Al3 58.86(2) . . ?
 Al5 Ce1 Al3 99.64(2) 1_554 . ?
 Al5 Ce1 Al3 50.44(2) . . ?
 Al3 Ce1 Al3 78.24(2) 1_554 . ?
 Al1 Ce1 Al6 140.153(10) 7_665 . ?
 Al1 Ce1 Al6 140.153(10) 7_664 . ?
 Al2 Ce1 Al6 52.824(17) 1_554 . ?
 Al2 Ce1 Al6 52.824(17) . . ?
 Al5 Ce1 Al6 103.63(2) 1_554 . ?
 Al5 Ce1 Al6 103.63(2) . . ?
 Al3 Ce1 Al6 54.110(16) 1_554 . ?
 Al3 Ce1 Al6 54.110(16) . . ?
 Al1 Ce1 Al4 56.46(2) 7_665 . ?
 Al1 Ce1 Al4 104.58(2) 7_664 . ?
 Al2 Ce1 Al4 99.34(2) 1_554 . ?
 Al2 Ce1 Al4 50.11(2) . . ?
 Al5 Ce1 Al4 155.09(2) 1_554 . ?
 Al5 Ce1 Al4 96.131(16) . . ?
 Al3 Ce1 Al4 153.30(2) 1_554 . ?
 Al3 Ce1 Al4 95.819(16) . . ?
 Al6 Ce1 Al4 101.256(18) . . ?
 Al1 Ce1 Al4 104.58(2) 7_665 1_554 ?
 Al1 Ce1 Al4 56.46(2) 7_664 1_554 ?
 Al2 Ce1 Al4 50.11(2) 1_554 1_554 ?
 Al2 Ce1 Al4 99.34(2) . 1_554 ?
 Al5 Ce1 Al4 96.131(16) 1_554 1_554 ?
 Al5 Ce1 Al4 155.09(2) . 1_554 ?
 Al3 Ce1 Al4 95.819(16) 1_554 1_554 ?
 Al3 Ce1 Al4 153.30(2) . 1_554 ?
 Al6 Ce1 Al4 101.256(18) . 1_554 ?
 Al4 Ce1 Al4 77.75(2) . 1_554 ?
 Al1 Ce1 Al9 51.330(14) 7_665 3 ?
 Al1 Ce1 Al9 51.330(14) 7_664 3 ?
 Al2 Ce1 Al9 102.444(18) 1_554 3 ?
 Al2 Ce1 Al9 102.444(18) . 3 ?
 Al5 Ce1 Al9 103.605(16) 1_554 3 ?
 Al5 Ce1 Al9 103.605(16) . 3 ?
 Al3 Ce1 Al9 140.574(10) 1_554 3 ?
 Al3 Ce1 Al9 140.574(10) . 3 ?
 Al6 Ce1 Al9 144.420(15) . 3 ?
 Al4 Ce1 Al9 53.326(14) . 3 ?
 Al4 Ce1 Al9 53.326(14) 1_554 3 ?
 Al9 Co2 Al6 109.78(2) . . ?
 Al9 Co2 Al7 125.42(3) . . ?

Al6 Co2 Al7 124.80(4) . . ?
 Al9 Co2 Al3 126.522(17) . . ?
 Al6 Co2 Al3 73.23(2) . . ?
 Al7 Co2 Al3 74.37(3) . . ?
 Al9 Co2 Al3 126.522(17) . 1_554 ?
 Al6 Co2 Al3 73.23(2) . 1_554 ?
 Al7 Co2 Al3 74.37(3) . 1_554 ?
 Al3 Co2 Al3 105.93(3) . 1_554 ?
 Al9 Co2 Al4 73.39(2) . 3_545 ?
 Al6 Co2 Al4 126.785(19) . 3_545 ?
 Al7 Co2 Al4 74.39(3) . 3_545 ?
 Al3 Co2 Al4 148.76(3) . 3_545 ?
 Al3 Co2 Al4 65.43(2) 1_554 3_545 ?
 Al9 Co2 Al4 73.39(2) . 3_546 ?
 Al6 Co2 Al4 126.785(19) . 3_546 ?
 Al7 Co2 Al4 74.39(3) . 3_546 ?
 Al3 Co2 Al4 65.43(2) . 3_546 ?
 Al3 Co2 Al4 148.76(3) 1_554 3_546 ?
 Al4 Co2 Al4 105.50(4) 3_545 3_546 ?
 Al9 Co2 Al1 68.55(2) . 1_554 ?
 Al6 Co2 Al1 68.96(2) . 1_554 ?
 Al7 Co2 Al1 129.052(16) . 1_554 ?
 Al3 Co2 Al1 142.19(3) . 1_554 ?
 Al3 Co2 Al1 63.27(2) 1_554 1_554 ?
 Al4 Co2 Al1 63.32(3) 3_545 1_554 ?
 Al4 Co2 Al1 141.94(3) 3_546 1_554 ?
 Al9 Co2 Al1 68.55(2) . . ?
 Al6 Co2 Al1 68.96(2) . . ?
 Al7 Co2 Al1 129.052(16) . . ?
 Al3 Co2 Al1 63.27(2) . . ?
 Al3 Co2 Al1 142.19(3) 1_554 . ?
 Al4 Co2 Al1 141.94(3) 3_545 . ?
 Al4 Co2 Al1 63.32(3) 3_546 . ?
 Al1 Co2 Al1 101.90(3) 1_554 . ?
 Al6 Co1 Al8 125.142(8) . . ?
 Al6 Co1 Al8 125.142(8) . 1_554 ?
 Al8 Co1 Al8 109.698(16) . 1_554 ?
 Al6 Co1 Al7 125.07(3) . 7_565 ?
 Al8 Co1 Al7 71.306(15) . 7_565 ?
 Al8 Co1 Al7 71.306(15) 1_554 7_565 ?
 Al6 Co1 Al7 122.65(3) . 3 ?
 Al8 Co1 Al7 71.273(13) . 3 ?
 Al8 Co1 Al7 71.273(13) 1_554 3 ?
 Al7 Co1 Al7 112.28(2) 7_565 3 ?
 Al6 Co1 Al2 70.08(3) . . ?
 Al8 Co1 Al2 63.302(18) . . ?
 Al8 Co1 Al2 145.95(3) 1_554 . ?
 Al7 Co1 Al2 128.584(15) 7_565 . ?
 Al7 Co1 Al2 75.15(3) 3 . ?
 Al6 Co1 Al2 70.08(3) . 1_554 ?
 Al8 Co1 Al2 145.95(3) . 1_554 ?
 Al8 Co1 Al2 63.302(18) 1_554 1_554 ?
 Al7 Co1 Al2 128.584(15) 7_565 1_554 ?
 Al7 Co1 Al2 75.15(3) 3 1_554 ?
 Al2 Co1 Al2 102.78(3) . 1_554 ?
 Al6 Co1 Al5 71.01(2) . 7_564 ?
 Al8 Co1 Al5 146.38(3) . 7_564 ?
 Al8 Co1 Al5 63.591(16) 1_554 7_564 ?
 Al7 Co1 Al5 75.58(3) 7_565 7_564 ?
 Al7 Co1 Al5 128.618(17) 3 7_564 ?
 Al2 Co1 Al5 141.08(3) . 7_564 ?
 Al2 Co1 Al5 63.72(2) 1_554 7_564 ?

Al6 Co1 Al5 71.01(2) . 7_565 ?
 Al8 Co1 Al5 63.591(16) . 7_565 ?
 Al8 Co1 Al5 146.38(3) 1_554 7_565 ?
 Al7 Co1 Al5 75.58(3) 7_565 7_565 ?
 Al7 Co1 Al5 128.618(17) 3 7_565 ?
 Al2 Co1 Al5 63.72(2) . 7_565 ?
 Al2 Co1 Al5 141.08(3) 1_554 7_565 ?
 Al5 Co1 Al5 102.74(3) 7_564 7_565 ?
 Al6 Co1 Co1 178.76(3) . 5_565 ?
 Al8 Co1 Co1 54.849(8) . 5_565 ?
 Al8 Co1 Co1 54.849(8) 1_554 5_565 ?
 Al7 Co1 Co1 56.17(3) 7_565 5_565 ?
 Al7 Co1 Co1 56.11(2) 3 5_565 ?
 Al2 Co1 Co1 109.23(3) . 5_565 ?
 Al2 Co1 Co1 109.23(3) 1_554 5_565 ?
 Al5 Co1 Co1 109.69(2) 7_564 5_565 ?
 Al5 Co1 Co1 109.69(2) 7_565 5_565 ?
 Al6 Co1 Fe1 178.76(3) . 5_565 ?
 Al8 Co1 Fe1 54.849(8) . 5_565 ?
 Al8 Co1 Fe1 54.849(8) 1_554 5_565 ?
 Al7 Co1 Fe1 56.17(3) 7_565 5_565 ?
 Al7 Co1 Fe1 56.11(2) 3 5_565 ?
 Al2 Co1 Fe1 109.23(3) . 5_565 ?
 Al2 Co1 Fe1 109.23(3) 1_554 5_565 ?
 Al5 Co1 Fe1 109.69(2) 7_564 5_565 ?
 Al5 Co1 Fe1 109.69(2) 7_565 5_565 ?
 Co1 Co1 Fe1 0.000(15) 5_565 5_565 ?
 Fe1 Al8 Co1 0.000(18) 5_566 5_566 ?
 Fe1 Al8 Co1 180.0 5_566 . ?
 Co1 Al8 Co1 180.0 5_566 . ?
 Fe1 Al8 Fe1 109.698(16) 5_566 5_565 ?
 Co1 Al8 Fe1 109.698(16) 5_566 5_565 ?
 Co1 Al8 Fe1 70.302(16) . 5_565 ?
 Fe1 Al8 Co1 109.698(16) 5_566 5_565 ?
 Co1 Al8 Co1 109.698(16) 5_566 5_565 ?
 Co1 Al8 Co1 70.302(16) . 5_565 ?
 Fe1 Al8 Co1 0.00(2) 5_565 5_565 ?
 Fe1 Al8 Co1 70.302(15) 5_566 1_556 ?
 Co1 Al8 Co1 70.302(15) 5_566 1_556 ?
 Co1 Al8 Co1 109.698(16) . 1_556 ?
 Fe1 Al8 Co1 180.000(16) 5_565 1_556 ?
 Co1 Al8 Co1 180.000(16) 5_565 1_556 ?
 Fe1 Al8 Fe1 70.302(15) 5_566 1_556 ?
 Co1 Al8 Fe1 70.302(15) 5_566 1_556 ?
 Co1 Al8 Fe1 109.698(16) . 1_556 ?
 Fe1 Al8 Fe1 180.000(16) 5_565 1_556 ?
 Co1 Al8 Fe1 180.000(16) 5_565 1_556 ?
 Co1 Al8 Fe1 0.000(16) 1_556 1_556 ?
 Fe1 Al8 Al2 60.454(10) 5_566 5_566 ?
 Co1 Al8 Al2 60.454(10) 5_566 5_566 ?
 Co1 Al8 Al2 119.546(10) . 5_566 ?
 Fe1 Al8 Al2 60.454(10) 5_565 5_566 ?
 Co1 Al8 Al2 60.454(10) 5_565 5_566 ?
 Co1 Al8 Al2 119.546(10) 1_556 5_566 ?
 Fe1 Al8 Al2 119.546(10) 1_556 5_566 ?
 Fe1 Al8 Al2 119.546(11) 5_566 . ?
 Co1 Al8 Al2 119.546(11) 5_566 . ?
 Co1 Al8 Al2 60.454(10) . . ?
 Fe1 Al8 Al2 119.546(11) 5_565 . ?
 Co1 Al8 Al2 119.546(11) 5_565 . ?
 Co1 Al8 Al2 60.454(10) 1_556 . ?
 Fe1 Al8 Al2 60.454(10) 1_556 . ?

Al2 Al8 Al2 180.0 5_566 . ?
 Fe1 Al8 Al5 119.690(10) 5_566 7_565 ?
 Co1 Al8 Al5 119.690(10) 5_566 7_565 ?
 Co1 Al8 Al5 60.310(10) . 7_565 ?
 Fe1 Al8 Al5 119.690(10) 5_565 7_565 ?
 Co1 Al8 Al5 119.690(10) 5_565 7_565 ?
 Co1 Al8 Al5 60.310(10) 1_556 7_565 ?
 Fe1 Al8 Al5 60.310(10) 1_556 7_565 ?
 Al2 Al8 Al5 118.28(3) 5_566 7_565 ?
 Al2 Al8 Al5 61.72(3) . 7_565 ?
 Fe1 Al8 Al5 60.310(10) 5_566 3_556 ?
 Co1 Al8 Al5 60.310(10) 5_566 3_556 ?
 Co1 Al8 Al5 119.690(10) . 3_556 ?
 Fe1 Al8 Al5 60.310(10) 5_565 3_556 ?
 Co1 Al8 Al5 60.310(10) 5_565 3_556 ?
 Co1 Al8 Al5 119.690(10) 1_556 3_556 ?
 Fe1 Al8 Al5 119.690(10) 1_556 3_556 ?
 Al2 Al8 Al5 61.72(3) 5_566 3_556 ?
 Al2 Al8 Al5 118.28(3) . 3_556 ?
 Al5 Al8 Al5 180.0 7_565 3_556 ?
 Fe2 Al9 Co2 0.00(2) 5 5 ?
 Fe2 Al9 Co2 180.00(2) 5 . ?
 Co2 Al9 Co2 180.00(2) 5 . ?
 Fe2 Al9 Al1 119.935(17) 5 . ?
 Co2 Al9 Al1 119.935(17) 5 . ?
 Co2 Al9 Al1 60.065(17) . . ?
 Fe2 Al9 Al1 60.065(17) 5 5 ?
 Co2 Al9 Al1 60.065(17) 5 5 ?
 Co2 Al9 Al1 119.935(17) . 5 ?
 Al1 Al9 Al1 180.00(3) . 5 ?
 Fe2 Al9 Al1 119.935(17) 5 1_554 ?
 Co2 Al9 Al1 119.935(17) 5 1_554 ?
 Co2 Al9 Al1 60.065(17) . 1_554 ?
 Al1 Al9 Al1 92.61(3) . 1_554 ?
 Al1 Al9 Al1 87.39(3) 5 1_554 ?
 Fe2 Al9 Al1 60.065(17) 5 5_556 ?
 Co2 Al9 Al1 60.065(17) 5 5_556 ?
 Co2 Al9 Al1 119.935(17) . 5_556 ?
 Al1 Al9 Al1 87.39(3) . 5_556 ?
 Al1 Al9 Al1 92.61(3) 5 5_556 ?
 Al1 Al9 Al1 180.00(4) 1_554 5_556 ?
 Fe2 Al9 Al4 56.332(17) 5 7_564 ?
 Co2 Al9 Al4 56.332(17) 5 7_564 ?
 Co2 Al9 Al4 123.668(17) . 7_564 ?
 Al1 Al9 Al4 123.72(2) . 7_564 ?
 Al1 Al9 Al4 56.28(2) 5 7_564 ?
 Al1 Al9 Al4 63.60(2) 1_554 7_564 ?
 Al1 Al9 Al4 116.40(2) 5_556 7_564 ?
 Fe2 Al9 Al4 123.668(17) 5 3_546 ?
 Co2 Al9 Al4 123.668(17) 5 3_546 ?
 Co2 Al9 Al4 56.332(17) . 3_546 ?
 Al1 Al9 Al4 56.28(2) . 3_546 ?
 Al1 Al9 Al4 123.72(2) 5 3_546 ?
 Al1 Al9 Al4 116.40(2) 1_554 3_546 ?
 Al1 Al9 Al4 63.60(2) 5_556 3_546 ?
 Al4 Al9 Al4 180.00(2) 7_564 3_546 ?
 Fe2 Al9 Al4 56.332(17) 5 7_565 ?
 Co2 Al9 Al4 56.332(17) 5 7_565 ?
 Co2 Al9 Al4 123.668(17) . 7_565 ?
 Al1 Al9 Al4 63.60(2) . 7_565 ?
 Al1 Al9 Al4 116.40(2) 5 7_565 ?
 Al1 Al9 Al4 123.72(2) 1_554 7_565 ?

Al1 Al9 Al4 56.28(2) 5_556 7_565 ?
 Al4 Al9 Al4 87.47(2) 7_564 7_565 ?
 Al4 Al9 Al4 92.53(2) 3_546 7_565 ?
 Fe2 Al9 Al4 123.668(17) 5 3_545 ?
 Co2 Al9 Al4 123.668(17) 5 3_545 ?
 Co2 Al9 Al4 56.332(17) . 3_545 ?
 Al1 Al9 Al4 116.40(2) . 3_545 ?
 Al1 Al9 Al4 63.60(2) 5 3_545 ?
 Al1 Al9 Al4 56.28(2) 1_554 3_545 ?
 Al1 Al9 Al4 123.72(2) 5_556 3_545 ?
 Al4 Al9 Al4 92.53(2) 7_564 3_545 ?
 Al4 Al9 Al4 87.47(2) 3_546 3_545 ?
 Al4 Al9 Al4 180.00(2) 7_565 3_545 ?
 Co1 Al2 Fe1 102.78(3) . 1_556 ?
 Co1 Al2 Co1 102.78(3) . 1_556 ?
 Fe1 Al2 Co1 0.000(14) 1_556 1_556 ?
 Co1 Al2 Al8 56.244(18) . . ?
 Fe1 Al2 Al8 56.244(18) 1_556 . ?
 Co1 Al2 Al8 56.244(18) 1_556 . ?
 Co1 Al2 Al4 112.92(3) . . ?
 Fe1 Al2 Al4 112.92(3) 1_556 . ?
 Co1 Al2 Al4 112.92(3) 1_556 . ?
 Al8 Al2 Al4 101.54(4) . . ?
 Co1 Al2 Al5 58.154(18) . 7_565 ?
 Fe1 Al2 Al5 58.154(18) 1_556 7_565 ?
 Co1 Al2 Al5 58.154(18) 1_556 7_565 ?
 Al8 Al2 Al5 59.34(2) . 7_565 ?
 Al4 Al2 Al5 160.88(5) . 7_565 ?
 Co1 Al2 Al6 50.812(19) . . ?
 Fe1 Al2 Al6 118.87(3) 1_556 . ?
 Co1 Al2 Al6 118.87(3) 1_556 . ?
 Al8 Al2 Al6 102.00(2) . . ?
 Al4 Al2 Al6 127.90(2) . . ?
 Al5 Al2 Al6 61.98(2) 7_565 . ?
 Co1 Al2 Al6 118.87(3) . 1_556 ?
 Fe1 Al2 Al6 50.812(19) 1_556 1_556 ?
 Co1 Al2 Al6 50.812(19) 1_556 1_556 ?
 Al8 Al2 Al6 102.00(2) . 1_556 ?
 Al4 Al2 Al6 127.90(2) . 1_556 ?
 Al5 Al2 Al6 61.98(2) 7_565 1_556 ?
 Al6 Al2 Al6 91.00(4) . 1_556 ?
 Co1 Al2 Ce1 167.48(3) . 1_556 ?
 Fe1 Al2 Ce1 88.605(9) 1_556 1_556 ?
 Co1 Al2 Ce1 88.605(9) 1_556 1_556 ?
 Al8 Al2 Ce1 136.131(19) . 1_556 ?
 Al4 Al2 Ce1 66.16(2) . 1_556 ?
 Al5 Al2 Ce1 126.57(3) 7_565 1_556 ?
 Al6 Al2 Ce1 118.97(4) . 1_556 ?
 Al6 Al2 Ce1 64.597(19) 1_556 1_556 ?
 Co1 Al2 Ce1 88.605(9) . . ?
 Fe1 Al2 Ce1 167.48(3) 1_556 . ?
 Co1 Al2 Ce1 167.48(3) 1_556 . ?
 Al8 Al2 Ce1 136.131(19) . . ?
 Al4 Al2 Ce1 66.16(2) . . ?
 Al5 Al2 Ce1 126.57(3) 7_565 . ?
 Al6 Al2 Ce1 64.597(19) . . ?
 Al6 Al2 Ce1 118.97(4) 1_556 . ?
 Ce1 Al2 Ce1 79.617(19) 1_556 . ?
 Fe1 Al5 Co1 0.00(2) 7_665 7_665 ?
 Fe1 Al5 Fe1 102.74(3) 7_665 7_666 ?
 Co1 Al5 Fe1 102.74(3) 7_665 7_666 ?
 Fe1 Al5 Co1 102.74(3) 7_665 7_666 ?

Co1 Al5 Co1 102.74(3) 7_665 7_666 ?
 Fe1 Al5 Co1 0.000(16) 7_666 7_666 ?
 Fe1 Al5 Al8 56.100(18) 7_665 3_546 ?
 Co1 Al5 Al8 56.100(18) 7_665 3_546 ?
 Fe1 Al5 Al8 56.100(18) 7_666 3_546 ?
 Co1 Al5 Al8 56.100(18) 7_666 3_546 ?
 Fe1 Al5 Al3 112.28(3) 7_665 . ?
 Co1 Al5 Al3 112.28(3) 7_665 . ?
 Fe1 Al5 Al3 112.28(3) 7_666 . ?
 Co1 Al5 Al3 112.28(3) 7_666 . ?
 Al8 Al5 Al3 100.71(3) 3_546 . ?
 Fe1 Al5 Al2 58.13(2) 7_665 7_665 ?
 Co1 Al5 Al2 58.13(2) 7_665 7_665 ?
 Fe1 Al5 Al2 58.13(2) 7_666 7_665 ?
 Co1 Al5 Al2 58.13(2) 7_666 7_665 ?
 Al8 Al5 Al2 58.94(3) 3_546 7_665 ?
 Al3 Al5 Al2 159.65(4) . 7_665 ?
 Fe1 Al5 Al6 117.67(4) 7_665 7_666 ?
 Co1 Al5 Al6 117.67(4) 7_665 7_666 ?
 Fe1 Al5 Al6 50.408(19) 7_666 7_666 ?
 Co1 Al5 Al6 50.408(19) 7_666 7_666 ?
 Al8 Al5 Al6 100.87(3) 3_546 7_666 ?
 Al3 Al5 Al6 129.54(2) . 7_666 ?
 Al2 Al5 Al6 60.77(3) 7_665 7_666 ?
 Fe1 Al5 Al6 50.408(19) 7_665 7_665 ?
 Co1 Al5 Al6 50.408(19) 7_665 7_665 ?
 Fe1 Al5 Al6 117.67(4) 7_666 7_665 ?
 Co1 Al5 Al6 117.67(4) 7_666 7_665 ?
 Al8 Al5 Al6 100.87(3) 3_546 7_665 ?
 Al3 Al5 Al6 129.54(2) . 7_665 ?
 Al2 Al5 Al6 60.77(3) 7_665 7_665 ?
 Al6 Al5 Al6 89.67(3) 7_666 7_665 ?
 Fe1 Al5 Al1 109.19(3) 7_665 7_665 ?
 Co1 Al5 Al1 109.19(3) 7_665 7_665 ?
 Fe1 Al5 Al1 109.19(3) 7_666 7_665 ?
 Co1 Al5 Al1 109.19(3) 7_666 7_665 ?
 Al8 Al5 Al1 148.45(4) 3_546 7_665 ?
 Al3 Al5 Al1 110.83(4) . 7_665 ?
 Al2 Al5 Al1 89.52(4) 7_665 7_665 ?
 Al6 Al5 Al1 58.78(2) 7_666 7_665 ?
 Al6 Al5 Al1 58.78(2) 7_665 7_665 ?
 Fe1 Al5 Ce1 167.78(3) 7_665 1_556 ?
 Co1 Al5 Ce1 167.78(3) 7_665 1_556 ?
 Fe1 Al5 Ce1 88.935(9) 7_666 1_556 ?
 Co1 Al5 Ce1 88.935(9) 7_666 1_556 ?
 Al8 Al5 Ce1 135.598(17) 3_546 1_556 ?
 Al3 Al5 Ce1 65.40(2) . 1_556 ?
 Al2 Al5 Ce1 128.01(2) 7_665 1_556 ?
 Al6 Al5 Ce1 67.234(18) 7_666 1_556 ?
 Al6 Al5 Ce1 120.79(3) 7_665 1_556 ?
 Al1 Al5 Ce1 62.745(19) 7_665 1_556 ?
 Fe1 Al5 Ce1 88.935(9) 7_665 . ?
 Co1 Al5 Ce1 88.935(9) 7_665 . ?
 Fe1 Al5 Ce1 167.78(3) 7_666 . ?
 Co1 Al5 Ce1 167.78(3) 7_666 . ?
 Al8 Al5 Ce1 135.598(17) 3_546 . ?
 Al3 Al5 Ce1 65.40(2) . . ?
 Al2 Al5 Ce1 128.01(2) 7_665 . ?
 Al6 Al5 Ce1 120.79(3) 7_666 . ?
 Al6 Al5 Ce1 67.234(18) 7_665 . ?
 Al1 Al5 Ce1 62.745(19) 7_665 . ?
 Ce1 Al5 Ce1 79.20(2) 1_556 . ?

Co2 Al3 Fe2 105.93(3) . 1_556 ?
 Co2 Al3 Co2 105.93(3) . 1_556 ?
 Fe2 Al3 Co2 0.00(2) 1_556 1_556 ?
 Co2 Al3 Al1 59.65(2) . . ?
 Fe2 Al3 Al1 59.65(2) 1_556 . ?
 Co2 Al3 Al1 59.65(2) 1_556 . ?
 Co2 Al3 Al5 115.96(2) . . ?
 Fe2 Al3 Al5 115.96(2) 1_556 . ?
 Co2 Al3 Al5 115.96(2) 1_556 . ?
 Al1 Al3 Al5 169.57(4) . . ?
 Co2 Al3 Al4 57.41(2) . 3_546 ?
 Fe2 Al3 Al4 57.41(2) 1_556 3_546 ?
 Co2 Al3 Al4 57.41(2) 1_556 3_546 ?
 Al1 Al3 Al4 59.56(3) . 3_546 ?
 Al5 Al3 Al4 110.01(4) . 3_546 ?
 Co2 Al3 Al6 50.602(19) . . ?
 Fe2 Al3 Al6 118.10(3) 1_556 . ?
 Co2 Al3 Al6 118.10(3) 1_556 . ?
 Al1 Al3 Al6 60.04(2) . . ?
 Al5 Al3 Al6 125.83(2) . . ?
 Al4 Al3 Al6 101.29(3) 3_546 . ?
 Co2 Al3 Al6 118.10(3) . 1_556 ?
 Fe2 Al3 Al6 50.602(19) 1_556 1_556 ?
 Co2 Al3 Al6 50.602(19) 1_556 1_556 ?
 Al1 Al3 Al6 60.04(2) . 1_556 ?
 Al5 Al3 Al6 125.83(2) . 1_556 ?
 Al4 Al3 Al6 101.29(3) 3_546 1_556 ?
 Al6 Al3 Al6 87.67(3) . 1_556 ?
 Co2 Al3 Ce1 163.74(3) . 1_556 ?
 Fe2 Al3 Ce1 87.286(10) 1_556 1_556 ?
 Co2 Al3 Ce1 87.286(10) 1_556 1_556 ?
 Al1 Al3 Ce1 123.01(3) . 1_556 ?
 Al5 Al3 Ce1 64.158(19) . 1_556 ?
 Al4 Al3 Ce1 138.781(14) 3_546 1_556 ?
 Al6 Al3 Ce1 114.94(3) . 1_556 ?
 Al6 Al3 Ce1 63.108(18) 1_556 1_556 ?
 Co2 Al3 Ce1 87.286(10) . . ?
 Fe2 Al3 Ce1 163.74(3) 1_556 . ?
 Co2 Al3 Ce1 163.74(3) 1_556 . ?
 Al1 Al3 Ce1 123.01(3) . . ?
 Al5 Al3 Ce1 64.158(19) . . ?
 Al4 Al3 Ce1 138.781(14) 3_546 . ?
 Al6 Al3 Ce1 63.108(18) . . ?
 Al6 Al3 Ce1 114.94(3) 1_556 . ?
 Ce1 Al3 Ce1 78.24(2) 1_556 . ?
 Fe2 Al4 Co2 0.000(16) 3_556 3_556 ?
 Fe2 Al4 Fe2 105.50(4) 3_556 3 ?
 Co2 Al4 Fe2 105.50(4) 3_556 3 ?
 Fe2 Al4 Co2 105.50(4) 3_556 3 ?
 Co2 Al4 Co2 105.50(4) 3_556 3 ?
 Fe2 Al4 Co2 0.000(16) 3 3 ?
 Fe2 Al4 Al1 59.48(2) 3_556 3_556 ?
 Co2 Al4 Al1 59.48(2) 3_556 3_556 ?
 Fe2 Al4 Al1 59.48(2) 3 3_556 ?
 Co2 Al4 Al1 59.48(2) 3 3_556 ?
 Fe2 Al4 Al2 115.74(2) 3_556 . ?
 Co2 Al4 Al2 115.74(2) 3_556 . ?
 Fe2 Al4 Al2 115.74(2) 3 . ?
 Co2 Al4 Al2 115.74(2) 3 . ?
 Al1 Al4 Al2 168.82(5) 3_556 . ?
 Fe2 Al4 Al3 57.16(2) 3_556 3_556 ?
 Co2 Al4 Al3 57.16(2) 3_556 3_556 ?

Fe2 Al4 Al3 57.16(2) 3 3_556 ?
 Co2 Al4 Al3 57.16(2) 3 3_556 ?
 Al1 Al4 Al3 59.35(3) 3_556 3_556 ?
 Al2 Al4 Al3 109.46(4) . 3_556 ?
 Fe2 Al4 Al9 50.278(12) 3_556 3_556 ?
 Co2 Al4 Al9 50.278(12) 3_556 3_556 ?
 Fe2 Al4 Al9 117.48(3) 3 3_556 ?
 Co2 Al4 Al9 117.48(3) 3 3_556 ?
 Al1 Al4 Al9 59.459(19) 3_556 3_556 ?
 Al2 Al4 Al9 126.74(2) . 3_556 ?
 Al3 Al4 Al9 100.54(3) 3_556 3_556 ?
 Fe2 Al4 Al9 117.48(3) 3_556 3 ?
 Co2 Al4 Al9 117.48(3) 3_556 3 ?
 Fe2 Al4 Al9 50.278(12) 3 3 ?
 Co2 Al4 Al9 50.278(12) 3 3 ?
 Al1 Al4 Al9 59.459(19) 3_556 3 ?
 Al2 Al4 Al9 126.74(2) . 3 ?
 Al3 Al4 Al9 100.54(3) 3_556 3 ?
 Al9 Al4 Al9 87.47(2) 3_556 3 ?
 Fe2 Al4 Ce1 164.13(3) 3_556 . ?
 Co2 Al4 Ce1 164.13(3) 3_556 . ?
 Fe2 Al4 Ce1 87.862(11) 3 . ?
 Co2 Al4 Ce1 87.862(11) 3 . ?
 Al1 Al4 Ce1 123.95(2) 3_556 . ?
 Al2 Al4 Ce1 63.73(2) . . ?
 Al3 Al4 Ce1 138.705(15) 3_556 . ?
 Al9 Al4 Ce1 116.04(3) 3_556 . ?
 Al9 Al4 Ce1 64.613(12) 3 . ?
 Fe2 Al4 Ce1 87.862(11) 3_556 1_556 ?
 Co2 Al4 Ce1 87.862(11) 3_556 1_556 ?
 Fe2 Al4 Ce1 164.13(3) 3 1_556 ?
 Co2 Al4 Ce1 164.13(3) 3 1_556 ?
 Al1 Al4 Ce1 123.95(2) 3_556 1_556 ?
 Al2 Al4 Ce1 63.73(2) . 1_556 ?
 Al3 Al4 Ce1 138.705(15) 3_556 1_556 ?
 Al9 Al4 Ce1 64.613(12) 3_556 1_556 ?
 Al9 Al4 Ce1 116.04(3) 3 1_556 ?
 Ce1 Al4 Ce1 77.75(2) . 1_556 ?
 Fe2 Al1 Co2 0.000(19) 1_556 1_556 ?
 Fe2 Al1 Co2 101.90(3) 1_556 . ?
 Co2 Al1 Co2 101.90(3) 1_556 . ?
 Fe2 Al1 Al3 57.085(18) 1_556 . ?
 Co2 Al1 Al3 57.085(18) 1_556 . ?
 Co2 Al1 Al3 57.085(18) . . ?
 Fe2 Al1 Al4 57.19(2) 1_556 3_546 ?
 Co2 Al1 Al4 57.19(2) 1_556 3_546 ?
 Co2 Al1 Al4 57.19(2) . 3_546 ?
 Al3 Al1 Al4 61.08(3) . 3_546 ?
 Fe2 Al1 Al9 119.93(3) 1_556 . ?
 Co2 Al1 Al9 119.93(3) 1_556 . ?
 Co2 Al1 Al9 51.384(13) . . ?
 Al3 Al1 Al9 105.09(3) . . ?
 Al4 Al1 Al9 64.26(2) 3_546 . ?
 Fe2 Al1 Al9 51.384(13) 1_556 1_556 ?
 Co2 Al1 Al9 51.384(13) 1_556 1_556 ?
 Co2 Al1 Al9 119.93(3) . 1_556 ?
 Al3 Al1 Al9 105.09(3) . 1_556 ?
 Al4 Al1 Al9 64.26(2) 3_546 1_556 ?
 Al9 Al1 Al9 92.61(3) . 1_556 ?
 Fe2 Al1 Al6 51.365(19) 1_556 1_556 ?
 Co2 Al1 Al6 51.365(19) 1_556 1_556 ?
 Co2 Al1 Al6 119.41(4) . 1_556 ?

Al3 Al1 Al6 63.94(3) . 1_556 ?
 Al4 Al1 Al6 105.07(3) 3_546 1_556 ?
 Al9 Al1 Al6 168.22(4) . 1_556 ?
 Al9 Al1 Al6 86.581(12) 1_556 1_556 ?
 Fe2 Al1 Al6 119.41(4) 1_556 . ?
 Co2 Al1 Al6 119.41(4) 1_556 . ?
 Co2 Al1 Al6 51.365(19) . . ?
 Al3 Al1 Al6 63.94(3) . . ?
 Al4 Al1 Al6 105.07(3) 3_546 . ?
 Al9 Al1 Al6 86.581(12) . . ?
 Al9 Al1 Al6 168.22(4) 1_556 . ?
 Al6 Al1 Al6 91.81(3) 1_556 . ?
 Fe2 Al1 Al5 111.93(3) 1_556 7_565 ?
 Co2 Al1 Al5 111.93(3) 1_556 7_565 ?
 Co2 Al1 Al5 111.93(3) . 7_565 ?
 Al3 Al1 Al5 95.96(4) . 7_565 ?
 Al4 Al1 Al5 157.04(4) 3_546 7_565 ?
 Al9 Al1 Al5 127.55(2) . 7_565 ?
 Al9 Al1 Al5 127.55(2) 1_556 7_565 ?
 Al6 Al1 Al5 60.58(2) 1_556 7_565 ?
 Al6 Al1 Al5 60.58(2) . 7_565 ?
 Fe2 Al1 Ce1 168.89(3) 1_556 7_565 ?
 Co2 Al1 Ce1 168.89(3) 1_556 7_565 ?
 Co2 Al1 Ce1 89.203(8) . 7_565 ?
 Al3 Al1 Ce1 131.77(2) . 7_565 ?
 Al4 Al1 Ce1 131.02(2) 3_546 7_565 ?
 Al9 Al1 Ce1 66.900(11) . 7_565 ?
 Al9 Al1 Ce1 122.29(3) 1_556 7_565 ?
 Al6 Al1 Ce1 123.14(3) 1_556 7_565 ?
 Al6 Al1 Ce1 68.060(18) . 7_565 ?
 Al5 Al1 Ce1 63.33(2) 7_565 7_565 ?
 Co2 Al7 Fe1 146.07(5) . 7_665 ?
 Co2 Al7 Co1 146.07(5) . 7_665 ?
 Fe1 Al7 Co1 0.000(18) 7_665 7_665 ?
 Co2 Al7 Co1 146.21(5) . 3_545 ?
 Fe1 Al7 Co1 67.72(2) 7_665 3_545 ?
 Co1 Al7 Co1 67.72(2) 7_665 3_545 ?
 Co2 Al7 Fe1 146.21(5) . 3_545 ?
 Fe1 Al7 Fe1 67.72(2) 7_665 3_545 ?
 Co1 Al7 Fe1 67.72(2) 7_665 3_545 ?
 Co1 Al7 Fe1 0.000(17) 3_545 3_545 ?
 Co2 Al7 Al8 136.382(11) . 3_546 ?
 Fe1 Al7 Al8 53.054(13) 7_665 3_546 ?
 Co1 Al7 Al8 53.054(13) 7_665 3_546 ?
 Co1 Al7 Al8 53.039(15) 3_545 3_546 ?
 Fe1 Al7 Al8 53.039(15) 3_545 3_546 ?
 Co2 Al7 Al8 136.382(11) . 3_545 ?
 Fe1 Al7 Al8 53.054(13) 7_665 3_545 ?
 Co1 Al7 Al8 53.054(13) 7_665 3_545 ?
 Co1 Al7 Al8 53.039(15) 3_545 3_545 ?
 Fe1 Al7 Al8 53.039(15) 3_545 3_545 ?
 Al8 Al7 Al8 87.24(2) 3_546 3_545 ?
 Co1 Al6 Co2 178.03(4) . . ?
 Co1 Al6 Al1 119.22(3) . 1_554 ?
 Co2 Al6 Al1 59.67(2) . 1_554 ?
 Co1 Al6 Al1 119.22(3) . . ?
 Co2 Al6 Al1 59.67(2) . . ?
 Al1 Al6 Al1 91.81(3) 1_554 . ?
 Co1 Al6 Al2 59.11(2) . . ?
 Co2 Al6 Al2 121.97(3) . . ?
 Al1 Al6 Al2 178.18(4) 1_554 . ?
 Al1 Al6 Al2 88.57(2) . . ?

```

Co1 Al6 Al2 59.11(2) . 1_554 ?
Co2 Al6 Al2 121.97(3) . 1_554 ?
Al1 Al6 Al2 88.57(2) 1_554 1_554 ?
Al1 Al6 Al2 178.18(4) . 1_554 ?
Al2 Al6 Al2 91.00(4) . 1_554 ?
Co1 Al6 Al5 58.58(2) . 7_564 ?
Co2 Al6 Al5 120.29(3) . 7_564 ?
Al1 Al6 Al5 60.64(2) 1_554 7_564 ?
Al1 Al6 Al5 121.50(4) . 7_564 ?
Al2 Al6 Al5 117.69(3) . 7_564 ?
Al2 Al6 Al5 57.24(2) 1_554 7_564 ?
Co1 Al6 Al5 58.58(2) . 7_565 ?
Co2 Al6 Al5 120.29(3) . 7_565 ?
Al1 Al6 Al5 121.50(4) 1_554 7_565 ?
Al1 Al6 Al5 60.64(2) . 7_565 ?
Al2 Al6 Al5 57.24(2) . 7_565 ?
Al2 Al6 Al5 117.69(3) 1_554 7_565 ?
Al5 Al6 Al5 89.67(3) 7_564 7_565 ?
Co1 Al6 Al3 124.90(2) . . ?
Co2 Al6 Al3 56.17(2) . . ?
Al1 Al6 Al3 115.85(3) 1_554 . ?
Al1 Al6 Al3 56.02(2) . . ?
Al2 Al6 Al3 65.80(2) . . ?
Al2 Al6 Al3 125.32(3) 1_554 . ?
Al5 Al6 Al3 176.17(4) 7_564 . ?
Al5 Al6 Al3 91.21(2) 7_565 . ?
Co1 Al6 Al3 124.90(2) . 1_554 ?
Co2 Al6 Al3 56.17(2) . 1_554 ?
Al1 Al6 Al3 56.02(2) 1_554 1_554 ?
Al1 Al6 Al3 115.85(3) . 1_554 ?
Al2 Al6 Al3 125.32(3) . 1_554 ?
Al2 Al6 Al3 65.80(2) 1_554 1_554 ?
Al5 Al6 Al3 91.21(2) 7_564 1_554 ?
Al5 Al6 Al3 176.17(4) 7_565 1_554 ?
Al3 Al6 Al3 87.67(3) . 1_554 ?

_diffn_measured_fraction_theta_max 0.997
_diffn_reflms_theta_full 30.45
_diffn_measured_fraction_theta_full 0.997
_refine_diff_density_max 1.417
_refine_diff_density_min -1.923
_refine_diff_density_rms 0.296

```

data_shelxl

```

_audit_creation_method SHELXL-97
_chemical_name_systematic
;
?
;
_chemical_name_common ?
_chemical_melting_point ?
_chemical_formula_moiety ?
_chemical_formula_sum
'Al8 Ce Co Ni'
_chemical_formula_weight 473.60

```

```

loop_
_atom_type_symbol
_atom_type_description
_atom_type_scatter_dispersion_real

```

```

_atom_type_scatter_dispersion_imag
_atom_type_scatter_source
'Ce' 'Ce' -0.2486 2.6331
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Co' 'Co' 0.3494 0.9721
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ni' 'Ni' 0.3393 1.1124
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Al' 'Al' 0.0645 0.0514
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

```

```

_symmetry_cell_setting ?
_symmetry_space_group_name_H-M ?

```

```

loop_
_symmetry_equiv_pos_as_xyz
'x, y, z'
'-x, -y, z'
'x+1/2, -y+1/2, -z'
'-x+1/2, y+1/2, -z'
'-x, -y, -z'
'x, y, -z'
'-x-1/2, y-1/2, z'
'x-1/2, -y-1/2, z'

```

```

_cell_length_a 12.4770(10)
_cell_length_b 14.393(4)
_cell_length_c 4.023(4)
_cell_angle_alpha 90.00
_cell_angle_beta 90.00
_cell_angle_gamma 90.00
_cell_volume 722.5(7)
_cell_formula_units_Z 4
_cell_measurement_temperature 293(2)
_cell_measurement_reflns_used ?
_cell_measurement_theta_min ?
_cell_measurement_theta_max ?

```

```

_exptl_crystal_description ?
_exptl_crystal_colour ?
_exptl_crystal_size_max ?
_exptl_crystal_size_mid ?
_exptl_crystal_size_min ?
_exptl_crystal_density_meas ?
_exptl_crystal_density_diffn 4.354
_exptl_crystal_density_method 'not measured'
_exptl_crystal_F_000 868
_exptl_absorpt_coefficient_mu 11.910
_exptl_absorpt_correction_type ?
_exptl_absorpt_correction_T_min ?
_exptl_absorpt_correction_T_max ?
_exptl_absorpt_process_details ?

```

```

_exptl_special_details
;
?
;

```

```

_diffn_ambient_temperature 293(2)
_diffn_radiation_wavelength 0.71073
_diffn_radiation_type MoK\alpha
_diffn_radiation_source 'fine-focus sealed tube'

```

```

_diffrn_radiation_monochromator graphite
_diffrn_measurement_device_type ?
_diffrn_measurement_method ?
_diffrn_detector_area_resol_mean ?
_diffrn_standards_number ?
_diffrn_standards_interval_count ?
_diffrn_standards_interval_time ?
_diffrn_standards_decay_% ?
_diffrn_reflns_number 2149
_diffrn_reflns_av_R_equivalents 0.0488
_diffrn_reflns_av_sigma/ntI 0.0556
_diffrn_reflns_limit_h_min -17
_diffrn_reflns_limit_h_max 18
_diffrn_reflns_limit_k_min -20
_diffrn_reflns_limit_k_max 20
_diffrn_reflns_limit_l_min -5
_diffrn_reflns_limit_l_max 5
_diffrn_reflns_theta_min 2.83
_diffrn_reflns_theta_max 31.19
_reflns_number_total 1303
_reflns_number_gt 942
_reflns_threshold_expression >2\s(I)

_computing_data_collection ?
_computing_cell_refinement ?
_computing_data_reduction ?
_computing_structure_solution ?
_computing_structure_refinement 'SHELXL-97
(Sheldrick, 2008)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F^2^ against ALL reflections. The
weighted R-factor wR and
goodness of fit S are based on F^2^, conventional R-
factors R are based
on F, with F set to zero for negative F^2^. The threshold
expression of
F^2^ > 2\s(F^2^) is used only for calculating R-factors(gt)
etc. and is
not relevant to the choice of reflections for refinement. R-
factors based
on F^2^ are statistically about twice as large as those based
on F, and R-
factors based on ALL data will be even larger.
;

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type full
_refine_ls_weighting_scheme calc
_refine_ls_weighting_details
'calc w=1/[\s^2^(Fo^2^)+(0.0112P)^2^+7.2986P] where
P=(Fo^2^+2Fc^2^)/3'
_atom_sites_solution_primary direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment mixed
_refine_ls_extinction_method SHELXL
_refine_ls_extinction_coef 0.00235(17)
_refine_ls_extinction_expression

```

```

Fc^*=kFc[1+0.001xFc^2^\l^3^\sin(2\q)]^-1/4^
_refine_ls_number_reflns 1303
_refine_ls_number_parameters 72
_refine_ls_number_restraints 0
_refine_ls_R_factor_all 0.0651
_refine_ls_R_factor_gt 0.0366
_refine_ls_wR_factor_ref 0.0767
_refine_ls_wR_factor_gt 0.0628
_refine_ls_goodness_of_fit_ref 1.060
_refine_ls_restrained_S_all 1.060
_refine_ls_shift/su_max 0.000
_refine_ls_shift/su_mean 0.000

```

```

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ce1 Ce 0.34044(4) 0.31848(3) 0.0000 0.01117(14) Uani 1
2 d S . .
Ni1 Ni 0.03473(9) 0.40571(8) 0.0000 0.0098(4) Uani
0.09(11) 2 d SP . .
Co1 Co 0.03473(9) 0.40571(8) 0.0000 0.0098(4) Uani
0.91(11) 2 d SP . .
Ni2 Ni 0.15175(9) 0.09640(7) 0.0000 0.0087(4) Uani
0.20(10) 2 d SP . .
Co2 Co 0.15175(9) 0.09640(7) 0.0000 0.0087(4) Uani
0.80(10) 2 d SP . .
Al1 Al 0.0253(2) 0.13172(17) 0.5000 0.0099(5) Uani 1 2 d
S . .
Al2 Al 0.1597(2) 0.37958(17) 0.5000 0.0101(5) Uani 1 2 d
S . .
Al3 Al 0.2366(2) 0.17235(18) 0.5000 0.0105(5) Uani 1 2 d
S . .
Al4 Al 0.3318(2) 0.49155(16) 0.5000 0.0099(5) Uani 1 2 d
S . .
Al5 Al 0.4523(2) 0.17948(18) 0.5000 0.0104(5) Uani 1 2 d
S . .
Al6 Al 0.0961(2) 0.25286(18) 0.0000 0.0105(5) Uani 1 2 d
S . .
Al7 Al 0.3399(2) 0.04426(17) 0.0000 0.0114(5) Uani 1 2 d
S . .
Al8 Al 0.0000 0.5000 0.5000 0.0098(8) Uani 1 4 d S . .
Al9 Al 0.0000 0.0000 0.0000 0.0109(7) Uani 1 4 d S . .

```

```

loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12

```

Ce1 0.0111(2) 0.0140(2) 0.0085(2) 0.000 0.000 -0.0010(2)
 Ni1 0.0113(6) 0.0099(6) 0.0082(6) 0.000 0.000 0.0008(4)
 Co1 0.0113(6) 0.0099(6) 0.0082(6) 0.000 0.000 0.0008(4)
 Ni2 0.0095(6) 0.0094(5) 0.0073(5) 0.000 0.000 -0.0002(5)
 Co2 0.0095(6) 0.0094(5) 0.0073(5) 0.000 0.000 -0.0002(5)
 Al1 0.0096(12) 0.0105(11) 0.0096(12) 0.000 0.000
 0.0001(10)
 Al2 0.0072(11) 0.0136(11) 0.0094(11) 0.000 0.000
 0.0004(10)
 Al3 0.0093(12) 0.0119(12) 0.0103(11) 0.000 0.000 -
 0.0012(10)
 Al4 0.0119(13) 0.0079(10) 0.0100(11) 0.000 0.000 -
 0.0009(10)
 Al5 0.0105(12) 0.0108(11) 0.0100(11) 0.000 0.000 -
 0.0001(10)
 Al6 0.0109(12) 0.0106(11) 0.0098(10) 0.000 0.000
 0.0011(9)
 Al7 0.0074(11) 0.0152(12) 0.0115(12) 0.000 0.000
 0.0033(11)
 Al8 0.0126(19) 0.0096(16) 0.0072(16) 0.000 0.000
 0.0008(13)
 Al9 0.0100(18) 0.0119(17) 0.0107(17) 0.000 0.000 -
 0.0027(14)

_geom_special_details

;
 All s.u.'s (except the s.u. in the dihedral angle between two
 l.s. planes)
 are estimated using the full covariance matrix. The cell
 s.u.'s are taken
 into account individually in the estimation of s.u.'s in
 distances, angles
 and torsion angles; correlations between s.u.'s in cell
 parameters are only
 used when they are defined by crystal symmetry. An
 approximate (isotropic)
 treatment of cell s.u.'s is used for estimating s.u.'s
 involving l.s. planes.
 ;

loop_

_geom_bond_atom_site_label_1
 _geom_bond_atom_site_label_2
 _geom_bond_distance
 _geom_bond_site_symmetry_2
 _geom_bond_publ_flag
 Ce1 Al1 3.143(2) 3_556 ?
 Ce1 Al1 3.143(2) 3 ?
 Ce1 Al2 3.148(3) 1_554 ?
 Ce1 Al2 3.148(3) . ?
 Ce1 Al5 3.162(2) 1_554 ?
 Ce1 Al5 3.162(2) . ?
 Ce1 Al3 3.186(2) 1_554 ?
 Ce1 Al3 3.186(2) . ?
 Ce1 Al6 3.191(3) . ?
 Ce1 Al4 3.204(2) . ?
 Ce1 Al4 3.204(2) 1_554 ?
 Ce1 Al9 3.2847(8) 3 ?
 Ni1 Al6 2.330(3) . ?
 Ni1 Al8 2.4649(18) . ?
 Ni1 Al8 2.4649(18) 1_554 ?
 Ni1 Al7 2.534(3) 7_665 ?

Ni1 Al7 2.535(3) 3_455 ?
 Ni1 Al5 2.570(2) 3_455 ?
 Ni1 Al5 2.570(2) 3_456 ?
 Ni1 Al2 2.573(2) . ?
 Ni1 Al2 2.573(2) 1_554 ?
 Ni1 Co1 2.849(2) 5_565 ?
 Ni1 Ni1 2.849(2) 5_565 ?
 Ni2 Al9 2.3473(12) . ?
 Ni2 Al6 2.356(3) . ?
 Ni2 Al7 2.465(3) . ?
 Ni2 Al3 2.522(2) . ?
 Ni2 Al3 2.522(2) 1_554 ?
 Ni2 Al4 2.523(2) 7_654 ?
 Ni2 Al4 2.523(2) 7_655 ?
 Ni2 Al1 2.607(2) 1_554 ?
 Ni2 Al1 2.607(2) . ?
 Al1 Co2 2.607(2) 1_556 ?
 Al1 Ni2 2.607(2) 1_556 ?
 Al1 Al4 2.693(4) 7_655 ?
 Al1 Al3 2.701(4) . ?
 Al1 Al9 2.782(2) . ?
 Al1 Al9 2.782(2) 1_556 ?
 Al1 Al6 2.805(3) 1_556 ?
 Al1 Al6 2.805(3) . ?
 Al1 Al5 2.866(4) 3_456 ?
 Al1 Al4 2.996(4) 3_456 ?
 Al2 Co1 2.573(2) 1_556 ?
 Al2 Ni1 2.573(2) 1_556 ?
 Al2 Al8 2.641(3) . ?
 Al2 Al4 2.685(4) . ?
 Al2 Al5 2.723(4) 3_456 ?
 Al2 Al6 2.829(3) . ?
 Al2 Al6 2.829(3) 1_556 ?
 Al2 Ce1 3.148(3) 1_556 ?
 Al3 Co2 2.522(2) 1_556 ?
 Al3 Ni2 2.522(2) 1_556 ?
 Al3 Al5 2.693(3) . ?
 Al3 Al4 2.739(4) 7_655 ?
 Al3 Al6 2.909(3) . ?
 Al3 Al6 2.909(3) 1_556 ?
 Al3 Ce1 3.186(2) 1_556 ?
 Al4 Co2 2.523(2) 7_666 ?
 Al4 Ni2 2.523(2) 7_666 ?
 Al4 Co2 2.523(2) 7_665 ?
 Al4 Ni2 2.523(2) 7_665 ?
 Al4 Al1 2.693(4) 7_665 ?
 Al4 Al3 2.739(4) 7_665 ?
 Al4 Al9 2.910(3) 3_556 ?
 Al4 Al9 2.910(3) 3 ?
 Al4 Al1 2.996(4) 3_556 ?
 Al4 Ce1 3.204(2) 1_556 ?
 Al5 Co1 2.570(2) 3 ?
 Al5 Ni1 2.570(2) 3 ?
 Al5 Co1 2.570(2) 3_556 ?
 Al5 Ni1 2.570(2) 3_556 ?
 Al5 Al8 2.651(3) 3_556 ?
 Al5 Al2 2.723(4) 3_556 ?
 Al5 Al1 2.866(4) 3_556 ?
 Al5 Al6 2.866(3) 3_556 ?
 Al5 Al6 2.866(3) 3 ?
 Al5 Ce1 3.162(2) 1_556 ?
 Al6 Al1 2.805(3) 1_554 ?

Al6 Al2 2.829(3) 1_554 ?
 Al6 Al5 2.866(3) 3_455 ?
 Al6 Al5 2.866(3) 3_456 ?
 Al6 Al3 2.909(3) 1_554 ?
 Al7 Co1 2.534(3) 7_655 ?
 Al7 Ni1 2.534(3) 7_655 ?
 Al7 Ni1 2.535(3) 3 ?
 Al7 Co1 2.535(3) 3 ?
 Al7 Al8 2.906(2) 3_556 ?
 Al7 Al8 2.906(2) 3 ?
 Al8 Co1 2.4649(18) 5_566 ?
 Al8 Ni1 2.4649(18) 5_566 ?
 Al8 Co1 2.4649(18) 5_565 ?
 Al8 Ni1 2.4649(18) 5_565 ?
 Al8 Ni1 2.4649(18) 1_556 ?
 Al8 Co1 2.4649(18) 1_556 ?
 Al8 Al2 2.641(3) 5_566 ?
 Al8 Al5 2.651(3) 3_456 ?
 Al8 Al5 2.651(3) 7_665 ?
 Al9 Co2 2.3473(12) 5 ?
 Al9 Ni2 2.3473(12) 5 ?
 Al9 Al1 2.782(2) 5 ?
 Al9 Al1 2.782(2) 5_556 ?
 Al9 Al1 2.782(2) 1_554 ?
 Al9 Al4 2.910(3) 7_655 ?
 Al9 Al4 2.910(3) 3_455 ?
 Al9 Al4 2.910(3) 7_654 ?
 Al9 Al4 2.910(3) 3_456 ?

loop_

_geom_angle_atom_site_label_1
 _geom_angle_atom_site_label_2
 _geom_angle_atom_site_label_3
 _geom_angle
 _geom_angle_site_symmetry_1
 _geom_angle_site_symmetry_3
 _geom_angle_publ_flag
 Al1 Ce1 Al1 79.59(9) 3_556 3 ?
 Al1 Ce1 Al2 150.58(7) 3_556 1_554 ?
 Al1 Ce1 Al2 93.04(7) 3 1_554 ?
 Al1 Ce1 Al2 93.04(7) 3_556 . ?
 Al1 Ce1 Al2 150.58(7) 3 . ?
 Al2 Ce1 Al2 79.44(9) 1_554 . ?
 Al1 Ce1 Al5 103.16(7) 3_556 1_554 ?
 Al1 Ce1 Al5 54.07(7) 3 1_554 ?
 Al2 Ce1 Al5 94.96(7) 1_554 1_554 ?
 Al2 Ce1 Al5 154.12(7) . 1_554 ?
 Al1 Ce1 Al5 54.07(7) 3_556 . ?
 Al1 Ce1 Al5 103.16(7) 3 . ?
 Al2 Ce1 Al5 154.12(7) 1_554 . ?
 Al2 Ce1 Al5 94.96(7) . ?
 Al5 Ce1 Al5 79.02(8) 1_554 . ?
 Al1 Ce1 Al3 148.56(7) 3_556 1_554 ?
 Al1 Ce1 Al3 92.57(7) 3 1_554 ?
 Al2 Ce1 Al3 59.30(7) 1_554 1_554 ?
 Al2 Ce1 Al3 107.25(7) . 1_554 ?
 Al5 Ce1 Al3 50.21(6) 1_554 1_554 ?
 Al5 Ce1 Al3 99.41(7) . 1_554 ?
 Al1 Ce1 Al3 92.57(7) 3_556 . ?
 Al1 Ce1 Al3 148.56(7) 3 . ?
 Al2 Ce1 Al3 107.25(7) 1_554 . ?
 Al2 Ce1 Al3 59.30(7) . ?

Al5 Ce1 Al3 99.41(7) 1_554 . ?
 Al5 Ce1 Al3 50.21(6) . ?
 Al3 Ce1 Al3 78.31(8) 1_554 . ?
 Al1 Ce1 Al6 140.21(4) 3_556 . ?
 Al1 Ce1 Al6 140.21(4) 3 . ?
 Al2 Ce1 Al6 53.00(6) 1_554 . ?
 Al2 Ce1 Al6 53.00(6) . ?
 Al5 Ce1 Al6 103.56(6) 1_554 . ?
 Al5 Ce1 Al6 103.56(6) . ?
 Al3 Ce1 Al6 54.28(5) 1_554 . ?
 Al3 Ce1 Al6 54.28(5) . ?
 Al1 Ce1 Al4 56.33(7) 3_556 . ?
 Al1 Ce1 Al4 104.44(7) 3 . ?
 Al2 Ce1 Al4 99.19(7) 1_554 . ?
 Al2 Ce1 Al4 50.00(7) . ?
 Al5 Ce1 Al4 155.01(7) 1_554 . ?
 Al5 Ce1 Al4 96.17(7) . ?
 Al3 Ce1 Al4 153.64(7) 1_554 . ?
 Al3 Ce1 Al4 95.92(7) . ?
 Al6 Ce1 Al4 101.41(7) . ?
 Al1 Ce1 Al4 104.44(7) 3_556 1_554 ?
 Al1 Ce1 Al4 56.33(7) 3 1_554 ?
 Al2 Ce1 Al4 50.00(7) 1_554 1_554 ?
 Al2 Ce1 Al4 99.19(7) . 1_554 ?
 Al5 Ce1 Al4 96.17(7) 1_554 1_554 ?
 Al5 Ce1 Al4 155.01(7) . 1_554 ?
 Al3 Ce1 Al4 95.92(7) 1_554 1_554 ?
 Al3 Ce1 Al4 153.64(7) . 1_554 ?
 Al6 Ce1 Al4 101.41(7) . 1_554 ?
 Al4 Ce1 Al4 77.79(8) . 1_554 ?
 Al1 Ce1 Al9 51.24(4) 3_556 3 ?
 Al1 Ce1 Al9 51.24(4) 3 3 ?
 Al2 Ce1 Al9 102.24(5) 1_554 3 ?
 Al2 Ce1 Al9 102.24(5) . 3 ?
 Al5 Ce1 Al9 103.64(5) 1_554 3 ?
 Al5 Ce1 Al9 103.64(5) . 3 ?
 Al3 Ce1 Al9 140.50(4) 1_554 3 ?
 Al3 Ce1 Al9 140.50(4) . 3 ?
 Al6 Ce1 Al9 144.52(5) . 3 ?
 Al4 Ce1 Al9 53.27(5) . 3 ?
 Al4 Ce1 Al9 53.27(5) 1_554 3 ?
 Al6 Ni1 Al8 125.29(3) . ?
 Al6 Ni1 Al8 125.29(3) . 1_554 ?
 Al8 Ni1 Al8 109.39(7) . 1_554 ?
 Al6 Ni1 Al7 122.69(11) . 7_665 ?
 Al8 Ni1 Al7 71.05(4) . 7_665 ?
 Al8 Ni1 Al7 71.05(4) 1_554 7_665 ?
 Al6 Ni1 Al7 125.70(10) . 3_455 ?
 Al8 Ni1 Al7 71.04(4) . 3_455 ?
 Al8 Ni1 Al7 71.04(4) 1_554 3_455 ?
 Al7 Ni1 Al7 111.61(8) 7_665 3_455 ?
 Al6 Ni1 Al5 71.40(7) . 3_455 ?
 Al8 Ni1 Al5 146.19(8) . 3_455 ?
 Al8 Ni1 Al5 63.49(7) 1_554 3_455 ?
 Al7 Ni1 Al5 128.48(6) 7_665 3_455 ?
 Al7 Ni1 Al5 75.63(7) 3_455 3_455 ?
 Al6 Ni1 Al5 71.40(7) . 3_456 ?
 Al8 Ni1 Al5 63.49(7) . 3_456 ?
 Al8 Ni1 Al5 146.19(8) 1_554 3_456 ?
 Al7 Ni1 Al5 128.48(6) 7_665 3_456 ?
 Al7 Ni1 Al5 75.63(7) 3_455 3_456 ?
 Al5 Ni1 Al5 102.99(11) 3_455 3_456 ?

Al6 Ni1 Al2 70.28(7) . . ?
 Al8 Ni1 Al2 63.19(7) . . ?
 Al8 Ni1 Al2 145.60(8) 1_554 . ?
 Al7 Ni1 Al2 74.99(7) 7_665 . ?
 Al7 Ni1 Al2 128.50(6) 3_455 . ?
 Al5 Ni1 Al2 141.68(9) 3_455 . ?
 Al5 Ni1 Al2 63.95(8) 3_456 . ?
 Al6 Ni1 Al2 70.28(7) . 1_554 ?
 Al8 Ni1 Al2 145.60(8) . 1_554 ?
 Al8 Ni1 Al2 63.19(7) 1_554 1_554 ?
 Al7 Ni1 Al2 74.99(7) 7_665 1_554 ?
 Al7 Ni1 Al2 128.50(6) 3_455 1_554 ?
 Al5 Ni1 Al2 63.95(8) 3_455 1_554 ?
 Al5 Ni1 Al2 141.68(9) 3_456 1_554 ?
 Al2 Ni1 Al2 102.87(12) . 1_554 ?
 Al6 Ni1 Co1 178.51(10) . 5_565 ?
 Al8 Ni1 Co1 54.69(3) . 5_565 ?
 Al8 Ni1 Co1 54.69(3) 1_554 5_565 ?
 Al7 Ni1 Co1 55.82(7) 7_665 5_565 ?
 Al7 Ni1 Co1 55.79(7) 3_455 5_565 ?
 Al5 Ni1 Co1 109.43(7) 3_455 5_565 ?
 Al5 Ni1 Co1 109.43(7) 3_456 5_565 ?
 Al2 Ni1 Co1 108.88(7) . 5_565 ?
 Al2 Ni1 Co1 108.88(7) 1_554 5_565 ?
 Al6 Ni1 Ni1 178.51(10) . 5_565 ?
 Al8 Ni1 Ni1 54.69(3) . 5_565 ?
 Al8 Ni1 Ni1 54.69(3) 1_554 5_565 ?
 Al7 Ni1 Ni1 55.82(7) 7_665 5_565 ?
 Al7 Ni1 Ni1 55.79(7) 3_455 5_565 ?
 Al5 Ni1 Ni1 109.43(7) 3_455 5_565 ?
 Al5 Ni1 Ni1 109.43(7) 3_456 5_565 ?
 Al2 Ni1 Ni1 108.88(7) . 5_565 ?
 Al2 Ni1 Ni1 108.88(7) 1_554 5_565 ?
 Co1 Ni1 Ni1 0.00(4) 5_565 5_565 ?
 Al9 Ni2 Al6 109.11(8) . . ?
 Al9 Ni2 Al7 126.04(7) . . ?
 Al6 Ni2 Al7 124.86(10) . . ?
 Al9 Ni2 Al3 126.49(6) . . ?
 Al6 Ni2 Al3 73.11(7) . . ?
 Al7 Ni2 Al3 74.47(7) . . ?
 Al9 Ni2 Al3 126.49(6) . 1_554 ?
 Al6 Ni2 Al3 73.11(7) . 1_554 ?
 Al7 Ni2 Al3 74.47(7) . 1_554 ?
 Al3 Ni2 Al3 105.78(12) . 1_554 ?
 Al9 Ni2 Al4 73.28(7) . 7_654 ?
 Al6 Ni2 Al4 126.56(6) . 7_654 ?
 Al7 Ni2 Al4 74.94(8) . 7_654 ?
 Al3 Ni2 Al4 149.41(10) . 7_654 ?
 Al3 Ni2 Al4 65.75(9) 1_554 7_654 ?
 Al9 Ni2 Al4 73.28(7) . 7_655 ?
 Al6 Ni2 Al4 126.56(6) . 7_655 ?
 Al7 Ni2 Al4 74.94(8) . 7_655 ?
 Al3 Ni2 Al4 65.75(9) . 7_655 ?
 Al3 Ni2 Al4 149.41(10) 1_554 7_655 ?
 Al4 Ni2 Al4 105.74(11) 7_654 7_655 ?
 Al9 Ni2 Al1 68.10(6) . 1_554 ?
 Al6 Ni2 Al1 68.61(7) . 1_554 ?
 Al7 Ni2 Al1 129.50(6) . 1_554 ?
 Al3 Ni2 Al1 141.72(9) . 1_554 ?
 Al3 Ni2 Al1 63.53(8) 1_554 1_554 ?
 Al4 Ni2 Al1 63.31(8) 7_654 1_554 ?
 Al4 Ni2 Al1 141.37(10) 7_655 1_554 ?

Al9 Ni2 Al1 68.10(6) . . ?
 Al6 Ni2 Al1 68.61(7) . . ?
 Al7 Ni2 Al1 129.50(6) . . ?
 Al3 Ni2 Al1 63.53(8) . . ?
 Al3 Ni2 Al1 141.72(9) 1_554 . ?
 Al4 Ni2 Al1 141.37(10) 7_654 . ?
 Al4 Ni2 Al1 63.31(8) 7_655 . ?
 Al1 Ni2 Al1 101.01(11) 1_554 . ?
 Co2 Al1 Ni2 0.00(5) 1_556 1_556 ?
 Co2 Al1 Ni2 101.01(11) 1_556 . ?
 Ni2 Al1 Ni2 101.01(11) 1_556 . ?
 Co2 Al1 Al4 56.83(6) 1_556 7_655 ?
 Ni2 Al1 Al4 56.83(6) 1_556 7_655 ?
 Ni2 Al1 Al4 56.83(6) . 7_655 ?
 Co2 Al1 Al3 56.71(6) 1_556 . ?
 Ni2 Al1 Al3 56.71(6) 1_556 . ?
 Ni2 Al1 Al3 56.71(6) . . ?
 Al4 Al1 Al3 61.02(10) 7_655 . ?
 Co2 Al1 Al9 119.58(10) 1_556 . ?
 Ni2 Al1 Al9 119.58(10) 1_556 . ?
 Ni2 Al1 Al9 51.52(5) . . ?
 Al4 Al1 Al9 64.19(6) 7_655 . ?
 Al3 Al1 Al9 104.96(8) . . ?
 Co2 Al1 Al9 51.52(5) 1_556 1_556 ?
 Ni2 Al1 Al9 51.52(5) 1_556 1_556 ?
 Ni2 Al1 Al9 119.58(10) . 1_556 ?
 Al4 Al1 Al9 64.19(6) 7_655 1_556 ?
 Al3 Al1 Al9 104.96(8) . 1_556 ?
 Al9 Al1 Al9 92.61(9) . 1_556 ?
 Co2 Al1 Al6 51.47(7) 1_556 1_556 ?
 Ni2 Al1 Al6 51.47(7) 1_556 1_556 ?
 Ni2 Al1 Al6 118.93(12) . 1_556 ?
 Al4 Al1 Al6 104.88(10) 7_655 1_556 ?
 Al3 Al1 Al6 63.75(8) . 1_556 ?
 Al9 Al1 Al6 167.91(12) . 1_556 ?
 Al9 Al1 Al6 86.61(7) 1_556 1_556 ?
 Co2 Al1 Al6 118.93(12) 1_556 . ?
 Ni2 Al1 Al6 118.93(12) 1_556 . ?
 Ni2 Al1 Al6 51.47(7) . . ?
 Al4 Al1 Al6 104.88(10) 7_655 . ?
 Al3 Al1 Al6 63.75(8) . . ?
 Al9 Al1 Al6 86.61(7) . . ?
 Al9 Al1 Al6 167.91(12) 1_556 . ?
 Al6 Al1 Al6 91.63(12) 1_556 . ?
 Co2 Al1 Al5 112.16(7) 1_556 3_456 ?
 Ni2 Al1 Al5 112.16(7) 1_556 3_456 ?
 Ni2 Al1 Al5 112.16(7) . 3_456 ?
 Al4 Al1 Al5 157.04(13) 7_655 3_456 ?
 Al3 Al1 Al5 96.02(11) . 3_456 ?
 Al9 Al1 Al5 127.60(6) . 3_456 ?
 Al9 Al1 Al5 127.60(6) 1_556 3_456 ?
 Al6 Al1 Al5 60.71(8) 1_556 3_456 ?
 Al6 Al1 Al5 60.71(8) . 3_456 ?
 Co2 Al1 Al4 111.86(8) 1_556 3_456 ?
 Ni2 Al1 Al4 111.86(8) 1_556 3_456 ?
 Ni2 Al1 Al4 111.86(8) . 3_456 ?
 Al4 Al1 Al4 95.17(11) 7_655 3_456 ?
 Al3 Al1 Al4 156.20(13) . 3_456 ?
 Al9 Al1 Al4 60.34(6) . 3_456 ?
 Al9 Al1 Al4 60.34(6) 1_556 3_456 ?
 Al6 Al1 Al4 128.47(8) 1_556 3_456 ?
 Al6 Al1 Al4 128.47(8) . 3_456 ?

Al5 Al1 Al4 107.79(11) 3_456 3_456 ?
 Ni1 Al2 Co1 102.87(12) . 1_556 ?
 Ni1 Al2 Ni1 102.87(12) . 1_556 ?
 Co1 Al2 Ni1 0.00(4) 1_556 1_556 ?
 Ni1 Al2 Al8 56.42(6) . . ?
 Co1 Al2 Al8 56.42(6) 1_556 . ?
 Ni1 Al2 Al8 56.42(6) 1_556 . ?
 Ni1 Al2 Al4 113.38(8) . . ?
 Co1 Al2 Al4 113.38(8) 1_556 . ?
 Ni1 Al2 Al4 113.38(8) 1_556 . ?
 Al8 Al2 Al4 102.09(10) . . ?
 Ni1 Al2 Al5 57.99(7) . 3_456 ?
 Co1 Al2 Al5 57.99(7) 1_556 3_456 ?
 Ni1 Al2 Al5 57.99(7) 1_556 3_456 ?
 Al8 Al2 Al5 59.21(8) . 3_456 ?
 Al4 Al2 Al5 161.30(13) . 3_456 ?
 Ni1 Al2 Al6 50.83(7) . . ?
 Co1 Al2 Al6 118.72(12) 1_556 . ?
 Ni1 Al2 Al6 118.72(12) 1_556 . ?
 Al8 Al2 Al6 102.23(9) . . ?
 Al4 Al2 Al6 127.68(8) . . ?
 Al5 Al2 Al6 62.13(8) 3_456 . ?
 Ni1 Al2 Al6 118.72(12) . 1_556 ?
 Co1 Al2 Al6 50.83(7) 1_556 1_556 ?
 Ni1 Al2 Al6 50.83(7) 1_556 1_556 ?
 Al8 Al2 Al6 102.23(9) . 1_556 ?
 Al4 Al2 Al6 127.68(8) . 1_556 ?
 Al5 Al2 Al6 62.13(8) 3_456 1_556 ?
 Al6 Al2 Al6 90.65(12) . 1_556 ?
 Ni1 Al2 Ce1 167.11(8) . 1_556 ?
 Co1 Al2 Ce1 88.59(6) 1_556 1_556 ?
 Ni1 Al2 Ce1 88.59(6) 1_556 1_556 ?
 Al8 Al2 Ce1 136.39(5) . 1_556 ?
 Al4 Al2 Ce1 66.08(7) . 1_556 ?
 Al5 Al2 Ce1 126.41(7) 3_456 1_556 ?
 Al6 Al2 Ce1 118.37(10) . 1_556 ?
 Al6 Al2 Ce1 64.29(7) 1_556 1_556 ?
 Ni1 Al2 Ce1 88.59(6) . . ?
 Co1 Al2 Ce1 167.11(8) 1_556 . ?
 Ni1 Al2 Ce1 167.11(8) 1_556 . ?
 Al8 Al2 Ce1 136.39(5) . . ?
 Al4 Al2 Ce1 66.08(7) . . ?
 Al5 Al2 Ce1 126.41(7) 3_456 . ?
 Al6 Al2 Ce1 64.29(7) . . ?
 Al6 Al2 Ce1 118.37(10) 1_556 . ?
 Ce1 Al2 Ce1 79.44(9) 1_556 . ?
 Ni2 Al3 Co2 105.78(12) . 1_556 ?
 Ni2 Al3 Ni2 105.78(12) . 1_556 ?
 Co2 Al3 Ni2 0.00(7) 1_556 1_556 ?
 Ni2 Al3 Al5 115.84(8) . . ?
 Co2 Al3 Al5 115.84(8) 1_556 . ?
 Ni2 Al3 Al5 115.84(8) 1_556 . ?
 Ni2 Al3 Al1 59.76(6) . . ?
 Co2 Al3 Al1 59.76(6) 1_556 . ?
 Ni2 Al3 Al1 59.76(6) 1_556 . ?
 Al5 Al3 Al1 169.68(14) . . ?
 Ni2 Al3 Al4 57.14(6) . 7_655 ?
 Co2 Al3 Al4 57.14(6) 1_556 7_655 ?
 Ni2 Al3 Al4 57.14(6) 1_556 7_655 ?
 Al5 Al3 Al4 110.33(13) . 7_655 ?
 Al1 Al3 Al4 59.35(10) . 7_655 ?
 Ni2 Al3 Al6 50.82(7) . . ?

Co2 Al3 Al6 118.12(12) 1_556 . ?
 Ni2 Al3 Al6 118.12(12) 1_556 . ?
 Al5 Al3 Al6 125.94(9) . . ?
 Al1 Al3 Al6 59.87(8) . . ?
 Al4 Al3 Al6 101.01(10) 7_655 . ?
 Ni2 Al3 Al6 118.12(12) . 1_556 ?
 Co2 Al3 Al6 50.82(7) 1_556 1_556 ?
 Ni2 Al3 Al6 50.82(7) 1_556 1_556 ?
 Al5 Al3 Al6 125.94(9) . 1_556 ?
 Al1 Al3 Al6 59.87(8) . 1_556 ?
 Al4 Al3 Al6 101.01(10) 7_655 1_556 ?
 Al6 Al3 Al6 87.50(12) . 1_556 ?
 Ni2 Al3 Ce1 163.82(9) . 1_556 ?
 Co2 Al3 Ce1 87.32(6) 1_556 1_556 ?
 Ni2 Al3 Ce1 87.32(6) 1_556 1_556 ?
 Al5 Al3 Ce1 64.43(7) . 1_556 ?
 Al1 Al3 Ce1 122.69(8) . 1_556 ?
 Al4 Al3 Ce1 138.94(5) 7_655 1_556 ?
 Al6 Al3 Ce1 114.75(10) . 1_556 ?
 Al6 Al3 Ce1 62.96(7) 1_556 1_556 ?
 Ni2 Al3 Ce1 87.32(6) . . ?
 Co2 Al3 Ce1 163.82(9) 1_556 . ?
 Ni2 Al3 Ce1 163.82(9) 1_556 . ?
 Al5 Al3 Ce1 64.43(7) . . ?
 Al1 Al3 Ce1 122.69(8) . . ?
 Al4 Al3 Ce1 138.94(5) 7_655 . ?
 Al6 Al3 Ce1 62.96(7) . . ?
 Al6 Al3 Ce1 114.75(10) 1_556 . ?
 Ce1 Al3 Ce1 78.31(8) 1_556 . ?
 Co2 Al4 Ni2 0.0 7_666 7_666 ?
 Co2 Al4 Co2 105.74(11) 7_666 7_665 ?
 Ni2 Al4 Co2 105.74(11) 7_666 7_665 ?
 Co2 Al4 Ni2 105.74(11) 7_666 7_665 ?
 Ni2 Al4 Ni2 105.74(11) 7_666 7_665 ?
 Co2 Al4 Ni2 0.00(4) 7_665 7_665 ?
 Co2 Al4 Al2 115.10(8) 7_666 . ?
 Ni2 Al4 Al2 115.10(8) 7_666 . ?
 Co2 Al4 Al2 115.10(8) 7_665 . ?
 Ni2 Al4 Al2 115.10(8) 7_665 . ?
 Co2 Al4 Al1 59.86(6) 7_666 7_665 ?
 Ni2 Al4 Al1 59.86(6) 7_666 7_665 ?
 Co2 Al4 Al1 59.86(6) 7_665 7_665 ?
 Ni2 Al4 Al1 59.86(6) 7_665 7_665 ?
 Al2 Al4 Al1 168.38(13) . 7_665 ?
 Co2 Al4 Al3 57.11(6) 7_666 7_665 ?
 Ni2 Al4 Al3 57.11(6) 7_666 7_665 ?
 Co2 Al4 Al3 57.11(6) 7_665 7_665 ?
 Ni2 Al4 Al3 57.11(6) 7_665 7_665 ?
 Al2 Al4 Al3 108.74(13) . 7_665 ?
 Al1 Al4 Al3 59.63(9) 7_665 7_665 ?
 Co2 Al4 Al9 50.58(5) 7_666 3_556 ?
 Ni2 Al4 Al9 50.58(5) 7_666 3_556 ?
 Co2 Al4 Al9 117.86(11) 7_665 3_556 ?
 Ni2 Al4 Al9 117.86(11) 7_665 3_556 ?
 Al2 Al4 Al9 127.02(6) . 3_556 ?
 Al1 Al4 Al9 59.39(6) 7_665 3_556 ?
 Al3 Al4 Al9 100.66(7) 7_665 3_556 ?
 Co2 Al4 Al9 117.86(11) 7_666 3 ?
 Ni2 Al4 Al9 117.86(11) 7_666 3 ?
 Co2 Al4 Al9 50.58(5) 7_665 3 ?
 Ni2 Al4 Al9 50.58(5) 7_665 3 ?
 Al2 Al4 Al9 127.02(6) . 3 ?

Al1 Al4 Al9 59.39(6) 7_665 3 ?
 Al3 Al4 Al9 100.66(7) 7_665 3 ?
 Al9 Al4 Al9 87.46(10) 3_556 3 ?
 Co2 Al4 Al1 106.77(9) 7_666 3_556 ?
 Ni2 Al4 Al1 106.77(9) 7_666 3_556 ?
 Co2 Al4 Al1 106.77(9) 7_665 3_556 ?
 Ni2 Al4 Al1 106.77(9) 7_665 3_556 ?
 Al2 Al4 Al1 106.80(11) . 3_556 ?
 Al1 Al4 Al1 84.83(11) 7_665 3_556 ?
 Al3 Al4 Al1 144.46(13) 7_665 3_556 ?
 Al9 Al4 Al1 56.18(6) 3_556 3_556 ?
 Al9 Al4 Al1 56.18(6) 3 3_556 ?
 Co2 Al4 Ce1 164.34(9) 7_666 . ?
 Ni2 Al4 Ce1 164.34(9) 7_666 . ?
 Co2 Al4 Ce1 87.81(6) 7_665 . ?
 Ni2 Al4 Ce1 87.81(6) 7_665 . ?
 Al2 Al4 Ce1 63.91(6) . . ?
 Al1 Al4 Ce1 124.06(9) 7_665 . ?
 Al3 Al4 Ce1 138.54(6) 7_665 . ?
 Al9 Al4 Ce1 116.24(9) 3_556 . ?
 Al9 Al4 Ce1 64.79(5) 3 . ?
 Al1 Al4 Ce1 60.81(6) 3_556 . ?
 Co2 Al4 Ce1 87.81(6) 7_666 1_556 ?
 Ni2 Al4 Ce1 87.81(6) 7_666 1_556 ?
 Co2 Al4 Ce1 164.34(9) 7_665 1_556 ?
 Ni2 Al4 Ce1 164.34(9) 7_665 1_556 ?
 Al2 Al4 Ce1 63.91(6) . 1_556 ?
 Al1 Al4 Ce1 124.06(9) 7_665 1_556 ?
 Al3 Al4 Ce1 138.54(6) 7_665 1_556 ?
 Al9 Al4 Ce1 64.79(5) 3_556 1_556 ?
 Al9 Al4 Ce1 116.24(9) 3 1_556 ?
 Al1 Al4 Ce1 60.81(6) 3_556 1_556 ?
 Ce1 Al4 Ce1 77.79(8) . 1_556 ?
 Co1 Al5 Ni1 0.00(6) 3 3 ?
 Co1 Al5 Co1 102.99(11) 3 3_556 ?
 Ni1 Al5 Co1 102.99(11) 3 3_556 ?
 Co1 Al5 Ni1 102.99(11) 3 3_556 ?
 Ni1 Al5 Ni1 102.99(11) 3 3_556 ?
 Co1 Al5 Ni1 0.00(4) 3_556 3_556 ?
 Co1 Al5 Al8 56.31(6) 3 3_556 ?
 Ni1 Al5 Al8 56.31(6) 3 3_556 ?
 Co1 Al5 Al8 56.31(6) 3_556 3_556 ?
 Ni1 Al5 Al8 56.31(6) 3_556 3_556 ?
 Co1 Al5 Al3 112.44(8) 3 . ?
 Ni1 Al5 Al3 112.44(8) 3 . ?
 Co1 Al5 Al3 112.44(8) 3_556 . ?
 Ni1 Al5 Al3 112.44(8) 3_556 . ?
 Al8 Al5 Al3 100.79(11) 3_556 . ?
 Co1 Al5 Al2 58.06(6) 3 3_556 ?
 Ni1 Al5 Al2 58.06(6) 3 3_556 ?
 Co1 Al5 Al2 58.06(6) 3_556 3_556 ?
 Ni1 Al5 Al2 58.06(6) 3_556 3_556 ?
 Al8 Al5 Al2 58.84(7) 3_556 3_556 ?
 Al3 Al5 Al2 159.63(14) . 3_556 ?
 Co1 Al5 Al1 108.98(8) 3 3_556 ?
 Ni1 Al5 Al1 108.98(8) 3 3_556 ?
 Co1 Al5 Al1 108.98(8) 3_556 3_556 ?
 Ni1 Al5 Al1 108.98(8) 3_556 3_556 ?
 Al8 Al5 Al1 148.50(11) 3_556 3_556 ?
 Al3 Al5 Al1 110.70(12) . 3_556 ?
 Al2 Al5 Al1 89.67(11) 3_556 3_556 ?
 Co1 Al5 Al6 117.44(11) 3 3_556 ?

Ni1 Al5 Al6 117.44(11) 3 3_556 ?
 Co1 Al5 Al6 50.38(7) 3_556 3_556 ?
 Ni1 Al5 Al6 50.38(7) 3_556 3_556 ?
 Al8 Al5 Al6 100.98(9) 3_556 3_556 ?
 Al3 Al5 Al6 129.69(8) . 3_556 ?
 Al2 Al5 Al6 60.74(8) 3_556 3_556 ?
 Al1 Al5 Al6 58.60(7) 3_556 3_556 ?
 Co1 Al5 Al6 50.38(7) 3 3 ?
 Ni1 Al5 Al6 50.38(7) 3 3 ?
 Co1 Al5 Al6 117.44(11) 3_556 3 ?
 Ni1 Al5 Al6 117.44(11) 3_556 3 ?
 Al8 Al5 Al6 100.98(9) 3_556 3 ?
 Al3 Al5 Al6 129.69(8) . 3 ?
 Al2 Al5 Al6 60.74(8) 3_556 3 ?
 Al1 Al5 Al6 58.60(7) 3_556 3 ?
 Al6 Al5 Al6 89.15(12) 3_556 3 ?
 Co1 Al5 Ce1 167.50(8) 3 1_556 ?
 Ni1 Al5 Ce1 167.50(8) 3 1_556 ?
 Co1 Al5 Ce1 88.89(6) 3_556 1_556 ?
 Ni1 Al5 Ce1 88.89(6) 3_556 1_556 ?
 Al8 Al5 Ce1 135.70(6) 3_556 1_556 ?
 Al3 Al5 Ce1 65.36(7) . 1_556 ?
 Al2 Al5 Ce1 128.09(7) 3_556 1_556 ?
 Al1 Al5 Ce1 62.63(6) 3_556 1_556 ?
 Al6 Al5 Ce1 67.35(7) 3_556 1_556 ?
 Al6 Al5 Ce1 120.52(10) 3 1_556 ?
 Co1 Al5 Ce1 88.89(6) 3 . ?
 Ni1 Al5 Ce1 88.89(6) 3 . ?
 Co1 Al5 Ce1 167.50(8) 3_556 . ?
 Ni1 Al5 Ce1 167.50(8) 3_556 . ?
 Al8 Al5 Ce1 135.70(5) 3_556 . ?
 Al3 Al5 Ce1 65.35(7) . . ?
 Al2 Al5 Ce1 128.09(7) 3_556 . ?
 Al1 Al5 Ce1 62.63(6) 3_556 . ?
 Al6 Al5 Ce1 120.52(10) 3_556 . ?
 Al6 Al5 Ce1 67.35(7) 3 . ?
 Ce1 Al5 Ce1 79.02(8) 1_556 . ?
 Ni1 Al6 Ni2 177.93(14) . . ?
 Ni1 Al6 Al1 118.91(9) . 1_554 ?
 Ni2 Al6 Al1 59.92(7) . 1_554 ?
 Ni1 Al6 Al1 118.91(9) . . ?
 Ni2 Al6 Al1 59.92(7) . . ?
 Al1 Al6 Al1 91.63(12) 1_554 . ?
 Ni1 Al6 Al2 58.89(7) . . ?
 Ni2 Al6 Al2 122.25(9) . . ?
 Al1 Al6 Al2 177.57(14) 1_554 . ?
 Al1 Al6 Al2 88.81(8) . . ?
 Ni1 Al6 Al2 58.89(7) . 1_554 ?
 Ni2 Al6 Al2 122.25(9) . 1_554 ?
 Al1 Al6 Al2 88.81(8) 1_554 1_554 ?
 Al1 Al6 Al2 177.57(14) . 1_554 ?
 Al2 Al6 Al2 90.65(12) . 1_554 ?
 Ni1 Al6 Al5 58.21(7) . 3_455 ?
 Ni2 Al6 Al5 120.60(9) . 3_455 ?
 Al1 Al6 Al5 60.70(8) 1_554 3_455 ?
 Al1 Al6 Al5 121.14(12) . 3_455 ?
 Al2 Al6 Al5 117.10(12) . 3_455 ?
 Al2 Al6 Al5 57.14(8) 1_554 3_455 ?
 Ni1 Al6 Al5 58.21(7) . 3_456 ?
 Ni2 Al6 Al5 120.60(9) . 3_456 ?
 Al1 Al6 Al5 121.14(12) 1_554 3_456 ?
 Al1 Al6 Al5 60.70(8) . 3_456 ?

Al2 Al6 Al5 57.14(8) . 3_456 ?
 Al2 Al6 Al5 117.10(12) 1_554 3_456 ?
 Al5 Al6 Al5 89.15(12) 3_455 3_456 ?
 Ni1 Al6 Al3 125.06(8) . . ?
 Ni2 Al6 Al3 56.07(7) . . ?
 Al1 Al6 Al3 115.99(12) 1_554 . ?
 Al1 Al6 Al3 56.38(8) . . ?
 Al2 Al6 Al3 66.18(8) . . ?
 Al2 Al6 Al3 125.43(13) 1_554 . ?
 Al5 Al6 Al3 176.33(13) 3_455 . ?
 Al5 Al6 Al3 91.56(7) 3_456 . ?
 Ni1 Al6 Al3 125.06(8) . 1_554 ?
 Ni2 Al6 Al3 56.07(7) . 1_554 ?
 Al1 Al6 Al3 56.38(8) 1_554 1_554 ?
 Al1 Al6 Al3 115.99(12) . 1_554 ?
 Al2 Al6 Al3 125.43(13) . 1_554 ?
 Al2 Al6 Al3 66.18(8) 1_554 1_554 ?
 Al5 Al6 Al3 91.56(7) 3_455 1_554 ?
 Al5 Al6 Al3 176.33(13) 3_456 1_554 ?
 Al3 Al6 Al3 87.50(12) . 1_554 ?
 Ni2 Al7 Co1 145.84(12) . 7_655 ?
 Ni2 Al7 Ni1 145.84(12) . 7_655 ?
 Co1 Al7 Ni1 0.00(5) 7_655 7_655 ?
 Ni2 Al7 Ni1 145.77(11) . 3 ?
 Co1 Al7 Ni1 68.39(8) 7_655 3 ?
 Ni1 Al7 Ni1 68.39(8) 7_655 3 ?
 Ni2 Al7 Co1 145.77(11) . 3 ?
 Co1 Al7 Co1 68.39(8) 7_655 3 ?
 Ni1 Al7 Co1 68.39(8) 7_655 3 ?
 Ni1 Al7 Co1 0.00(5) 3 3 ?
 Ni2 Al7 Al8 136.19(5) . 3_556 ?
 Co1 Al7 Al8 53.36(5) 7_655 3_556 ?
 Ni1 Al7 Al8 53.36(5) 7_655 3_556 ?
 Ni1 Al7 Al8 53.35(5) 3 3_556 ?
 Co1 Al7 Al8 53.35(5) 3 3_556 ?
 Ni2 Al7 Al8 136.19(5) . 3 ?
 Co1 Al7 Al8 53.36(5) 7_655 3 ?
 Ni1 Al7 Al8 53.36(5) 7_655 3 ?
 Ni1 Al7 Al8 53.35(5) 3 3 ?
 Co1 Al7 Al8 53.35(5) 3 3 ?
 Al8 Al7 Al8 87.62(10) 3_556 3 ?
 Co1 Al8 Ni1 180.0 5_566 . ?
 Co1 Al8 Ni1 0.00(5) 5_566 5_566 ?
 Ni1 Al8 Ni1 180.0 . 5_566 ?
 Co1 Al8 Co1 109.39(7) 5_566 5_565 ?
 Ni1 Al8 Co1 70.61(7) . 5_565 ?
 Ni1 Al8 Co1 109.39(7) 5_566 5_565 ?
 Co1 Al8 Ni1 109.39(7) 5_566 5_565 ?
 Ni1 Al8 Ni1 70.61(7) . 5_565 ?
 Ni1 Al8 Ni1 109.39(7) 5_566 5_565 ?
 Co1 Al8 Ni1 0.00(7) 5_565 5_565 ?
 Co1 Al8 Ni1 70.61(7) 5_566 1_556 ?
 Ni1 Al8 Ni1 109.39(7) . 1_556 ?
 Ni1 Al8 Ni1 70.61(7) 5_566 1_556 ?
 Co1 Al8 Ni1 180.00(4) 5_565 1_556 ?
 Ni1 Al8 Ni1 180.00(4) 5_565 1_556 ?
 Co1 Al8 Co1 70.61(7) 5_566 1_556 ?
 Ni1 Al8 Co1 109.39(7) . 1_556 ?
 Ni1 Al8 Co1 70.61(7) 5_566 1_556 ?
 Co1 Al8 Co1 180.00(4) 5_565 1_556 ?
 Ni1 Al8 Co1 180.00(4) 5_565 1_556 ?
 Ni1 Al8 Co1 0.00(4) 1_556 1_556 ?

Co1 Al8 Al2 60.40(4) 5_566 5_566 ?
 Ni1 Al8 Al2 119.60(4) . 5_566 ?
 Ni1 Al8 Al2 60.40(4) 5_566 5_566 ?
 Co1 Al8 Al2 60.40(4) 5_565 5_566 ?
 Ni1 Al8 Al2 60.40(4) 5_565 5_566 ?
 Ni1 Al8 Al2 119.60(4) 1_556 5_566 ?
 Co1 Al8 Al2 119.60(4) 1_556 5_566 ?
 Co1 Al8 Al2 119.60(4) 5_566 . ?
 Ni1 Al8 Al2 60.40(4) . . ?
 Ni1 Al8 Al2 119.60(4) 5_566 . ?
 Co1 Al8 Al2 119.60(4) 5_565 . ?
 Ni1 Al8 Al2 119.60(4) 5_565 . ?
 Ni1 Al8 Al2 60.40(4) 1_556 . ?
 Co1 Al8 Al2 60.40(4) 1_556 . ?
 Al2 Al8 Al2 180.0 5_566 . ?
 Co1 Al8 Al5 119.81(4) 5_566 3_456 ?
 Ni1 Al8 Al5 60.19(4) . 3_456 ?
 Ni1 Al8 Al5 119.81(4) 5_566 3_456 ?
 Co1 Al8 Al5 119.81(4) 5_565 3_456 ?
 Ni1 Al8 Al5 119.81(4) 5_565 3_456 ?
 Ni1 Al8 Al5 60.19(4) 1_556 3_456 ?
 Co1 Al8 Al5 60.19(4) 1_556 3_456 ?
 Al2 Al8 Al5 118.05(8) 5_566 3_456 ?
 Al2 Al8 Al5 61.95(8) . 3_456 ?
 Co1 Al8 Al5 60.19(4) 5_566 7_665 ?
 Ni1 Al8 Al5 119.81(4) . 7_665 ?
 Ni1 Al8 Al5 60.19(4) 5_566 7_665 ?
 Co1 Al8 Al5 60.19(4) 5_565 7_665 ?
 Ni1 Al8 Al5 60.19(4) 5_565 7_665 ?
 Ni1 Al8 Al5 119.81(4) 1_556 7_665 ?
 Co1 Al8 Al5 119.81(4) 1_556 7_665 ?
 Al2 Al8 Al5 61.95(8) 5_566 7_665 ?
 Al2 Al8 Al5 118.05(8) . 7_665 ?
 Al5 Al8 Al5 180.0 3_456 7_665 ?
 Co2 Al9 Ni2 0.00(5) 5 5 ?
 Co2 Al9 Ni2 180.00(5) 5 . ?
 Ni2 Al9 Ni2 180.00(5) 5 . ?
 Co2 Al9 Al1 60.38(6) 5 5 ?
 Ni2 Al9 Al1 60.38(6) 5 5 ?
 Ni2 Al9 Al1 119.62(6) . 5 ?
 Co2 Al9 Al1 119.62(6) 5 . ?
 Ni2 Al9 Al1 119.62(6) 5 . ?
 Ni2 Al9 Al1 60.38(6) . . ?
 Al1 Al9 Al1 180.00(7) 5 . ?
 Co2 Al9 Al1 60.38(6) 5 5_556 ?
 Ni2 Al9 Al1 60.38(6) 5 5_556 ?
 Ni2 Al9 Al1 119.62(6) . 5_556 ?
 Al1 Al9 Al1 92.61(9) 5 5_556 ?
 Al1 Al9 Al1 87.39(9) . 5_556 ?
 Co2 Al9 Al1 119.62(6) 5 1_554 ?
 Ni2 Al9 Al1 119.62(6) 5 1_554 ?
 Ni2 Al9 Al1 60.38(6) . 1_554 ?
 Al1 Al9 Al1 87.39(9) 5 1_554 ?
 Al1 Al9 Al1 92.61(9) . 1_554 ?
 Al1 Al9 Al1 180.00(13) 5_556 1_554 ?
 Co2 Al9 Al4 123.86(5) 5 7_655 ?
 Ni2 Al9 Al4 123.86(5) 5 7_655 ?
 Ni2 Al9 Al4 56.14(5) . 7_655 ?
 Al1 Al9 Al4 123.58(7) 5 7_655 ?
 Al1 Al9 Al4 56.42(7) . 7_655 ?
 Al1 Al9 Al4 63.48(8) 5_556 7_655 ?
 Al1 Al9 Al4 116.52(8) 1_554 7_655 ?

```

Co2 Al9 Al4 56.14(5) 5 3_455 ?
Ni2 Al9 Al4 56.14(5) 5 3_455 ?
Ni2 Al9 Al4 123.86(5) . 3_455 ?
Al1 Al9 Al4 56.42(7) 5 3_455 ?
Al1 Al9 Al4 123.58(7) . 3_455 ?
Al1 Al9 Al4 116.52(8) 5_556 3_455 ?
Al1 Al9 Al4 63.48(8) 1_554 3_455 ?
Al4 Al9 Al4 180.00(12) 7_655 3_455 ?
Co2 Al9 Al4 123.86(5) 5 7_654 ?
Ni2 Al9 Al4 123.86(5) 5 7_654 ?
Ni2 Al9 Al4 56.14(5) . 7_654 ?
Al1 Al9 Al4 63.48(8) 5 7_654 ?
Al1 Al9 Al4 116.52(8) . 7_654 ?
Al1 Al9 Al4 123.58(7) 5_556 7_654 ?
Al1 Al9 Al4 56.42(7) 1_554 7_654 ?
Al4 Al9 Al4 87.46(10) 7_655 7_654 ?
Al4 Al9 Al4 92.54(10) 3_455 7_654 ?
Co2 Al9 Al4 56.14(5) 5 3_456 ?
Ni2 Al9 Al4 56.14(5) 5 3_456 ?
Ni2 Al9 Al4 123.86(5) . 3_456 ?
Al1 Al9 Al4 116.52(8) 5 3_456 ?
Al1 Al9 Al4 63.48(8) . 3_456 ?
Al1 Al9 Al4 56.42(7) 5_556 3_456 ?
Al1 Al9 Al4 123.58(7) 1_554 3_456 ?
Al4 Al9 Al4 92.54(10) 7_655 3_456 ?
Al4 Al9 Al4 87.46(10) 3_455 3_456 ?
Al4 Al9 Al4 180.00(8) 7_654 3_456 ?

_diffn_measured_fraction_theta_max 0.990
_diffn_reflns_theta_full 31.19
_diffn_measured_fraction_theta_full 0.990
_refine_diff_density_max 1.301
_refine_diff_density_min -1.392
_refine_diff_density_rms 0.342

data_shelxl

_audit_creation_method SHELXL-97
_chemical_name_systematic
;
?
;
_chemical_name_common ?
_chemical_melting_point ?
_chemical_formula_moiety ?
_chemical_formula_sum
'Al8 Ce Co Ni'
_chemical_formula_weight 473.60

loop_
_atom_type_symbol
_atom_type_description
_atom_type_scatter_dispersion_real
_atom_type_scatter_dispersion_imag
_atom_type_scatter_source
'Ce' 'Ce' -0.2486 2.6331
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Co' 'Co' 0.3494 0.9721
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ni' 'Ni' 0.3393 1.1124
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

'Al' 'Al' 0.0645 0.0514
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

_symmetry_cell_setting ?
_symmetry_space_group_name_H-M ?

loop_
_symmetry_equiv_pos_as_xyz
'x, y, z'
'-x, -y, z'
'x+1/2, -y+1/2, -z'
'-x+1/2, y+1/2, -z'
'-x, -y, -z'
'x, y, -z'
'-x-1/2, y-1/2, z'
'x-1/2, -y-1/2, z'

_cell_length_a 12.4710(5)
_cell_length_b 14.386(2)
_cell_length_c 4.022(3)
_cell_angle_alpha 90.00
_cell_angle_beta 90.00
_cell_angle_gamma 90.00
_cell_volume 721.6(5)
_cell_formula_units_Z 4
_cell_measurement_temperature 293(2)
_cell_measurement_reflns_used ?
_cell_measurement_theta_min ?
_cell_measurement_theta_max ?

_exptl_crystal_description ?
_exptl_crystal_colour ?
_exptl_crystal_size_max ?
_exptl_crystal_size_mid ?
_exptl_crystal_size_min ?
_exptl_crystal_density_meas ?
_exptl_crystal_density_diffn 4.360
_exptl_crystal_density_method 'not measured'
_exptl_crystal_F_000 868
_exptl_absorpt_coefficient_mu 11.925
_exptl_absorpt_correction_type ?
_exptl_absorpt_correction_T_min ?
_exptl_absorpt_correction_T_max ?
_exptl_absorpt_process_details ?

_exptl_special_details
;
?
;

_diffn_ambient_temperature 293(2)
_diffn_radiation_wavelength 0.71073
_diffn_radiation_type MoK\alpha
_diffn_radiation_source 'fine-focus sealed tube'
_diffn_radiation_monochromator graphite
_diffn_measurement_device_type ?
_diffn_measurement_method ?
_diffn_detector_area_resol_mean ?
_diffn_standards_number ?
_diffn_standards_interval_count ?
_diffn_standards_interval_time ?
_diffn_standards_decay_% ?

```

```

_diffn_reflms_number      2197
_diffn_reflms_av_R_equivalents 0.0299
_diffn_reflms_av_signal/netI 0.0345
_diffn_reflms_limit_h_min -17
_diffn_reflms_limit_h_max 17
_diffn_reflms_limit_k_min -20
_diffn_reflms_limit_k_max 20
_diffn_reflms_limit_l_min -5
_diffn_reflms_limit_l_max 5
_diffn_reflms_theta_min 2.83
_diffn_reflms_theta_max 31.01
_reflms_number_total      1297
_reflms_number_gt         1053
_reflms_threshold_expression >2\s(I)

_computing_data_collection ?
_computing_cell_refinement ?
_computing_data_reduction ?
_computing_structure_solution ?
_computing_structure_refinement 'SHELXL-97
(Sheldrick, 2008)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F^2^ against ALL reflections. The
weighted R-factor wR and
goodness of fit S are based on F^2^, conventional R-
factors R are based
on F, with F set to zero for negative F^2^. The threshold
expression of
 $F^2 > 2\sigma(F^2)$  is used only for calculating R-factors(gt)
etc. and is
not relevant to the choice of reflections for refinement. R-
factors based
on F^2^ are statistically about twice as large as those based
on F, and R-
factors based on ALL data will be even larger.
;

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type full
_refine_ls_weighting_scheme calc
_refine_ls_weighting_details
'calc w=1/[\sigma^2(Fo^2)+(0.0382P)^2+0.7057P] where
P=(Fo^2+2Fc^2)/3'
_atom_sites_solution_primary direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment mixed
_refine_ls_extinction_method SHELXL
_refine_ls_extinction_coef 0.0050(3)
_refine_ls_extinction_expression
'Fc^2=kFc[1+0.001xFc^2/l^3/sin(2q)]^-1/4^'
_refine_ls_number_reflms 1297
_refine_ls_number_parameters 72
_refine_ls_number_restraints 0
_refine_ls_R_factor_all 0.0417
_refine_ls_R_factor_gt 0.0290
_refine_ls_wR_factor_ref 0.0719
_refine_ls_wR_factor_gt 0.0659

```

```

_refine_ls_goodness_of_fit_ref 1.015
_refine_ls_restrained_S_all 1.015
_refine_ls_shift/su_max 0.001
_refine_ls_shift/su_mean 0.000

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ce1 Ce 0.34035(2) 0.31849(2) 0.0000 0.01152(11) Uani 1
2 d S . .
Co2 Co 0.15185(5) 0.09639(5) 0.0000 0.0089(3) Uani
0.89(8) 2 d SP . .
Ni2 Ni 0.15185(5) 0.09639(5) 0.0000 0.0089(3) Uani
0.11(8) 2 d SP . .
Co1 Co 0.03469(5) 0.40569(5) 0.0000 0.0100(2) Uani
0.4858(17) 2 d SP . .
Ni1 Ni 0.03469(5) 0.40569(5) 0.0000 0.0100(2) Uani
0.4858(17) 2 d SP . .
Al8 Al 0.0000 0.5000 0.5000 0.0110(4) Uani 1 4 d S . .
Al9 Al 0.0000 0.0000 0.0000 0.0111(4) Uani 1 4 d S . .
Al2 Al 0.15972(12) 0.37922(12) 0.5000 0.0107(3) Uani 1 2
d S . .
Al5 Al 0.45256(13) 0.17966(11) 0.5000 0.0109(3) Uani 1 2
d S . .
Al3 Al 0.23631(13) 0.17248(11) 0.5000 0.0110(3) Uani 1 2
d S . .
Al4 Al 0.33148(13) 0.49133(11) 0.5000 0.0109(3) Uani 1 2
d S . .
Al1 Al 0.02525(13) 0.13192(11) 0.5000 0.0109(3) Uani 1 2
d S . .
Al7 Al 0.33977(12) 0.04458(12) 0.0000 0.0122(3) Uani 1 2
d S . .
Al6 Al 0.09608(12) 0.25288(11) 0.0000 0.0110(3) Uani 1 2
d S . .

loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12
Ce1 0.01072(17) 0.01428(17) 0.00958(16) 0.000 0.000 -
0.00112(11)
Co2 0.0094(4) 0.0084(4) 0.0088(4) 0.000 0.000 0.0005(3)
Ni2 0.0094(4) 0.0084(4) 0.0088(4) 0.000 0.000 0.0005(3)
Co1 0.0107(4) 0.0094(4) 0.0100(4) 0.000 0.000 0.0009(3)
Ni1 0.0107(4) 0.0094(4) 0.0100(4) 0.000 0.000 0.0009(3)
Al8 0.0138(11) 0.0091(10) 0.0102(10) 0.000 0.000
0.0013(8)

```

Al9 0.0106(10) 0.0099(10) 0.0128(10) 0.000 0.000 -
0.0011(8)
Al2 0.0086(7) 0.0121(7) 0.0115(7) 0.000 0.000 -0.0008(6)
Al5 0.0107(7) 0.0102(7) 0.0117(7) 0.000 0.000 0.0003(6)
Al3 0.0102(7) 0.0112(8) 0.0117(7) 0.000 0.000 -0.0015(6)
Al4 0.0119(7) 0.0098(7) 0.0109(7) 0.000 0.000 -0.0013(6)
Al1 0.0105(7) 0.0115(7) 0.0106(7) 0.000 0.000 0.0012(6)
Al7 0.0087(7) 0.0139(8) 0.0139(8) 0.000 0.000 0.0022(6)
Al6 0.0126(8) 0.0086(7) 0.0119(7) 0.000 0.000 0.0001(6)

_geom_special_details

;
All s.u.'s (except the s.u. in the dihedral angle between two
l.s. planes)
are estimated using the full covariance matrix. The cell
s.u.'s are taken
into account individually in the estimation of s.u.'s in
distances, angles
and torsion angles; correlations between s.u.'s in cell
parameters are only
used when they are defined by crystal symmetry. An
approximate (isotropic)
treatment of cell s.u.'s is used for estimating s.u.'s
involving l.s. planes.
;

loop_

_geom_bond_atom_site_label_1
_geom_bond_atom_site_label_2
_geom_bond_distance
_geom_bond_site_symmetry_2
_geom_bond_publ_flag
Ce1 Al1 3.1417(16) 3_556 ?
Ce1 Al1 3.1417(16) 3 ?
Ce1 Al2 3.1436(16) 1_554 ?
Ce1 Al2 3.1436(16) . ?
Ce1 Al5 3.1609(16) . ?
Ce1 Al5 3.1609(16) 1_554 ?
Ce1 Al3 3.1843(16) 1_554 ?
Ce1 Al3 3.1843(16) . ?
Ce1 Al6 3.1891(16) . ?
Ce1 Al4 3.1998(16) . ?
Ce1 Al4 3.1998(16) 1_554 ?
Ce1 Al9 3.2837(4) 3 ?
Co2 Al9 2.3471(7) . ?
Co2 Al6 2.3563(17) . ?
Co2 Al7 2.4593(17) . ?
Co2 Al3 2.5203(16) . ?
Co2 Al3 2.5203(16) 1_554 ?
Co2 Al4 2.5242(16) 7_654 ?
Co2 Al4 2.5242(16) 7_655 ?
Co2 Al1 2.6073(16) 1_554 ?
Co2 Al1 2.6073(16) . ?
Co1 Al6 2.3278(17) . ?
Co1 Al8 2.4641(13) . ?
Co1 Al8 2.4641(13) 1_554 ?
Co1 Al7 2.5339(16) 3_455 ?
Co1 Al7 2.5383(18) 7_665 ?
Co1 Al5 2.5693(16) 3_455 ?
Co1 Al5 2.5693(16) 3_456 ?
Co1 Al2 2.5730(16) . ?
Co1 Al2 2.5730(16) 1_554 ?

Co1 Ni1 2.8480(15) 5_565 ?
Co1 Co1 2.8480(15) 5_565 ?
Al8 Ni1 2.4641(13) 5_566 ?
Al8 Co1 2.4641(13) 5_566 ?
Al8 Ni1 2.4641(13) 5_565 ?
Al8 Co1 2.4641(13) 5_565 ?
Al8 Co1 2.4641(13) 1_556 ?
Al8 Ni1 2.4641(13) 1_556 ?
Al8 Al2 2.6432(16) . ?
Al8 Al2 2.6432(16) 5_566 ?
Al8 Al5 2.6514(16) 7_665 ?
Al8 Al5 2.6514(16) 3_456 ?
Al9 Ni2 2.3471(7) 5 ?
Al9 Co2 2.3471(7) 5 ?
Al9 Al1 2.7830(16) 5 ?
Al9 Al1 2.7830(16) . ?
Al9 Al1 2.7830(16) 5_556 ?
Al9 Al1 2.7830(16) 1_554 ?
Al9 Al4 2.9114(15) 7_655 ?
Al9 Al4 2.9114(15) 3_455 ?
Al9 Al4 2.9114(15) 7_654 ?
Al9 Al4 2.9114(15) 3_456 ?
Al2 Ni1 2.5730(16) 1_556 ?
Al2 Co1 2.5730(16) 1_556 ?
Al2 Al4 2.681(2) . ?
Al2 Al5 2.719(2) 3_456 ?
Al2 Al6 2.824(2) . ?
Al2 Al6 2.824(2) 1_556 ?
Al2 Ce1 3.1436(16) 1_556 ?
Al5 Ni1 2.5693(16) 3 ?
Al5 Co1 2.5693(16) 3 ?
Al5 Ni1 2.5693(16) 3_556 ?
Al5 Co1 2.5693(16) 3_556 ?
Al5 Al8 2.6514(16) 3_556 ?
Al5 Al3 2.699(2) . ?
Al5 Al2 2.719(2) 3_556 ?
Al5 Al1 2.858(2) 3_556 ?
Al5 Al6 2.8618(19) 3_556 ?
Al5 Al6 2.8618(19) 3 ?
Al5 Ce1 3.1609(16) 1_556 ?
Al3 Ni2 2.5203(16) 1_556 ?
Al3 Co2 2.5203(16) 1_556 ?
Al3 Al1 2.696(2) . ?
Al3 Al4 2.740(2) 7_655 ?
Al3 Al6 2.9052(19) . ?
Al3 Al6 2.9052(19) 1_556 ?
Al3 Ce1 3.1843(16) 1_556 ?
Al4 Ni2 2.5242(16) 7_666 ?
Al4 Co2 2.5242(16) 7_666 ?
Al4 Ni2 2.5242(16) 7_665 ?
Al4 Co2 2.5242(16) 7_665 ?
Al4 Al1 2.699(2) 7_665 ?
Al4 Al3 2.740(2) 7_665 ?
Al4 Al9 2.9114(15) 3_556 ?
Al4 Al9 2.9114(15) 3 ?
Al4 Al1 2.997(2) 3_556 ?
Al4 Ce1 3.1998(16) 1_556 ?
Al1 Ni2 2.6073(16) 1_556 ?
Al1 Co2 2.6073(16) 1_556 ?
Al1 Al4 2.699(2) 7_655 ?
Al1 Al9 2.7830(16) 1_556 ?
Al1 Al6 2.8022(19) 1_556 ?

Al1 Al6 2.8022(19) . ?
 Al1 Al5 2.858(2) 3_456 ?
 Al1 Al4 2.997(2) 3_456 ?
 Al7 Ni1 2.5339(16) 3 ?
 Al7 Co1 2.5339(16) 3 ?
 Al7 Ni1 2.5383(18) 7_655 ?
 Al7 Co1 2.5383(18) 7_655 ?
 Al7 Al8 2.9066(15) 3_556 ?
 Al7 Al8 2.9066(15) 3 ?
 Al6 Al1 2.8022(19) 1_554 ?
 Al6 Al2 2.824(2) 1_554 ?
 Al6 Al5 2.8618(19) 3_455 ?
 Al6 Al5 2.8618(19) 3_456 ?
 Al6 Al3 2.9052(19) 1_554 ?

loop_

_geom_angle_atom_site_label_1
 _geom_angle_atom_site_label_2
 _geom_angle_atom_site_label_3
 _geom_angle
 _geom_angle_site_symmetry_1
 _geom_angle_site_symmetry_3
 _geom_angle_publ_flag
 Al1 Ce1 Al1 79.60(6) 3_556 3 ?
 Al1 Ce1 Al2 150.73(5) 3_556 1_554 ?
 Al1 Ce1 Al2 93.06(5) 3 1_554 ?
 Al1 Ce1 Al2 93.06(5) 3_556 . ?
 Al1 Ce1 Al2 150.73(5) 3 . ?
 Al2 Ce1 Al2 79.54(6) 1_554 . ?
 Al1 Ce1 Al5 53.94(4) 3_556 . ?
 Al1 Ce1 Al5 103.05(5) 3 . ?
 Al2 Ce1 Al5 154.14(4) 1_554 . ?
 Al2 Ce1 Al5 94.92(5) . ?
 Al1 Ce1 Al5 103.05(5) 3_556 1_554 ?
 Al1 Ce1 Al5 53.94(4) 3 1_554 ?
 Al2 Ce1 Al5 94.92(5) 1_554 1_554 ?
 Al2 Ce1 Al5 154.14(4) . 1_554 ?
 Al5 Ce1 Al5 79.02(6) . 1_554 ?
 Al1 Ce1 Al3 148.55(4) 3_556 1_554 ?
 Al1 Ce1 Al3 92.56(5) 3 1_554 ?
 Al2 Ce1 Al3 59.16(4) 1_554 1_554 ?
 Al2 Ce1 Al3 107.18(5) . 1_554 ?
 Al5 Ce1 Al3 99.52(5) . 1_554 ?
 Al5 Ce1 Al3 50.34(4) 1_554 1_554 ?
 Al1 Ce1 Al3 92.56(5) 3_556 . ?
 Al1 Ce1 Al3 148.55(4) 3 . ?
 Al2 Ce1 Al3 107.18(5) 1_554 . ?
 Al2 Ce1 Al3 59.16(4) . ?
 Al5 Ce1 Al3 50.34(4) . ?
 Al5 Ce1 Al3 99.52(5) 1_554 . ?
 Al3 Ce1 Al3 78.33(6) 1_554 . ?
 Al1 Ce1 Al6 140.20(3) 3_556 . ?
 Al1 Ce1 Al6 140.20(3) 3 . ?
 Al2 Ce1 Al6 52.97(3) 1_554 . ?
 Al2 Ce1 Al6 52.97(3) . ?
 Al5 Ce1 Al6 103.64(4) . ?
 Al5 Ce1 Al6 103.64(4) 1_554 . ?
 Al3 Ce1 Al6 54.24(3) 1_554 . ?
 Al3 Ce1 Al6 54.24(3) . ?
 Al1 Ce1 Al4 56.40(4) 3_556 . ?
 Al1 Ce1 Al4 104.55(5) 3 . ?
 Al2 Ce1 Al4 99.28(5) 1_554 . ?

Al2 Ce1 Al4 50.00(4) . ?
 Al5 Ce1 Al4 96.11(5) . ?
 Al5 Ce1 Al4 154.98(4) 1_554 . ?
 Al3 Ce1 Al4 153.56(4) 1_554 . ?
 Al3 Ce1 Al4 95.83(5) . ?
 Al6 Ce1 Al4 101.36(4) . ?
 Al1 Ce1 Al4 104.55(5) 3_556 1_554 ?
 Al1 Ce1 Al4 56.40(4) 3 1_554 ?
 Al2 Ce1 Al4 50.00(4) 1_554 1_554 ?
 Al2 Ce1 Al4 99.28(5) . 1_554 ?
 Al5 Ce1 Al4 154.98(4) . 1_554 ?
 Al5 Ce1 Al4 96.11(5) 1_554 1_554 ?
 Al3 Ce1 Al4 95.83(5) 1_554 1_554 ?
 Al3 Ce1 Al4 153.56(4) . 1_554 ?
 Al6 Ce1 Al4 101.36(4) . 1_554 ?
 Al4 Ce1 Al4 77.88(6) . 1_554 ?
 Al1 Ce1 Al9 51.27(3) 3_556 3 ?
 Al1 Ce1 Al9 51.27(3) 3 3 ?
 Al2 Ce1 Al9 102.33(3) 1_554 3 ?
 Al2 Ce1 Al9 102.33(3) . 3 ?
 Al5 Ce1 Al9 103.53(3) . 3 ?
 Al5 Ce1 Al9 103.53(3) 1_554 3 ?
 Al3 Ce1 Al9 140.50(3) 1_554 3 ?
 Al3 Ce1 Al9 140.50(3) . 3 ?
 Al6 Ce1 Al9 144.54(3) . 3 ?
 Al4 Ce1 Al9 53.35(3) . 3 ?
 Al4 Ce1 Al9 53.35(3) 1_554 3 ?
 Al9 Co2 Al6 109.05(5) . ?
 Al9 Co2 Al7 126.15(5) . ?
 Al6 Co2 Al7 124.81(6) . ?
 Al9 Co2 Al3 126.43(4) . ?
 Al6 Co2 Al3 73.04(5) . ?
 Al7 Co2 Al3 74.54(5) . ?
 Al9 Co2 Al3 126.43(4) . 1_554 ?
 Al6 Co2 Al3 73.04(5) . 1_554 ?
 Al7 Co2 Al3 74.54(5) . 1_554 ?
 Al3 Co2 Al3 105.86(8) . 1_554 ?
 Al9 Co2 Al4 73.30(4) . 7_654 ?
 Al6 Co2 Al4 126.61(4) . 7_654 ?
 Al7 Co2 Al4 74.93(5) . 7_654 ?
 Al3 Co2 Al4 149.47(6) . 7_654 ?
 Al3 Co2 Al4 65.79(6) 1_554 7_654 ?
 Al9 Co2 Al4 73.30(4) . 7_655 ?
 Al6 Co2 Al4 126.61(4) . 7_655 ?
 Al7 Co2 Al4 74.93(5) . 7_655 ?
 Al3 Co2 Al4 65.79(6) . 7_655 ?
 Al3 Co2 Al4 149.47(6) 1_554 7_655 ?
 Al4 Co2 Al4 105.63(8) 7_654 7_655 ?
 Al9 Co2 Al1 68.12(4) . 1_554 ?
 Al6 Co2 Al1 68.53(4) . 1_554 ?
 Al7 Co2 Al1 129.53(4) . 1_554 ?
 Al3 Co2 Al1 141.57(6) . 1_554 ?
 Al3 Co2 Al1 63.41(6) 1_554 1_554 ?
 Al4 Co2 Al1 63.43(6) 7_654 1_554 ?
 Al4 Co2 Al1 141.42(6) 7_655 1_554 ?
 Al9 Co2 Al1 68.12(4) . ?
 Al6 Co2 Al1 68.53(4) . ?
 Al7 Co2 Al1 129.53(4) . ?
 Al3 Co2 Al1 63.41(6) . ?
 Al3 Co2 Al1 141.57(6) 1_554 . ?
 Al4 Co2 Al1 141.42(6) 7_654 . ?
 Al4 Co2 Al1 63.43(6) 7_655 . ?

Al1 Co2 Al1 100.94(7) 1_554 . ?
 Al6 Co1 Al8 125.29(2) . . ?
 Al6 Co1 Al8 125.29(2) . 1_554 ?
 Al8 Co1 Al8 109.39(5) . 1_554 ?
 Al6 Co1 Al7 125.60(6) . 3_455 ?
 Al8 Co1 Al7 71.10(3) . 3_455 ?
 Al8 Co1 Al7 71.10(3) 1_554 3_455 ?
 Al6 Co1 Al7 122.72(6) . 7_665 ?
 Al8 Co1 Al7 71.03(3) . 7_665 ?
 Al8 Co1 Al7 71.03(3) 1_554 7_665 ?
 Al7 Co1 Al7 111.68(5) 3_455 7_665 ?
 Al6 Co1 Al5 71.32(5) . 3_455 ?
 Al8 Co1 Al5 146.30(5) . 3_455 ?
 Al8 Co1 Al5 63.53(5) 1_554 3_455 ?
 Al7 Co1 Al5 75.67(5) 3_455 3_455 ?
 Al7 Co1 Al5 128.47(4) 7_665 3_455 ?
 Al6 Co1 Al5 71.32(5) . 3_456 ?
 Al8 Co1 Al5 63.53(5) . 3_456 ?
 Al8 Co1 Al5 146.30(5) 1_554 3_456 ?
 Al7 Co1 Al5 75.67(5) 3_455 3_456 ?
 Al7 Co1 Al5 128.47(4) 7_665 3_456 ?
 Al5 Co1 Al5 103.02(7) 3_455 3_456 ?
 Al6 Co1 Al2 70.18(5) . . ?
 Al8 Co1 Al2 63.26(5) . . ?
 Al8 Co1 Al2 145.67(5) 1_554 . ?
 Al7 Co1 Al2 128.54(4) 3_455 . ?
 Al7 Co1 Al2 75.09(5) 7_665 . ?
 Al5 Co1 Al2 141.50(6) 3_455 . ?
 Al5 Co1 Al2 63.84(6) 3_456 . ?
 Al6 Co1 Al2 70.18(5) . 1_554 ?
 Al8 Co1 Al2 145.67(5) . 1_554 ?
 Al8 Co1 Al2 63.26(5) 1_554 1_554 ?
 Al7 Co1 Al2 128.54(4) 3_455 1_554 ?
 Al7 Co1 Al2 75.09(5) 7_665 1_554 ?
 Al5 Co1 Al2 63.84(5) 3_455 1_554 ?
 Al5 Co1 Al2 141.50(6) 3_456 1_554 ?
 Al2 Co1 Al2 102.81(7) . 1_554 ?
 Al6 Co1 Ni1 178.49(6) . 5_565 ?
 Al8 Co1 Ni1 54.70(2) . 5_565 ?
 Al8 Co1 Ni1 54.70(2) 1_554 5_565 ?
 Al7 Co1 Ni1 55.91(4) 3_455 5_565 ?
 Al7 Co1 Ni1 55.77(4) 7_665 5_565 ?
 Al5 Co1 Ni1 109.52(4) 3_455 5_565 ?
 Al5 Co1 Ni1 109.52(4) 3_456 5_565 ?
 Al2 Co1 Ni1 108.97(5) . 5_565 ?
 Al2 Co1 Ni1 108.97(5) 1_554 5_565 ?
 Al6 Co1 Co1 178.49(6) . 5_565 ?
 Al8 Co1 Co1 54.70(2) . 5_565 ?
 Al8 Co1 Co1 54.70(2) 1_554 5_565 ?
 Al7 Co1 Co1 55.91(4) 3_455 5_565 ?
 Al7 Co1 Co1 55.77(4) 7_665 5_565 ?
 Al5 Co1 Co1 109.52(4) 3_455 5_565 ?
 Al5 Co1 Co1 109.52(4) 3_456 5_565 ?
 Al2 Co1 Co1 108.97(5) . 5_565 ?
 Al2 Co1 Co1 108.97(5) 1_554 5_565 ?
 Ni1 Co1 Co1 0.00(3) 5_565 5_565 ?
 Ni1 Al8 Co1 0.00(3) 5_566 5_566 ?
 Ni1 Al8 Co1 180.0 5_566 . ?
 Co1 Al8 Co1 180.0 5_566 . ?
 Ni1 Al8 Ni1 109.39(5) 5_566 5_565 ?
 Co1 Al8 Ni1 109.39(5) 5_566 5_565 ?
 Co1 Al8 Ni1 70.61(5) . 5_565 ?

Ni1 Al8 Co1 109.39(5) 5_566 5_565 ?
 Co1 Al8 Co1 109.39(5) 5_566 5_565 ?
 Co1 Al8 Co1 70.61(5) . 5_565 ?
 Ni1 Al8 Co1 0.00(4) 5_565 5_565 ?
 Ni1 Al8 Co1 70.61(5) 5_566 1_556 ?
 Co1 Al8 Co1 70.61(5) 5_566 1_556 ?
 Co1 Al8 Co1 109.39(5) . 1_556 ?
 Ni1 Al8 Co1 180.00(3) 5_565 1_556 ?
 Co1 Al8 Co1 180.00(3) 5_565 1_556 ?
 Ni1 Al8 Ni1 70.61(5) 5_566 1_556 ?
 Co1 Al8 Ni1 70.61(5) 5_566 1_556 ?
 Co1 Al8 Ni1 109.39(5) . 1_556 ?
 Ni1 Al8 Ni1 180.00(3) 5_565 1_556 ?
 Co1 Al8 Ni1 180.00(3) 5_565 1_556 ?
 Co1 Al8 Ni1 0.00(3) 1_556 1_556 ?
 Ni1 Al8 Al2 119.62(2) 5_566 . ?
 Co1 Al8 Al2 119.62(2) 5_566 . ?
 Co1 Al8 Al2 60.38(2) . . ?
 Ni1 Al8 Al2 119.62(2) 5_565 . ?
 Co1 Al8 Al2 119.62(2) 5_565 . ?
 Co1 Al8 Al2 60.38(2) 1_556 . ?
 Ni1 Al8 Al2 60.38(2) 1_556 . ?
 Ni1 Al8 Al2 60.38(2) 5_566 5_566 ?
 Co1 Al8 Al2 60.38(2) 5_566 5_566 ?
 Co1 Al8 Al2 119.62(2) . 5_566 ?
 Ni1 Al8 Al2 60.38(2) 5_565 5_566 ?
 Co1 Al8 Al2 60.38(2) 5_565 5_566 ?
 Co1 Al8 Al2 119.62(2) 1_556 5_566 ?
 Ni1 Al8 Al2 119.62(2) 1_556 5_566 ?
 Al2 Al8 Al2 180.0 . 5_566 ?
 Ni1 Al8 Al5 60.16(3) 5_566 7_665 ?
 Co1 Al8 Al5 60.16(3) 5_566 7_665 ?
 Co1 Al8 Al5 119.84(3) . 7_665 ?
 Ni1 Al8 Al5 60.16(3) 5_565 7_665 ?
 Co1 Al8 Al5 60.16(3) 5_565 7_665 ?
 Co1 Al8 Al5 119.84(3) 1_556 7_665 ?
 Ni1 Al8 Al5 119.84(3) 1_556 7_665 ?
 Al2 Al8 Al5 118.20(5) . 7_665 ?
 Al2 Al8 Al5 61.80(5) 5_566 7_665 ?
 Ni1 Al8 Al5 119.84(3) 5_566 3_456 ?
 Co1 Al8 Al5 119.84(3) 5_566 3_456 ?
 Co1 Al8 Al5 60.16(3) 1_556 3_456 ?
 Ni1 Al8 Al5 60.16(3) 1_556 3_456 ?
 Al2 Al8 Al5 61.80(5) . 3_456 ?
 Al2 Al8 Al5 118.20(5) 5_566 3_456 ?
 Al5 Al8 Al5 180.0 7_665 3_456 ?
 Ni2 Al9 Co2 0.00(3) 5 5 ?
 Ni2 Al9 Co2 180.00(3) 5 . ?
 Co2 Al9 Co2 180.00(3) 5 . ?
 Ni2 Al9 Al1 60.39(3) 5 5 ?
 Co2 Al9 Al1 60.39(3) 5 5 ?
 Co2 Al9 Al1 119.61(3) . 5 ?
 Ni2 Al9 Al1 119.61(3) 5 . ?
 Co2 Al9 Al1 119.61(3) 5 . ?
 Co2 Al9 Al1 60.39(3) . . ?
 Al1 Al9 Al1 180.00(8) 5 . ?
 Ni2 Al9 Al1 60.39(3) 5 5_556 ?
 Co2 Al9 Al1 60.39(3) 5 5_556 ?
 Co2 Al9 Al1 119.61(3) . 5_556 ?

Al1 Al9 Al1 92.54(6) 5 5_556 ?
 Al1 Al9 Al1 87.46(6) . 5_556 ?
 Ni2 Al9 Al1 119.61(3) 5 1_554 ?
 Co2 Al9 Al1 119.61(3) 5 1_554 ?
 Co2 Al9 Al1 60.39(3) . 1_554 ?
 Al1 Al9 Al1 87.46(6) 5 1_554 ?
 Al1 Al9 Al1 92.54(6) . 1_554 ?
 Al1 Al9 Al1 180.00(8) 5_556 1_554 ?
 Ni2 Al9 Al4 123.85(3) 5 7_655 ?
 Co2 Al9 Al4 123.85(3) 5 7_655 ?
 Co2 Al9 Al4 56.15(3) . 7_655 ?
 Al1 Al9 Al4 123.48(5) 5 7_655 ?
 Al1 Al9 Al4 56.52(5) . 7_655 ?
 Al1 Al9 Al4 63.47(5) 5_556 7_655 ?
 Al1 Al9 Al4 116.53(5) 1_554 7_655 ?
 Ni2 Al9 Al4 56.15(3) 5 3_455 ?
 Co2 Al9 Al4 56.15(3) 5 3_455 ?
 Co2 Al9 Al4 123.85(3) . 3_455 ?
 Al1 Al9 Al4 56.52(5) 5 3_455 ?
 Al1 Al9 Al4 123.48(5) . 3_455 ?
 Al1 Al9 Al4 116.53(5) 5_556 3_455 ?
 Al1 Al9 Al4 63.47(5) 1_554 3_455 ?
 Al4 Al9 Al4 180.00(8) 7_655 3_455 ?
 Ni2 Al9 Al4 123.85(3) 5 7_654 ?
 Co2 Al9 Al4 123.85(3) 5 7_654 ?
 Co2 Al9 Al4 56.15(3) . 7_654 ?
 Al1 Al9 Al4 63.47(5) 5 7_654 ?
 Al1 Al9 Al4 116.53(5) . 7_654 ?
 Al1 Al9 Al4 123.48(5) 5_556 7_654 ?
 Al1 Al9 Al4 56.52(5) 1_554 7_654 ?
 Al4 Al9 Al4 87.38(6) 7_655 7_654 ?
 Al4 Al9 Al4 92.62(6) 3_455 7_654 ?
 Ni2 Al9 Al4 56.15(3) 5 3_456 ?
 Co2 Al9 Al4 56.15(3) 5 3_456 ?
 Co2 Al9 Al4 123.85(3) . 3_456 ?
 Al1 Al9 Al4 116.53(5) 5 3_456 ?
 Al1 Al9 Al4 63.47(5) . 3_456 ?
 Al1 Al9 Al4 56.52(5) 5_556 3_456 ?
 Al1 Al9 Al4 123.48(5) 1_554 3_456 ?
 Al4 Al9 Al4 92.62(6) 7_655 3_456 ?
 Al4 Al9 Al4 87.38(6) 3_455 3_456 ?
 Al4 Al9 Al4 180.00(4) 7_654 3_456 ?
 Co1 Al2 Ni1 102.81(7) . 1_556 ?
 Co1 Al2 Co1 102.81(7) . 1_556 ?
 Ni1 Al2 Co1 0.00(2) 1_556 1_556 ?
 Co1 Al2 Al8 56.36(4) . . ?
 Ni1 Al2 Al8 56.36(4) 1_556 . ?
 Co1 Al2 Al8 56.36(4) 1_556 . ?
 Co1 Al2 Al4 113.27(5) . . ?
 Ni1 Al2 Al4 113.27(5) 1_556 . ?
 Co1 Al2 Al4 113.27(5) 1_556 . ?
 Al8 Al2 Al4 101.93(7) . . ?
 Co1 Al2 Al5 58.01(4) . 3_456 ?
 Ni1 Al2 Al5 58.01(4) 1_556 3_456 ?
 Co1 Al2 Al5 58.01(4) 1_556 3_456 ?
 Al8 Al2 Al5 59.25(5) . 3_456 ?
 Al4 Al2 Al5 161.18(9) . 3_456 ?
 Co1 Al2 Al6 50.84(4) . . ?
 Ni1 Al2 Al6 118.78(7) 1_556 . ?
 Co1 Al2 Al6 118.78(7) 1_556 . ?
 Al8 Al2 Al6 102.20(5) . . ?
 Al4 Al2 Al6 127.70(5) . . ?

Al5 Al2 Al6 62.13(5) 3_456 . ?
 Co1 Al2 Al6 118.78(7) . 1_556 ?
 Ni1 Al2 Al6 50.84(4) 1_556 1_556 ?
 Co1 Al2 Al6 50.84(4) 1_556 1_556 ?
 Al8 Al2 Al6 102.20(5) . 1_556 ?
 Al4 Al2 Al6 127.70(5) . 1_556 ?
 Al5 Al2 Al6 62.13(5) 3_456 1_556 ?
 Al6 Al2 Al6 90.80(8) . 1_556 ?
 Co1 Al2 Ce1 167.26(5) . 1_556 ?
 Ni1 Al2 Ce1 88.59(4) 1_556 1_556 ?
 Co1 Al2 Ce1 88.59(4) 1_556 1_556 ?
 Al8 Al2 Ce1 136.28(4) . 1_556 ?
 Al4 Al2 Ce1 66.09(4) . 1_556 ?
 Al5 Al2 Ce1 126.47(5) 3_456 1_556 ?
 Al6 Al2 Ce1 118.55(7) . 1_556 ?
 Al6 Al2 Ce1 64.34(4) 1_556 1_556 ?
 Co1 Al2 Ce1 88.59(4) . . ?
 Ni1 Al2 Ce1 167.26(5) 1_556 . ?
 Co1 Al2 Ce1 167.26(5) 1_556 . ?
 Al8 Al2 Ce1 136.28(4) . . ?
 Al4 Al2 Ce1 66.09(4) . . ?
 Al5 Al2 Ce1 126.47(5) 3_456 . ?
 Al6 Al2 Ce1 64.34(4) . . ?
 Al6 Al2 Ce1 118.55(7) 1_556 . ?
 Ce1 Al2 Ce1 79.54(6) 1_556 . ?
 Ni1 Al5 Co1 0.00(4) 3 3 ?
 Ni1 Al5 Ni1 103.02(7) 3 3_556 ?
 Co1 Al5 Ni1 103.02(7) 3 3_556 ?
 Ni1 Al5 Co1 103.02(7) 3 3_556 ?
 Co1 Al5 Co1 103.02(7) 3 3_556 ?
 Ni1 Al5 Co1 0.00(3) 3_556 3_556 ?
 Ni1 Al5 Al8 56.30(4) 3 3_556 ?
 Co1 Al5 Al8 56.30(4) 3 3_556 ?
 Ni1 Al5 Al8 56.30(4) 3_556 3_556 ?
 Co1 Al5 Al8 56.30(4) 3_556 3_556 ?
 Ni1 Al5 Al3 112.34(5) 3 . ?
 Co1 Al5 Al3 112.34(5) 3 . ?
 Ni1 Al5 Al3 112.34(5) 3_556 . ?
 Co1 Al5 Al3 112.34(5) 3_556 . ?
 Al8 Al5 Al3 100.70(6) 3_556 . ?
 Ni1 Al5 Al2 58.15(4) 3 3_556 ?
 Co1 Al5 Al2 58.15(4) 3 3_556 ?
 Ni1 Al5 Al2 58.15(4) 3_556 3_556 ?
 Co1 Al5 Al2 58.15(4) 3_556 3_556 ?
 Al8 Al5 Al2 58.95(5) 3_556 3_556 ?
 Al3 Al5 Al2 159.65(8) . 3_556 ?
 Ni1 Al5 Al1 109.07(5) 3 3_556 ?
 Co1 Al5 Al1 109.07(5) 3 3_556 ?
 Ni1 Al5 Al1 109.07(5) 3_556 3_556 ?
 Co1 Al5 Al1 109.07(5) 3_556 3_556 ?
 Al8 Al5 Al1 148.61(7) 3_556 3_556 ?
 Al3 Al5 Al1 110.69(7) . 3_556 ?
 Al2 Al5 Al1 89.66(7) 3_556 3_556 ?
 Ni1 Al5 Al6 117.56(7) 3 3_556 ?
 Co1 Al5 Al6 117.56(7) 3 3_556 ?
 Ni1 Al5 Al6 50.41(4) 3_556 3_556 ?
 Co1 Al5 Al6 50.41(4) 3_556 3_556 ?
 Al8 Al5 Al6 101.01(5) 3_556 3_556 ?
 Al3 Al5 Al6 129.64(5) . 3_556 ?
 Al2 Al5 Al6 60.75(5) 3_556 3_556 ?
 Al1 Al5 Al6 58.67(5) 3_556 3_556 ?
 Ni1 Al5 Al6 50.41(4) 3 3 ?

Co1 Al5 Al6 50.41(4) 3 3 ?
 Ni1 Al5 Al6 117.56(7) 3_556 3 ?
 Co1 Al5 Al6 117.56(7) 3_556 3 ?
 Al8 Al5 Al6 101.01(5) 3_556 3 ?
 Al3 Al5 Al6 129.64(5) . 3 ?
 Al2 Al5 Al6 60.75(5) 3_556 3 ?
 Al1 Al5 Al6 58.67(5) 3_556 3 ?
 Al6 Al5 Al6 89.29(8) 3_556 3 ?
 Ni1 Al5 Ce1 167.54(5) 3 1_556 ?
 Co1 Al5 Ce1 167.54(5) 3 1_556 ?
 Ni1 Al5 Ce1 88.88(4) 3_556 1_556 ?
 Co1 Al5 Ce1 88.88(4) 3_556 1_556 ?
 Al8 Al5 Ce1 135.62(4) 3_556 1_556 ?
 Al3 Al5 Ce1 65.28(4) . 1_556 ?
 Al2 Al5 Ce1 128.14(5) 3_556 1_556 ?
 Al1 Al5 Ce1 62.69(4) 3_556 1_556 ?
 Al6 Al5 Ce1 67.39(4) 3_556 1_556 ?
 Al6 Al5 Ce1 120.64(6) 3 1_556 ?
 Ni1 Al5 Ce1 88.88(4) 3 . ?
 Co1 Al5 Ce1 88.88(4) 3 . ?
 Ni1 Al5 Ce1 167.54(5) 3_556 . ?
 Co1 Al5 Ce1 167.54(5) 3_556 . ?
 Al8 Al5 Ce1 135.62(4) 3_556 . ?
 Al3 Al5 Ce1 65.28(4) . . ?
 Al2 Al5 Ce1 128.14(5) 3_556 . ?
 Al1 Al5 Ce1 62.69(4) 3_556 . ?
 Al6 Al5 Ce1 120.64(6) 3_556 . ?
 Al6 Al5 Ce1 67.39(4) 3 . ?
 Ce1 Al5 Ce1 79.02(6) 1_556 . ?
 Co2 Al3 Ni2 105.86(8) . 1_556 ?
 Co2 Al3 Co2 105.86(8) . 1_556 ?
 Ni2 Al3 Co2 0.00(4) 1_556 1_556 ?
 Co2 Al3 Al1 59.87(4) . . ?
 Ni2 Al3 Al1 59.87(4) 1_556 . ?
 Co2 Al3 Al1 59.87(4) 1_556 . ?
 Co2 Al3 Al5 115.74(5) . . ?
 Ni2 Al3 Al5 115.74(5) 1_556 . ?
 Co2 Al3 Al5 115.74(5) 1_556 . ?
 Al1 Al3 Al5 169.69(8) . . ?
 Co2 Al3 Al4 57.17(4) . 7_655 ?
 Ni2 Al3 Al4 57.17(4) 1_556 7_655 ?
 Co2 Al3 Al4 57.17(4) 1_556 7_655 ?
 Al1 Al3 Al4 59.53(6) . 7_655 ?
 Al5 Al3 Al4 110.17(7) . 7_655 ?
 Co2 Al3 Al6 50.88(4) . . ?
 Ni2 Al3 Al6 118.27(7) 1_556 . ?
 Co2 Al3 Al6 118.27(7) 1_556 . ?
 Al1 Al3 Al6 59.90(5) . . ?
 Al5 Al3 Al6 125.89(5) . . ?
 Al4 Al3 Al6 101.13(6) 7_655 . ?
 Co2 Al3 Al6 118.27(7) . 1_556 ?
 Ni2 Al3 Al6 50.88(4) 1_556 1_556 ?
 Co2 Al3 Al6 50.88(4) 1_556 1_556 ?
 Al1 Al3 Al6 59.90(5) . 1_556 ?
 Al5 Al3 Al6 125.89(5) . 1_556 ?
 Al4 Al3 Al6 101.13(6) 7_655 1_556 ?
 Al6 Al3 Al6 87.61(7) . 1_556 ?
 Co2 Al3 Ce1 163.89(5) . 1_556 ?
 Ni2 Al3 Ce1 87.30(4) 1_556 1_556 ?
 Co2 Al3 Ce1 87.30(4) 1_556 1_556 ?
 Al1 Al3 Ce1 122.72(5) . 1_556 ?
 Al5 Al3 Ce1 64.38(4) . 1_556 ?

Al4 Al3 Ce1 138.87(3) 7_655 1_556 ?
 Al6 Al3 Ce1 114.82(6) . 1_556 ?
 Al6 Al3 Ce1 62.97(4) 1_556 1_556 ?
 Co2 Al3 Ce1 87.30(4) . . ?
 Ni2 Al3 Ce1 163.89(5) 1_556 . ?
 Co2 Al3 Ce1 163.89(5) 1_556 . ?
 Al1 Al3 Ce1 122.72(5) . . ?
 Al5 Al3 Ce1 64.38(4) . . ?
 Al4 Al3 Ce1 138.87(3) 7_655 . ?
 Al6 Al3 Ce1 62.97(4) . . ?
 Al6 Al3 Ce1 114.82(6) 1_556 . ?
 Ce1 Al3 Ce1 78.33(6) 1_556 . ?
 Ni2 Al4 Co2 0.0 7_666 7_666 ?
 Ni2 Al4 Ni2 105.63(8) 7_666 7_665 ?
 Co2 Al4 Ni2 105.63(8) 7_666 7_665 ?
 Ni2 Al4 Co2 105.63(8) 7_666 7_665 ?
 Co2 Al4 Co2 105.63(8) 7_666 7_665 ?
 Ni2 Al4 Co2 0.00(3) 7_665 7_665 ?
 Ni2 Al4 Al2 115.21(5) 7_666 . ?
 Co2 Al4 Al2 115.21(5) 7_666 . ?
 Ni2 Al4 Al2 115.21(5) 7_665 . ?
 Co2 Al4 Al2 115.21(5) 7_665 . ?
 Ni2 Al4 Al1 59.78(4) 7_666 7_665 ?
 Co2 Al4 Al1 59.78(4) 7_666 7_665 ?
 Ni2 Al4 Al1 59.78(4) 7_665 7_665 ?
 Co2 Al4 Al1 59.78(4) 7_665 7_665 ?
 Al2 Al4 Al1 168.43(9) . 7_665 ?
 Ni2 Al4 Al3 57.04(4) 7_666 7_665 ?
 Co2 Al4 Al3 57.04(4) 7_666 7_665 ?
 Ni2 Al4 Al3 57.04(4) 7_665 7_665 ?
 Co2 Al4 Al3 57.04(4) 7_665 7_665 ?
 Al2 Al4 Al3 109.00(7) . 7_665 ?
 Al1 Al4 Al3 59.43(6) 7_665 7_665 ?
 Ni2 Al4 Al9 50.55(3) 7_666 3_556 ?
 Co2 Al4 Al9 50.55(3) 7_666 3_556 ?
 Ni2 Al4 Al9 117.72(6) 7_665 3_556 ?
 Co2 Al4 Al9 117.72(6) 7_665 3_556 ?
 Al2 Al4 Al9 127.05(4) . 3_556 ?
 Al1 Al4 Al9 59.34(4) 7_665 3_556 ?
 Al3 Al4 Al9 100.49(5) 7_665 3_556 ?
 Ni2 Al4 Al9 117.72(6) 7_666 3 ?
 Co2 Al4 Al9 117.72(6) 7_666 3 ?
 Ni2 Al4 Al9 50.55(3) 7_665 3 ?
 Co2 Al4 Al9 50.55(3) 7_665 3 ?
 Al2 Al4 Al9 127.05(4) . 3 ?
 Al1 Al4 Al9 59.34(4) 7_665 3 ?
 Al3 Al4 Al9 100.49(5) 7_665 3 ?
 Al9 Al4 Al9 87.38(6) 3_556 3 ?
 Ni2 Al4 Al1 106.73(5) 7_666 3_556 ?
 Co2 Al4 Al1 106.73(5) 7_666 3_556 ?
 Ni2 Al4 Al1 106.73(5) 7_665 3_556 ?
 Co2 Al4 Al1 106.73(5) 7_665 3_556 ?
 Al2 Al4 Al1 106.76(7) . 3_556 ?
 Al1 Al4 Al1 84.81(6) 7_665 3_556 ?
 Al3 Al4 Al1 144.24(7) 7_665 3_556 ?
 Al9 Al4 Al1 56.18(3) 3_556 3_556 ?
 Al9 Al4 Al1 56.18(3) 3 3_556 ?
 Ni2 Al4 Ce1 164.39(5) 7_666 . ?
 Co2 Al4 Ce1 164.39(5) 7_666 . ?
 Ni2 Al4 Ce1 87.81(5) 7_665 . ?
 Co2 Al4 Ce1 87.81(5) 7_665 . ?
 Al2 Al4 Ce1 63.91(4) . . ?

Al1 Al4 Ce1 124.02(5) 7_665 . ?
 Al3 Al4 Ce1 138.57(3) 7_665 . ?
 Al9 Al4 Ce1 116.26(6) 3_556 . ?
 Al9 Al4 Ce1 64.80(3) 3 . ?
 Al1 Al4 Ce1 60.82(4) 3_556 . ?
 Ni2 Al4 Ce1 87.81(5) 7_666 1_556 ?
 Co2 Al4 Ce1 87.81(5) 7_666 1_556 ?
 Ni2 Al4 Ce1 164.39(5) 7_665 1_556 ?
 Co2 Al4 Ce1 164.39(5) 7_665 1_556 ?
 Al2 Al4 Ce1 63.91(4) . 1_556 ?
 Al1 Al4 Ce1 124.02(5) 7_665 1_556 ?
 Al3 Al4 Ce1 138.57(3) 7_665 1_556 ?
 Al9 Al4 Ce1 64.80(3) 3_556 1_556 ?
 Al9 Al4 Ce1 116.26(6) 3 1_556 ?
 Al1 Al4 Ce1 60.82(4) 3_556 1_556 ?
 Ce1 Al4 Ce1 77.88(6) . 1_556 ?
 Ni2 Al1 Co2 0.00(3) 1_556 1_556 ?
 Ni2 Al1 Co2 100.94(7) 1_556 . ?
 Co2 Al1 Co2 100.94(7) 1_556 . ?
 Ni2 Al1 Al3 56.72(4) 1_556 . ?
 Co2 Al1 Al3 56.72(4) 1_556 . ?
 Co2 Al1 Al3 56.72(4) . . ?
 Ni2 Al1 Al4 56.78(4) 1_556 7_655 ?
 Co2 Al1 Al4 56.78(4) 1_556 7_655 ?
 Co2 Al1 Al4 56.78(4) . 7_655 ?
 Al3 Al1 Al4 61.04(6) . 7_655 ?
 Ni2 Al1 Al9 119.48(7) 1_556 . ?
 Co2 Al1 Al9 119.48(7) 1_556 . ?
 Co2 Al1 Al9 51.50(3) . . ?
 Al3 Al1 Al9 104.95(5) . . ?
 Al4 Al1 Al9 64.14(4) 7_655 . ?
 Ni2 Al1 Al9 51.50(3) 1_556 1_556 ?
 Co2 Al1 Al9 51.50(3) 1_556 1_556 ?
 Co2 Al1 Al9 119.48(7) . 1_556 ?
 Al3 Al1 Al9 104.95(5) . 1_556 ?
 Al4 Al1 Al9 64.14(4) 7_655 1_556 ?
 Al9 Al1 Al9 92.54(6) . 1_556 ?
 Ni2 Al1 Al6 51.49(4) 1_556 1_556 ?
 Co2 Al1 Al6 51.49(4) 1_556 1_556 ?
 Co2 Al1 Al6 118.97(7) . 1_556 ?
 Al3 Al1 Al6 63.76(5) . 1_556 ?
 Al4 Al1 Al6 104.87(6) 7_655 1_556 ?
 Al9 Al1 Al6 167.88(7) . 1_556 ?
 Al9 Al1 Al6 86.59(5) 1_556 1_556 ?
 Ni2 Al1 Al6 118.97(7) 1_556 . ?
 Co2 Al1 Al6 118.97(7) 1_556 . ?
 Co2 Al1 Al6 51.49(4) . . ?
 Al3 Al1 Al6 63.76(5) . . ?
 Al4 Al1 Al6 104.87(6) 7_655 . ?
 Al9 Al1 Al6 86.59(5) . . ?
 Al9 Al1 Al6 167.88(7) 1_556 . ?
 Al6 Al1 Al6 91.72(8) 1_556 . ?
 Ni2 Al1 Al5 112.21(5) 1_556 3_456 ?
 Co2 Al1 Al5 112.21(5) 1_556 3_456 ?
 Co2 Al1 Al5 112.21(5) . 3_456 ?
 Al3 Al1 Al5 95.99(7) . 3_456 ?
 Al4 Al1 Al5 157.04(8) 7_655 3_456 ?
 Al9 Al1 Al5 127.65(4) . 3_456 ?
 Al9 Al1 Al5 127.65(4) 1_556 3_456 ?
 Al6 Al1 Al5 60.73(5) 1_556 3_456 ?
 Al6 Al1 Al5 60.73(5) . 3_456 ?
 Ni2 Al1 Al4 111.85(5) 1_556 3_456 ?

Co2 Al1 Al4 111.85(5) 1_556 3_456 ?
 Co2 Al1 Al4 111.85(5) . 3_456 ?
 Al3 Al1 Al4 156.23(8) . 3_456 ?
 Al4 Al1 Al4 95.19(6) 7_655 3_456 ?
 Al9 Al1 Al4 60.35(4) . 3_456 ?
 Al9 Al1 Al4 60.35(4) 1_556 3_456 ?
 Al6 Al1 Al4 128.43(5) 1_556 3_456 ?
 Al6 Al1 Al4 128.43(5) . 3_456 ?
 Al5 Al1 Al4 107.78(7) 3_456 3_456 ?
 Co2 Al7 Ni1 145.96(8) . 3 ?
 Co2 Al7 Co1 145.96(8) . 3 ?
 Ni1 Al7 Co1 0.00(3) 3 3 ?
 Co2 Al7 Ni1 145.72(8) . 7_655 ?
 Ni1 Al7 Ni1 68.32(5) 3 7_655 ?
 Co1 Al7 Ni1 68.32(5) 3 7_655 ?
 Co2 Al7 Co1 145.72(8) . 7_655 ?
 Ni1 Al7 Co1 68.32(5) 3 7_655 ?
 Co1 Al7 Co1 68.32(5) 3 7_655 ?
 Ni1 Al7 Co1 0.00(3) 7_655 7_655 ?
 Co2 Al7 Al8 136.22(3) . 3_556 ?
 Ni1 Al7 Al8 53.33(3) 3 3_556 ?
 Co1 Al7 Al8 53.33(3) 3 3_556 ?
 Ni1 Al7 Al8 53.30(3) 7_655 3_556 ?
 Co1 Al7 Al8 53.30(3) 7_655 3_556 ?
 Co2 Al7 Al8 136.22(3) . 3 ?
 Ni1 Al7 Al8 53.33(3) 3 3 ?
 Co1 Al7 Al8 53.33(3) 3 3 ?
 Ni1 Al7 Al8 53.30(3) 7_655 3 ?
 Co1 Al7 Al8 53.30(3) 7_655 3 ?
 Al8 Al7 Al8 87.56(6) 3_556 3 ?
 Co1 Al6 Co2 177.97(8) . . ?
 Co1 Al6 Al1 118.87(5) . 1_554 ?
 Co2 Al6 Al1 59.98(5) . 1_554 ?
 Co1 Al6 Al1 118.87(5) . . ?
 Co2 Al6 Al1 59.98(5) . . ?
 Al1 Al6 Al1 91.72(8) 1_554 . ?
 Co1 Al6 Al2 58.98(5) . . ?
 Co2 Al6 Al2 122.13(5) . . ?
 Al1 Al6 Al2 177.63(8) 1_554 . ?
 Al1 Al6 Al2 88.69(6) . . ?
 Co1 Al6 Al2 58.98(5) . 1_554 ?
 Co2 Al6 Al2 122.13(5) . 1_554 ?
 Al1 Al6 Al2 88.69(6) 1_554 1_554 ?
 Al1 Al6 Al2 177.63(8) . 1_554 ?
 Al2 Al6 Al2 90.80(8) . 1_554 ?
 Co1 Al6 Al5 58.27(4) . 3_455 ?
 Co2 Al6 Al5 120.57(5) . 3_455 ?
 Al1 Al6 Al5 60.60(5) 1_554 3_455 ?
 Al1 Al6 Al5 121.18(7) . 3_455 ?
 Al2 Al6 Al5 117.25(7) . 3_455 ?
 Al2 Al6 Al5 57.12(5) 1_554 3_455 ?
 Co1 Al6 Al5 58.27(4) . 3_456 ?
 Co2 Al6 Al5 120.57(5) . 3_456 ?
 Al1 Al6 Al5 121.18(7) 1_554 3_456 ?
 Al1 Al6 Al5 60.60(5) . 3_456 ?
 Al2 Al6 Al5 57.12(5) . 3_456 ?
 Al2 Al6 Al5 117.25(7) 1_554 3_456 ?
 Al5 Al6 Al5 89.29(8) 3_455 3_456 ?
 Co1 Al6 Al3 125.03(5) . . ?
 Co2 Al6 Al3 56.08(4) . . ?
 Al1 Al6 Al3 116.06(7) 1_554 . ?
 Al1 Al6 Al3 56.34(5) . . ?

| | |
|---|--|
| Al2 Al6 Al3 66.06(5) . . ? | 'x-1/2, -y-1/2, z' |
| Al2 Al6 Al3 125.45(7) 1_554 . ? | '-x-1/2, y-1/2, z' |
| Al5 Al6 Al3 176.31(7) 3_455 . ? | |
| Al5 Al6 Al3 91.44(5) 3_456 . ? | _cell_length_a 12.4654(5) |
| Co1 Al6 Al3 125.03(5) . 1_554 ? | _cell_length_b 14.3872(6) |
| Co2 Al6 Al3 56.08(4) . 1_554 ? | _cell_length_c 4.0219(2) |
| Al1 Al6 Al3 56.34(5) 1_554 1_554 ? | _cell_angle_alpha 90.00 |
| Al1 Al6 Al3 116.06(7) . 1_554 ? | _cell_angle_beta 90.00 |
| Al2 Al6 Al3 125.45(7) . 1_554 ? | _cell_angle_gamma 90.00 |
| Al2 Al6 Al3 66.06(5) 1_554 1_554 ? | _cell_volume 721.30(6) |
| Al5 Al6 Al3 91.44(5) 3_455 1_554 ? | _cell_formula_units_Z 4 |
| Al5 Al6 Al3 176.31(7) 3_456 1_554 ? | _cell_measurement_temperature 298(2) |
| Al3 Al6 Al3 87.61(7) . 1_554 ? | _cell_measurement_reflns_used ? |
| | _cell_measurement_theta_min ? |
| | _cell_measurement_theta_max ? |
| _diffn_measured_fraction_theta_max 0.997 | |
| _diffn_reflns_theta_full 31.01 | |
| _diffn_measured_fraction_theta_full 0.997 | _exptl_crystal_description ? |
| _refine_diff_density_max 1.915 | _exptl_crystal_colour ? |
| _refine_diff_density_min -1.416 | _exptl_crystal_size_max 0.08 |
| _refine_diff_density_rms 0.251 | _exptl_crystal_size_mid 0.04 |
| | _exptl_crystal_size_min 0.02 |
| | _exptl_crystal_density_meas ? |
| | _exptl_crystal_density_diffn 4.361 |
| | _exptl_crystal_density_method 'not measured' |
| | _exptl_crystal_F_000 868 |
| | _exptl_absorpt_coefficient_mu 11.930 |
| | _exptl_absorpt_correction_type ? |
| | _exptl_absorpt_correction_T_min 0.4487 |
| | _exptl_absorpt_correction_T_max 0.7963 |
| | _exptl_absorpt_process_details ? |
| | |
| | _exptl_special_details |
| | ; |
| | ? |
| | ; |
| data_scd0007 | |
| _audit_creation_method SHELXL-97 | |
| _chemical_name_systematic | |
| ; | |
| ? | |
| ; | |
| _chemical_name_common ? | |
| _chemical_melting_point ? | |
| _chemical_formula_moiety ? | |
| _chemical_formula_sum | |
| 'Al8 Ce Co Ni' | |
| _chemical_formula_weight 473.60 | |
| | |
| loop_ | |
| _atom_type_symbol | _diffn_ambient_temperature 298(2) |
| _atom_type_description | _diffn_radiation_wavelength 0.71073 |
| _atom_type_scatter_dispersion_real | _diffn_radiation_type MoK α |
| _atom_type_scatter_dispersion_imag | _diffn_radiation_source 'fine-focus sealed tube' |
| _atom_type_scatter_source | _diffn_radiation_monochromator graphite |
| 'Al' 'Al' 0.0645 0.0514 | _diffn_measurement_device_type ? |
| 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4' | _diffn_measurement_method ? |
| 'Ce' 'Ce' -0.2486 2.6331 | _diffn_detector_area_resol_mean ? |
| 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4' | _diffn_standards_number ? |
| 'Co' 'Co' 0.3494 0.9721 | _diffn_standards_interval_count ? |
| 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4' | _diffn_standards_interval_time ? |
| 'Ni' 'Ni' 0.3393 1.1124 | _diffn_standards_decay_% ? |
| 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4' | _diffn_reflns_number 8692 |
| | _diffn_reflns_av_R_equivalents 0.0279 |
| | _diffn_reflns_av_sigmaI/netI 0.0199 |
| _symmetry_cell_setting ? | _diffn_reflns_limit_h_min -14 |
| _symmetry_space_group_name_H-M ? | _diffn_reflns_limit_h_max 17 |
| | _diffn_reflns_limit_k_min -20 |
| loop_ | _diffn_reflns_limit_k_max 17 |
| _symmetry_equiv_pos_as_xyz | _diffn_reflns_limit_l_min -5 |
| 'x, y, z' | _diffn_reflns_limit_l_max 5 |
| '-x, -y, z' | _diffn_reflns_theta_min 2.83 |
| '-x+1/2, y+1/2, -z' | _diffn_reflns_theta_max 30.50 |
| 'x+1/2, -y+1/2, -z' | _reflns_number_total 1249 |
| '-x, -y, -z' | _reflns_number_gt 1070 |
| 'x, y, -z' | _reflns_threshold_expression >2 σ (I) |

```

_computing_data_collection      ?
_computing_cell_refinement      ?
_computing_data_reduction       ?
_computing_structure_solution    ?
_computing_structure_refinement 'SHELXL-97
(Sheldrick, 2008)'
_computing_molecular_graphics    ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F2 against ALL reflections. The
weighted R-factor wR and
goodness of fit S are based on F2, conventional R-
factors R are based
on F, with F set to zero for negative F2. The threshold
expression of
F2 > 2σ(F2) is used only for calculating R-factors(gt)
etc. and is
not relevant to the choice of reflections for refinement. R-
factors based
on F2 are statistically about twice as large as those based
on F, and R-
factors based on ALL data will be even larger.
;

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type          full
_refine_ls_weighting_scheme      calc
_refine_ls_weighting_details
'calc w=1/[σ2(F2)+(0.0136P)2+0.0000P] where
P=(F2+2Fc2)/3'
_atom_sites_solution_primary     direct
_atom_sites_solution_secondary   difmap
_atom_sites_solution_hydrogens   geom
_refine_ls_hydrogen_treatment    mixed
_refine_ls_extinction_method      SHELXL
_refine_ls_extinction_coef        0.00000(8)
_refine_ls_extinction_expression
'Fc*2=kFc[1+0.001xFc2/σ2(q)]-1/4'
_refine_ls_number_reflns         1249
_refine_ls_number_parameters      74
_refine_ls_number_restraints      0
_refine_ls_R_factor_all           0.0264
_refine_ls_R_factor_gt           0.0181
_refine_ls_wR_factor_ref          0.0323
_refine_ls_wR_factor_gt          0.0309
_refine_ls_goodness_of_fit_ref    1.096
_refine_ls_restrained_S_all       1.096
_refine_ls_shift/su_max           6.801
_refine_ls_shift/su_mean          0.113

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy

```

```

_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ce1 Ce 0.340227(13) 0.318594(11) 0.0000 0.00855(5)
Uani 1 2 d S . .
Co2 Co 0.15196(3) 0.09630(3) 0.0000 0.00635(12) Uani
0.69(4) 2 d SP . .
Ni2 Ni 0.15196(3) 0.09630(3) 0.0000 0.00635(12) Uani
0.31(4) 2 d SP . .
Co1 Co 0.03483(3) 0.40579(3) 0.0000 0.00739(12) Uani
0.67(4) 2 d SP . .
Ni1 Ni 0.03483(3) 0.40579(3) 0.0000 0.00739(12) Uani
0.32(3) 2 d SP . .
Al8 Al 0.0000 0.5000 0.5000 0.0077(2) Uani 1 4 d S . .
Al9 Al 0.0000 0.0000 0.0000 0.0081(2) Uani 1 4 d S . .
Al2 Al 0.15982(7) 0.37920(6) 0.5000 0.00797(17) Uani 1 2
d S . .
Al5 Al 0.45238(7) 0.17950(6) 0.5000 0.00779(17) Uani 1 2
d S . .
Al3 Al 0.23642(7) 0.17233(6) 0.5000 0.00835(18) Uani 1 2
d S . .
Al4 Al 0.33142(7) 0.49123(6) 0.5000 0.00814(17) Uani 1 2
d S . .
Al1 Al 0.02547(7) 0.13188(6) 0.5000 0.00757(17) Uani 1 2
d S . .
Al7 Al 0.33977(7) 0.04459(6) 0.0000 0.01066(18) Uani 1 2
d S . .
Al6 Al 0.09611(7) 0.25282(6) 0.0000 0.00818(17) Uani 1 2
d S . .

loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12
Ce1 0.00829(9) 0.01112(9) 0.00623(8) 0.000 0.000 -
0.00108(7)
Co2 0.0065(2) 0.0067(2) 0.00580(18) 0.000 0.000
0.00004(15)
Ni2 0.0065(2) 0.0067(2) 0.00580(18) 0.000 0.000
0.00004(15)
Co1 0.0094(2) 0.0068(2) 0.00597(18) 0.000 0.000
0.00061(16)
Ni1 0.0094(2) 0.0068(2) 0.00597(18) 0.000 0.000
0.00061(16)
Al8 0.0106(7) 0.0066(6) 0.0060(5) 0.000 0.000 0.0012(5)
Al9 0.0083(6) 0.0072(6) 0.0087(5) 0.000 0.000 -0.0021(5)
Al2 0.0061(4) 0.0093(4) 0.0085(4) 0.000 0.000 -0.0003(3)
Al5 0.0070(4) 0.0076(4) 0.0088(4) 0.000 0.000 0.0013(3)
Al3 0.0080(5) 0.0098(4) 0.0073(4) 0.000 0.000 -0.0022(3)
Al4 0.0094(5) 0.0073(4) 0.0077(4) 0.000 0.000 -0.0013(3)
Al1 0.0073(4) 0.0082(4) 0.0072(4) 0.000 0.000 0.0002(4)
Al7 0.0065(4) 0.0136(5) 0.0118(4) 0.000 0.000 0.0022(4)
Al6 0.0094(5) 0.0060(4) 0.0092(4) 0.000 0.000 0.0010(3)

_geom_special_details
;

```

All s.u.'s (except the s.u. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell s.u.'s are taken into account individually in the estimation of s.u.'s in distances, angles and torsion angles; correlations between s.u.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell s.u.'s is used for estimating s.u.'s involving l.s. planes.

;

loop_

_geom_bond_atom_site_label_1
_geom_bond_atom_site_label_2
_geom_bond_distance
_geom_bond_site_symmetry_2
_geom_bond_publ_flag
Cel Al2 3.1403(7) 1_554 ?
Cel Al2 3.1403(7) . ?
Cel Al1 3.1438(7) 7_665 ?
Cel Al1 3.1438(7) 7_664 ?
Cel Al5 3.1627(7) 1_554 ?
Cel Al5 3.1627(6) . ?
Cel Al3 3.1853(7) 1_554 ?
Cel Al3 3.1853(7) . ?
Cel Al6 3.1867(9) . ?
Cel Al4 3.1977(7) . ?
Cel Al4 3.1977(7) 1_554 ?
Cel Al9 3.28304(19) 3 ?
Co2 Al9 2.3468(4) . ?
Co2 Al6 2.3571(9) . ?
Co2 Al7 2.4565(9) . ?
Co2 Al3 2.5197(6) . ?
Co2 Al3 2.5197(6) 1_554 ?
Co2 Al4 2.5242(6) 3_545 ?
Co2 Al4 2.5242(6) 3_546 ?
Co2 Al1 2.6062(6) 1_554 ?
Co2 Al1 2.6062(6) . ?
Co1 Al6 2.3296(9) . ?
Co1 Al8 2.4636(2) . ?
Co1 Al8 2.4636(2) 1_554 ?
Co1 Al7 2.5340(9) 7_565 ?
Co1 Al7 2.5360(9) 3 ?
Co1 Al5 2.5702(6) 7_564 ?
Co1 Al5 2.5702(6) 7_565 ?
Co1 Al2 2.5726(6) . ?
Co1 Al2 2.5726(6) 1_554 ?
Co1 Co1 2.8465(7) 5_565 ?
Co1 Ni1 2.8465(7) 5_565 ?
Al8 Ni1 2.4636(2) 5_566 ?
Al8 Co1 2.4636(2) 5_566 ?
Al8 Ni1 2.4636(2) 5_565 ?
Al8 Co1 2.4636(2) 1_556 ?
Al8 Ni1 2.4636(2) 1_556 ?
Al8 Al2 2.6438(9) 5_566 ?
Al8 Al2 2.6438(9) . ?
Al8 Al5 2.6499(8) 7_565 ?
Al8 Al5 2.6499(8) 3_556 ?

Al9 Ni2 2.3468(4) 5 ?
Al9 Co2 2.3468(4) 5 ?
Al9 Al1 2.7829(6) . ?
Al9 Al1 2.7829(6) 5 ?
Al9 Al1 2.7829(6) 5_556 ?
Al9 Al1 2.7829(6) 1_554 ?
Al9 Al4 2.9113(6) 7_564 ?
Al9 Al4 2.9113(6) 3_546 ?
Al9 Al4 2.9113(6) 3_545 ?
Al9 Al4 2.9113(6) 7_565 ?
Al2 Ni1 2.5726(6) 1_556 ?
Al2 Co1 2.5726(6) 1_556 ?
Al2 Al4 2.6783(12) . ?
Al2 Al5 2.7202(12) 7_565 ?
Al2 Al6 2.8250(8) . ?
Al2 Al6 2.8250(8) 1_556 ?
Al2 Ce1 3.1403(7) 1_556 ?
Al5 Ni1 2.5702(6) 7_665 ?
Al5 Co1 2.5702(6) 7_665 ?
Al5 Ni1 2.5702(6) 7_666 ?
Al5 Co1 2.5702(6) 7_666 ?
Al5 Al8 2.6499(8) 3_546 ?
Al5 Al3 2.6940(13) . ?
Al5 Al2 2.7202(12) 7_665 ?
Al5 Al1 2.8625(12) 7_665 ?
Al5 Al6 2.8639(9) 7_666 ?
Al5 Al6 2.8639(9) 7_665 ?
Al5 Ce1 3.1627(6) 1_556 ?
Al3 Ni2 2.5197(6) 1_556 ?
Al3 Co2 2.5197(6) 1_556 ?
Al3 Al1 2.6933(13) . ?
Al3 Al4 2.7393(12) 3_546 ?
Al3 Al6 2.9059(9) . ?
Al3 Al6 2.9059(9) 1_556 ?
Al3 Ce1 3.1853(7) 1_556 ?
Al4 Ni2 2.5242(6) 3_556 ?
Al4 Co2 2.5242(6) 3_556 ?
Al4 Ni2 2.5242(6) 3 ?
Al4 Co2 2.5242(6) 3 ?
Al4 Al1 2.6977(12) 3_556 ?
Al4 Al3 2.7393(12) 3_556 ?
Al4 Al9 2.9113(6) 3_556 ?
Al4 Al9 2.9113(6) 3 ?
Al4 Al1 2.9981(12) 7_665 ?
Al4 Ce1 3.1977(7) 1_556 ?
Al1 Ni2 2.6062(6) 1_556 ?
Al1 Co2 2.6062(6) 1_556 ?
Al1 Al4 2.6977(12) 3_546 ?
Al1 Al9 2.7829(6) 1_556 ?
Al1 Al6 2.8013(8) 1_556 ?
Al1 Al6 2.8013(8) . ?
Al1 Al5 2.8625(12) 7_565 ?
Al1 Al4 2.9981(12) 7_565 ?
Al7 Ni1 2.5340(9) 7_665 ?
Al7 Co1 2.5340(9) 7_665 ?
Al7 Co1 2.5360(9) 3_545 ?
Al7 Ni1 2.5360(9) 3_545 ?
Al7 Al8 2.9060(6) 3_546 ?
Al7 Al8 2.9060(6) 3_545 ?
Al6 Al1 2.8013(8) 1_554 ?
Al6 Al2 2.8250(8) 1_554 ?
Al6 Al5 2.8639(9) 7_564 ?

Al6 Al5 2.8639(9) 7_565 ?
Al6 Al3 2.9059(9) 1_554 ?

loop_

_geom_angle_atom_site_label_1
_geom_angle_atom_site_label_2
_geom_angle_atom_site_label_3
_geom_angle
_geom_angle_site_symmetry_1
_geom_angle_site_symmetry_3
_geom_angle_publ_flag
Al2 Ce1 Al2 79.64(2) 1_554 . ?
Al2 Ce1 Al1 150.77(2) 1_554 7_665 ?
Al2 Ce1 Al1 93.063(17) . 7_665 ?
Al2 Ce1 Al1 93.063(17) 1_554 7_664 ?
Al2 Ce1 Al1 150.77(2) . 7_664 ?
Al1 Ce1 Al1 79.53(2) 7_665 7_664 ?
Al2 Ce1 Al5 94.880(16) 1_554 1_554 ?
Al2 Ce1 Al5 154.08(2) . 1_554 ?
Al1 Ce1 Al5 103.03(2) 7_665 1_554 ?
Al1 Ce1 Al5 53.99(2) 7_664 1_554 ?
Al2 Ce1 Al5 154.08(2) 1_554 . ?
Al2 Ce1 Al5 94.880(16) . . ?
Al1 Ce1 Al5 53.99(2) 7_665 . ?
Al1 Ce1 Al5 103.03(2) 7_664 . ?
Al5 Ce1 Al5 78.96(2) 1_554 . ?
Al2 Ce1 Al3 59.22(2) 1_554 1_554 ?
Al2 Ce1 Al3 107.27(2) . 1_554 ?
Al1 Ce1 Al3 148.42(2) 7_665 1_554 ?
Al1 Ce1 Al3 92.537(17) 7_664 1_554 ?
Al5 Ce1 Al3 50.22(2) 1_554 1_554 ?
Al5 Ce1 Al3 99.380(19) . 1_554 ?
Al2 Ce1 Al3 107.27(2) 1_554 . ?
Al2 Ce1 Al3 59.22(2) . . ?
Al1 Ce1 Al3 92.537(17) 7_665 . ?
Al1 Ce1 Al3 148.42(2) 7_664 . ?
Al5 Ce1 Al3 99.380(19) 1_554 . ?
Al5 Ce1 Al3 50.22(2) . . ?
Al3 Ce1 Al3 78.29(2) 1_554 . ?
Al2 Ce1 Al6 53.032(17) 1_554 . ?
Al2 Ce1 Al6 53.032(17) . . ?
Al1 Ce1 Al6 140.234(11) 7_665 . ?
Al1 Ce1 Al6 140.234(11) 7_664 . ?
Al5 Ce1 Al6 103.55(2) 1_554 . ?
Al5 Ce1 Al6 103.55(2) . . ?
Al3 Ce1 Al6 54.263(17) 1_554 . ?
Al3 Ce1 Al6 54.263(17) . . ?
Al2 Ce1 Al4 99.350(19) 1_554 . ?
Al2 Ce1 Al4 49.99(2) . . ?
Al1 Ce1 Al4 56.42(2) 7_665 . ?
Al1 Ce1 Al4 104.56(2) 7_664 . ?
Al5 Ce1 Al4 155.02(2) 1_554 . ?
Al5 Ce1 Al4 96.130(16) . . ?
Al3 Ce1 Al4 153.66(2) 1_554 . ?
Al3 Ce1 Al4 95.864(15) . . ?
Al6 Ce1 Al4 101.41(2) . . ?
Al2 Ce1 Al4 49.99(2) 1_554 1_554 ?
Al2 Ce1 Al4 99.350(19) . 1_554 ?
Al1 Ce1 Al4 104.56(2) 7_665 1_554 ?
Al1 Ce1 Al4 56.42(2) 7_664 1_554 ?
Al5 Ce1 Al4 96.130(16) 1_554 1_554 ?
Al5 Ce1 Al4 155.02(2) . 1_554 ?

Al3 Ce1 Al4 95.864(15) 1_554 1_554 ?
Al3 Ce1 Al4 153.66(2) . 1_554 ?
Al6 Ce1 Al4 101.41(2) . 1_554 ?
Al4 Ce1 Al4 77.93(2) . 1_554 ?
Al2 Ce1 Al9 102.340(16) 1_554 3 ?
Al2 Ce1 Al9 102.340(16) . 3 ?
Al1 Ce1 Al9 51.263(14) 7_665 3 ?
Al1 Ce1 Al9 51.263(14) 7_664 3 ?
Al5 Ce1 Al9 103.581(16) 1_554 3 ?
Al5 Ce1 Al9 103.581(16) . 3 ?
Al3 Ce1 Al9 140.499(10) 1_554 3 ?
Al3 Ce1 Al9 140.499(10) . 3 ?
Al6 Ce1 Al9 144.622(16) . 3 ?
Al4 Ce1 Al9 53.369(14) . 3 ?
Al4 Ce1 Al9 53.369(14) 1_554 3 ?
Al9 Co2 Al6 109.00(3) . . ?
Al9 Co2 Al7 126.19(3) . . ?
Al6 Co2 Al7 124.81(3) . . ?
Al9 Co2 Al3 126.410(18) . . ?
Al6 Co2 Al3 73.06(2) . . ?
Al7 Co2 Al3 74.53(3) . . ?
Al9 Co2 Al3 126.410(18) . 1_554 ?
Al6 Co2 Al3 73.06(2) . 1_554 ?
Al7 Co2 Al3 74.53(3) . 1_554 ?
Al3 Co2 Al3 105.89(3) . 1_554 ?
Al9 Co2 Al4 73.31(2) . 3_545 ?
Al6 Co2 Al4 126.609(18) . 3_545 ?
Al7 Co2 Al4 74.96(2) . 3_545 ?
Al3 Co2 Al4 149.48(3) . 3_545 ?
Al3 Co2 Al4 65.79(2) 1_554 3_545 ?
Al9 Co2 Al4 73.31(2) . 3_546 ?
Al6 Co2 Al4 126.609(18) . 3_546 ?
Al7 Co2 Al4 74.96(2) . 3_546 ?
Al3 Co2 Al4 65.79(2) . 3_546 ?
Al3 Co2 Al4 149.48(3) 1_554 3_546 ?
Al4 Co2 Al4 105.63(3) 3_545 3_546 ?
Al9 Co2 Al1 68.14(2) . 1_554 ?
Al6 Co2 Al1 68.51(2) . 1_554 ?
Al7 Co2 Al1 129.502(16) . 1_554 ?
Al3 Co2 Al1 141.57(3) . 1_554 ?
Al3 Co2 Al1 63.37(3) 1_554 1_554 ?
Al4 Co2 Al1 63.42(2) 3_545 1_554 ?
Al4 Co2 Al1 141.44(3) 3_546 1_554 ?
Al9 Co2 Al1 68.14(2) . . ?
Al6 Co2 Al1 68.51(2) . . ?
Al7 Co2 Al1 129.502(16) . . ?
Al3 Co2 Al1 63.37(3) . . ?
Al3 Co2 Al1 141.57(3) 1_554 . ?
Al4 Co2 Al1 141.44(3) 3_545 . ?
Al4 Co2 Al1 63.42(2) 3_546 . ?
Al1 Co2 Al1 100.99(3) 1_554 . ?
Al6 Co1 Al8 125.277(7) . . ?
Al6 Co1 Al8 125.277(7) . 1_554 ?
Al8 Co1 Al8 109.422(14) . 1_554 ?
Al6 Co1 Al7 125.51(3) . 7_565 ?
Al8 Co1 Al7 71.091(13) . 7_565 ?
Al8 Co1 Al7 71.091(13) 1_554 7_565 ?
Al6 Co1 Al7 122.80(3) . 3 ?
Al8 Co1 Al7 71.058(13) . 3 ?
Al8 Co1 Al7 71.058(13) 1_554 3 ?
Al7 Co1 Al7 111.69(3) 7_565 3 ?
Al6 Co1 Al5 71.34(2) . 7_564 ?

Al8 Co1 Al5 146.19(2) . 7_564 ?
 Al8 Co1 Al5 63.486(16) 1_554 7_564 ?
 Al7 Co1 Al5 75.57(2) 7_565 7_564 ?
 Al7 Co1 Al5 128.493(16) 3 7_564 ?
 Al6 Co1 Al5 71.34(2) . 7_565 ?
 Al8 Co1 Al5 63.486(16) . 7_565 ?
 Al8 Co1 Al5 146.19(2) 1_554 7_565 ?
 Al7 Co1 Al5 75.57(2) 7_565 7_565 ?
 Al7 Co1 Al5 128.493(16) 3 7_565 ?
 Al5 Co1 Al5 102.96(3) 7_564 7_565 ?
 Al6 Co1 Al2 70.18(2) . . ?
 Al8 Co1 Al2 63.288(17) . . ?
 Al8 Co1 Al2 145.75(2) 1_554 . ?
 Al7 Co1 Al2 128.539(16) 7_565 . ?
 Al7 Co1 Al2 75.15(2) 3 . ?
 Al5 Co1 Al2 141.51(3) 7_564 . ?
 Al5 Co1 Al2 63.87(2) 7_565 . ?
 Al6 Co1 Al2 70.18(2) . 1_554 ?
 Al8 Co1 Al2 145.75(2) . 1_554 ?
 Al8 Co1 Al2 63.288(17) 1_554 1_554 ?
 Al7 Co1 Al2 128.539(16) 7_565 1_554 ?
 Al7 Co1 Al2 75.15(2) 3 1_554 ?
 Al5 Co1 Al2 63.87(2) 7_564 1_554 ?
 Al5 Co1 Al2 141.51(3) 7_565 1_554 ?
 Al2 Co1 Al2 102.83(3) . 1_554 ?
 Al6 Co1 Co1 178.62(3) . 5_565 ?
 Al8 Co1 Co1 54.711(7) . 5_565 ?
 Al8 Co1 Co1 54.711(7) 1_554 5_565 ?
 Al7 Co1 Co1 55.88(2) 7_565 5_565 ?
 Al7 Co1 Co1 55.81(2) 3 5_565 ?
 Al5 Co1 Co1 109.44(2) 7_564 5_565 ?
 Al5 Co1 Co1 109.44(2) 7_565 5_565 ?
 Al2 Co1 Co1 109.05(2) . 5_565 ?
 Al2 Co1 Co1 109.05(2) 1_554 5_565 ?
 Al6 Co1 Ni1 178.62(3) . 5_565 ?
 Al8 Co1 Ni1 54.711(7) . 5_565 ?
 Al8 Co1 Ni1 54.711(7) 1_554 5_565 ?
 Al7 Co1 Ni1 55.88(2) 7_565 5_565 ?
 Al7 Co1 Ni1 55.81(2) 3 5_565 ?
 Al5 Co1 Ni1 109.44(2) 7_564 5_565 ?
 Al5 Co1 Ni1 109.44(2) 7_565 5_565 ?
 Al2 Co1 Ni1 109.05(2) . 5_565 ?
 Al2 Co1 Ni1 109.05(2) 1_554 5_565 ?
 Co1 Co1 Ni1 0.000(15) 5_565 5_565 ?
 Ni1 Al8 Co1 0.000(17) 5_566 5_566 ?
 Ni1 Al8 Co1 180.0 5_566 . ?
 Co1 Al8 Co1 180.0 5_566 . ?
 Ni1 Al8 Ni1 109.422(14) 5_566 5_565 ?
 Co1 Al8 Ni1 109.422(14) 5_566 5_565 ?
 Co1 Al8 Ni1 70.578(14) . 5_565 ?
 Ni1 Al8 Co1 109.422(14) 5_566 5_565 ?
 Co1 Al8 Co1 109.422(14) 5_566 5_565 ?
 Co1 Al8 Co1 70.578(14) . 5_565 ?
 Ni1 Al8 Co1 0.00(2) 5_565 5_565 ?
 Ni1 Al8 Co1 70.578(14) 5_566 1_556 ?
 Co1 Al8 Co1 70.578(14) 5_566 1_556 ?
 Co1 Al8 Co1 109.422(14) . 1_556 ?
 Ni1 Al8 Co1 180.000(14) 5_565 1_556 ?
 Co1 Al8 Co1 180.000(14) 5_565 1_556 ?
 Ni1 Al8 Ni1 70.578(14) 5_566 1_556 ?
 Co1 Al8 Ni1 70.578(14) 5_566 1_556 ?
 Co1 Al8 Ni1 109.422(14) . 1_556 ?

Ni1 Al8 Ni1 180.000(14) 5_565 1_556 ?
 Co1 Al8 Ni1 180.000(14) 5_565 1_556 ?
 Co1 Al8 Ni1 0.000(14) 1_556 1_556 ?
 Ni1 Al8 Al2 60.366(10) 5_566 5_566 ?
 Co1 Al8 Al2 60.366(10) 5_566 5_566 ?
 Co1 Al8 Al2 119.634(10) . 5_566 ?
 Ni1 Al8 Al2 60.366(10) 5_565 5_566 ?
 Co1 Al8 Al2 60.366(10) 5_565 5_566 ?
 Co1 Al8 Al2 119.634(10) 1_556 5_566 ?
 Ni1 Al8 Al2 119.634(10) 1_556 5_566 ?
 Ni1 Al8 Al2 119.634(10) 5_566 . ?
 Co1 Al8 Al2 119.634(10) 5_566 . ?
 Co1 Al8 Al2 60.366(10) . . ?
 Ni1 Al8 Al2 119.634(10) 5_565 . ?
 Co1 Al8 Al2 119.634(10) 5_565 . ?
 Co1 Al8 Al2 60.366(10) 1_556 . ?
 Ni1 Al8 Al2 60.366(10) 1_556 . ?
 Al2 Al8 Al2 180.0 5_566 . ?
 Ni1 Al8 Al5 119.783(10) 5_566 7_565 ?
 Co1 Al8 Al5 119.783(10) 5_566 7_565 ?
 Co1 Al8 Al5 60.217(10) . 7_565 ?
 Ni1 Al8 Al5 119.783(10) 5_565 7_565 ?
 Co1 Al8 Al5 119.783(10) 5_565 7_565 ?
 Co1 Al8 Al5 60.217(10) 1_556 7_565 ?
 Ni1 Al8 Al5 60.217(10) 1_556 7_565 ?
 Al2 Al8 Al5 118.16(3) 5_566 7_565 ?
 Al2 Al8 Al5 61.84(3) . 7_565 ?
 Ni1 Al8 Al5 60.217(10) 5_566 3_556 ?
 Co1 Al8 Al5 60.217(10) 5_566 3_556 ?
 Co1 Al8 Al5 119.783(10) . 3_556 ?
 Ni1 Al8 Al5 60.217(10) 5_565 3_556 ?
 Co1 Al8 Al5 60.217(10) 5_565 3_556 ?
 Co1 Al8 Al5 119.783(10) 1_556 3_556 ?
 Ni1 Al8 Al5 119.783(10) 1_556 3_556 ?
 Al2 Al8 Al5 61.84(3) 5_566 3_556 ?
 Al2 Al8 Al5 118.16(3) . 3_556 ?
 Al5 Al8 Al5 180.0 7_565 3_556 ?
 Co2 Al9 Ni2 180.000(18) . 5 ?
 Co2 Al9 Co2 180.000(18) . 5 ?
 Ni2 Al9 Co2 0.000(18) 5 5 ?
 Co2 Al9 Al1 60.359(17) . . ?
 Ni2 Al9 Al1 119.641(17) 5 . ?
 Co2 Al9 Al1 119.641(17) 5 . ?
 Co2 Al9 Al1 119.641(17) . 5 ?
 Ni2 Al9 Al1 60.359(17) 5 5 ?
 Co2 Al9 Al1 60.359(17) 5 5 ?
 Al1 Al9 Al1 180.00(4) . 5 ?
 Co2 Al9 Al1 119.641(17) . 5_556 ?
 Ni2 Al9 Al1 60.359(17) 5 5_556 ?
 Co2 Al9 Al1 60.359(17) 5 5_556 ?
 Al1 Al9 Al1 87.46(3) . 5_556 ?
 Al1 Al9 Al1 92.54(3) 5 5_556 ?
 Co2 Al9 Al1 60.359(17) . 1_554 ?
 Ni2 Al9 Al1 119.641(17) 5 1_554 ?
 Co2 Al9 Al1 119.641(17) 5 1_554 ?
 Al1 Al9 Al1 92.54(3) . 1_554 ?
 Al1 Al9 Al1 87.46(3) 5 1_554 ?
 Al1 Al9 Al1 180.00(4) 5_556 1_554 ?
 Co2 Al9 Al4 123.852(16) . 7_564 ?
 Ni2 Al9 Al4 56.148(16) 5 7_564 ?
 Co2 Al9 Al4 56.148(16) 5 7_564 ?
 Al1 Al9 Al4 123.50(2) . 7_564 ?

Al1 Al9 Al4 56.50(2) 5 7_564 ?
 Al1 Al9 Al4 116.51(2) 5_556 7_564 ?
 Al1 Al9 Al4 63.49(2) 1_554 7_564 ?
 Co2 Al9 Al4 56.148(16) . 3_546 ?
 Ni2 Al9 Al4 123.852(16) 5 3_546 ?
 Co2 Al9 Al4 123.852(16) 5 3_546 ?
 Al1 Al9 Al4 56.50(2) . 3_546 ?
 Al1 Al9 Al4 123.50(2) 5 3_546 ?
 Al1 Al9 Al4 63.49(2) 5_556 3_546 ?
 Al1 Al9 Al4 116.51(2) 1_554 3_546 ?
 Al4 Al9 Al4 180.00(2) 7_564 3_546 ?
 Co2 Al9 Al4 56.148(16) . 3_545 ?
 Ni2 Al9 Al4 123.852(16) 5 3_545 ?
 Co2 Al9 Al4 123.852(16) 5 3_545 ?
 Al1 Al9 Al4 116.51(2) . 3_545 ?
 Al1 Al9 Al4 63.49(2) 5 3_545 ?
 Al1 Al9 Al4 123.50(2) 5_556 3_545 ?
 Al1 Al9 Al4 56.50(2) 1_554 3_545 ?
 Al4 Al9 Al4 92.62(2) 7_564 3_545 ?
 Al4 Al9 Al4 87.38(2) 3_546 3_545 ?
 Co2 Al9 Al4 123.852(16) . 7_565 ?
 Ni2 Al9 Al4 56.148(16) 5 7_565 ?
 Co2 Al9 Al4 56.148(16) 5 7_565 ?
 Al1 Al9 Al4 63.49(2) . 7_565 ?
 Al1 Al9 Al4 116.51(2) 5 7_565 ?
 Al1 Al9 Al4 56.50(2) 5_556 7_565 ?
 Al1 Al9 Al4 123.50(2) 1_554 7_565 ?
 Al4 Al9 Al4 87.38(2) 7_564 7_565 ?
 Al4 Al9 Al4 92.62(2) 3_546 7_565 ?
 Al4 Al9 Al4 180.00(2) 3_545 7_565 ?
 Co1 Al2 Ni1 102.83(3) . 1_556 ?
 Co1 Al2 Co1 102.83(3) . 1_556 ?
 Ni1 Al2 Co1 0.000(13) 1_556 1_556 ?
 Co1 Al2 Al8 56.346(18) . . ?
 Ni1 Al2 Al8 56.346(18) 1_556 . ?
 Co1 Al2 Al8 56.346(18) 1_556 . ?
 Co1 Al2 Al4 113.22(3) . . ?
 Ni1 Al2 Al4 113.22(3) 1_556 . ?
 Co1 Al2 Al4 113.22(3) 1_556 . ?
 Al8 Al2 Al4 101.90(3) . . ?
 Co1 Al2 Al5 58.024(19) . 7_565 ?
 Ni1 Al2 Al5 58.024(19) 1_556 7_565 ?
 Co1 Al2 Al5 58.024(19) 1_556 7_565 ?
 Al8 Al2 Al5 59.19(3) . 7_565 ?
 Al4 Al2 Al5 161.09(4) . 7_565 ?
 Co1 Al2 Al6 50.88(2) . . ?
 Ni1 Al2 Al6 118.81(4) 1_556 . ?
 Co1 Al2 Al6 118.81(4) 1_556 . ?
 Al8 Al2 Al6 102.20(3) . . ?
 Al4 Al2 Al6 127.72(3) . . ?
 Al5 Al2 Al6 62.16(3) 7_565 . ?
 Co1 Al2 Al6 118.81(4) . 1_556 ?
 Ni1 Al2 Al6 50.88(2) 1_556 1_556 ?
 Co1 Al2 Al6 50.88(2) 1_556 1_556 ?
 Al8 Al2 Al6 102.20(3) . 1_556 ?
 Al4 Al2 Al6 127.72(3) . 1_556 ?
 Al5 Al2 Al6 62.16(3) 7_565 1_556 ?
 Al6 Al2 Al6 90.77(3) . 1_556 ?
 Co1 Al2 Ce1 167.32(3) . 1_556 ?
 Ni1 Al2 Ce1 88.536(9) 1_556 1_556 ?
 Co1 Al2 Ce1 88.536(9) 1_556 1_556 ?
 Al8 Al2 Ce1 136.233(16) . 1_556 ?

Al4 Al2 Ce1 66.12(2) . 1_556 ?
 Al5 Al2 Ce1 126.48(2) 7_565 1_556 ?
 Al6 Al2 Ce1 118.59(3) . 1_556 ?
 Al6 Al2 Ce1 64.33(2) 1_556 1_556 ?
 Co1 Al2 Ce1 88.536(9) . . ?
 Ni1 Al2 Ce1 167.32(3) 1_556 . ?
 Co1 Al2 Ce1 167.32(3) 1_556 . ?
 Al8 Al2 Ce1 136.233(16) . . ?
 Al4 Al2 Ce1 66.12(2) . . ?
 Al5 Al2 Ce1 126.48(2) 7_565 . ?
 Al6 Al2 Ce1 64.33(2) . . ?
 Al6 Al2 Ce1 118.59(3) 1_556 . ?
 Ce1 Al2 Ce1 79.64(2) 1_556 . ?
 Ni1 Al5 Co1 0.00(2) 7_665 7_665 ?
 Ni1 Al5 Ni1 102.96(3) 7_665 7_666 ?
 Co1 Al5 Ni1 102.96(3) 7_665 7_666 ?
 Ni1 Al5 Co1 102.96(3) 7_665 7_666 ?
 Co1 Al5 Co1 102.96(3) 7_665 7_666 ?
 Ni1 Al5 Co1 0.000(14) 7_666 7_666 ?
 Ni1 Al5 Al8 56.297(17) 7_665 3_546 ?
 Co1 Al5 Al8 56.297(17) 7_665 3_546 ?
 Ni1 Al5 Al8 56.297(17) 7_666 3_546 ?
 Co1 Al5 Al8 56.297(17) 7_666 3_546 ?
 Ni1 Al5 Al3 112.41(3) 7_665 . ?
 Co1 Al5 Al3 112.41(3) 7_665 . ?
 Ni1 Al5 Al3 112.41(3) 7_666 . ?
 Co1 Al5 Al3 112.41(3) 7_666 . ?
 Al8 Al5 Al3 100.75(3) 3_546 . ?
 Ni1 Al5 Al2 58.108(19) 7_665 7_665 ?
 Co1 Al5 Al2 58.108(19) 7_665 7_665 ?
 Ni1 Al5 Al2 58.108(19) 7_666 7_665 ?
 Co1 Al5 Al2 58.108(19) 7_666 7_665 ?
 Al8 Al5 Al2 58.97(3) 3_546 7_665 ?
 Al3 Al5 Al2 159.72(4) . 7_665 ?
 Ni1 Al5 Al1 108.99(3) 7_665 7_665 ?
 Co1 Al5 Al1 108.99(3) 7_665 7_665 ?
 Ni1 Al5 Al1 108.99(3) 7_666 7_665 ?
 Co1 Al5 Al1 108.99(3) 7_666 7_665 ?
 Al8 Al5 Al1 148.50(4) 3_546 7_665 ?
 Al3 Al5 Al1 110.75(4) . 7_665 ?
 Al2 Al5 Al1 89.53(4) 7_665 7_665 ?
 Ni1 Al5 Al6 117.49(4) 7_665 7_666 ?
 Co1 Al5 Al6 117.49(4) 7_665 7_666 ?
 Ni1 Al5 Al6 50.416(19) 7_666 7_666 ?
 Co1 Al5 Al6 50.416(19) 7_666 7_666 ?
 Al8 Al5 Al6 101.02(3) 3_546 7_666 ?
 Al3 Al5 Al6 129.66(2) . 7_666 ?
 Al2 Al5 Al6 60.72(3) 7_665 7_666 ?
 Al1 Al5 Al6 58.57(2) 7_665 7_666 ?
 Ni1 Al5 Al6 50.416(19) 7_665 7_665 ?
 Co1 Al5 Al6 50.416(19) 7_665 7_665 ?
 Ni1 Al5 Al6 117.49(4) 7_666 7_665 ?
 Co1 Al5 Al6 117.49(4) 7_666 7_665 ?
 Al8 Al5 Al6 101.02(3) 3_546 7_665 ?
 Al3 Al5 Al6 129.66(2) . 7_665 ?
 Al2 Al5 Al6 60.72(3) 7_665 7_665 ?
 Al1 Al5 Al6 58.57(2) 7_665 7_665 ?
 Al6 Al5 Al6 89.20(3) 7_666 7_665 ?
 Ni1 Al5 Ce1 167.50(3) 7_665 1_556 ?
 Co1 Al5 Ce1 167.50(3) 7_665 1_556 ?
 Ni1 Al5 Ce1 88.932(9) 7_666 1_556 ?
 Co1 Al5 Ce1 88.932(9) 7_666 1_556 ?

Al8 Al5 Ce1 135.696(16) 3_546 1_556 ?
 Al3 Al5 Ce1 65.32(2) . 1_556 ?
 Al2 Al5 Ce1 128.07(2) 7_665 1_556 ?
 Al1 Al5 Ce1 62.669(19) 7_665 1_556 ?
 Al6 Al5 Ce1 67.355(19) 7_666 1_556 ?
 Al6 Al5 Ce1 120.52(3) 7_665 1_556 ?
 Ni1 Al5 Ce1 88.932(9) 7_665 . ?
 Co1 Al5 Ce1 88.932(9) 7_665 . ?
 Ni1 Al5 Ce1 167.50(3) 7_666 . ?
 Co1 Al5 Ce1 167.50(3) 7_666 . ?
 Al8 Al5 Ce1 135.696(16) 3_546 . ?
 Al3 Al5 Ce1 65.32(2) . . ?
 Al2 Al5 Ce1 128.07(2) 7_665 . ?
 Al1 Al5 Ce1 62.669(19) 7_665 . ?
 Al6 Al5 Ce1 120.52(3) 7_666 . ?
 Al6 Al5 Ce1 67.355(19) 7_665 . ?
 Ce1 Al5 Ce1 78.962(19) 1_556 . ?
 Co2 Al3 Ni2 105.89(3) . 1_556 ?
 Co2 Al3 Co2 105.89(3) . 1_556 ?
 Ni2 Al3 Co2 0.00(2) 1_556 1_556 ?
 Co2 Al3 Al1 59.88(2) . . ?
 Ni2 Al3 Al1 59.88(2) 1_556 . ?
 Co2 Al3 Al1 59.88(2) 1_556 . ?
 Co2 Al3 Al5 115.73(2) . . ?
 Ni2 Al3 Al5 115.73(2) 1_556 . ?
 Co2 Al3 Al5 115.73(2) 1_556 . ?
 Al1 Al3 Al5 169.72(4) . . ?
 Co2 Al3 Al4 57.185(19) . 3_546 ?
 Ni2 Al3 Al4 57.185(19) 1_556 3_546 ?
 Co2 Al3 Al4 57.185(19) 1_556 3_546 ?
 Al1 Al3 Al4 59.54(3) . 3_546 ?
 Al5 Al3 Al4 110.18(4) . 3_546 ?
 Co2 Al3 Al6 50.89(2) . . ?
 Ni2 Al3 Al6 118.28(4) 1_556 . ?
 Co2 Al3 Al6 118.28(4) 1_556 . ?
 Al1 Al3 Al6 59.90(3) . . ?
 Al5 Al3 Al6 125.89(3) . . ?
 Al4 Al3 Al6 101.14(3) 3_546 . ?
 Co2 Al3 Al6 118.28(4) . 1_556 ?
 Ni2 Al3 Al6 50.89(2) 1_556 1_556 ?
 Co2 Al3 Al6 50.89(2) 1_556 1_556 ?
 Al1 Al3 Al6 59.90(3) . 1_556 ?
 Al5 Al3 Al6 125.89(3) . 1_556 ?
 Al4 Al3 Al6 101.14(3) 3_546 1_556 ?
 Al6 Al3 Al6 87.58(3) . 1_556 ?
 Co2 Al3 Ce1 163.82(3) . 1_556 ?
 Ni2 Al3 Ce1 87.289(10) 1_556 1_556 ?
 Co2 Al3 Ce1 87.289(10) 1_556 1_556 ?
 Al1 Al3 Ce1 122.64(3) . 1_556 ?
 Al5 Al3 Ce1 64.45(2) . 1_556 ?
 Al4 Al3 Ce1 138.918(14) 3_546 1_556 ?
 Al6 Al3 Ce1 114.72(3) . 1_556 ?
 Al6 Al3 Ce1 62.892(19) 1_556 1_556 ?
 Co2 Al3 Ce1 87.289(10) . . ?
 Ni2 Al3 Ce1 163.82(3) 1_556 . ?
 Co2 Al3 Ce1 163.82(3) 1_556 . ?
 Al1 Al3 Ce1 122.64(3) . . ?
 Al5 Al3 Ce1 64.45(2) . . ?
 Al4 Al3 Ce1 138.918(14) 3_546 . ?
 Al6 Al3 Ce1 62.892(19) . . ?
 Al6 Al3 Ce1 114.72(3) 1_556 . ?
 Ce1 Al3 Ce1 78.29(2) 1_556 . ?

Ni2 Al4 Co2 0.000(13) 3_556 3_556 ?
 Ni2 Al4 Ni2 105.63(3) 3_556 3 ?
 Co2 Al4 Ni2 105.63(3) 3_556 3 ?
 Ni2 Al4 Co2 105.63(3) 3_556 3 ?
 Co2 Al4 Co2 105.63(3) 3_556 3 ?
 Ni2 Al4 Co2 0.000(13) 3 3 ?
 Ni2 Al4 Al2 115.21(3) 3_556 . ?
 Co2 Al4 Al2 115.21(3) 3_556 . ?
 Ni2 Al4 Al2 115.21(3) 3 . ?
 Co2 Al4 Al2 115.21(3) 3 . ?
 Ni2 Al4 Al1 59.77(2) 3_556 3_556 ?
 Co2 Al4 Al1 59.77(2) 3_556 3_556 ?
 Ni2 Al4 Al1 59.77(2) 3 3_556 ?
 Co2 Al4 Al1 59.77(2) 3 3_556 ?
 Al2 Al4 Al1 168.40(5) . 3_556 ?
 Ni2 Al4 Al3 57.028(19) 3_556 3_556 ?
 Co2 Al4 Al3 57.028(19) 3_556 3_556 ?
 Ni2 Al4 Al3 57.028(19) 3 3_556 ?
 Co2 Al4 Al3 57.028(19) 3 3_556 ?
 Al2 Al4 Al3 109.02(4) . 3_556 ?
 Al1 Al4 Al3 59.38(3) 3_556 3_556 ?
 Ni2 Al4 Al9 50.545(13) 3_556 3_556 ?
 Co2 Al4 Al9 50.545(13) 3_556 3_556 ?
 Ni2 Al4 Al9 117.72(3) 3 3_556 ?
 Co2 Al4 Al9 117.72(3) 3 3_556 ?
 Al2 Al4 Al9 127.05(2) . 3_556 ?
 Al1 Al4 Al9 59.346(19) 3_556 3_556 ?
 Al3 Al4 Al9 100.46(3) 3_556 3_556 ?
 Ni2 Al4 Al9 117.72(3) 3_556 3 ?
 Co2 Al4 Al9 117.72(3) 3_556 3 ?
 Ni2 Al4 Al9 50.545(13) 3 3 ?
 Co2 Al4 Al9 50.545(13) 3 3 ?
 Al2 Al4 Al9 127.05(2) . 3 ?
 Al1 Al4 Al9 59.346(19) 3_556 3 ?
 Al3 Al4 Al9 100.46(3) 3_556 3 ?
 Al9 Al4 Al9 87.38(2) 3_556 3 ?
 Ni2 Al4 Al1 106.71(3) 3_556 7_665 ?
 Co2 Al4 Al1 106.71(3) 3_556 7_665 ?
 Ni2 Al4 Al1 106.71(3) 3 7_665 ?
 Co2 Al4 Al1 106.71(3) 3 7_665 ?
 Al2 Al4 Al1 106.79(4) . 7_665 ?
 Al1 Al4 Al1 84.81(3) 3_556 7_665 ?
 Al3 Al4 Al1 144.20(4) 3_556 7_665 ?
 Al9 Al4 Al1 56.167(17) 3_556 7_665 ?
 Al9 Al4 Al1 56.167(17) 3 7_665 ?
 Ni2 Al4 Ce1 164.43(3) 3_556 . ?
 Co2 Al4 Ce1 164.43(3) 3_556 . ?
 Ni2 Al4 Ce1 87.783(10) 3 . ?
 Co2 Al4 Ce1 87.783(10) 3 . ?
 Al2 Al4 Ce1 63.89(2) . . ?
 Al1 Al4 Ce1 124.05(3) 3_556 . ?
 Al3 Al4 Ce1 138.539(16) 3_556 . ?
 Al9 Al4 Ce1 116.31(3) 3_556 . ?
 Al9 Al4 Ce1 64.816(11) 3 . ?
 Al1 Al4 Ce1 60.882(19) 7_665 . ?
 Ni2 Al4 Ce1 87.783(10) 3_556 1_556 ?
 Co2 Al4 Ce1 87.783(10) 3_556 1_556 ?
 Ni2 Al4 Ce1 164.43(3) 3 1_556 ?
 Co2 Al4 Ce1 164.43(3) 3 1_556 ?
 Al2 Al4 Ce1 63.89(2) . 1_556 ?
 Al1 Al4 Ce1 124.05(3) 3_556 1_556 ?
 Al3 Al4 Ce1 138.539(16) 3_556 1_556 ?

Al9 Al4 Ce1 64.816(11) 3_556 1_556 ?
 Al9 Al4 Ce1 116.31(3) 3 1_556 ?
 Al1 Al4 Ce1 60.882(19) 7_665 1_556 ?
 Ce1 Al4 Ce1 77.93(2) . 1_556 ?
 Ni2 Al1 Co2 0.000(16) 1_556 1_556 ?
 Ni2 Al1 Co2 100.99(3) 1_556 . ?
 Co2 Al1 Co2 100.99(3) 1_556 . ?
 Ni2 Al1 Al3 56.751(19) 1_556 . ?
 Co2 Al1 Al3 56.751(19) 1_556 . ?
 Co2 Al1 Al3 56.751(19) . . ?
 Ni2 Al1 Al4 56.81(2) 1_556 3_546 ?
 Co2 Al1 Al4 56.81(2) 1_556 3_546 ?
 Co2 Al1 Al4 56.81(2) . 3_546 ?
 Al3 Al1 Al4 61.08(3) . 3_546 ?
 Ni2 Al1 Al9 119.51(3) 1_556 . ?
 Co2 Al1 Al9 119.51(3) 1_556 . ?
 Co2 Al1 Al9 51.503(12) . . ?
 Al3 Al1 Al9 104.99(3) . . ?
 Al4 Al1 Al9 64.15(2) 3_546 . ?
 Ni2 Al1 Al9 51.503(12) 1_556 1_556 ?
 Co2 Al1 Al9 51.503(12) 1_556 1_556 ?
 Co2 Al1 Al9 119.51(3) . 1_556 ?
 Al3 Al1 Al9 104.99(3) . 1_556 ?
 Al4 Al1 Al9 64.15(2) 3_546 1_556 ?
 Al9 Al1 Al9 92.54(3) . 1_556 ?
 Ni2 Al1 Al6 51.53(2) 1_556 1_556 ?
 Co2 Al1 Al6 51.53(2) 1_556 1_556 ?
 Co2 Al1 Al6 119.06(4) . 1_556 ?
 Al3 Al1 Al6 63.82(3) . 1_556 ?
 Al4 Al1 Al6 104.95(3) 3_546 1_556 ?
 Al9 Al1 Al6 167.98(4) . 1_556 ?
 Al9 Al1 Al6 86.596(13) 1_556 1_556 ?
 Ni2 Al1 Al6 119.06(4) 1_556 . ?
 Co2 Al1 Al6 119.06(4) 1_556 . ?
 Co2 Al1 Al6 51.53(2) . . ?
 Al3 Al1 Al6 63.82(3) . . ?
 Al4 Al1 Al6 104.95(3) 3_546 . ?
 Al9 Al1 Al6 86.596(13) . . ?
 Al9 Al1 Al6 167.98(4) 1_556 . ?
 Al6 Al1 Al6 91.76(4) 1_556 . ?
 Ni2 Al1 Al5 112.26(3) 1_556 7_565 ?
 Co2 Al1 Al5 112.26(3) 1_556 7_565 ?
 Co2 Al1 Al5 112.26(3) . 7_565 ?
 Al3 Al1 Al5 96.08(4) . 7_565 ?
 Al4 Al1 Al5 157.16(4) 3_546 7_565 ?
 Al9 Al1 Al5 127.59(2) . 7_565 ?
 Al9 Al1 Al5 127.59(2) 1_556 7_565 ?
 Al6 Al1 Al5 60.74(2) 1_556 7_565 ?
 Al6 Al1 Al5 60.74(2) . 7_565 ?
 Ni2 Al1 Al4 111.84(2) 1_556 7_565 ?
 Co2 Al1 Al4 111.84(2) 1_556 7_565 ?
 Co2 Al1 Al4 111.84(2) . 7_565 ?
 Al3 Al1 Al4 156.26(4) . 7_565 ?
 Al4 Al1 Al4 95.19(3) 3_546 7_565 ?
 Al9 Al1 Al4 60.341(18) . 7_565 ?
 Al9 Al1 Al4 60.341(18) 1_556 7_565 ?
 Al6 Al1 Al4 128.36(2) 1_556 7_565 ?
 Al6 Al1 Al4 128.36(2) . 7_565 ?
 Al5 Al1 Al4 107.66(4) 7_565 7_565 ?
 Co2 Al7 Ni1 146.01(4) . 7_665 ?
 Co2 Al7 Co1 146.01(4) . 7_665 ?
 Ni1 Al7 Co1 0.000(16) 7_665 7_665 ?

Co2 Al7 Co1 145.68(4) . 3_545 ?
 Ni1 Al7 Co1 68.31(3) 7_665 3_545 ?
 Co1 Al7 Co1 68.31(3) 7_665 3_545 ?
 Co2 Al7 Ni1 145.68(4) . 3_545 ?
 Ni1 Al7 Ni1 68.31(3) 7_665 3_545 ?
 Co1 Al7 Ni1 68.31(3) 7_665 3_545 ?
 Co1 Al7 Ni1 0.000(17) 3_545 3_545 ?
 Co2 Al7 Al8 136.211(12) . 3_546 ?
 Ni1 Al7 Al8 53.325(15) 7_665 3_546 ?
 Co1 Al7 Al8 53.325(15) 7_665 3_546 ?
 Co1 Al7 Al8 53.310(15) 3_545 3_546 ?
 Ni1 Al7 Al8 53.310(15) 3_545 3_546 ?
 Co2 Al7 Al8 136.211(12) . 3_545 ?
 Ni1 Al7 Al8 53.325(15) 7_665 3_545 ?
 Co1 Al7 Al8 53.325(15) 7_665 3_545 ?
 Co1 Al7 Al8 53.310(15) 3_545 3_545 ?
 Ni1 Al7 Al8 53.310(15) 3_545 3_545 ?
 Al8 Al7 Al8 87.58(2) 3_546 3_545 ?
 Co1 Al6 Co2 178.03(4) . . ?
 Co1 Al6 Al1 118.93(3) . 1_554 ?
 Co2 Al6 Al1 59.96(2) . 1_554 ?
 Co1 Al6 Al1 118.93(3) . . ?
 Co2 Al6 Al1 59.96(2) . . ?
 Al1 Al6 Al1 91.76(4) 1_554 . ?
 Co1 Al6 Al2 58.95(2) . . ?
 Co2 Al6 Al2 122.13(3) . . ?
 Al1 Al6 Al2 177.67(4) 1_554 . ?
 Al1 Al6 Al2 88.690(19) . . ?
 Co1 Al6 Al2 58.95(2) . 1_554 ?
 Co2 Al6 Al2 122.13(3) . 1_554 ?
 Al1 Al6 Al2 88.690(19) 1_554 1_554 ?
 Al1 Al6 Al2 177.67(4) . 1_554 ?
 Al2 Al6 Al2 90.77(3) . 1_554 ?
 Co1 Al6 Al5 58.24(2) . 7_564 ?
 Co2 Al6 Al5 120.64(3) . 7_564 ?
 Al1 Al6 Al5 60.69(2) 1_554 7_564 ?
 Al1 Al6 Al5 121.24(4) . 7_564 ?
 Al2 Al6 Al5 117.19(4) . 7_564 ?
 Al2 Al6 Al5 57.13(2) 1_554 7_564 ?
 Co1 Al6 Al5 58.24(2) . 7_565 ?
 Co2 Al6 Al5 120.64(3) . 7_565 ?
 Al1 Al6 Al5 121.24(4) 1_554 7_565 ?
 Al1 Al6 Al5 60.69(2) . 7_565 ?
 Al2 Al6 Al5 57.13(2) . 7_565 ?
 Al2 Al6 Al5 117.19(4) 1_554 7_565 ?
 Al5 Al6 Al5 89.20(3) 7_564 7_565 ?
 Co1 Al6 Al3 125.02(3) . . ?
 Co2 Al6 Al3 56.05(2) . . ?
 Al1 Al6 Al3 116.01(4) 1_554 . ?
 Al1 Al6 Al3 56.28(3) . . ?
 Al2 Al6 Al3 66.09(2) . . ?
 Al2 Al6 Al3 125.44(4) 1_554 . ?
 Al5 Al6 Al3 176.33(4) 7_564 . ?
 Al5 Al6 Al3 91.496(18) 7_565 . ?
 Co1 Al6 Al3 125.02(3) . 1_554 ?
 Co2 Al6 Al3 56.05(2) . 1_554 ?
 Al1 Al6 Al3 56.28(3) 1_554 1_554 ?
 Al1 Al6 Al3 116.01(4) . 1_554 ?
 Al2 Al6 Al3 125.44(4) . 1_554 ?
 Al2 Al6 Al3 66.09(2) 1_554 1_554 ?
 Al5 Al6 Al3 91.496(18) 7_564 1_554 ?
 Al5 Al6 Al3 176.33(4) 7_565 1_554 ?

Al3 Al6 Al3 87.58(3) . 1_554 ?

_diffn_measured_fraction_theta_max 0.996
_diffn_reflns_theta_full 30.50
_diffn_measured_fraction_theta_full 0.996
_refine_diff_density_max 1.382
_refine_diff_density_min -0.677
_refine_diff_density_rms 0.161

```

data_shelx
_audit_creation_method      SHELXL-97
_chemical_name_systematic
;
?
;
_chemical_name_common      ?
_chemical_melting_point    ?
_chemical_formula_moiety    ?
_chemical_formula_sum       'Er Fe Ga3'
_chemical_formula_weight    432.27
loop_
_atom_type_symbol           'Zr, Y, X'
_atom_type_description      'X, Y, Z'
_atom_type_scatter_real     'X, Y, Z'
_atom_type_scatter_imag     'X, Y, Z'
'Er' 'Er' -0.2586 4.9576    '-Z, -X, -Y'
'Fe' 'Fe' 0.3463 0.8444     '-Z, X, Y'
'Ga' 'Ga' 0.2307 1.6083     'Z, X, -Y'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Fe' 'Fe' 0.3463 0.8444     'Z, -X, Y'
'Ga' 'Ga' 0.2307 1.6083     'Y, -Z, X'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     '-Y, Z, X'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     'Y, Z, -X'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     '-Y, -X, Z'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     'Y, X, Z'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     '-Y, X, -Z'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     'Y, -X, -Z'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     '-X, -Z, Y'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     'X, -Z, -Y'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     'X, Z, Y'
'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'
'Ga' 'Ga' 0.2307 1.6083     '-X, Z, -Y'
_symmetry_cell_setting      ?
_symmetry_space_group_name_H-M ?
loop_
_symmetry_equiv_pos_as_xyz
'X, Y, Z'
'-X, -Y, Z'
'-X, Y, -Z'
'X, -Y, -Z'
'Z, X, Y'
'Z, -X, -Y'
'-Z, -X, Y'
'-Z, X, -Y'
'Y, Z, X'
'-Y, Z, -X'
'Y, -Z, -X'
'-Y, -Z, X'
'Y, X, -Z'
'-Y, -X, -Z'
'Y, -X, Z'
'-Y, X, Z'
'X, Z, -Y'
'-X, Z, Y'
'-X, -Z, -Y'
'X, -Z, Y'
'Z, Y, -X'
'Z, -Y, X'
_cell_length_a              4.2227(4)
_cell_length_b              4.2227(4)
_cell_length_c              4.2227(4)
_cell_angle_alpha           90.00
_cell_angle_beta            90.00
_cell_angle_gamma           90.00
_cell_volume                 75.296(12)
_cell_formula_units_Z        1
_cell_measurement_temperature 294(2)
_cell_measurement_reflns_used ?
_cell_measurement_theta_min  ?
_cell_measurement_theta_max  ?
_exptl_crystal_description   ?
_exptl_crystal_colour        ?
_exptl_crystal_size_max      ?
_exptl_crystal_size_mid      ?
_exptl_crystal_size_min      ?
_exptl_crystal_density_meas  ?
_exptl_crystal_density_diffn 9.533
_exptl_crystal_density_method 'not measured'
_exptl_crystal_F_000         187
_exptl_absorpt_coefficient_mu 58.423
_exptl_absorpt_correction_type ?

```

```

_exptl_absorpt_correction_T_min ?
_exptl_absorpt_correction_T_max ?
_exptl_absorpt_process_details ?

_exptl_special_details
;
?
;

_diffn_ambient_temperature 294(2)
_diffn_radiation_wavelength 0.71073
_diffn_radiation_type MoK $\alpha$ 
_diffn_radiation_source 'fine-focus sealed tube'
_diffn_radiation_monochromator graphite
_diffn_measurement_device_type ?
_diffn_measurement_method ?
_diffn_detector_area_resol_mean ?
_diffn_standards_number ?
_diffn_standards_interval_count ?
_diffn_standards_interval_time ?
_diffn_standards_decay_% ?
_diffn_reflns_number 734
_diffn_reflns_av_R_equivalents 0.0550
_diffn_reflns_av_sigma/netl 0.0217
_diffn_reflns_limit_h_min -4
_diffn_reflns_limit_h_max 6
_diffn_reflns_limit_k_min -5
_diffn_reflns_limit_k_max 5
_diffn_reflns_limit_l_min -6
_diffn_reflns_limit_l_max 5
_diffn_reflns_theta_min 4.83
_diffn_reflns_theta_max 30.33
_reflns_number_total 41
_reflns_number_gt 41
_reflns_threshold_expression >2sigma(I)

_computing_data_collection ?
_computing_cell_refinement ?
_computing_data_reduction ?
_computing_structure_solution 'SHELXS-97 (Sheldrick, 1990)'
_computing_structure_refinement 'SHELXL-97 (Sheldrick, 1997)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of  $F^2$  against ALL reflections. The weighted
R-factor wR and
goodness of fit S are based on  $F^2$ , conventional R-
factors R are based
on F, with F set to zero for negative  $F^2$ . The threshold
expression of
 $F^2 > 2\sigma(F^2)$  is used only for calculating R-
factors(gt) etc. and is
not relevant to the choice of reflections for refinement.
R-factors based

```

on F^2 are statistically about twice as large as those based on F, and R-factors based on ALL data will be even larger.

```

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type full
_refine_ls_weighting_scheme calc
_refine_ls_weighting_details
'calc w=1/[\s^2(Fo^2)+(0.0000P)^2+0.0026P] where
P=(Fo^2+2Fc^2)/3'
_atom_sites_solution_primary direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment mixed
_refine_ls_extinction_method SHELXL
_refine_ls_extinction_coef 0.17(2)
_refine_ls_extinction_expression
'Fc^*=kFc[1+0.001xFc^2\l^3/sin(2\q)]^-1/4'
_refine_ls_number_reflns 41
_refine_ls_number_parameters 10
_refine_ls_number_restraints 0
_refine_ls_R_factor_all 0.0099
_refine_ls_R_factor_gt 0.0099
_refine_ls_wR_factor_ref 0.0204
_refine_ls_wR_factor_gt 0.0204
_refine_ls_goodness_of_fit_ref 1.416
_refine_ls_restrained_S_all 1.416
_refine_ls_shift/su_max 0.000
_refine_ls_shift/su_mean 0.000

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ga1 Ga 0.0000 0.5000 0.5000 0.0110(14) Uiso 0.76(8) 16 d
SP . .
Ga2 Ga 0.061(8) 0.5000 0.5000 0.011(3) Uiso 0.16(4) 8 d
SP . .
Fe Fe 0.5000 0.5000 0.5000 0.005(7) Uani 0.062(8) 48 d SP
. .
Er1 Er 0.0000 0.0000 0.0000 0.0082(5) Uani 1 48 d S . .

loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33

```

```

_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12
Fe 0.005(7) 0.005(7) 0.005(7) 0.000 0.000 0.000
Er1 0.0082(5) 0.0082(5) 0.0082(5) 0.000 0.000 0.000

_geom_special_details
;
All esds (except the esd in the dihedral angle between two
l.s. planes)
are estimated using the full covariance matrix. The cell
esds are taken
into account individually in the estimation of esds in
distances, angles
and torsion angles; correlations between esds in cell
parameters are only
used when they are defined by crystal symmetry. An
approximate (isotropic)
treatment of cell esds is used for estimating esds involving
l.s. planes.
;

loop_
_geom_bond_atom_site_label_1
_geom_bond_atom_site_label_2
_geom_bond_distance
_geom_bond_site_symmetry_2
_geom_bond_publ_flag
Ga1 Ga2 0.26(3) 25_566 ?
Ga1 Fe 2.1113(2) 1_455 ?
Ga1 Fe 2.1113(2) . ?
Ga1 Ga2 2.81(2) 33_666 ?
Ga1 Ga2 2.81(2) 9_455 ?
Ga1 Ga2 2.81(2) 29_666 ?
Ga1 Ga2 2.81(2) 5_455 ?
Ga1 Ga2 2.81(2) 33_566 ?
Ga1 Ga2 2.81(2) 9 ?
Ga1 Ga2 2.81(2) 29_566 ?
Ga1 Ga2 2.81(2) 5 ?
Ga1 Er1 2.9859(3) 1_566 ?
Ga2 Ga2 0.51(6) 25_566 ?
Ga2 Fe 1.86(3) . ?
Ga2 Fe 2.37(3) 1_455 ?
Ga2 Ga2 2.62(5) 33_666 ?
Ga2 Ga2 2.62(5) 29_666 ?
Ga2 Ga2 2.62(5) 9 ?
Ga2 Ga2 2.62(5) 5 ?
Ga2 Ga1 2.81(2) 5_565 ?
Ga2 Ga1 2.81(2) 9_556 ?
Ga2 Ga1 2.81(2) 5 ?
Ga2 Ga1 2.81(2) 9 ?
Ga2 Er1 2.997(3) . ?
Fe Ga2 1.86(3) 33_666 ?
Fe Ga2 1.86(3) 9 ?
Fe Ga2 1.86(3) 29_666 ?
Fe Ga2 1.86(3) 5 ?
Fe Ga2 1.86(3) 25_666 ?
Fe Ga1 2.1113(2) 9_556 ?

```

```

Fe Ga1 2.1113(2) 9 ?
Fe Ga1 2.1114(2) 1_655 ?
Fe Ga1 2.1113(2) 5_565 ?
Fe Ga1 2.1113(2) 5 ?
Er1 Ga1 2.9859(3) 9 ?
Er1 Ga1 2.9859(3) 9_445 ?
Er1 Ga1 2.9859(3) 1_544 ?
Er1 Ga1 2.9859(3) 5 ?
Er1 Ga1 2.9859(3) 5_454 ?
Er1 Ga1 2.9859(3) 9_455 ?
Er1 Ga1 2.9859(3) 5_554 ?
Er1 Ga1 2.9859(3) 5_455 ?
Er1 Ga1 2.9859(3) 1_545 ?
Er1 Ga1 2.9859(3) 1_554 ?
Er1 Ga1 2.9859(3) 9_545 ?

loop_
_geom_angle_atom_site_label_1
_geom_angle_atom_site_label_2
_geom_angle_atom_site_label_3
_geom_angle
_geom_angle_site_symmetry_1
_geom_angle_site_symmetry_3
_geom_angle_publ_flag
Ga2 Ga1 Fe 0.000(13) 25_566 1_455 ?
Ga2 Ga1 Fe 180.000(13) 25_566 . ?
Fe Ga1 Fe 180.0 1_455 . ?
Ga2 Ga1 Ga2 138.7(5) 25_566 33_666 ?
Fe Ga1 Ga2 138.7(5) 1_455 33_666 ?
Fe Ga1 Ga2 41.3(5) . 33_666 ?
Ga2 Ga1 Ga2 41.3(5) 25_566 9_455 ?
Fe Ga1 Ga2 41.3(5) 1_455 9_455 ?
Fe Ga1 Ga2 138.7(5) . 9_455 ?
Ga2 Ga1 Ga2 180.0 33_666 9_455 ?
Ga2 Ga1 Ga2 138.7(5) 25_566 29_666 ?
Fe Ga1 Ga2 138.7(5) 1_455 29_666 ?
Fe Ga1 Ga2 41.3(5) . 29_666 ?
Ga2 Ga1 Ga2 55.7(6) 33_666 29_666 ?
Ga2 Ga1 Ga2 124.3(6) 9_455 29_666 ?
Ga2 Ga1 Ga2 41.3(5) 25_566 5_455 ?
Fe Ga1 Ga2 41.3(5) 1_455 5_455 ?
Fe Ga1 Ga2 138.7(5) . 5_455 ?
Ga2 Ga1 Ga2 124.3(6) 33_666 5_455 ?
Ga2 Ga1 Ga2 55.7(6) 9_455 5_455 ?
Ga2 Ga1 Ga2 180.0 29_666 5_455 ?
Ga2 Ga1 Ga2 41.3(5) 25_566 33_566 ?
Fe Ga1 Ga2 41.3(5) 1_455 33_566 ?
Fe Ga1 Ga2 138.7(5) . 33_566 ?
Ga2 Ga1 Ga2 97.4(10) 33_666 33_566 ?
Ga2 Ga1 Ga2 82.6(10) 9_455 33_566 ?
Ga2 Ga1 Ga2 124.3(6) 29_666 33_566 ?
Ga2 Ga1 Ga2 55.7(6) 5_455 33_566 ?
Ga2 Ga1 Ga2 138.7(5) 25_566 9 ?
Fe Ga1 Ga2 138.7(5) 1_455 9 ?
Fe Ga1 Ga2 41.3(5) . 9 ?
Ga2 Ga1 Ga2 82.6(10) 33_666 9 ?
Ga2 Ga1 Ga2 97.4(10) 9_455 9 ?
Ga2 Ga1 Ga2 55.7(6) 29_666 9 ?

```

Ga2 Ga1 Ga2 124.3(6) 5_455 9 ?
 Ga2 Ga1 Ga2 180.0 33_566 9 ?
 Ga2 Ga1 Ga2 41.3(5) 25_566 29_566 ?
 Fe Ga1 Ga2 41.3(5) 1_455 29_566 ?
 Fe Ga1 Ga2 138.7(5) . 29_566 ?
 Ga2 Ga1 Ga2 124.3(6) 33_666 29_566 ?
 Ga2 Ga1 Ga2 55.7(6) 9_455 29_566 ?
 Ga2 Ga1 Ga2 97.4(10) 29_666 29_566 ?
 Ga2 Ga1 Ga2 82.6(10) 5_455 29_566 ?
 Ga2 Ga1 Ga2 55.7(6) 33_566 29_566 ?
 Ga2 Ga1 Ga2 124.3(6) 9 29_566 ?
 Ga2 Ga1 Ga2 138.7(5) 25_566 5 ?
 Fe Ga1 Ga2 138.7(5) 1_455 5 ?
 Fe Ga1 Ga2 41.3(5) . 5 ?
 Ga2 Ga1 Ga2 55.7(6) 33_666 5 ?
 Ga2 Ga1 Ga2 124.3(6) 9_455 5 ?
 Ga2 Ga1 Ga2 82.6(10) 29_666 5 ?
 Ga2 Ga1 Ga2 97.4(10) 5_455 5 ?
 Ga2 Ga1 Ga2 124.3(6) 33_566 5 ?
 Ga2 Ga1 Ga2 55.7(6) 9 5 ?
 Ga2 Ga1 Ga2 180.000(2) 29_566 5 ?
 Ga2 Ga1 Er1 90.000(11) 25_566 1_566 ?
 Fe Ga1 Er1 90.0 1_455 1_566 ?
 Fe Ga1 Er1 90.0 . 1_566 ?
 Ga2 Ga1 Er1 62.2(3) 33_666 1_566 ?
 Ga2 Ga1 Er1 117.8(3) 9_455 1_566 ?
 Ga2 Ga1 Er1 62.2(3) 29_666 1_566 ?
 Ga2 Ga1 Er1 117.8(3) 5_455 1_566 ?
 Ga2 Ga1 Er1 62.2(3) 33_566 1_566 ?
 Ga2 Ga1 Er1 117.8(3) 9 1_566 ?
 Ga2 Ga1 Er1 62.2(3) 29_566 1_566 ?
 Ga2 Ga1 Er1 117.8(3) 5 1_566 ?
 Ga2 Ga2 Fe 180.000(6) 25_566 . ?
 Ga2 Ga2 Fe 0.000(8) 25_566 1_455 ?
 Fe Ga2 Fe 180.0 . 1_455 ?
 Ga2 Ga2 Ga2 135.000(2) 25_566 33_666 ?
 Fe Ga2 Ga2 45.000(2) . 33_666 ?
 Fe Ga2 Ga2 135.000(2) 1_455 33_666 ?
 Ga2 Ga2 Ga2 135.000(13) 25_566 29_666 ?
 Fe Ga2 Ga2 45.000(2) . 29_666 ?
 Fe Ga2 Ga2 135.0 1_455 29_666 ?
 Ga2 Ga2 Ga2 60.000(4) 33_666 29_666 ?
 Ga2 Ga2 Ga2 135.000(2) 25_566 9 ?
 Fe Ga2 Ga2 45.000(2) . 9 ?
 Fe Ga2 Ga2 135.000(2) 1_455 9 ?
 Ga2 Ga2 Ga2 90.000(6) 33_666 9 ?
 Ga2 Ga2 Ga2 60.000(6) 29_666 9 ?
 Ga2 Ga2 Ga2 135.000(2) 25_566 5 ?
 Fe Ga2 Ga2 45.0 . 5 ?
 Fe Ga2 Ga2 135.000(4) 1_455 5 ?
 Ga2 Ga2 Ga2 60.000(4) 33_666 5 ?
 Ga2 Ga2 Ga2 90.000(6) 29_666 5 ?
 Ga2 Ga2 Ga2 60.0 9 5 ?
 Ga2 Ga2 Ga1 131.3(5) 25_566 5_565 ?
 Fe Ga2 Ga1 48.7(5) . 5_565 ?
 Fe Ga2 Ga1 131.3(5) 1_455 5_565 ?
 Ga2 Ga2 Ga1 62.2(3) 33_666 5_565 ?
 Ga2 Ga2 Ga1 3.7(5) 29_666 5_565 ?

Ga2 Ga2 Ga1 62.2(3) 9 5_565 ?
 Ga2 Ga2 Ga1 93.7(5) 5 5_565 ?
 Ga2 Ga2 Ga1 131.3(5) 25_566 9_556 ?
 Fe Ga2 Ga1 48.7(5) . 9_556 ?
 Fe Ga2 Ga1 131.3(5) 1_455 9_556 ?
 Ga2 Ga2 Ga1 3.7(5) 33_666 9_556 ?
 Ga2 Ga2 Ga1 62.2(3) 29_666 9_556 ?
 Ga2 Ga2 Ga1 93.7(5) 9 9_556 ?
 Ga2 Ga2 Ga1 62.2(3) 5 9_556 ?
 Ga1 Ga2 Ga1 64.2(5) 5_565 9_556 ?
 Ga2 Ga2 Ga1 131.3(5) 25_566 5 ?
 Fe Ga2 Ga1 48.7(5) . 5 ?
 Fe Ga2 Ga1 131.3(5) 1_455 5 ?
 Ga2 Ga2 Ga1 62.2(3) 33_666 5 ?
 Ga2 Ga2 Ga1 93.7(5) 29_666 5 ?
 Ga2 Ga2 Ga1 62.2(3) 9 5 ?
 Ga2 Ga2 Ga1 3.7(5) 5 5 ?
 Ga1 Ga2 Ga1 97.4(10) 5_565 5 ?
 Ga1 Ga2 Ga1 64.2(5) 9_556 5 ?
 Ga2 Ga2 Ga1 131.3(5) 25_566 9 ?
 Fe Ga2 Ga1 48.7(5) . 9 ?
 Fe Ga2 Ga1 131.3(5) 1_455 9 ?
 Ga2 Ga2 Ga1 93.7(5) 33_666 9 ?
 Ga2 Ga2 Ga1 62.2(3) 29_666 9 ?
 Ga2 Ga2 Ga1 3.7(5) 9 9 ?
 Ga2 Ga2 Ga1 62.2(3) 5 9 ?
 Ga1 Ga2 Ga1 64.2(5) 5_565 9 ?
 Ga1 Ga2 Ga1 97.4(10) 9_556 9 ?
 Ga1 Ga2 Ga1 64.2(5) 5 9 ?
 Ga2 Ga2 Er1 85.1(6) 25_566 . ?
 Fe Ga2 Er1 94.9(6) . . ?
 Fe Ga2 Er1 85.1(6) 1_455 . ?
 Ga2 Ga2 Er1 124.0(5) 33_666 . ?
 Ga2 Ga2 Er1 124.0(5) 29_666 . ?
 Ga2 Ga2 Er1 64.0(5) 9 . ?
 Ga2 Ga2 Er1 64.0(5) 5 . ?
 Ga1 Ga2 Er1 125.8(7) 5_565 . ?
 Ga1 Ga2 Er1 125.8(7) 9_556 . ?
 Ga1 Ga2 Er1 61.78(19) 5 . ?
 Ga1 Ga2 Er1 61.78(19) 9 . ?
 Ga2 Fe Ga2 180.000(2) 33_666 9 ?
 Ga2 Fe Ga2 90.000(4) 33_666 29_666 ?
 Ga2 Fe Ga2 90.0 9 29_666 ?
 Ga2 Fe Ga2 90.0 33_666 5 ?
 Ga2 Fe Ga2 90.000(4) 9 5 ?
 Ga2 Fe Ga2 180.000(2) 29_666 5 ?
 Ga2 Fe Ga2 90.000(8) 33_666 25_666 ?
 Ga2 Fe Ga2 90.0 9 25_666 ?
 Ga2 Fe Ga2 90.000(9) 29_666 25_666 ?
 Ga2 Fe Ga2 90.000(2) 5 25_666 ?
 Ga2 Fe Ga2 90.0 33_666 . ?
 Ga2 Fe Ga2 90.000(8) 9 . ?
 Ga2 Fe Ga2 90.000(2) 29_666 . ?
 Ga2 Fe Ga2 90.000(9) 5 . ?
 Ga2 Fe Ga2 180.000(2) 25_666 . ?
 Ga2 Fe Ga1 90.000(4) 33_666 . ?
 Ga2 Fe Ga1 90.000(4) 9 . ?
 Ga2 Fe Ga1 90.000(4) 29_666 . ?

Ga2 Fe Ga1 90.000(4) 5 . ?
 Ga2 Fe Ga1 180.000(2) 25_666 . ?
 Ga2 Fe Ga1 0.000(2) . . ?
 Ga2 Fe Ga1 0.000(6) 33_666 9_556 ?
 Ga2 Fe Ga1 180.000(2) 9 9_556 ?
 Ga2 Fe Ga1 90.000(2) 29_666 9_556 ?
 Ga2 Fe Ga1 90.000(2) 5 9_556 ?
 Ga2 Fe Ga1 90.000(2) 25_666 9_556 ?
 Ga2 Fe Ga1 90.000(2) . 9_556 ?
 Ga1 Fe Ga1 90.0 . 9_556 ?
 Ga2 Fe Ga1 180.000(6) 33_666 9 ?
 Ga2 Fe Ga1 0.000(2) 9 9 ?
 Ga2 Fe Ga1 90.000(2) 29_666 9 ?
 Ga2 Fe Ga1 90.000(2) 5 9 ?
 Ga2 Fe Ga1 90.000(2) 25_666 9 ?
 Ga2 Fe Ga1 90.000(2) . 9 ?
 Ga1 Fe Ga1 90.0 . 9 ?
 Ga1 Fe Ga1 180.0 9_556 9 ?
 Ga2 Fe Ga1 90.000(4) 33_666 1_655 ?
 Ga2 Fe Ga1 90.000(4) 9 1_655 ?
 Ga2 Fe Ga1 90.000(4) 29_666 1_655 ?
 Ga2 Fe Ga1 90.000(4) 5 1_655 ?
 Ga2 Fe Ga1 0.000(2) 25_666 1_655 ?
 Ga2 Fe Ga1 180.000(2) . 1_655 ?
 Ga1 Fe Ga1 180.0 . 1_655 ?
 Ga1 Fe Ga1 90.0 9_556 1_655 ?
 Ga1 Fe Ga1 90.0 9 1_655 ?
 Ga2 Fe Ga1 90.000(2) 33_666 5_565 ?
 Ga2 Fe Ga1 90.000(2) 9 5_565 ?
 Ga2 Fe Ga1 0.000(6) 29_666 5_565 ?
 Ga2 Fe Ga1 180.000(2) 5 5_565 ?
 Ga2 Fe Ga1 90.0 25_666 5_565 ?
 Ga2 Fe Ga1 90.000(2) . 5_565 ?
 Ga1 Fe Ga1 90.0 . 5_565 ?
 Ga1 Fe Ga1 90.0 9_556 5_565 ?
 Ga1 Fe Ga1 90.0 9 5_565 ?
 Ga1 Fe Ga1 90.0 1_655 5_565 ?
 Ga2 Fe Ga1 90.000(2) 33_666 5 ?
 Ga2 Fe Ga1 90.000(2) 9 5 ?
 Ga2 Fe Ga1 180.000(6) 29_666 5 ?
 Ga2 Fe Ga1 0.000(2) 5 5 ?
 Ga2 Fe Ga1 90.0 25_666 5 ?
 Ga2 Fe Ga1 90.000(4) . 5 ?
 Ga1 Fe Ga1 90.0 . 5 ?
 Ga1 Fe Ga1 90.0 9_556 5 ?
 Ga1 Fe Ga1 90.0 9 5 ?
 Ga1 Fe Ga1 90.0 1_655 5 ?
 Ga1 Fe Ga1 180.0 5_565 5 ?
 Ga1 Er1 Ga1 60.0 9 . ?
 Ga1 Er1 Ga1 180.0 9 9_445 ?
 Ga1 Er1 Ga1 120.0 . 9_445 ?
 Ga1 Er1 Ga1 120.0 9 1_544 ?
 Ga1 Er1 Ga1 180.0 . 1_544 ?
 Ga1 Er1 Ga1 60.0 9_445 1_544 ?
 Ga1 Er1 Ga1 60.0 9 5 ?
 Ga1 Er1 Ga1 60.0 . 5 ?
 Ga1 Er1 Ga1 120.0 9_445 5 ?
 Ga1 Er1 Ga1 120.0 1_544 5 ?

Ga1 Er1 Ga1 120.0 9 5_454 ?
 Ga1 Er1 Ga1 120.0 . 5_454 ?
 Ga1 Er1 Ga1 60.0 9_445 5_454 ?
 Ga1 Er1 Ga1 60.0 1_544 5_454 ?
 Ga1 Er1 Ga1 180.0 5 5_454 ?
 Ga1 Er1 Ga1 90.0 9 9_455 ?
 Ga1 Er1 Ga1 60.0 . 9_455 ?
 Ga1 Er1 Ga1 90.0 9_445 9_455 ?
 Ga1 Er1 Ga1 120.0 1_544 9_455 ?
 Ga1 Er1 Ga1 120.0 5 9_455 ?
 Ga1 Er1 Ga1 60.0 5_454 9_455 ?
 Ga1 Er1 Ga1 60.0 9 5_554 ?
 Ga1 Er1 Ga1 120.0 . 5_554 ?
 Ga1 Er1 Ga1 120.0 9_445 5_554 ?
 Ga1 Er1 Ga1 60.0 1_544 5_554 ?
 Ga1 Er1 Ga1 90.0 5 5_554 ?
 Ga1 Er1 Ga1 90.0 5_454 5_554 ?
 Ga1 Er1 Ga1 120.0 9_455 5_554 ?
 Ga1 Er1 Ga1 120.0 9 5_455 ?
 Ga1 Er1 Ga1 60.0 . 5_455 ?
 Ga1 Er1 Ga1 60.0 9_445 5_455 ?
 Ga1 Er1 Ga1 120.0 1_544 5_455 ?
 Ga1 Er1 Ga1 90.0 5 5_455 ?
 Ga1 Er1 Ga1 90.0 5_454 5_455 ?
 Ga1 Er1 Ga1 60.0 9_455 5_455 ?
 Ga1 Er1 Ga1 180.0 5_554 5_455 ?
 Ga1 Er1 Ga1 120.0 9 1_545 ?
 Ga1 Er1 Ga1 90.0 . 1_545 ?
 Ga1 Er1 Ga1 60.0 9_445 1_545 ?
 Ga1 Er1 Ga1 90.0 1_544 1_545 ?
 Ga1 Er1 Ga1 60.0 5 1_545 ?
 Ga1 Er1 Ga1 120.0 5_454 1_545 ?
 Ga1 Er1 Ga1 120.0 9_455 1_545 ?
 Ga1 Er1 Ga1 120.0 5_554 1_545 ?
 Ga1 Er1 Ga1 60.0 5_455 1_545 ?
 Ga1 Er1 Ga1 60.0 9 1_554 ?
 Ga1 Er1 Ga1 90.0 . 1_554 ?
 Ga1 Er1 Ga1 120.0 9_445 1_554 ?
 Ga1 Er1 Ga1 90.0 1_544 1_554 ?
 Ga1 Er1 Ga1 120.0 5 1_554 ?
 Ga1 Er1 Ga1 60.0 5_454 1_554 ?
 Ga1 Er1 Ga1 60.0 9_455 1_554 ?
 Ga1 Er1 Ga1 60.0 5_554 1_554 ?
 Ga1 Er1 Ga1 120.0 5_455 1_554 ?
 Ga1 Er1 Ga1 180.0 1_545 1_554 ?
 Ga1 Er1 Ga1 90.0 9 9_545 ?
 Ga1 Er1 Ga1 120.0 . 9_545 ?
 Ga1 Er1 Ga1 90.0 9_445 9_545 ?
 Ga1 Er1 Ga1 60.0 1_544 9_545 ?
 Ga1 Er1 Ga1 60.0 5 9_545 ?
 Ga1 Er1 Ga1 120.0 5_454 9_545 ?
 Ga1 Er1 Ga1 180.0 9_455 9_545 ?
 Ga1 Er1 Ga1 60.0 5_554 9_545 ?
 Ga1 Er1 Ga1 120.0 5_455 9_545 ?
 Ga1 Er1 Ga1 60.0 1_545 9_545 ?
 Ga1 Er1 Ga1 120.0 1_554 9_545 ?

_diffn_measured_fraction_theta_max 1.000

| | | | |
|---|-----------|---------------------------------|----------------|
| _diffn_reflns_theta_full | 30.33 | 'z, y, -x' | |
| _diffn_measured_fraction_theta_full | 1.000 | 'z, -y, x' | |
| _refine_diff_density_max | 0.895 | '-z, y, x' | |
| _refine_diff_density_min | -0.681 | '-z, -y, -x' | |
| _refine_diff_density_rms | 0.193 | '-x, -y, -z' | |
| | | 'x, y, -z' | |
| data_shelx | | 'x, -y, z' | |
| | | '-x, y, z' | |
| _audit_creation_method | SHELXL-97 | '-z, -x, -y' | |
| _chemical_name_systematic | | '-z, x, y' | |
| ; | | 'z, x, -y' | |
| ? | | 'z, -x, y' | |
| ; | | '-y, -z, -x' | |
| _chemical_name_common | ? | 'y, -z, x' | |
| _chemical_melting_point | ? | '-y, z, x' | |
| _chemical_formula_moiety | ? | 'y, z, -x' | |
| _chemical_formula_sum | | '-y, -x, z' | |
| 'Er Fe Ga3' | | 'y, x, z' | |
| _chemical_formula_weight | 432.27 | '-y, x, -z' | |
| | | 'y, -x, -z' | |
| loop_ | | '-x, -z, y' | |
| _atom_type_symbol | | 'x, -z, -y' | |
| _atom_type_description | | 'x, z, y' | |
| _atom_type_scatter_dispersion_real | | '-x, z, -y' | |
| _atom_type_scatter_dispersion_imag | | '-z, -y, x' | |
| _atom_type_scatter_source | | '-z, y, -x' | |
| 'Fe' 'Fe' 0.3463 0.8444 | | 'z, -y, -x' | |
| 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4' | | 'z, y, x' | |
| 'Ga' 'Ga' 0.2307 1.6083 | | | |
| 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4' | | _cell_length_a | 4.2263(5) |
| 'Er' 'Er' -0.2586 4.9576 | | _cell_length_b | 4.2263(5) |
| 'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4' | | _cell_length_c | 4.2263(5) |
| | | _cell_angle_alpha | 90.00 |
| _symmetry_cell_setting | ? | _cell_angle_beta | 90.00 |
| _symmetry_space_group_name_H-M | ? | _cell_angle_gamma | 90.00 |
| | | _cell_volume | 75.489(15) |
| loop_ | | _cell_formula_units_Z | 1 |
| _symmetry_equiv_pos_as_xyz | | _cell_measurement_temperature | 294(2) |
| 'x, y, z' | | _cell_measurement_reflns_used | ? |
| '-x, -y, z' | | _cell_measurement_theta_min | ? |
| '-x, y, -z' | | _cell_measurement_theta_max | ? |
| 'x, -y, -z' | | | |
| 'z, x, y' | | _exptl_crystal_description | ? |
| 'z, -x, -y' | | _exptl_crystal_colour | ? |
| '-z, -x, y' | | _exptl_crystal_size_max | ? |
| '-z, x, -y' | | _exptl_crystal_size_mid | ? |
| 'y, z, x' | | _exptl_crystal_size_min | ? |
| '-y, z, -x' | | _exptl_crystal_density_meas | ? |
| 'y, -z, -x' | | _exptl_crystal_density_diffn | 9.509 |
| '-y, -z, x' | | _exptl_crystal_density_method | 'not measured' |
| 'y, x, -z' | | _exptl_crystal_F_000 | 187 |
| '-y, -x, -z' | | _exptl_absorpt_coefficient_mu | 58.274 |
| 'y, -x, z' | | _exptl_absorpt_correction_type | ? |
| '-y, x, z' | | _exptl_absorpt_correction_T_min | ? |
| 'x, z, -y' | | _exptl_absorpt_correction_T_max | ? |
| '-x, z, y' | | _exptl_absorpt_process_details | ? |
| '-x, -z, -y' | | | |
| 'x, -z, y' | | _exptl_special_details | |

```

;
?
;

_diffrn_ambient_temperature 294(2)
_diffrn_radiation_wavelength 0.71073
_diffrn_radiation_type MoK\alpha
_diffrn_radiation_source 'fine-focus sealed tube'
_diffrn_radiation_monochromator graphite
_diffrn_measurement_device_type ?
_diffrn_measurement_method ?
_diffrn_detector_area_resol_mean ?
_diffrn_standards_number ?
_diffrn_standards_interval_count ?
_diffrn_standards_interval_time ?
_diffrn_standards_decay_% ?
_diffrn_reflns_number 756
_diffrn_reflns_av_R_equivalents 0.0578
_diffrn_reflns_av_sigma/netl 0.0226
_diffrn_reflns_limit_h_min -6
_diffrn_reflns_limit_h_max 4
_diffrn_reflns_limit_k_min -5
_diffrn_reflns_limit_k_max 5
_diffrn_reflns_limit_l_min -5
_diffrn_reflns_limit_l_max 6
_diffrn_reflns_theta_min 4.82
_diffrn_reflns_theta_max 30.30
_reflns_number_total 41
_reflns_number_gt 41
_reflns_threshold_expression >2sigma(I)

_computing_data_collection ?
_computing_cell_refinement ?
_computing_data_reduction ?
_computing_structure_solution 'SHELXS-97 (Sheldrick, 1990)'
_computing_structure_refinement 'SHELXL-97 (Sheldrick, 1997)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F^2 against ALL reflections. The weighted
R-factor wR and
goodness of fit S are based on F^2, conventional R-
factors R are based
on F, with F set to zero for negative F^2. The threshold
expression of
F^2 > 2sigma(F^2) is used only for calculating R-
factors(gt) etc. and is
not relevant to the choice of reflections for refinement.
R-factors based
on F^2 are statistically about twice as large as those
based on F, and R-
factors based on ALL data will be even larger.
;

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type full
_refine_ls_weighting_scheme calc
_refine_ls_weighting_details
'calc w=1/[sigma^2(Fo^2)+(0.0281P)^2+0.0251P] where
P=(Fo^2+2Fc^2)/3'
_atom_sites_solution_primary direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment mixed
_refine_ls_extinction_method SHELXL
_refine_ls_extinction_coef 0.21(5)
_refine_ls_extinction_expression
'Fc^2=kFc[1+0.001xFc^2/l^3/sin(2\theta)]^-1/4'
_refine_ls_number_reflns 41
_refine_ls_number_parameters 10
_refine_ls_number_restraints 0
_refine_ls_R_factor_all 0.0184
_refine_ls_R_factor_gt 0.0184
_refine_ls_wR_factor_ref 0.0392
_refine_ls_wR_factor_gt 0.0392
_refine_ls_goodness_of_fit_ref 1.269
_refine_ls_restrained_S_all 1.269
_refine_ls_shift/su_max 0.000
_refine_ls_shift/su_mean 0.000

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ga1 Ga 0.0000 0.5000 0.5000 0.007(2) Uiso 0.72(9) 16 d SP
..
Ga2 Ga 0.070(9) 0.5000 0.5000 0.004(4) Uiso 0.16(4) 8 d
SP . .
Fe Fe 0.5000 0.5000 0.5000 0.002(8) Uani 0.105(18) 48 d
SP . .
Er1 Er 0.0000 0.0000 0.0000 0.0037(9) Uani 1 48 d S . .

loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12
Fe 0.002(8) 0.002(8) 0.002(8) 0.000 0.000 0.000
Er1 0.0037(9) 0.0037(9) 0.0037(9) 0.000 0.000 0.000

```

```

_geom_special_details
;
All esds (except the esd in the dihedral angle between two
l.s. planes)
are estimated using the full covariance matrix. The cell
esds are taken
into account individually in the estimation of esds in
distances, angles
and torsion angles; correlations between esds in cell
parameters are only
used when they are defined by crystal symmetry. An
approximate (isotropic)
treatment of cell esds is used for estimating esds involving
l.s. planes.
;

```

```

loop_
  _geom_bond_atom_site_label_1
  _geom_bond_atom_site_label_2
  _geom_bond_distance
  _geom_bond_site_symmetry_2
  _geom_bond_publ_flag
Ga1 Ga2 0.29(4) 25_566 ?
Ga1 Fe 2.1131(3) 1_455 ?
Ga1 Fe 2.1131(3) . ?
Ga1 Ga2 2.79(2) 33_666 ?
Ga1 Ga2 2.79(2) 9_455 ?
Ga1 Ga2 2.79(2) 29_666 ?
Ga1 Ga2 2.79(2) 5_455 ?
Ga1 Ga2 2.79(2) 33_566 ?
Ga1 Ga2 2.79(2) 9 ?
Ga1 Ga2 2.79(2) 29_566 ?
Ga1 Ga2 2.79(2) 5 ?
Ga1 Er1 2.9884(4) 1_566 ?
Ga2 Ga2 0.59(7) 25_566 ?
Ga2 Fe 1.82(4) . ?
Ga2 Fe 2.41(4) 1_455 ?
Ga2 Ga2 2.57(5) 33_666 ?
Ga2 Ga2 2.57(5) 29_666 ?
Ga2 Ga2 2.57(5) 9 ?
Ga2 Ga2 2.57(5) 5 ?
Ga2 Ga1 2.79(2) 5_565 ?
Ga2 Ga1 2.79(2) 9_556 ?
Ga2 Ga1 2.79(2) 5 ?
Ga2 Ga1 2.79(2) 9 ?
Ga2 Er1 3.003(4) . ?
Fe Ga2 1.82(4) 33_666 ?
Fe Ga2 1.82(4) 9 ?
Fe Ga2 1.82(4) 29_666 ?
Fe Ga2 1.82(4) 5 ?
Fe Ga2 1.82(4) 25_666 ?
Fe Ga1 2.1131(3) 9_556 ?
Fe Ga1 2.1132(3) 1_655 ?
Fe Ga1 2.1131(3) 5 ?
Fe Ga1 2.1131(3) 9 ?
Fe Ga1 2.1131(3) 5_565 ?
Er1 Ga1 2.9884(4) 9 ?

```

```

Er1 Ga1 2.9884(4) 9_445 ?
Er1 Ga1 2.9884(4) 1_544 ?
Er1 Ga1 2.9884(4) 5 ?
Er1 Ga1 2.9884(4) 5_454 ?
Er1 Ga1 2.9884(4) 9_455 ?
Er1 Ga1 2.9884(4) 5_554 ?
Er1 Ga1 2.9884(4) 5_455 ?
Er1 Ga1 2.9884(4) 1_545 ?
Er1 Ga1 2.9884(4) 1_554 ?
Er1 Ga1 2.9884(4) 9_545 ?

```

```

loop_
  _geom_angle_atom_site_label_1
  _geom_angle_atom_site_label_2
  _geom_angle_atom_site_label_3
  _geom_angle
  _geom_angle_site_symmetry_1
  _geom_angle_site_symmetry_3
  _geom_angle_publ_flag
Ga2 Ga1 Fe 0.000(13) 25_566 1_455 ?
Ga2 Ga1 Fe 180.000(13) 25_566 . ?
Fe Ga1 Fe 180.0 1_455 . ?
Ga2 Ga1 Ga2 139.3(6) 25_566 33_666 ?
Fe Ga1 Ga2 139.3(6) 1_455 33_666 ?
Fe Ga1 Ga2 40.7(6) . 33_666 ?
Ga2 Ga1 Ga2 40.7(6) 25_566 9_455 ?
Fe Ga1 Ga2 40.7(6) 1_455 9_455 ?
Fe Ga1 Ga2 139.3(6) . 9_455 ?
Ga2 Ga1 Ga2 180.000(2) 33_666 9_455 ?
Ga2 Ga1 Ga2 139.3(6) 25_566 29_666 ?
Fe Ga1 Ga2 139.3(6) 1_455 29_666 ?
Fe Ga1 Ga2 40.7(6) . 29_666 ?
Ga2 Ga1 Ga2 54.9(7) 33_666 29_666 ?
Ga2 Ga1 Ga2 125.1(7) 9_455 29_666 ?
Ga2 Ga1 Ga2 40.7(6) 25_566 5_455 ?
Fe Ga1 Ga2 40.7(6) 1_455 5_455 ?
Fe Ga1 Ga2 139.3(6) . 5_455 ?
Ga2 Ga1 Ga2 125.1(7) 33_666 5_455 ?
Ga2 Ga1 Ga2 54.9(7) 9_455 5_455 ?
Ga2 Ga1 Ga2 180.0 29_666 5_455 ?
Ga2 Ga1 Ga2 40.7(6) 25_566 33_566 ?
Fe Ga1 Ga2 40.7(6) 1_455 33_566 ?
Fe Ga1 Ga2 139.3(6) . 33_566 ?
Ga2 Ga1 Ga2 98.6(11) 33_666 33_566 ?
Ga2 Ga1 Ga2 81.4(11) 9_455 33_566 ?
Ga2 Ga1 Ga2 125.1(7) 29_666 33_566 ?
Ga2 Ga1 Ga2 54.9(7) 5_455 33_566 ?
Ga2 Ga1 Ga2 139.3(6) 25_566 9 ?
Fe Ga1 Ga2 139.3(6) 1_455 9 ?
Fe Ga1 Ga2 40.7(6) . 9 ?
Ga2 Ga1 Ga2 81.4(11) 33_666 9 ?
Ga2 Ga1 Ga2 98.6(11) 9_455 9 ?
Ga2 Ga1 Ga2 54.9(7) 29_666 9 ?
Ga2 Ga1 Ga2 125.1(7) 5_455 9 ?
Ga2 Ga1 Ga2 180.000(2) 33_566 9 ?
Ga2 Ga1 Ga2 40.7(6) 25_566 29_566 ?
Fe Ga1 Ga2 40.7(6) 1_455 29_566 ?
Fe Ga1 Ga2 139.3(6) . 29_566 ?

```

Ga2 Ga1 Ga2 125.1(7) 33_666 29_566 ?
 Ga2 Ga1 Ga2 54.9(7) 9_455 29_566 ?
 Ga2 Ga1 Ga2 98.6(11) 29_666 29_566 ?
 Ga2 Ga1 Ga2 81.4(11) 5_455 29_566 ?
 Ga2 Ga1 Ga2 54.9(7) 33_566 29_566 ?
 Ga2 Ga1 Ga2 125.1(7) 9_29_566 ?
 Ga2 Ga1 Ga2 139.3(6) 25_566 5 ?
 Fe Ga1 Ga2 139.3(6) 1_455 5 ?
 Fe Ga1 Ga2 40.7(6) . 5 ?
 Ga2 Ga1 Ga2 54.9(7) 33_666 5 ?
 Ga2 Ga1 Ga2 125.1(7) 9_455 5 ?
 Ga2 Ga1 Ga2 81.4(11) 29_666 5 ?
 Ga2 Ga1 Ga2 98.6(11) 5_455 5 ?
 Ga2 Ga1 Ga2 125.1(7) 33_566 5 ?
 Ga2 Ga1 Ga2 54.9(7) 9 5 ?
 Ga2 Ga1 Ga2 180.000(2) 29_566 5 ?
 Ga2 Ga1 Er1 90.000(11) 25_566 1_566 ?
 Fe Ga1 Er1 90.0 1_455 1_566 ?
 Fe Ga1 Er1 90.0 . 1_566 ?
 Ga2 Ga1 Er1 62.5(3) 33_666 1_566 ?
 Ga2 Ga1 Er1 117.5(3) 9_455 1_566 ?
 Ga2 Ga1 Er1 62.5(3) 29_666 1_566 ?
 Ga2 Ga1 Er1 117.5(3) 5_455 1_566 ?
 Ga2 Ga1 Er1 62.5(3) 33_566 1_566 ?
 Ga2 Ga1 Er1 117.5(3) 9 1_566 ?
 Ga2 Ga1 Er1 62.5(3) 29_566 1_566 ?
 Ga2 Ga1 Er1 117.5(3) 5 1_566 ?
 Ga2 Ga2 Fe 180.000(6) 25_566 . ?
 Ga2 Ga2 Fe 0.000(6) 25_566 1_455 ?
 Fe Ga2 Fe 180.0 . 1_455 ?
 Ga2 Ga2 Ga2 135.000(2) 25_566 33_666 ?
 Fe Ga2 Ga2 45.000(2) . 33_666 ?
 Fe Ga2 Ga2 135.000(1) 1_455 33_666 ?
 Ga2 Ga2 Ga2 135.000(13) 25_566 29_666 ?
 Fe Ga2 Ga2 45.000(2) . 29_666 ?
 Fe Ga2 Ga2 135.0 1_455 29_666 ?
 Ga2 Ga2 Ga2 60.000(4) 33_666 29_666 ?
 Ga2 Ga2 Ga2 135.0 25_566 9 ?
 Fe Ga2 Ga2 45.000(4) . 9 ?
 Fe Ga2 Ga2 135.000(2) 1_455 9 ?
 Ga2 Ga2 Ga2 90.000(4) 33_666 9 ?
 Ga2 Ga2 Ga2 60.000(2) 29_666 9 ?
 Ga2 Ga2 Ga2 135.000(2) 25_566 5 ?
 Fe Ga2 Ga2 45.000(2) . 5 ?
 Fe Ga2 Ga2 135.000(6) 1_455 5 ?
 Ga2 Ga2 Ga2 60.0 33_666 5 ?
 Ga2 Ga2 Ga2 90.000(4) 29_666 5 ?
 Ga2 Ga2 Ga2 60.0 9 5 ?
 Ga2 Ga2 Ga1 130.7(6) 25_566 5_565 ?
 Fe Ga2 Ga1 49.3(6) . 5_565 ?
 Fe Ga2 Ga1 130.7(6) 1_455 5_565 ?
 Ga2 Ga2 Ga1 62.5(3) 33_666 5_565 ?
 Ga2 Ga2 Ga1 4.3(6) 29_666 5_565 ?
 Ga2 Ga2 Ga1 62.5(3) 9 5_565 ?
 Ga2 Ga2 Ga1 94.3(6) 5 5_565 ?
 Ga2 Ga2 Ga1 130.7(6) 25_566 9_556 ?
 Fe Ga2 Ga1 49.3(6) . 9_556 ?
 Fe Ga2 Ga1 130.7(6) 1_455 9_556 ?

Ga2 Ga2 Ga1 4.3(6) 33_666 9_556 ?
 Ga2 Ga2 Ga1 62.5(3) 29_666 9_556 ?
 Ga2 Ga2 Ga1 94.3(6) 9 9_556 ?
 Ga2 Ga2 Ga1 62.5(3) 5 9_556 ?
 Ga1 Ga2 Ga1 64.8(6) 5_565 9_556 ?
 Ga2 Ga2 Ga1 130.7(6) 25_566 5 ?
 Fe Ga2 Ga1 49.3(6) . 5 ?
 Fe Ga2 Ga1 130.7(6) 1_455 5 ?
 Ga2 Ga2 Ga1 62.5(3) 33_666 5 ?
 Ga2 Ga2 Ga1 94.3(6) 29_666 5 ?
 Ga2 Ga2 Ga1 62.5(3) 9 5 ?
 Ga2 Ga2 Ga1 4.3(6) 5 5 ?
 Ga1 Ga2 Ga1 98.6(11) 5_565 5 ?
 Ga1 Ga2 Ga1 64.8(6) 9_556 5 ?
 Ga2 Ga2 Ga1 130.7(6) 25_566 9 ?
 Fe Ga2 Ga1 49.3(6) . 9 ?
 Fe Ga2 Ga1 130.7(6) 1_455 9 ?
 Ga2 Ga2 Ga1 94.3(6) 33_666 9 ?
 Ga2 Ga2 Ga1 62.5(3) 29_666 9 ?
 Ga2 Ga2 Ga1 4.3(6) 9 9 ?
 Ga2 Ga2 Ga1 62.5(3) 5 9 ?
 Ga1 Ga2 Ga1 64.8(6) 5_565 9 ?
 Ga1 Ga2 Ga1 98.6(11) 9_556 9 ?
 Ga1 Ga2 Ga1 64.8(6) 5 9 ?
 Ga2 Ga2 Er1 84.4(7) 25_566 . ?
 Fe Ga2 Er1 95.6(7) . . ?
 Fe Ga2 Er1 84.4(7) 1_455 . ?
 Ga2 Ga2 Er1 124.5(5) 33_666 . ?
 Ga2 Ga2 Er1 124.5(5) 29_666 . ?
 Ga2 Ga2 Er1 64.6(6) 9 . ?
 Ga2 Ga2 Er1 64.6(6) 5 . ?
 Ga1 Ga2 Er1 126.7(8) 5_565 . ?
 Ga1 Ga2 Er1 126.7(8) 9_556 . ?
 Ga1 Ga2 Er1 62.0(2) 5 . ?
 Ga1 Ga2 Er1 62.0(2) 9 . ?
 Ga2 Fe Ga2 90.000(6) . 33_666 ?
 Ga2 Fe Ga2 90.000(6) . 9 ?
 Ga2 Fe Ga2 180.000(2) 33_666 9 ?
 Ga2 Fe Ga2 90.000(6) . 29_666 ?
 Ga2 Fe Ga2 90.000(4) 33_666 29_666 ?
 Ga2 Fe Ga2 90.0 9 29_666 ?
 Ga2 Fe Ga2 90.000(11) . 5 ?
 Ga2 Fe Ga2 90.0 33_666 5 ?
 Ga2 Fe Ga2 90.000(4) 9 5 ?
 Ga2 Fe Ga2 180.000(2) 29_666 5 ?
 Ga2 Fe Ga2 180.000(2) . 25_666 ?
 Ga2 Fe Ga2 90.000(9) 33_666 25_666 ?
 Ga2 Fe Ga2 90.0 9 25_666 ?
 Ga2 Fe Ga2 90.000(11) 29_666 25_666 ?
 Ga2 Fe Ga2 90.000(2) 5 25_666 ?
 Ga2 Fe Ga1 0.000(2) . . ?
 Ga2 Fe Ga1 90.000(4) 33_666 . ?
 Ga2 Fe Ga1 90.000(4) 9 . ?
 Ga2 Fe Ga1 90.000(4) 29_666 . ?
 Ga2 Fe Ga1 90.000(4) 5 . ?
 Ga2 Fe Ga1 180.000(2) 25_666 . ?
 Ga2 Fe Ga1 90.000(2) . 9_556 ?
 Ga2 Fe Ga1 0.000(6) 33_666 9_556 ?

Ga2 Fe Ga1 180.000(2) 9 9_556 ?
 Ga2 Fe Ga1 90.000(2) 29_666 9_556 ?
 Ga2 Fe Ga1 90.000(2) 5 9_556 ?
 Ga2 Fe Ga1 90.000(2) 25_666 9_556 ?
 Ga1 Fe Ga1 90.0 . 9_556 ?
 Ga2 Fe Ga1 180.000(2) . 1_655 ?
 Ga2 Fe Ga1 90.000(4) 33_666 1_655 ?
 Ga2 Fe Ga1 90.000(4) 9 1_655 ?
 Ga2 Fe Ga1 90.000(4) 29_666 1_655 ?
 Ga2 Fe Ga1 90.000(4) 5 1_655 ?
 Ga2 Fe Ga1 0.000(2) 25_666 1_655 ?
 Ga1 Fe Ga1 180.0 . 1_655 ?
 Ga1 Fe Ga1 90.0 9_556 1_655 ?
 Ga2 Fe Ga1 90.000(4) . 5 ?
 Ga2 Fe Ga1 90.000(2) 33_666 5 ?
 Ga2 Fe Ga1 90.000(2) 9 5 ?
 Ga2 Fe Ga1 180.000(6) 29_666 5 ?
 Ga2 Fe Ga1 0.000(2) 5 5 ?
 Ga2 Fe Ga1 90.0 25_666 5 ?
 Ga1 Fe Ga1 90.0 . 5 ?
 Ga1 Fe Ga1 90.0 9_556 5 ?
 Ga1 Fe Ga1 90.0 1_655 5 ?
 Ga2 Fe Ga1 90.000(2) . 9 ?
 Ga2 Fe Ga1 180.000(6) 33_666 9 ?
 Ga2 Fe Ga1 0.000(2) 9 9 ?
 Ga2 Fe Ga1 90.000(2) 29_666 9 ?
 Ga2 Fe Ga1 90.000(2) 5 9 ?
 Ga2 Fe Ga1 90.000(2) 25_666 9 ?
 Ga1 Fe Ga1 90.0 . 9 ?
 Ga1 Fe Ga1 180.0 9_556 9 ?
 Ga1 Fe Ga1 90.0 1_655 9 ?
 Ga1 Fe Ga1 90.0 5 9 ?
 Ga2 Fe Ga1 90.000(2) . 5_565 ?
 Ga2 Fe Ga1 90.000(2) 33_666 5_565 ?
 Ga2 Fe Ga1 90.000(2) 9 5_565 ?
 Ga2 Fe Ga1 0.000(6) 29_666 5_565 ?
 Ga2 Fe Ga1 180.000(2) 5 5_565 ?
 Ga2 Fe Ga1 90.0 25_666 5_565 ?
 Ga1 Fe Ga1 90.0 . 5_565 ?
 Ga1 Fe Ga1 90.0 9_556 5_565 ?
 Ga1 Fe Ga1 90.0 1_655 5_565 ?
 Ga1 Fe Ga1 180.0 5 5_565 ?
 Ga1 Fe Ga1 90.0 9 5_565 ?
 Ga1 Er1 Ga1 60.0 9 . ?
 Ga1 Er1 Ga1 180.0 9 9_445 ?
 Ga1 Er1 Ga1 120.0 . 9_445 ?
 Ga1 Er1 Ga1 120.0 9 1_544 ?
 Ga1 Er1 Ga1 180.0 . 1_544 ?
 Ga1 Er1 Ga1 60.0 9_445 1_544 ?
 Ga1 Er1 Ga1 60.0 9 5 ?
 Ga1 Er1 Ga1 60.0 . 5 ?
 Ga1 Er1 Ga1 120.0 9_445 5 ?
 Ga1 Er1 Ga1 120.0 1_544 5 ?
 Ga1 Er1 Ga1 120.0 9 5_454 ?
 Ga1 Er1 Ga1 120.0 . 5_454 ?
 Ga1 Er1 Ga1 60.0 9_445 5_454 ?
 Ga1 Er1 Ga1 60.0 1_544 5_454 ?
 Ga1 Er1 Ga1 180.0 5 5_454 ?

Ga1 Er1 Ga1 90.0 9 9_455 ?
 Ga1 Er1 Ga1 60.0 . 9_455 ?
 Ga1 Er1 Ga1 90.0 9_445 9_455 ?
 Ga1 Er1 Ga1 120.0 1_544 9_455 ?
 Ga1 Er1 Ga1 120.0 5 9_455 ?
 Ga1 Er1 Ga1 60.0 5_454 9_455 ?
 Ga1 Er1 Ga1 60.0 9 5_554 ?
 Ga1 Er1 Ga1 120.0 . 5_554 ?
 Ga1 Er1 Ga1 120.0 9_445 5_554 ?
 Ga1 Er1 Ga1 60.0 1_544 5_554 ?
 Ga1 Er1 Ga1 90.0 5 5_554 ?
 Ga1 Er1 Ga1 90.0 5_454 5_554 ?
 Ga1 Er1 Ga1 120.0 9_455 5_554 ?
 Ga1 Er1 Ga1 120.0 9 5_455 ?
 Ga1 Er1 Ga1 60.0 . 5_455 ?
 Ga1 Er1 Ga1 60.0 9_445 5_455 ?
 Ga1 Er1 Ga1 120.0 1_544 5_455 ?
 Ga1 Er1 Ga1 90.0 5 5_455 ?
 Ga1 Er1 Ga1 90.0 5_454 5_455 ?
 Ga1 Er1 Ga1 60.0 9_455 5_455 ?
 Ga1 Er1 Ga1 180.0 5_554 5_455 ?
 Ga1 Er1 Ga1 120.0 9 1_545 ?
 Ga1 Er1 Ga1 90.0 . 1_545 ?
 Ga1 Er1 Ga1 60.0 9_445 1_545 ?
 Ga1 Er1 Ga1 90.0 1_544 1_545 ?
 Ga1 Er1 Ga1 60.0 5 1_545 ?
 Ga1 Er1 Ga1 120.0 5_454 1_545 ?
 Ga1 Er1 Ga1 120.0 9_455 1_545 ?
 Ga1 Er1 Ga1 120.0 5_554 1_545 ?
 Ga1 Er1 Ga1 60.0 5_455 1_545 ?
 Ga1 Er1 Ga1 60.0 9 1_554 ?
 Ga1 Er1 Ga1 90.0 . 1_554 ?
 Ga1 Er1 Ga1 120.0 9_445 1_554 ?
 Ga1 Er1 Ga1 90.0 1_544 1_554 ?
 Ga1 Er1 Ga1 120.0 5 1_554 ?
 Ga1 Er1 Ga1 60.0 5_454 1_554 ?
 Ga1 Er1 Ga1 60.0 9_455 1_554 ?
 Ga1 Er1 Ga1 60.0 5_554 1_554 ?
 Ga1 Er1 Ga1 120.0 5_455 1_554 ?
 Ga1 Er1 Ga1 180.0 1_545 1_554 ?
 Ga1 Er1 Ga1 90.0 9 9_545 ?
 Ga1 Er1 Ga1 120.0 . 9_545 ?
 Ga1 Er1 Ga1 90.0 9_445 9_545 ?
 Ga1 Er1 Ga1 60.0 1_544 9_545 ?
 Ga1 Er1 Ga1 60.0 5 9_545 ?
 Ga1 Er1 Ga1 120.0 5_454 9_545 ?
 Ga1 Er1 Ga1 180.0 9_455 9_545 ?
 Ga1 Er1 Ga1 60.0 5_554 9_545 ?
 Ga1 Er1 Ga1 120.0 5_455 9_545 ?
 Ga1 Er1 Ga1 60.0 1_545 9_545 ?
 Ga1 Er1 Ga1 120.0 1_554 9_545 ?

_diffn_measured_fraction_theta_max 1.000
 _diffn_reflns_theta_full 30.30
 _diffn_measured_fraction_theta_full 1.000
 _refine_diff_density_max 1.026
 _refine_diff_density_min -1.845
 _refine_diff_density_rms 0.334

data_shelx

_audit_creation_method SHELXL-97

_chemical_name_systematic

;

?

;

_chemical_name_common ?

_chemical_melting_point ?

_chemical_formula_moiety ?

_chemical_formula_sum

'Co Er Ga3'

_chemical_formula_weight 435.35

loop_

_atom_type_symbol

_atom_type_description

_atom_type_scatter_dispersion_real

_atom_type_scatter_dispersion_imag

_atom_type_scatter_source

'Co' 'Co' 0.3494 0.9721

'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

'Ga' 'Ga' 0.2307 1.6083

'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

'Er' 'Er' -0.2586 4.9576

'International Tables Vol C Tables 4.2.6.8 and 6.1.1.4'

_symmetry_cell_setting ?

_symmetry_space_group_name_H-M ?

loop_

_symmetry_equiv_pos_as_xyz

'x, y, z'

'-x, -y, z'

'-x, y, -z'

'x, -y, -z'

'z, x, y'

'z, -x, -y'

'-z, -x, y'

'-z, x, -y'

'y, z, x'

'-y, z, -x'

'y, -z, -x'

'-y, -z, x'

'y, x, -z'

'-y, -x, -z'

'y, -x, z'

'-y, x, z'

'x, z, -y'

'-x, z, y'

'-x, -z, -y'

'x, -z, y'

'z, y, -x'

'z, -y, x'

'-z, y, x'

'-z, -y, -x'

'-x, -y, -z'

'x, y, -z'

'x, -y, z'

'-x, y, z'

'-z, -x, -y'

'-z, x, y'

'z, x, -y'

'z, -x, y'

'-y, -z, -x'

'y, -z, x'

'-y, z, x'

'y, z, -x'

'-y, -x, z'

'y, x, z'

'-y, x, -z'

'y, -x, -z'

'-x, -z, y'

'x, -z, -y'

'x, z, y'

'-x, z, -y'

'-z, -y, x'

'-z, y, -x'

'z, -y, -x'

'z, y, x'

_cell_length_a 4.2201(7)

_cell_length_b 4.2201(7)

_cell_length_c 4.2201(7)

_cell_angle_alpha 90.00

_cell_angle_beta 90.00

_cell_angle_gamma 90.00

_cell_volume 75.16(2)

_cell_formula_units_Z 1

_cell_measurement_temperature 294(2)

_cell_measurement_reflns_used ?

_cell_measurement_theta_min ?

_cell_measurement_theta_max ?

_exptl_crystal_description ?

_exptl_crystal_colour ?

_exptl_crystal_size_max 0.06

_exptl_crystal_size_mid 0.04

_exptl_crystal_size_min 0.02

_exptl_crystal_density_meas ?

_exptl_crystal_density_diffn 9.619

_exptl_crystal_density_method 'not measured'

_exptl_crystal_F_000 188

_exptl_absorpt_coefficient_mu 59.223

_exptl_absorpt_correction_type ?

_exptl_absorpt_correction_T_min 0.1253

_exptl_absorpt_correction_T_max 0.3838

_exptl_absorpt_process_details ?

_exptl_special_details

;

?

;

_diffn_ambient_temperature 294(2)

```

_diffrn_radiation_wavelength  0.71073
_diffrn_radiation_type        MoK\alpha
_diffrn_radiation_source      'fine-focus sealed tube'
_diffrn_radiation_monochromator graphite
_diffrn_measurement_device_type ?
_diffrn_measurement_method    ?
_diffrn_detector_area_resol_mean ?
_diffrn_standards_number      ?
_diffrn_standards_interval_count ?
_diffrn_standards_interval_time ?
_diffrn_standards_decay_%     ?
_diffrn_reflns_number         320
_diffrn_reflns_av_R_equivalents 0.0356
_diffrn_reflns_av_sigmal/netl  0.0236
_diffrn_reflns_limit_h_min    -5
_diffrn_reflns_limit_h_max    5
_diffrn_reflns_limit_k_min    -5
_diffrn_reflns_limit_k_max    5
_diffrn_reflns_limit_l_min    -5
_diffrn_reflns_limit_l_max    4
_diffrn_reflns_theta_min      4.83
_diffrn_reflns_theta_max      30.35
_reflns_number_total          38
_reflns_number_gt             38
_reflns_threshold_expression   >2sigma(I)

_computing_data_collection    ?
_computing_cell_refinement    ?
_computing_data_reduction     ?
_computing_structure_solution 'SHELXS-97 (Sheldrick,
1990)'
_computing_structure_refinement 'SHELXL-97 (Sheldrick,
1997)'
_computing_molecular_graphics ?
_computing_publication_material ?

_refine_special_details
;
Refinement of F2 against ALL reflections. The weighted
R-factor wR and
goodness of fit S are based on F2, conventional R-
factors R are based
on F, with F set to zero for negative F2. The threshold
expression of
F2 > 2sigma(F2) is used only for calculating R-
factors(gt) etc. and is
not relevant to the choice of reflections for refinement.
R-factors based
on F2 are statistically about twice as large as those
based on F, and R-
factors based on ALL data will be even larger.
;

_refine_ls_structure_factor_coef Fsqd
_refine_ls_matrix_type        full
_refine_ls_weighting_scheme    calc
_refine_ls_weighting_details

```

```

'calc w=1/[\s^2^(Fo^2^)+(0.0168P)^2^+0.5117P] where
P=(Fo^2^+2Fc^2^)/3'
_atom_sites_solution_primary  direct
_atom_sites_solution_secondary difmap
_atom_sites_solution_hydrogens geom
_refine_ls_hydrogen_treatment mixed
_refine_ls_extinction_method  SHELXL
_refine_ls_extinction_coef    0.008(9)
_refine_ls_extinction_expression
'Fc^*=kFc[1+0.001xFc^2^\l^3^/sin(2\q)]^-1/4^'
_refine_ls_number_reflns     38
_refine_ls_number_parameters  10
_refine_ls_number_restraints  0
_refine_ls_R_factor_all      0.0212
_refine_ls_R_factor_gt       0.0212
_refine_ls_wR_factor_ref     0.0495
_refine_ls_wR_factor_gt      0.0495
_refine_ls_goodness_of_fit_ref 1.529
_refine_ls_restrained_S_all    1.529
_refine_ls_shift/su_max        0.000
_refine_ls_shift/su_mean       0.000

loop_
_atom_site_label
_atom_site_type_symbol
_atom_site_fract_x
_atom_site_fract_y
_atom_site_fract_z
_atom_site_U_iso_or_equiv
_atom_site_adp_type
_atom_site_occupancy
_atom_site_symmetry_multiplicity
_atom_site_calc_flag
_atom_site_refinement_flags
_atom_site_disorder_assembly
_atom_site_disorder_group
Ga1 Ga 0.0000 0.5000 0.5000 0.010(2) Uiso 0.83(10) 16 d
SP . .
Ga2 Ga 0.08(2) 0.5000 0.5000 0.015(11) Uiso 0.10(5) 8 d
SP . .
FE1 Co 0.5000 0.5000 0.5000 0.02(3) Uani 0.06(2) 48 d SP .
.
Er1 Er 0.0000 0.0000 0.0000 0.0083(8) Uani 1 48 d S . .

loop_
_atom_site_aniso_label
_atom_site_aniso_U_11
_atom_site_aniso_U_22
_atom_site_aniso_U_33
_atom_site_aniso_U_23
_atom_site_aniso_U_13
_atom_site_aniso_U_12
FE1 0.02(3) 0.02(3) 0.02(3) 0.000 0.000 0.000
Er1 0.0083(8) 0.0083(8) 0.0083(8) 0.000 0.000 0.000

_geom_special_details
;

```


All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

;

```
loop_
  _geom_bond_atom_site_label_1
  _geom_bond_atom_site_label_2
  _geom_bond_distance
  _geom_bond_site_symmetry_2
  _geom_bond_publ_flag
Ga1 Ga2 0.33(10) 25_566 ?
Ga1 FE1 2.1100(4) 1_455 ?
Ga1 FE1 2.1100(4) . ?
Ga1 Ga2 2.76(6) 33_666 ?
Ga1 Ga2 2.76(6) 9_455 ?
Ga1 Ga2 2.76(6) 29_666 ?
Ga1 Ga2 2.76(6) 5_455 ?
Ga1 Ga2 2.76(6) 33_566 ?
Ga1 Ga2 2.76(6) 9 ?
Ga1 Ga2 2.76(6) 29_566 ?
Ga1 Ga2 2.76(6) 5 ?
Ga1 Er1 2.9841(5) 1_566 ?
Ga2 Ga2 0.66(19) 25_566 ?
Ga2 FE1 1.78(10) . ?
Ga2 FE1 2.44(10) 1_455 ?
Ga2 Ga2 2.52(14) 33_666 ?
Ga2 Ga2 2.52(14) 29_666 ?
Ga2 Ga2 2.52(14) 9 ?
Ga2 Ga2 2.52(14) 5 ?
Ga2 Ga1 2.76(6) 5_565 ?
Ga2 Ga1 2.76(6) 9_556 ?
Ga2 Ga1 2.76(6) 5 ?
Ga2 Ga1 2.76(6) 9 ?
Ga2 Er1 3.002(11) . ?
FE1 Ga2 1.78(10) 33_666 ?
FE1 Ga2 1.78(10) 9 ?
FE1 Ga2 1.78(10) 29_666 ?
FE1 Ga2 1.78(10) 5 ?
FE1 Ga2 1.78(10) 25_666 ?
FE1 Ga1 2.1100(4) 9_556 ?
FE1 Ga1 2.1100(4) 9 ?
FE1 Ga1 2.1101(4) 1_655 ?
FE1 Ga1 2.1100(4) 5_565 ?
FE1 Ga1 2.1100(4) 5 ?
Er1 Ga1 2.9841(5) 9 ?
Er1 Ga1 2.9841(5) 9_445 ?
Er1 Ga1 2.9841(5) 1_544 ?
Er1 Ga1 2.9841(5) 5 ?
```

```
Er1 Ga1 2.9841(5) 5_454 ?
Er1 Ga1 2.9841(5) 9_455 ?
Er1 Ga1 2.9841(5) 5_554 ?
Er1 Ga1 2.9841(5) 5_455 ?
Er1 Ga1 2.9841(5) 1_545 ?
Er1 Ga1 2.9841(5) 1_554 ?
Er1 Ga1 2.9841(5) 9_545 ?

loop_
  _geom_angle_atom_site_label_1
  _geom_angle_atom_site_label_2
  _geom_angle_atom_site_label_3
  _geom_angle
  _geom_angle_site_symmetry_1
  _geom_angle_site_symmetry_3
  _geom_angle_publ_flag
Ga2 Ga1 FE1 0.00(3) 25_566 1_455 ?
Ga2 Ga1 FE1 180.00(3) 25_566 . ?
FE1 Ga1 FE1 180.0 1_455 . ?
Ga2 Ga1 Ga2 139.8(15) 25_566 33_666 ?
FE1 Ga1 Ga2 139.8(15) 1_455 33_666 ?
FE1 Ga1 Ga2 40.2(15) . 33_666 ?
Ga2 Ga1 Ga2 40.2(15) 25_566 9_455 ?
FE1 Ga1 Ga2 40.2(15) 1_455 9_455 ?
FE1 Ga1 Ga2 139.8(15) . 9_455 ?
Ga2 Ga1 Ga2 180.0 33_666 9_455 ?
Ga2 Ga1 Ga2 139.8(16) 25_566 29_666 ?
FE1 Ga1 Ga2 139.8(15) 1_455 29_666 ?
FE1 Ga1 Ga2 40.2(15) . 29_666 ?
Ga2 Ga1 Ga2 54.3(18) 33_666 29_666 ?
Ga2 Ga1 Ga2 125.7(19) 9_455 29_666 ?
Ga2 Ga1 Ga2 40.2(16) 25_566 5_455 ?
FE1 Ga1 Ga2 40.2(15) 1_455 5_455 ?
FE1 Ga1 Ga2 139.8(15) . 5_455 ?
Ga2 Ga1 Ga2 125.7(18) 33_666 5_455 ?
Ga2 Ga1 Ga2 54.3(19) 9_455 5_455 ?
Ga2 Ga1 Ga2 180.0 29_666 5_455 ?
Ga2 Ga1 Ga2 40.2(15) 25_566 33_566 ?
FE1 Ga1 Ga2 40.2(15) 1_455 33_566 ?
FE1 Ga1 Ga2 139.8(15) . 33_566 ?
Ga2 Ga1 Ga2 100(3) 33_666 33_566 ?
Ga2 Ga1 Ga2 80(3) 9_455 33_566 ?
Ga2 Ga1 Ga2 125.7(19) 29_666 33_566 ?
Ga2 Ga1 Ga2 54.3(18) 5_455 33_566 ?
Ga2 Ga1 Ga2 139.8(15) 25_566 9 ?
FE1 Ga1 Ga2 139.8(15) 1_455 9 ?
FE1 Ga1 Ga2 40.2(15) . 9 ?
Ga2 Ga1 Ga2 80(3) 33_666 9 ?
Ga2 Ga1 Ga2 100(3) 9_455 9 ?
Ga2 Ga1 Ga2 54.3(19) 29_666 9 ?
Ga2 Ga1 Ga2 125.7(19) 5_455 9 ?
Ga2 Ga1 Ga2 180.0 33_566 9 ?
Ga2 Ga1 Ga2 40.2(15) 25_566 29_566 ?
FE1 Ga1 Ga2 40.2(15) 1_455 29_566 ?
FE1 Ga1 Ga2 139.8(15) . 29_566 ?
Ga2 Ga1 Ga2 125.7(18) 33_666 29_566 ?
Ga2 Ga1 Ga2 54.3(18) 9_455 29_566 ?
Ga2 Ga1 Ga2 100(3) 29_666 29_566 ?
```

Ga2 Ga1 Ga2 80(3) 5_455 29_566 ?
 Ga2 Ga1 Ga2 54.3(18) 33_566 29_566 ?
 Ga2 Ga1 Ga2 125.7(19) 9 29_566 ?
 Ga2 Ga1 Ga2 139.8(15) 25_566 5 ?
 FE1 Ga1 Ga2 139.8(15) 1_455 5 ?
 FE1 Ga1 Ga2 40.2(15) . 5 ?
 Ga2 Ga1 Ga2 54.3(19) 33_666 5 ?
 Ga2 Ga1 Ga2 125.7(19) 9_455 5 ?
 Ga2 Ga1 Ga2 80(3) 29_666 5 ?
 Ga2 Ga1 Ga2 100(3) 5_455 5 ?
 Ga2 Ga1 Ga2 125.7(19) 33_566 5 ?
 Ga2 Ga1 Ga2 54.3(18) 9 5 ?
 Ga2 Ga1 Ga2 180.000(6) 29_566 5 ?
 Ga2 Ga1 Er1 90.00(3) 25_566 1_566 ?
 FE1 Ga1 Er1 90.0 1_455 1_566 ?
 FE1 Ga1 Er1 90.0 . 1_566 ?
 Ga2 Ga1 Er1 62.9(9) 33_666 1_566 ?
 Ga2 Ga1 Er1 117.1(9) 9_455 1_566 ?
 Ga2 Ga1 Er1 62.9(9) 29_666 1_566 ?
 Ga2 Ga1 Er1 117.1(9) 5_455 1_566 ?
 Ga2 Ga1 Er1 62.9(9) 33_566 1_566 ?
 Ga2 Ga1 Er1 117.1(9) 9 1_566 ?
 Ga2 Ga1 Er1 62.9(9) 29_566 1_566 ?
 Ga2 Ga1 Er1 117.1(9) 5 1_566 ?
 Ga2 Ga2 FE1 180.000(17) 25_566 . ?
 Ga2 Ga2 FE1 0.000(17) 25_566 1_455 ?
 FE1 Ga2 FE1 180.0 . 1_455 ?
 Ga2 Ga2 Ga2 135.000(6) 25_566 33_666 ?
 FE1 Ga2 Ga2 45.0 . 33_666 ?
 FE1 Ga2 Ga2 135.0 1_455 33_666 ?
 Ga2 Ga2 Ga2 135.00(3) 25_566 29_666 ?
 FE1 Ga2 Ga2 45.000(6) . 29_666 ?
 FE1 Ga2 Ga2 135.0 1_455 29_666 ?
 Ga2 Ga2 Ga2 60.000(11) 33_666 29_666 ?
 Ga2 Ga2 Ga2 135.0 25_566 9 ?
 FE1 Ga2 Ga2 45.000(6) . 9 ?
 FE1 Ga2 Ga2 135.0 1_455 9 ?
 Ga2 Ga2 Ga2 90.00(2) 33_666 9 ?
 Ga2 Ga2 Ga2 60.000(11) 29_666 9 ?
 Ga2 Ga2 Ga2 135.0 25_566 5 ?
 FE1 Ga2 Ga2 45.000(6) . 5 ?
 FE1 Ga2 Ga2 135.000(6) 1_455 5 ?
 Ga2 Ga2 Ga2 60.0 33_666 5 ?
 Ga2 Ga2 Ga2 90.00(2) 29_666 5 ?
 Ga2 Ga2 Ga2 60.000(6) 9 5 ?
 Ga2 Ga2 Ga1 130.2(15) 25_566 5_565 ?
 FE1 Ga2 Ga1 49.8(15) . 5_565 ?
 FE1 Ga2 Ga1 130.2(15) 1_455 5_565 ?
 Ga2 Ga2 Ga1 62.9(9) 33_666 5_565 ?
 Ga2 Ga2 Ga1 4.8(15) 29_666 5_565 ?
 Ga2 Ga2 Ga1 62.9(9) 9 5_565 ?
 Ga2 Ga2 Ga1 94.8(15) 5 5_565 ?
 Ga2 Ga2 Ga1 130.2(15) 25_566 9_556 ?
 FE1 Ga2 Ga1 49.8(15) . 9_556 ?
 FE1 Ga2 Ga1 130.2(15) 1_455 9_556 ?
 Ga2 Ga2 Ga1 4.8(15) 33_666 9_556 ?
 Ga2 Ga2 Ga1 62.9(9) 29_666 9_556 ?
 Ga2 Ga2 Ga1 94.8(15) 9 9_556 ?

Ga2 Ga2 Ga1 62.9(9) 5 9_556 ?
 Ga1 Ga2 Ga1 65.4(16) 5_565 9_556 ?
 Ga2 Ga2 Ga1 130.2(15) 25_566 5 ?
 FE1 Ga2 Ga1 49.8(15) . 5 ?
 FE1 Ga2 Ga1 130.2(15) 1_455 5 ?
 Ga2 Ga2 Ga1 62.9(9) 33_666 5 ?
 Ga2 Ga2 Ga1 94.8(15) 29_666 5 ?
 Ga2 Ga2 Ga1 62.9(9) 9 5 ?
 Ga2 Ga2 Ga1 4.8(15) 5 5 ?
 Ga1 Ga2 Ga1 100(3) 5_565 5 ?
 Ga1 Ga2 Ga1 65.4(16) 9_556 5 ?
 Ga2 Ga2 Ga1 130.2(15) 25_566 9 ?
 FE1 Ga2 Ga1 49.8(15) . 9 ?
 FE1 Ga2 Ga1 130.2(15) 1_455 9 ?
 Ga2 Ga2 Ga1 94.8(15) 33_666 9 ?
 Ga2 Ga2 Ga1 62.9(9) 29_666 9 ?
 Ga2 Ga2 Ga1 4.8(15) 9 9 ?
 Ga2 Ga2 Ga1 62.9(9) 5 9 ?
 Ga1 Ga2 Ga1 65.4(16) 5_565 9 ?
 Ga1 Ga2 Ga1 100(3) 9_556 9 ?
 Ga1 Ga2 Ga1 65.4(16) 5 9 ?
 Ga2 Ga2 Er1 83.7(18) 25_566 . ?
 FE1 Ga2 Er1 96.3(18) . . ?
 FE1 Ga2 Er1 83.7(18) 1_455 . ?
 Ga2 Ga2 Er1 125.1(14) 33_666 . ?
 Ga2 Ga2 Er1 125.1(14) 29_666 . ?
 Ga2 Ga2 Er1 65.2(15) 9 . ?
 Ga2 Ga2 Er1 65.2(15) 5 . ?
 Ga1 Ga2 Er1 127(2) 5_565 . ?
 Ga1 Ga2 Er1 127(2) 9_556 . ?
 Ga1 Ga2 Er1 62.2(5) 5 . ?
 Ga1 Ga2 Er1 62.2(5) 9 . ?
 Ga2 FE1 Ga2 180.000(6) 33_666 9 ?
 Ga2 FE1 Ga2 90.000(11) 33_666 29_666 ?
 Ga2 FE1 Ga2 90.0 9 29_666 ?
 Ga2 FE1 Ga2 90.0 33_666 5 ?
 Ga2 FE1 Ga2 90.000(11) 9 5 ?
 Ga2 FE1 Ga2 180.000(6) 29_666 5 ?
 Ga2 FE1 Ga2 90.00(2) 33_666 25_666 ?
 Ga2 FE1 Ga2 90.0 9 25_666 ?
 Ga2 FE1 Ga2 90.00(3) 29_666 25_666 ?
 Ga2 FE1 Ga2 90.000(6) 5 25_666 ?
 Ga2 FE1 Ga2 90.0 33_666 . ?
 Ga2 FE1 Ga2 90.00(2) 9 . ?
 Ga2 FE1 Ga2 90.000(6) 29_666 . ?
 Ga2 FE1 Ga2 90.00(3) 5 . ?
 Ga2 FE1 Ga2 180.000(6) 25_666 . ?
 Ga2 FE1 Ga1 90.000(11) 33_666 . ?
 Ga2 FE1 Ga1 90.000(11) 9 . ?
 Ga2 FE1 Ga1 90.000(11) 29_666 . ?
 Ga2 FE1 Ga1 90.000(11) 5 . ?
 Ga2 FE1 Ga1 180.000(6) 25_666 . ?
 Ga2 FE1 Ga1 0.000(6) . . ?
 Ga2 FE1 Ga1 0.000(17) 33_666 9_556 ?
 Ga2 FE1 Ga1 180.000(6) 9 9_556 ?
 Ga2 FE1 Ga1 90.000(6) 29_666 9_556 ?
 Ga2 FE1 Ga1 90.000(6) 5 9_556 ?
 Ga2 FE1 Ga1 90.000(6) 25_666 9_556 ?

Ga2 FE1 Ga1 90.000(6) . 9_556 ?
 Ga1 FE1 Ga1 90.0 . 9_556 ?
 Ga2 FE1 Ga1 180.000(17) 33_666 9 ?
 Ga2 FE1 Ga1 0.000(6) 9 9 ?
 Ga2 FE1 Ga1 90.000(6) 29_666 9 ?
 Ga2 FE1 Ga1 90.000(6) 5 9 ?
 Ga2 FE1 Ga1 90.000(6) 25_666 9 ?
 Ga2 FE1 Ga1 90.000(6) . 9 ?
 Ga1 FE1 Ga1 90.0 . 9 ?
 Ga1 FE1 Ga1 180.0 9_556 9 ?
 Ga2 FE1 Ga1 90.000(11) 33_666 1_655 ?
 Ga2 FE1 Ga1 90.000(11) 9 1_655 ?
 Ga2 FE1 Ga1 90.000(11) 29_666 1_655 ?
 Ga2 FE1 Ga1 90.000(11) 5 1_655 ?
 Ga2 FE1 Ga1 0.000(6) 25_666 1_655 ?
 Ga2 FE1 Ga1 180.000(6) . 1_655 ?
 Ga1 FE1 Ga1 180.0 . 1_655 ?
 Ga1 FE1 Ga1 90.0 9_556 1_655 ?
 Ga1 FE1 Ga1 90.0 9 1_655 ?
 Ga2 FE1 Ga1 90.000(6) 33_666 5_565 ?
 Ga2 FE1 Ga1 90.000(6) 9 5_565 ?
 Ga2 FE1 Ga1 0.000(17) 29_666 5_565 ?
 Ga2 FE1 Ga1 180.000(6) 5 5_565 ?
 Ga2 FE1 Ga1 90.0 25_666 5_565 ?
 Ga2 FE1 Ga1 90.000(11) . 5_565 ?
 Ga1 FE1 Ga1 90.0 . 5_565 ?
 Ga1 FE1 Ga1 90.0 9_556 5_565 ?
 Ga1 FE1 Ga1 90.0 9 5_565 ?
 Ga1 FE1 Ga1 90.0 1_655 5_565 ?
 Ga2 FE1 Ga1 90.000(6) 33_666 5 ?
 Ga2 FE1 Ga1 90.000(6) 9 5 ?
 Ga2 FE1 Ga1 180.000(17) 29_666 5 ?
 Ga2 FE1 Ga1 0.000(6) 5 5 ?
 Ga2 FE1 Ga1 90.0 25_666 5 ?
 Ga2 FE1 Ga1 90.000(11) . 5 ?
 Ga1 FE1 Ga1 90.0 . 5 ?
 Ga1 FE1 Ga1 90.0 9_556 5 ?
 Ga1 FE1 Ga1 90.0 9 5 ?
 Ga1 FE1 Ga1 90.0 1_655 5 ?
 Ga1 FE1 Ga1 180.0 5_565 5 ?
 Ga1 Er1 Ga1 60.0 9 . ?
 Ga1 Er1 Ga1 180.0 9 9_445 ?
 Ga1 Er1 Ga1 120.0 . 9_445 ?
 Ga1 Er1 Ga1 120.0 9 1_544 ?
 Ga1 Er1 Ga1 180.0 . 1_544 ?
 Ga1 Er1 Ga1 60.0 9_445 1_544 ?
 Ga1 Er1 Ga1 60.0 9 5 ?
 Ga1 Er1 Ga1 60.0 . 5 ?
 Ga1 Er1 Ga1 120.0 9_445 5 ?
 Ga1 Er1 Ga1 120.0 1_544 5 ?
 Ga1 Er1 Ga1 120.0 9 5_454 ?
 Ga1 Er1 Ga1 60.0 9_445 5_454 ?
 Ga1 Er1 Ga1 60.0 1_544 5_454 ?
 Ga1 Er1 Ga1 180.0 5_454 ?
 Ga1 Er1 Ga1 90.0 9 9_455 ?
 Ga1 Er1 Ga1 60.0 . 9_455 ?
 Ga1 Er1 Ga1 90.0 9_445 9_455 ?

Ga1 Er1 Ga1 120.0 1_544 9_455 ?
 Ga1 Er1 Ga1 120.0 5 9_455 ?
 Ga1 Er1 Ga1 60.0 5_454 9_455 ?
 Ga1 Er1 Ga1 60.0 9 5_554 ?
 Ga1 Er1 Ga1 120.0 . 5_554 ?
 Ga1 Er1 Ga1 120.0 9_445 5_554 ?
 Ga1 Er1 Ga1 60.0 1_544 5_554 ?
 Ga1 Er1 Ga1 90.0 5 5_554 ?
 Ga1 Er1 Ga1 90.0 5_454 5_554 ?
 Ga1 Er1 Ga1 120.0 9_455 5_554 ?
 Ga1 Er1 Ga1 120.0 9 5_455 ?
 Ga1 Er1 Ga1 60.0 . 5_455 ?
 Ga1 Er1 Ga1 60.0 9_445 5_455 ?
 Ga1 Er1 Ga1 120.0 1_544 5_455 ?
 Ga1 Er1 Ga1 90.0 5 5_455 ?
 Ga1 Er1 Ga1 90.0 5_454 5_455 ?
 Ga1 Er1 Ga1 60.0 9_455 5_455 ?
 Ga1 Er1 Ga1 180.0 5_554 5_455 ?
 Ga1 Er1 Ga1 120.0 9 1_545 ?
 Ga1 Er1 Ga1 90.0 . 1_545 ?
 Ga1 Er1 Ga1 60.0 9_445 1_545 ?
 Ga1 Er1 Ga1 90.0 1_544 1_545 ?
 Ga1 Er1 Ga1 60.0 5 1_545 ?
 Ga1 Er1 Ga1 120.0 5_454 1_545 ?
 Ga1 Er1 Ga1 120.0 9_455 1_545 ?
 Ga1 Er1 Ga1 120.0 5_554 1_545 ?
 Ga1 Er1 Ga1 60.0 5_455 1_545 ?
 Ga1 Er1 Ga1 60.0 9 1_554 ?
 Ga1 Er1 Ga1 90.0 . 1_554 ?
 Ga1 Er1 Ga1 120.0 9_445 1_554 ?
 Ga1 Er1 Ga1 90.0 1_544 1_554 ?
 Ga1 Er1 Ga1 120.0 5 1_554 ?
 Ga1 Er1 Ga1 60.0 5_454 1_554 ?
 Ga1 Er1 Ga1 60.0 9_455 1_554 ?
 Ga1 Er1 Ga1 60.0 5_554 1_554 ?
 Ga1 Er1 Ga1 120.0 5_455 1_554 ?
 Ga1 Er1 Ga1 180.0 1_545 1_554 ?
 Ga1 Er1 Ga1 90.0 9 9_545 ?
 Ga1 Er1 Ga1 120.0 . 9_545 ?
 Ga1 Er1 Ga1 90.0 9_445 9_545 ?
 Ga1 Er1 Ga1 60.0 1_544 9_545 ?
 Ga1 Er1 Ga1 60.0 5 9_545 ?
 Ga1 Er1 Ga1 120.0 5_454 9_545 ?
 Ga1 Er1 Ga1 180.0 9_455 9_545 ?
 Ga1 Er1 Ga1 60.0 5_554 9_545 ?
 Ga1 Er1 Ga1 120.0 5_455 9_545 ?
 Ga1 Er1 Ga1 60.0 1_545 9_545 ?
 Ga1 Er1 Ga1 120.0 1_554 9_545 ?

_diffn_measured_fraction_theta_max 0.927
 _diffn_reflms_theta_full 30.35
 _diffn_measured_fraction_theta_full 0.927
 _refine_diff_density_max 1.226
 _refine_diff_density_min -1.102
 _refine_diff_density_rms 0.356

Vita

LaRico Juan Treadwell was born in 1987, in Batesville, Mississippi to Stephen and Adrienne Robinson. He is the oldest of five children (Brycen, Byron, Bryen, and Melissa) and has one child (Latrell Treadwell). LaRico received his high school diploma from South Panola High School in Batesville, Mississippi, in May of 2006. In August of 2006, he began his studies in chemistry at The University of Mississippi, where he became an Ole Miss First Scholar, AGEM Scholar, and the Ronald E. McNair Scholar. He completed The University of Mississippi with a Bachelor of Science in Chemistry in 2010.

LaRico began his graduate career at Louisiana State University in August of 2010, under the direction of Professor Julia Y Chan. At LSU, he received the Board of Regents Fellowship and made significant contributions to the chemistry of materials that can be seen in various publications. Also, LaRico has attended numerous national scientific meeting. In 2012, he presented a poster at the NOBCChE conference in Washington D.C. and attended a neutron powder diffraction workshop at Oak Ridge National Laboratory. In 2013, LaRico presented a poster at the ACS National Meeting in New Orleans and NOBCChE in Indianapolis and gave an invited talk the ACS Southwest Regional Meeting in Waco, TX. In 2014, he gave an invited talk at the ACS National Meeting in Dallas, TX. In his graduate career, he has participated in numerous outreach programs (SuperScience Saturday, X-ray Crystallography Demonstration, chemistry demonstration at K-12 schools), organized a poster session, and held presidential positions for the local LSU NOBCChE chapter and chemistry graduate student council (CGSC). Also, he has organized/hosted a poster symposium for LSU STEM majors, South Louisiana Organic Symposium, and recruitment/collaborative efforts with LSU-Morehouse.

In December of 2014, LaRico J Treadwell will graduate and be awarded with a Doctor of Philosophy degree in chemistry.